

Disorder Induced Fluctuations of the Pairing Parameter in P-Wave Superconductors *

GRZEGORZ LITAK

Department of Mechanics, Technical University of Lublin, Nabystrzycka 36,
20-618 Lublin, Poland

We study the effect of site diagonal disorder on the pairing amplitude by a perturbation method. Using an extended Hubbard model with the intersite attraction we analyze fluctuations of order parameter in presence of non-magnetic disorder and discuss the instability of various solutions with p -wave pairing.

PACS numbers: 74.70.Pq, 74.20.Rp, 74.62.Dh

1. Introduction

In case of an anisotropic superconductor non-magnetic disorder leads eventually to pair breaking effect via Abrikosov–Gorkov formula [1, 2, 3, 4, 5], like for magnetic impurities, for any value of a coherence length ξ . By analogy to an isotropic s -wave pairing, for superconductors with an enough large coherence length ξ , the amplitude of pairing potential $|\Delta(ij)|$ tends to be the same for all bonds but disorder induces the effect of fluctuations in the amplitude leading, in this way, to destruction of pairing. Here we will calculate fluctuating potentials standard deviations $\langle \delta|\Delta_{ij}|^2 \rangle$ and $\langle \varepsilon_i^2 \rangle$. Their ratio $\Gamma = \langle \delta|\Delta_{ij}|^2 \rangle / \langle \varepsilon_i^2 \rangle$ will be a criterion of pairing potential fluctuations [6].

2. P-wave solutions for a clean system

We start a single band, extended, Hubbard model with effective nearest neighbour intersite attraction W_{ij} ($W_{ii} = 0$) [7]. Taking the Fourier transform of the Green function for a clean system we can write its equation of

* Presented at XII International School of Modern Physics on Phase Transitions and Critical Phenomena, Łądek Zdrój 2001

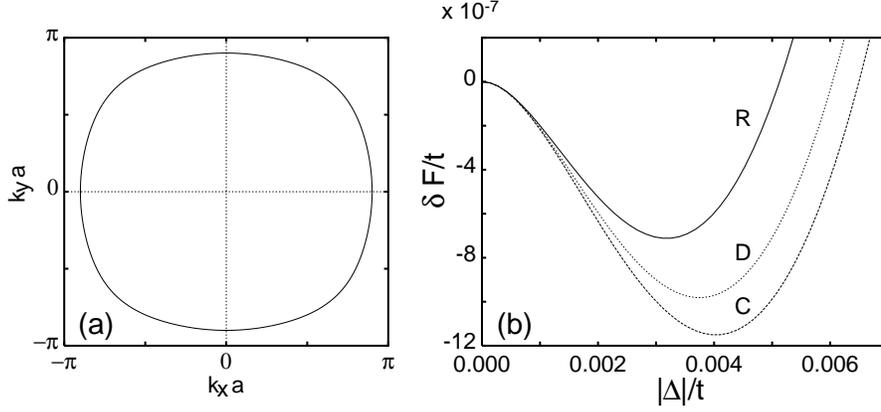


Fig. 1. (a) The Fermi surface and (b) the Free energy δF as a function of pairing potential $|\Delta|$ ($|\Delta| = \sqrt{\Delta_x^2 + \Delta_y^2}$) for different solutions: dipole (D) real (R) and complex (C) order parameters, respectively; for γ band of Sr_2RuO_4 electronic structure ($t' = 0.45t$, $n/2 = 0.66$). The intersite attraction $W = -0.446t$, temperature $T = 0$

motion:

$$\begin{bmatrix} (\omega - \epsilon_{\mathbf{k}} + \mu)\mathbf{1} & \Delta_{\mathbf{k}} \\ \Delta_{\mathbf{k}}^* & (\omega + \epsilon_{\mathbf{k}} - \mu)\mathbf{1} \end{bmatrix} \mathbf{G}^0(\mathbf{k}; \omega) = \mathbf{1}, \quad (1)$$

where $\Delta_{\mathbf{k}} = \Delta_x \sin k_x + \Delta_y \sin k_y$ defines 2×2 matrix of a pairing potential. For a clean system t_{ij} can be expressed in \mathbf{k} -space: $\epsilon_{\mathbf{k}} = \sum_j t_{ij} e^{-i\mathbf{R}_{ij} \cdot \mathbf{k}} = -2t(\cos k_x + \cos k_y) - 4t' \cos k_x \cos k_y$, where t represents the nearest neighbour site amplitude of electron hopping, while t' corresponds to next nearest neighbour one. For the assumed solution [8] $\Delta_{\mathbf{k}} = i\hat{\sigma}_y \hat{\sigma} \cdot \mathbf{d}(\mathbf{k})$, with $\mathbf{d}(\mathbf{k}) = (0, 0, d^z(\mathbf{k}))$ and $d^z(\mathbf{k}) = \Delta_{\mathbf{k}}$. The corresponding free energy F for a finite temperature T can be found from the standard formula:

$$F = \sum_{\mathbf{k}} \left[-(n-1)(\epsilon_{\mathbf{k}} - \mu) - 2k_B T \ln \left(2 \cosh \frac{E_{\mathbf{k}}}{2k_B T} \right) - \frac{|\Delta_{\mathbf{k}}(T)|^2}{W} \right], \quad (2)$$

where $E_{\mathbf{k}}$ denotes the eigenvalue. To perform numerical calculations we have fitted our one band system parameters to the realistic γ band structure of Sr_2RuO_4 [5, 9, 10, 11] Fig. 1a presents the corresponding Fermi surface. For the above assumptions we have found three solutions with p -wave pairing. Namely, depending on relative values Δ_x and Δ_y , the dipole one ($\Delta_x \neq 0$ and $\Delta_y = 0$), the real one ($\Delta_x = \Delta_y$) and the complex one ($\Delta_x = i\Delta_y$). They correspond to minima of free energy curves ($\delta F(|\Delta|) = F(|\Delta|) - F(0)$) in Fig. 1b, denoted by D, R and C, respectively. The interaction parameter used in calculations ($W = -0.446t$) were chosen to

give $T_c = 1.5\text{K}$ as for clean Sr_2RuO_4 . One can easily see that the complex solution reaches the global minimum of free energy F .

3. Fluctuations of pairing potential.

In this section we investigate the stability of superconducting p -wave states in presence of a weak disorder. Here, we apply the same strategy as in [6] and we treat random site energies ε_i as perturbations. To proceed we write the Dyson equation for a Green function $\mathbf{G}(i, j; \omega)$ evaluated at a frequency ω :

$$\mathbf{G}(i, j; \omega) = \mathbf{G}^0(i, j; \omega) + \sum_l \mathbf{G}^0(i, j; \omega) \mathbf{V}_l \mathbf{G}(l, j; \omega), \quad (3)$$

where $\mathbf{V}_l = \varepsilon_l \boldsymbol{\sigma}_3$ is the impurity potential matrix.

Following Eq. (3) we express quantity order parameter Δ_{ij} , in the lowest order of ε_i perturbations by means of disordered Green function and calculate the mean square deviation of the pairing Δ_{ij} along the bond of nearest neighbour sites i and j . For site independent energies ε_i :

$$\langle \delta |\Delta_{ij}|^2 \rangle = \Gamma_{ij} \langle \varepsilon_i^2 \rangle. \quad (4)$$

Finally, we calculate the coefficient Γ_{ij} [6]:

$$\Gamma_{ij} = \frac{1}{N} \sum_{\mathbf{q}} \left| \frac{W_{ij}}{2N} \sum_{\mathbf{k}} \frac{\Delta_{\mathbf{k}} \tilde{\varepsilon}_{\mathbf{k}} + \Delta_{\mathbf{k}} \tilde{\varepsilon}_{\mathbf{k}-\mathbf{q}}}{(E_{\mathbf{k}} + E_{\mathbf{k}-\mathbf{q}}) E_{\mathbf{k}} E_{\mathbf{k}-\mathbf{q}}} e^{i(\mathbf{R}_i - \mathbf{R}_j) \cdot \mathbf{k}} \right|^2, \quad (5)$$

Having found the pairing potentials (Fig. 1b, Eq. 1) for the clean system, we calculated Γ (Eq. 5) for all three solutions we obtained. In all cases Γ has a very small value (of order $\sim 10^{-8}$). This implies that fluctuations of Δ_{ij} are relatively small in this system. Interestingly, a real type solution is characterized by the smallest fluctuations ($\Gamma = 5.15 \cdot 10^{-9}$) while $\Gamma = 13.93 \cdot 10^{-9}$ for the dipole solution and $\Gamma = 8.12 \cdot 10^{-9}$ for the complex one. This could mean that the real solution is favoured by disorder.

4. Conclusions and Discussion

We have analyzed the effect of a weak disorder on a p -wave superconductor in context of newly discovered superconductor Sr_2RuO_4 [11, 12]. Unfortunately the order parameter structure in this compound is still unknown [12]. Fitting our system parameters to its γ band structure we have asked about the stability of various solution in presence of disorder. We have found three solutions with the same critical temperature $T_C = 1.5\text{K}$:

dipole and real solutions with line nodes in the gap and complex one with a finite gap in any direction. Note that, all these solutions have the same critical temperature T_C and the Abrikosov–Gorkov formula [2, 4] does not differentiate any of them. Our preliminary results at $T = 0$ indicate that the complex type of solution has the global minimum of free energy F but the real one is favoured by disorder. That result was obtained in one band model in the lowest order of perturbation method and should be confirmed by a more sophisticated method like Coherent Potential Approximation [4, 5] considering more realistic three bands structure of Sr_2RuO_4 .

Acknowledgements: This work has been partially supported by KBN grant No. 5P03B00221 and the Royal Society Joint Project. The author would like to thank Profs. K.I. Wysokiński, B.L. Györfly and Dr. J.F. Annett for discussions.

REFERENCES

- [1] A.A. Abrikosov and L.P. Gorkov, *Sov. Phys. JETP* **8**, (1959) 1090.
- [2] K. Maki in *Superconductivity*, edited by R.D. Parks (Marcel Dekker, New York 1969) Vol. 2, Chapter 8.
- [3] G. Harań and A.D.S. Nagi, *Phys. Rev. B* **6301**, (2001) 2503.
- [4] A.M. Martin, G. Litak, B.L. Györfly, *et al.*, *Phys. Rev. B* **60** (1999) 7523.
- [5] G. Litak, J.F. Annett, B.L. Györfly, *Acta Phys. Pol. A* **97**, (2000) 149.
- [6] B.L. Györfly, G. Litak, K.I. Wysokiński, in *Fluctuation Phenomena in High Critical Temperature Superconducting Ceramics* Eds. M. Ausloos and A.A. Varlamov (Kluwer Academic Publishers NATO ASI Series Dordrecht 1997) 385.
- [7] R. Micnas, J. Ranninger, S. Robaszkiewicz, *et al.*, *Phys. Rev. B* **37**, (1988) 9410.
- [8] G. Litak, J.F. Annett, B.L. Györfly *et al.*, *Mol. Phys. Rep.* (2001) in press, preprint cond-mat/0105376.
- [9] G. Litak, J.F. Annett, B.L. Györfly, in *Open Problems in Strongly Correlated Electron Systems*, Eds. J. Bonca *et al.*, (Kluwer Academic Publishers NATO Science Series, Dordrecht 2001) 425.
- [10] A.P. Mackenzie, S.R. Julian, A.J. Diver *et al.*, *Phys. Rev. Lett.* **76** (1996) 3786; A.P. Mackenzie *et al.*, *J. Phys. Soc. Jpn.* **67** (1998) 385.
- [11] D. F. Agterberg, T. M. Rice and M. Sgrist, *Phys. Rev. Lett.* **73** (1997) 3374.
- [12] Y. Maeno, T.M. Rice, M. Sgrist, *Physics Today*, January 42 (2001).