

Phase diagram of heavy fermion systems

J. Flouquet^{a,d,*}, Y. Haga^b, P. Haen^c, D. Braithwaite^a, G. Knebel^a, S. Raymond^a,
S. Kambe^b

^a*Département de Recherche Fondamentale sur la Matière Condensée, SPSMS, CEA Grenoble, 38054 Grenoble, France*

^b*Advanced Science Research Center JAERI, Tokai, Ibaraki 319-1195, Japan*

^c*CRTBT-CNRS, BP 166X, 38042 Grenoble-Cédex, France*

^d*Department of Physical Science, Graduate School of Engineering Science, Osaka University, Japan*

Abstract

The Meccano of heavy fermion systems is shown on different cases going from anomalous monochalcogenides to cerium intermetallic compounds with special focus on the ideal case of the CeRu₂Si₂ series. Discussion is made in the frame of the interplay between valence, electronic structure (Fermi surface), and magnetism. The nice tools given by the temperature, the pressure, and the magnetic field allow to explore different ground states as well as the slow downhill “race” before reaching a Fermi liquid finish line at very low temperature. Experimentally, the Grüneisen parameter i.e. the ratio of the thermal expansion by the specific heat is a coloured magic number; its temperature, pressure, and magnetic field dependence is a deep disclosure of competing hierarchies and the conversion of this adaptive matter to external responses.

Key words: Kondo lattice, valence instability, magnetism, superconductivity

PACS: 71.10.Hf, 71.27.+a, 74.70.Tx, 75.30.Mb

Heavy fermion physics are approached by pedestrian looking of basic questions on the electronic occupancy n_{4f} of the $4f$ shell and the magnetic properties. The monochalcogenide cases of Sm and Tm compounds are revisited with recent data obtained on SmS [1,2]. For the cerium intermetallic compounds, special attention is given close to the so called magnetic quantum criticality i.e. near the critical electronic density ρ_c or pressure P_c where drastic changes occur on the ground state. Pressure and magnetic field are elegant tool to modify the weight or even the sign of the magnetic interactions by comparison to the strong local fluctuations inherent to Kondo lattices. Emphasis is given on the results on the CeRu₂Si₂ family since the pure compound i.e. with vanishing disorder allows to scan through different temperature and field regimes [3].

1. Monochalcogenides of Sm and Tm: conduction, valence, and magnetism

In the monochalcogenides of anomalous rare earths (RE) like Sm or Tm the equilibrium between two valence states (Sm²⁺/Sm³⁺ or Tm²⁺/Tm³⁺) governs the release of a $5d$ electron [4]. Let us start with our new guided tour of the canonical example of SmS. The full line T_{B-G} of the $(T-P)$ phase diagram (see Fig.1) represents the first order isostructural transition between the black (B) insulating (I) Sm²⁺ phase and the so called gold (G) phase where the Sm ions jumps to an intermediate valence state $v \approx 2.7$. In this gold phase, smoothly increasing the pressure must lead to recover a trivalent Sm³⁺; it is a Kramers ion, long range magnetic order must appear above this threshold $P = P_c$.

Furthermore a sound experimental fact is that up to $P_\Delta = 20$ kbar in the low pressure gold phase a many body insulating phase is smoothly formed

* Corresponding author. Tel.: +33-438-785423; FAX +33-438-785098

Email address: flouquet@cea.fr (J. Flouquet).

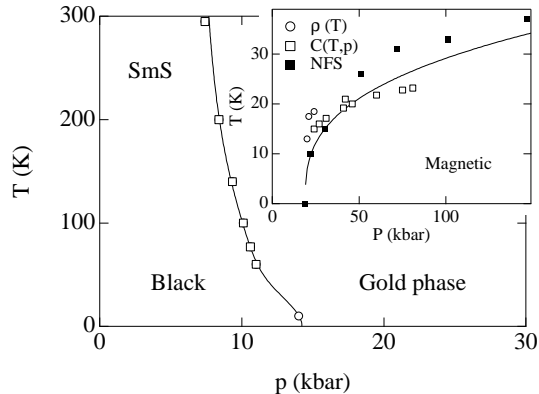


Fig. 1. Phase diagram of SmS with the first order line between the black and the gold phase. Insert: Zoom on the metallic gold phase and the discovery of magnetism by three different techniques: specific heat (C), transport (ρ) and nuclear forward scattering (NFS).

on cooling. Whatever the sample quality and the pressure conditions, P_{Δ} is a fixed pressure above which the sample is clearly metallic i.e. its resistivity ρ decreases on cooling after reaching a maximum ρ_{max} at T_m [5,6,7,8]. The recent combination of macroscopic measurements by transport and ac specific heat and of the microscopic probe of the hyperfine field on the Sm nuclei by nuclear forward scattering (NFS) using ESRF facility demonstrates that long range antiferromagnetic (AF) order appears at $P_c \sim P_{\Delta}$. As the pressure variation of T_m now identified as the Néel temperature T_N is huge, P_c is presumably a first order point associated with a lattice parameter discontinuity i.e. a tiny valence jump at $P_v = P_c$ towards the trivalent state.

By contrast to the Sm case where the valence fluctuations occur between the Sm^{2+} state with a zero angular momentum ($J = 0$) and Sm^{3+} with a $J = 5/2$ angular momentum, for the Tm ions the mixing is between two finite angular momentum states, respectively $J = 7/2$ (Tm^{2+}) and $J = 6$ (Tm^{3+}). Whatever the pressure i.e. the valence and even the electronic conduction, the ground state is magnetic. However, the similarity with SmS is a link between magnetic properties and $4f$ localisation. For TmTe as shown on Fig. 2, the P sequence of ground states is AF/I up to P_{BG} , ferromagnetic (F) and metallic (M) up to P_v and finally the entrance to a AF metallic state [9,10]; the rapid collapse of T_{Curie} just below P_v and the fast increase of T_N just above P_v suggests a first order transition. For TmSe, already in the gold phase at $P = 0$, the switch at P_v occurs between an AF insulating phase $P < P_v - \epsilon$ and another AF metallic state above P_v [11]. TmS itself appears already at $P = 0$ as a quiet quasitrivalent metallic state, in principle

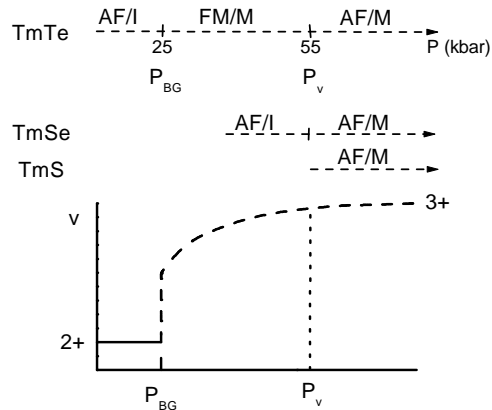


Fig. 2. Pressure cascade of ground states in Tm chalcogenides: v is the rare earth valence.

the ideal Kondo lattice [12].

2. Cerium heavy fermion systems: valence and magnetism

As pointed out already, the cerium heavy fermion problem can be summarized by two major (T, P) phase diagrams. The wellknown $T_{\alpha, \gamma}$ first order transition of the cerium metal and the up to date magnetic phase diagram T_N or T_{Curie} versus pressure where the ordering temperature may collapse at P_c [13]. For the cerium metal, the treatment of the magnetism can be crude as all characteristic temperatures $T_{\alpha, \gamma}$ are high by comparison to any hypothetical T_N or any fine structure as the crystal field splitting C_{CF} of the trivalent γ phase. At $P = 0$, $T_{\alpha, \gamma}(0)$ is already positive, finite and near 100 K and the critical end points $T_{cr} = 700$ K, $P_{cr} = 22$ kbar are large. For typical cerium heavy fermion compounds P_c is lower or comparable to P_{cr} and of course $T_{\alpha, \gamma}(P = 0)$ and $T_{cr}(P_{cr})$ will be negative. However, the $4f$ electron will feel the distance from P_{cr} and cause the crossing through a characteristic pressure P_v where the local susceptibility loses the anisotropy given by its reaction to the crystal field (that corresponds to the well known condition $k_B T_K$ (Kondo energy) greater than C_{CF}). Above P_v , the $4f$ electron stays rigidly linked to the full degeneracy of the $J = 5/2$ angular momentum. At P_v , the sensitivity of the $4f$ electron to the crystal field has vanished; P_v is characteristic of a valence crossover. The relative location of P_c and the hidden parameter P_v is one of the key issue. The idea that singular properties is underpinned by a quantum critical point i.e. pressure is one of the trends of strongly correlated electronic sys-

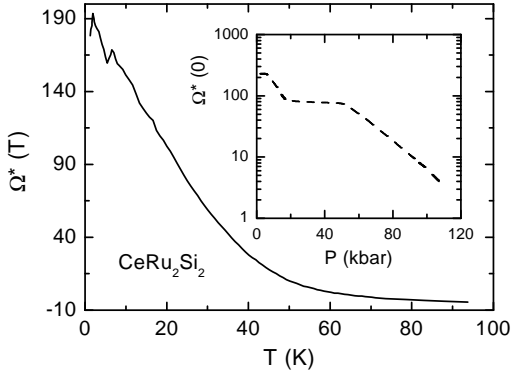


Fig. 3. Temperature variation of the Grüneisen parameter $\Omega^*(T)$ of CeRu_2Si_2 . Insert: pressure dependence of $\Omega^*(0)$, the extrapolated zero temperature limit.

tems (see references [14] for the hidden order of URu_2Si_2 or [15] for the metamagnetic quantum criticality in $\text{Sr}_3\text{Ru}_2\text{O}_7$ and [16] for the conversion of a Kondo gas to heavy electron Kondo liquid).

Recently special focus has been given on systems just on the paramagnetic verge of P_c i.e. at $P_c + \epsilon$ [17]. The Non Fermi liquid (NFL) label refers to the difficulty to reach the standard Fermi liquid regime where usual laws are found, even for non-interacting Fermi gas (specific heat $C = \gamma T$ linear in temperature T , susceptibility in T^2 , scattering rate proportional to T^2); the NFL label guarantee “vintage” describes a very large temperature crossover before reaching the Fermi liquid graal or a new state of matter.

To clarify the complexity of this strongly correlated electronic system, an old fashioned approach via thermodynamic languages will be carried out [18,19,20,21]. In the same spirit as the Clapeyron and Ehrenfest relations on the P, T feedback for first or second order transitions, the Grüneisen parameter

$$\Omega^*(T) = \frac{\alpha V_0}{C \kappa} \quad (1)$$

(where α , V_0 and κ are respectively the volume thermal expansion, the molar volume and the isothermal compressibility) is a unique experimental gauge of interfering hierarchies. It will be reduced to a constant $\Omega^*(0)$ only if the free energy F can be expressed by a unique parameter T^* i.e.

$$F(T) = T\Phi\left(\frac{T}{T^*}\right) \quad \text{with} \quad \Omega^*(0) = -\frac{\partial \log T^*}{\partial \log V} \quad (2)$$

Figure 3 represents the temperature variation of the Grüneisen parameter of CeRu_2Si_2 at $P = 0$ i.e. roughly 3 kbar above the critical pressure $P_c = -3$ kbar. The two singular points are: (i) the huge extrapolated value of $\Omega^*(0) = +190$ and (ii) the slow entrance in a simple regime ($T \approx 1$ K) where

α and C reach their proportionality [22,23]. The pressure dependence of Ω_0^* is shown in the insert of fig.3. At low pressure close to P_c , $\Omega^*(0)$ is weakly pressure dependent changing from 190 to 220 for a negative shift of $P = 2$ kbar [22] while Ω_0^* drops to 80 at P_v [23]. Other values of $\Omega_P^*(0)$ can be listed crudely for other heavy fermion system. In a double logarithmic representation of the volume dependence of the A coefficient of the well known AT^2 Fermi liquid resistivity assuming the usual Kadowaki-Woods rule $A \propto \gamma^2$, $\Omega^*(0)$ is directly linked to the slope of the curve [24].

3. Magnetic field switch from AF correlation to F interactions

The compound CeRu_2Si_2 is a quasi-ideal Kondo lattice with a nice ordered tetragonal lattice, a robust Ising character of the local susceptibility, the realization of a clean limit condition i.e. a mean free path higher than 1000 Å far larger than an hypothetical superconducting coherence length with temperature $T_s = 200$ mK and good enough to obtain the complete determination of the Fermi surface (FS) at least above P_c (see references in [3]).

The application of a magnetic field H along the easy c axis leads to a switch through a drastic continuous crossover at $H = H_m$ from a low field paramagnetic phase (Pa) dominated by AF correlations at a finite wavevector k_0 to a highly polarized state (PP) dominated by the low wavevector q excitation. The microscopic vision of CeRu_2Si_2 was nicely given by inelastic neutron scattering experiments, (i) with at $H = 0$, the balance between the local response and the intersite coupling, (ii) with, under magnetic field, the continuous spreading of the AF response with the same characteristic glumly energy $\omega_{AF} \sim 1.6$ meV up to H_m [25] and the observation just in the vicinity of H_m of an inelastic ferromagnetic signal at far lower energy transfer $\omega_F \sim 0.4$ meV than ω_{AF} (see Fig.4) [26,27].

A skilful mechanism characteristic of the Kondo lattice CeRu_2Si_2 controls the “ping-pong” between the magnetic interactions. Quite remarkably, the field and temperature response is well reproduced by a simple form of the thermodynamic as the entropy.

$$S = S\left(\frac{T}{T^*}, \frac{H}{H_m}\right) \quad (3)$$

with equal Grüneisen parameters $\Omega_{T^*} = \Omega_{H_m} = -190$. With this hypothesis one can predict the field variation of γ_H knowing the field variation of

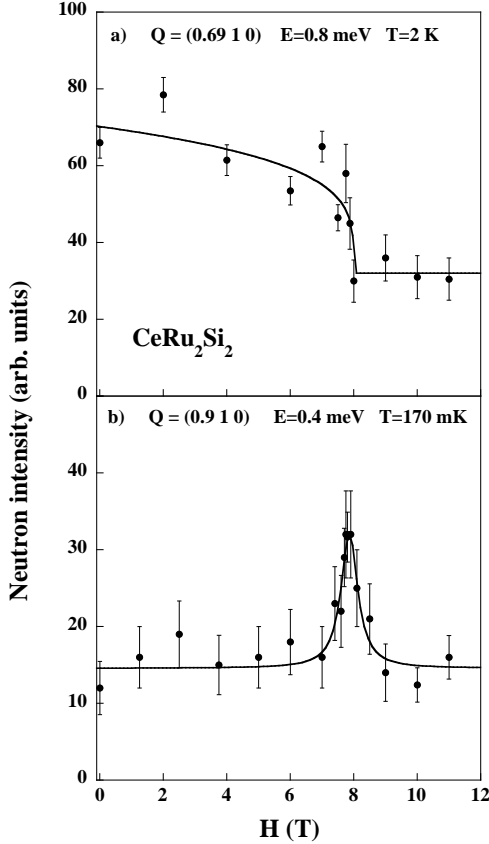


Fig. 4. (a) Field variation of the inelastic response at the energy transfer $E = 0.8$ meV measured at the AF wave vector $(0.69, 1, 0)$; the AF contribution vanishes at H_m while the local one survives. (b) Appearance of low energy ferromagnetic fluctuation ($E = 0.4$ meV) on crossing H_m .

the linear thermal expansion $\alpha_v = a_H T$. A satisfactory agreement is found between this scaling derivation of γ_H and the bare determination either by specific heat or by magnetization [22,28]. Physically, the adaptive formation of the many body Kondo lattice bands is characterized by a pseudogap. The Ising spin character of the bare local magnetic ion plays a capital role in the sharpness of this electronic substructure and correlatively for the pseudo-metamagnetism [29]. The pseudogap ingredient is a key input in any theory which needs to respect the scaling behavior [30]. Reminiscent of the $\alpha - \gamma$ collapse of the cerium metal, the associated spectacular lattice softening ($\approx 30\%$) is again in agreement with the push pull between magnetic, electronic and lattice instabilities [3] and the underpinned vicinity of a quantum critical end point.

4. To be or not to be? Speculations on superconductivity

After a lecture describing the “beauty” CeRu_2Si_2 to quantum criticality, the first attack is to produce the proofs that CeRu_2Si_2 is close to a magnetic instability. Looking back to the primitive results one decade ago on the CeRu_2Si_2 series either sweeping electronic density (doping or pressure) or magnetic field, a NFL increase of C/T on cooling in a given temperature window justifies the proximity to P_c [31]. Furthermore, this variation is not drastically different from that popularized in the canonical example of $\text{CeCu}_{5.9}\text{Au}_{0.1}$ [32] after a rescaling of the temperature by some phenomenological parameter describing the proximity to P_c and also differences in physical ingredients. As on approaching P_c , no drastic pressure dependence of $\Omega^*(0)$ occurs. Collapsing to P_c on the paramagnetic side does not lead to an “earthquake” even if of course T^* will collapse when $T \rightarrow 0$. The deviation from any singular scaling law of the imaginary part of the dynamical susceptibility $\chi'' T^\alpha \propto \Phi(\frac{\omega}{T})$ becomes also quite difficult to point out. The yet unanswered dilemma is if a new state of matter occurs right at P_c .

The obsessive focus just at P_c or on the paramagnetic (Pa) side ($P > P_c$) leads to neglect the disappearance of long range magnetism. As many tunings were realized by doping i.e. at the cost of an increase of disorder, P_c appears as a second order quantum phase transition. Comparison with the previous chalcogenide cases, recent NMR experiments on CeIn_3 close to $P_c - \epsilon$ with evidence of AF and Pa magnetic phase separation [33] as well as drastic Fermi surface changes at P_c in CeRh_2Si_2 [34] point out that at the limit of a pure lattice at P_c the transition may be first order. Today one key question is to determine precisely the Fermi surface on both sides of P_c knowing the two limit conditions of a localized $4f$ picture at low pressure ($P \ll P_c$) and an itinerant $4f$ picture at high pressure ($P \gg P_c$). Progress will imply a deep interdisciplinary collaboration between experimentalists and theoreticians eager to track carefully the P and H variations including the modification of the Brillouin zone and the differentiation between spin up and spin down effective mass carriers.

For unconventional superconductivity, the nature of the phase transition at P_c is not critical as proved by the occurrence of superconductivity in CeIn_3 and CeRh_2Si_2 . There are examples like CePd_2Si_2 , CeIn_3 and CeRh_2Si_2 where the superconducting pocket is stocked to $P_c \sim P_v$; there

are cases like CeCu₂Si₂ [35], CeCu₂Ge₂ [36] and CeNi₂Ge₂ [37] where two superconducting domains are centered on distinct pressures P_c and P_v . We will test soon if superconductivity appears on the verge of $P_v \approx 20$ kbar in CeRu₂Si₂; near $P_c = -3$ kbar, the Ising character of the spin allows only longitudinal magnetic fluctuations which does not favor the observation of d wave pairing [38,39] while near P_v this superconductivity can be promoted by the emergence of transverse magnetic modes as well as valence fluctuations [40,41].

It is time to concentrate on the complete bundle of curves on each side of P_c in CeRu₂Si₂ as well as in the other cerium tetragonal lattices and Yb homologues following our Dresden colleagues [42].

Acknowledgements J. F. wants to thank the Lorentz center for its invitation to the workshop “Non Fermi liquid behavior and quantum phase transitions” (May 2003) and FERLIN ESF support during four years.

References

- [1] Y. Haga et al. to be published.
- [2] A. Barla et al. to be published.
- [3] J. Flouquet et al. *Physica B* **319** (2002) 251.
- [4] P. Wachter, *Handbook of Physics and Chemistry of Rare Earths* Vol. 19, p. 177, edited by K. A. Gscheidner, L. Eyring, G. H. Lander, and G. R. Choppin (North Holland-Amsterdam, 1994).
- [5] F. Holtzberg and J. Wittig, *Solid State Commun.* **40** (1981) 315.
- [6] F. Lapiere et al., *Solid State Commun.* **40** (1981) 317.
- [7] H. Konzykowski et al. *Solid State Commun.* **40** (1981) 517.
- [8] M. Ohashi et al., *Rev. High Pressure Sci. Technology* **7** (1998) 611.
- [9] P. Link et al., *Phys. Rev. Lett.* **80** (1997) 173.
- [10] J. M. Mignot et al., *J. Magn. Magn. Mater* **211** (2001) 226.
- [11] M. Ribault et al., *Phys. Rev. Lett.* **45** (1980) 1295.
- [12] F. Holtzberg et al., *J. Appl. Phys.* **57** (1985) 3067.
- [13] S. Kambe et al., *J. Phys. Soc. Jpn.* **69** (2000) 41.
- [14] F. Bourdarot et al., to be published.
- [15] M. Chiao et al., cond-mat/0207657.
- [16] S. Nakatsujii et al., cond-mat/0305427.
- [17] A. Schröder et al., *Nature (London)* **407** (2000) 351.
- [18] A. Benoit et al., *Conference on Valence Fluctuations in Solids*, p. 283, edited by L. M. Falicov, W. Hanke, M. B. Maple (Santa Barbara, 1981).
- [19] J. Flouquet et al., *J. Appl. Phys.* **53** (1982) 2127.
- [20] S. Kambe et al., *J. Phys.: Condens. Matter* **9** (1997) 4917.
- [21] L. Zhu et al., to be published, cond-mat/0212335.
- [22] A. Lacerda, Thesis, University of Grenoble, 1990, unpublished, and A. Lacerda et al., *Phys. Rev. B* **40** (1989) 8759.
- [23] S. Holtmeier, Thesis, University of Grenoble, 1993, unpublished, and K. Payer et al., *Physica B* **186-188** (1993) 503.
- [24] J. Flouquet, to be published in: *Progress Low Temperature Physics*
- [25] S. Raymond et al., *Physica B* **259-261** (1999) 48.
- [26] M. Sato et al., *J. Phys. Soc. Jpn.* **70** (2001) Suppl. A, 118.
- [27] S. Raymond et al. to be published.
- [28] C. Paulsen et al., *J. Low Temp. Phys.* **81** (1990) 317.
- [29] Y. Aoki et al., *J. Magn. Magn. Mater.* **177-181** (1998) 271.
- [30] F. Ohkawa, *Phys. Rev. B* **57** (1998) 5891.
- [31] R. A. Fisher et al., *J. Low Temp. Phys.* **84** (1991) 49.
- [32] H. v. Löhneysen et al., *Phys. Rev. Lett.* **72** (1994) 3262.
- [33] S. Kawasaki et al., private communication.
- [34] S. Araki et al., *Phys. Rev. B* **64** (2001) 224417.
- [35] B. Bellarbi et al., *Phys. Rev. B* **30** (1984) 779.
- [36] D. Jaccard et al., *Phys. Lett. A* **163** (1992) 475
- [37] See D. Braithwaite et al., *J. Phys.: Condens. Matter* **12** (2000) 1339.
- [38] See P. Monthoux and G. G. Lonzarich, *Phys. Rev. B* **66** (2002) 224504.
- [39] G. G. Lonzarich, this conference.
- [40] Y. Onishi and K. Miyake, *J. Phys. Soc. Jpn.* **69** (2000) 3955.
- [41] A. Holmes et al., cond-mat/0306054.
- [42] See S. Paschen et al., this conference.