

Statistics of randomly branched polymers in a semi-space

M.V.Tamm¹, S.K.Nechaev², I.Ya.Erukhimovich³

¹*Physics Department, Moscow State University 119992, Moscow, Russia*

²*LPTMS, Université Paris Sud, 91405 Orsay Cedex, France*

³*A.N.Nesmeyanov Institute of Organoelement Compounds RAS, Vavilova str. 28, 119991, Moscow, Russia*

(Dated: April 21, 2019)

We investigate the statistical properties of a randomly branched 3-functional N -link polymer chain without excluded volume, whose one point is fixed at the distance d from the impenetrable surface in a 3-dimensional space. Exactly solving the Dyson-type equation for the partition function $Z(N, d) = N^{-\theta} e^{\gamma N}$ in 3D, we find the "surface" critical exponent $\theta = \frac{5}{2}$, as well as the density profiles of 3-functional units and of dead ends. Our approach enables to compute also the pairwise correlation function of a randomly branched polymer in a 3D semi-space.

I. INTRODUCTION

Rapid development of statistical physics of macromolecules is indebted, in first turn, to the representation of linear polymers by Markov chains. The application of a theory of Markov processes for a description of conformational properties of linear polymer chains has become invaluable [1, 2, 3]. Besides the linear chains, the polymers of complex geometry, such as, for example, stars, brushes and branched chains, are of extreme importance in physical and chemical properties of macromolecular compounds [1, 4, 5].

Randomly branched macromolecules are ones of the most interesting polymer systems with nonlinear structure. The possibility to form topologically different architectures leads to an extra contribution to the conformational entropy of samples constituted by randomly branched chains. There is a deep relation between statistical properties of randomly branched polymers and "lattice animals" appeared in percolation [6, 7, 8] and physics of self-assembled systems, like gelation processes [9, 10, 11, 12, 13, 14, 15, 16]. There are various methods for statistical description of annealed randomly branched chains. On the one hand, we know successful attempts to compute various conformational properties of randomly branched polymers in terms of branched Markov processes [17, 18, 19, 20]. On the other hand, special attention should be paid to the application of the supersymmetry in the description of thermodynamic characteristics of randomly branched chains. During last two decades since the seminal works [21, 22, 23] (see also the short self-reviews [24]) the supersymmetry becomes a powerful tool for the investigation of statistics of randomly branched chains. In particular one has to note the recent contributions [25, 26] which give the impact in understanding the very origin of the supersymmetric dimensional reduction for randomly branched polymers.

The basic question in the statistical theory of randomly branched chains concerns the evaluation of the partition function $Z(N)$ of a phantom (i.e. self-intersecting) branched structure without loops. Briefly, the problem is formulated as follows. Take N elementary units (monomers) such that each monomer has no more than f_m branches (we call them f_m -functional monomers) and compute all possible ways to arrange them in a *single-connected* loopless cluster. We call such a cluster "a f_m -branching random tree". In what follows we shall consider for simplicity only the case $f_m = 3$. The problem of calculating of the partition function $Z(N)$ in the free space does not meet any difficulties and has been solved by various methods mainly based on the supersymmetric approach (see the citations above). However the influence of boundary conditions on statistical properties of randomly branched polymers is far from being as clear as the bulk properties. It seems to be instructive to compare this situation to the boundary behavior of linear phantom chains. The boundary effect for linear random walks can be easily taken into account by using the "image" principle which enables to represent the partition function of a linear polymer with, say, Dirichlet boundary conditions in terms of a linear combination of two shifted bulk partition functions [27, 28]. *A priori* the same "image" method seems to be inapplicable for randomly branched chains.

In the present work we generalize the technique developed in the earlier work [12, 13] for a problem of thermoreversible gelation to compute a partition function, $Z(N, d)$, and calculate various thermodynamic characteristics of annealed randomly branched loopless N -link polymer in a 3-dimensional space, whose one point is fixed at the distance d from the impenetrable wall. The approach used in our work is based on a diagram expansion of a partition function of randomly branched polymer in a semi-space. Summing the diagrams we then construct and solve directly the Dyson-type equation for the aforementioned partition function. The developed method enables us also to compute the density profiles of 3-functional units and dead ends as well as to derive an expression for the correlation function, $G(r_1, r_2, N)$, of the branched polymer in a semi-space. Finally we compare our approach with the supersymmetric treatment of the similar problem [29, 30] and show the physical transparency and simplicity of our method.

The paper is organized as follows. In the Section II we present the model of randomly branched polymers and discuss in details the methods we are using. The brief review of known main results concerning the randomly branched polymers in the bulk is given in the Section III. The Section IV is devoted to the calculation of a generating function of branched random walk in a semi-space. That is the central part of our paper. In the Sections V–VII, using the expression for the generating function, we compute respectively: the partition function of an N -link random tree, the distribution of branchings in the tree, and the pairwise correlation function. In the last Section we briefly summarize and discuss the obtained results.

II. THE METHODS AND THE MODEL

In order to make the paper self-consistent, it seems to be instructive to formulate the general thermodynamic language which has been elaborated for the description of the thermoreversible gelation process [12, 13] and is very convenient for our needs. To begin with, let us consider a system of N identical 3-functional units capable to form reversible bonds between each other. The partition function $Z(N)$ of such a system can be written as a product of two terms:

$$Z(N) = Z_{\text{str}}(N)Z_{\text{int}}(N) \quad (1)$$

where $Z_{\text{str}}(N)$ and $Z_{\text{int}}(N)$ denote correspondingly the "structural" and "interactional" parts of the partition function.

The structural contribution to the partition function, i.e. the one due to the formation of clusters of specific structure reads:

$$Z_{\text{str}}(N) = \int \sum_{\{T\}} \frac{1}{r_T} \prod_{\{i,j\} \in T} [\beta g(r_i, r_j)] dr_i \quad (2)$$

where:

- the product is taken over all pairs of particles forming the manifold with topology T characterized by the symmetry index r_T ;
- the external sum runs over all possible topological structures T of the system;
- the factor β is the weight of pairing;
- the function $g(r_i, r_j) = g(r_i - r_j)$ is the probability density to find two connected particles at the points r_i and r_j correspondingly [3, 12, 13, 31]. We assume this function to be the normalized Gaussian:

$$g(r) = \left(\frac{3}{2\pi a^2} \right)^{3/2} \exp\left(-\frac{3r^2}{2a^2} \right) \quad (3)$$

where a is a mean-square length of the bond:

$$a^2 = \int r^2 g(r) dr \quad (4)$$

The partition function $Z_{\text{int}}(N)$ is purely energetic and is due to the interactions among particles and between particles and an external field:

$$\begin{aligned} Z_{\text{int}}(N) &= \int e^{-U(\{r_i\})/T} \prod dr_i \\ U(\{r_i\}) &= \sum_i \phi(r_i) + \sum_{i,j} V(r_i, r_j) \end{aligned} \quad (5)$$

where:

- the potentials $\phi(r_i)$ and $V(r_i, r_j)$ are correspondingly an external field at the point r_i and a pairwise interaction energy in the system;

– T is the temperature measured in energetic units.

In what follows we neglect the volume interactions between particles and therefore we set $V(r_i, r_j) = 0$.

In the present article we restrict ourselves to the investigation of randomly branched polymers only, i.e. we totally neglect the possibility of formation of any closed loops of bonds in the system. In that case the calculation of the partition function $Z(N)$ becomes rather transparent and can be described by the simple diagrammatic technique (see Fig.1 as an example).

$$\begin{aligned}
 Z(4) = & \left(\begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \right) + \left(\begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \right) \\
 & + \left(\begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \right) + \left(\begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \right) \\
 & + \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} + \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array} \begin{array}{c} \diagup \\ | \\ \diagdown \end{array}
 \end{aligned}$$

FIG. 1: The diagrammatic representation of the statistical sum $Z(N)$ for $N = 4$.

Indeed, let us consider a system consisting of N 3-functional monomers bonded in such a way that no closed loops are present. In general, such a system consists of many disconnected trees. It is convenient to describe the structure of each tree by a diagram, where each monomer is represented by a vertex (with an assigned radius-vector r), the chemical bond between two monomers is represented by a line connecting the vertices corresponding to the bonded monomers and if a monomer has less than 3 bonds with other monomers than each missing bond is represented by a short line (dead end). Next, let us attribute the weights $e^{-\phi(r)/T}$, $\beta g(r_i, r_j)$ and 1 to the vertices, long lines (connections), and short lines (dead ends), respectively. Following the prescription (2), the weight of each diagram is given by a multiplication of all the weights, integration over all space coordinates and, finally, division by the symmetry index r_T . Now, the desired partition function $Z(N)$ is a sum running over all (connected and disconnected) weighted diagrams. To proceed further let us introduce the generating function $\Xi(\lambda)$ of all diagrams (connected and disconnected) as follows:

$$\begin{aligned}
 \Xi(\lambda) &= 1 + \sum_{N=1}^{\infty} Z(N)\lambda^N \\
 Z_{all}(N) &= \frac{1}{2\pi i} \oint \frac{\Xi(\lambda)}{\lambda^{N+1}} d\lambda
 \end{aligned}$$

The function $\Xi(\lambda)$ is just the partition function of the grand canonical ensemble with a fixed chemical potential $\mu = T \ln \lambda$. As it follows from the so-called "first Mayer theorem" (see, for example, [32]), we can represent $\Xi(\lambda)$ in the following form:

$$\Xi(\lambda) = \exp \chi(\lambda, \phi(r)) \quad (6)$$

where $\chi(\lambda, \phi(r))$ is the generating functional of all the *single connected* diagrams. Accordingly, the partition function of all *single-connected* trees consisting of N monomers is

$$Z_{con}(N) = \frac{1}{2\pi i} \oint \frac{\chi(\lambda)}{\lambda^{N+1}} d\lambda \quad (7)$$

The simplest way to calculate $\chi(\lambda, \phi(r))$ is to define first the generating function of all the rooted diagrams (i.e.

diagrams with one labelled vertex) $\sigma(\lambda, \beta, r) = -T\delta\chi(\lambda, \phi(r))/\delta\phi(r)$ as it is shown in the equation below:

$$\begin{aligned} \frac{\sigma(\lambda, \beta, r)}{\lambda e^{-\phi(r)/T}} &= \frac{1}{6} + \frac{\lambda\beta}{4} \int g(r, r_1) e^{-\phi(r_1)/T} dr_1 + \frac{\lambda^2\beta^2}{4} \int g(r, r_1)g(r_1, r_2) \prod_{i=1}^2 e^{-\phi(r_i)/T} dr_i \\ &+ \frac{\lambda^2\beta^2}{8} \int g(r, r_1)g(r, r_2) \prod_{i=1}^2 e^{-\phi(r_i)/T} dr_i + \frac{\lambda^3\beta^3}{4} \int g(r, r_1)g(r_1, r_2)g(r_2, r_3) \prod_{i=1}^3 e^{-\phi(r_i)/T} dr_i \\ &+ \frac{\lambda^3\beta^3}{4} \int g(r, r_1)g(r, r_2)g(r_2, r_3) \prod_{i=1}^3 e^{-\phi(r_i)/T} dr_i + \frac{\lambda^3\beta^3}{48} \int g(r, r_1)g(r, r_2)g(r, r_3) \prod_{i=1}^3 e^{-\phi(r_i)/T} dr_i \\ &+ \frac{\lambda^3\beta^3}{16} \int g(r, r_1)g(r_1, r_2)g(r_1, r_3) \prod_{i=1}^3 e^{-\phi(r_i)/T} dr_i + \{\text{terms of higher orders in } \lambda \text{ and } \beta\} \end{aligned} \quad (8)$$

The equation (8) can be easily visualized. The corresponding diagrammatic expansion is displayed in Fig.2.

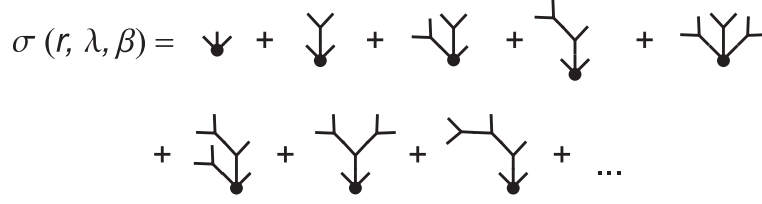


FIG. 2: The series of root diagrams for the function $\sigma(\lambda, \beta, r)$ up to 4 terms (see Eq.(8)).

Note that $\lambda^{-1}e^{\phi(r)/T}\sigma(\lambda, \beta, r)$ is a functional of $\phi(r)$ and a function of $z\beta$ only, which is due to the fact that the number of bonds in a tree-like cluster is always one less than the number of connected units: $N_{bond} = N - 1$. Therefore, in what follows we redefine

$$\epsilon = \lambda\beta$$

and rewrite $\sigma(\lambda, \beta, r)$ as

$$\sigma(\lambda, \epsilon, r) = \lambda e^{-\phi(r)/T} \sum_{N=1}^{\infty} C_N \epsilon^{N-1} \quad (9)$$

It is noteworthy that the coefficient $\lambda e^{-\phi(r)/T} C_N \epsilon^{N-1}$ has a simple physical meaning—it is equal to the partition function of a randomly branched polymer consisting of $N + 1$ links with one link fixed at the point r .

Now, it is easy to see that the following relationship holds:

$$\lambda d\chi(\lambda, \beta, \phi(r))/d\lambda = \int \rho(\lambda, r) d^3r \quad (10)$$

Thus, to find the function $\chi(\epsilon)$ we should just integrate the generating function $\sigma(\lambda, \beta, r)$:

$$\chi(\lambda, \beta) = \beta^{-1} e^{-\phi(r)/T} \sum_{N=1}^{\infty} \frac{C_N}{N+1} \beta^N = z^{-1} \int_0^\beta \rho(\lambda, \tau, r) d\tau \quad (11)$$

Since the weights of the different branches of any tree are factorized under assumption of the absence of closed loops and volume interactions in the system, the generating function σ can be written in the factorized form:

$$\sigma(\lambda, \epsilon, r) = \frac{\lambda}{6} e^{-\phi(r)/T} t^3(\epsilon, r). \quad (12)$$

Here $t(\epsilon, r)$ is a generating function of one branch, which has the following series expansion:

$$\begin{aligned} t(\epsilon, r) &= 1 + \frac{\epsilon}{2} \int g(r, r_1) e^{-\phi(r_1)/T} dr_1 + \frac{\epsilon^2}{2} \int g(r, r_1)g(r_1, r_2) \prod_{i=1}^2 e^{-\phi(r_i)/T} dr_i \\ &+ \frac{\epsilon^3}{2} \int g(r, r_1)g(r_1, r_2)g(r_2, r_3) \prod_{i=1}^3 e^{-\phi(r_i)/T} dr_i + \frac{\epsilon^3}{8} \int g(r, r_1)g(r_1, r_2)g(r_1, r_3) \prod_{i=1}^3 e^{-\phi(r_i)/T} dr_i + \dots \end{aligned} \quad (13)$$

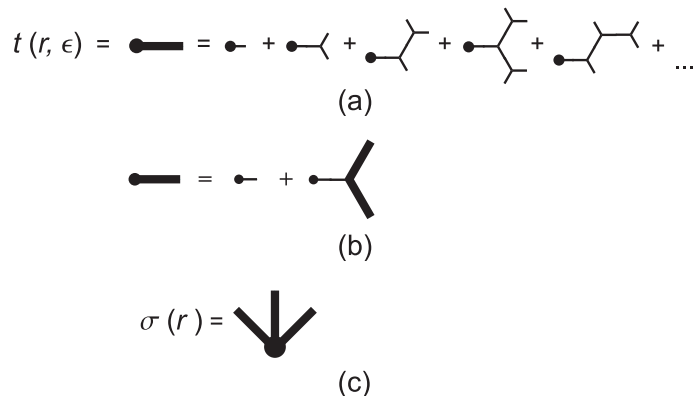


FIG. 3: Diagrammatic form of: (a) Eq.(13), (b) Eq.(14), (c) Eq.(12).

The diagrammatic form of this expansion is shown in fig. 3a.

The infinite series (13) could be easily evaluated taking into account the aforementioned statistical independence of different branches. Indeed, it is easy to see that all the terms in (13) are similar to that of the right-hand side of the diagrammatic equation presented in fig.3b. Therefore, the generating function t satisfies the following exact non-perturbative equation :

$$t(\epsilon, r) = 1 + \frac{\epsilon}{2} \int g(r, r_1) e^{-\phi(r_1)/T} t^2(\epsilon, r_1) dr_1. \quad (14)$$

The equation (14) plays a central role in our paper. Solving it, one gets both "rooted" and "unrooted" generating functions σ and χ and obtain the partition functions Ξ and Z . The method of generating functions enables also easily to compute the numbers ρ_f of the *nodes* having exactly f dead ends. The corresponding generation functions are, obviously,

$$\sigma_f(\lambda, r) = \frac{\lambda e^{-\phi(r_1)/T}}{f!(3-f)!} (t-1)^{3-f} = \lambda e^{-\phi(r_1)/T} \sum_{N=1}^{\infty} C_N^{(f)}(r) \epsilon^{N-1} \quad (15)$$

The N -th term $C_N^{(f)}(r)$ in the series expansion of σ_f has a clear physical meaning. It is just a partition function of a randomly branched $(N+1)$ -link polymer with: i) a root fixed at the given point r , and ii) exactly f branches starting from this root. Comparing this definition with that of C_N (see equation 9 and discussion below), we get the probability $p_f(r)$ for a vertex of a randomly branched $N+1$ -link polymer situated at the point r to be f -functional, which equals

$$p_f(r) = \frac{C_N^{(f)}(r)}{C_N(r)} \quad (16)$$

Note, that starting from the generating function t one can also calculate the pairwise correlation function in a rather straightforward way. Indeed, the correlation function $G(r_1, r_2)$ satisfies the following Dyson equation

$$G(r_1, r_2) = g(r_1 - r_2) + \epsilon \int g(r_1 - r_3) t(r_3) e^{-\phi(r_3)/T} G(r_3, r_2) dr_3 \quad (17)$$

which is represented in the diagrammatic form in Fig.4.



FIG. 4: Visualization of the Dyson equation Eq.(17).

In Fig.4 the correlation function G is shown by a double line. Note that equation (17), though rather trivial, differs from that suggested earlier in [34] where $t(r_3)$ was improperly replaced by $\int G(r_3, r_4) dr_4$.

III. THE BULK PROPERTIES OF A RANDOMLY BRANCHED POLYMER

In this section we use the formalism introduced above to re-derive the well-known main characteristics of the randomly branched polymers in the infinite space, which will be useful to compare with the results in the semi-space to be obtained in the subsequent sections.

In the infinite homogenous space (i.e. for $\phi(r) \equiv 0$) the equation defining the generating function of branches t (14) has a unique solution which is invariant with respect to translations and tends to unity when $\epsilon \rightarrow 0$. This solution is easy to find as equation (14) becomes purely algebraic due to the aforementioned translation invariance:

$$t = \frac{1 - \sqrt{1 - 2\epsilon}}{\epsilon} \quad (18)$$

where we allowed for the normalization of function $g(r, r')$. Note that all other solutions (in particular the one which tends to infinity when $\epsilon \rightarrow 0$) do not have any physical meaning and therefore in case of spatially inhomogeneous external field we will be interested only in solutions of eq.(14) which approaches this one when $r \rightarrow \infty$; $\phi(r) \rightarrow 0$

The equilibrium densities of junctions and dead ends can be easily calculated in the way prescribed in the previous section. Indeed, we have

$$\sigma = \lambda \frac{t^3}{6} = \lambda \frac{(2 - 3\epsilon) - (2 - \epsilon)\sqrt{1 - 2\epsilon}}{3\epsilon^3} \quad (19)$$

for the generating function of all rooted randomly branched trees. The general expression for randomly branched trees with f dead ends in the root (compare to (15)) reads

$$\sigma_f = \lambda \frac{(t - 1)^{(3-f)}}{f!(3 - f)!} \quad (20)$$

In particular,

$$\sigma_3 = \lambda \frac{(t - 1)^3}{6} = \lambda \frac{(4 - 12\epsilon + 9\epsilon^2 - \epsilon^3) - (4 - 8\epsilon + 3\epsilon^2)\sqrt{1 - 2\epsilon}}{6\epsilon^3} \quad (21)$$

for the rooted randomly branched trees with no dead ends in the root (we call such a root the junction point).

Expanding Eqs. (19), (21) and (20) into series with respect of ϵ and substituting the results into eq.(16) one obtains finally the probabilities of junctions and dead ends:

$$p_3(N) = \frac{(N - 2)(N - 1)}{2(N + 1)(2N + 1)}; \quad p_1(N) = \frac{(N + 5)}{2(2N + 1)} \quad (22)$$

both values approaching 1/4 as N tends to infinity.

To calculate the correlation function in the bulk one should solve (17) with $\phi(r_3) \equiv 0$ and $t(r_3)$ given by (18). The equation to solve, can be written as follows

$$G(r) = g(r) + (1 - \sqrt{1 - 2\epsilon}) \int g(r')G(r - r')d^3r' \quad (23)$$

(note that the correlation function in the bulk depends only on the distance between two roots $r = r_1 - r_2$).

There are various methods of solving (23), we will stick here to the one which seems to be the most suitable from the point of view of its comparison with the corresponding solution in the semi-space. As soon as we are interested mostly in the asymptotic characteristics of the trees when N is large, we can fully neglect all the short-range (i.e. on the scales of order $r \sim a$) peculiarities of a correlation function. We therefore replace the first term of the r.h.s. of (23) by a Dirac delta-function $\delta(r)$ (see eqs.(3)–(4)) and expand the slowly changing function $G(r - r')$ into the series up to the second order in $(r - r')$ (see also [33]). After calculating the integrals we arrive at the following differential equation:

$$G(r) = \delta(r) + (1 - \xi) \left(G(r) + \frac{a^2}{6} \Delta G(r) \right) \quad (24)$$

where we introduced a new variable

$$\xi = \sqrt{1 - 2\epsilon}$$

As the function $G(r)$ depends on r only, we can rewrite the Laplace operator as $\Delta = r^{-2} \frac{d}{dr} \left(r^2 \frac{d}{dr} \right)$. Denoting $R = \frac{r\sqrt{6}}{a} \sqrt{\frac{\xi}{1-\xi}}$, we can rewrite the equation (24) as follows (for $R > 0$):

$$G''(R) + 2R^{-1}G'(R) - G(R) = 0 \quad (25)$$

Therefore, one gets finally the correlation function in the bulk

$$G(r) = A \frac{\exp(-R)}{R} \quad (26)$$

which allows us to re-derive the well-known result (see [34, 35]) for the gyration radius of the tree:

$$\langle r^2(\epsilon) \rangle = \frac{\int r^2 G(r) d^3 r}{\int G(r) d^3 r} \sim a^2 (\xi^{-1} - 1); \quad \langle r^2(N) \rangle \sim a^2 N^{1/2} \quad (27)$$

It is worthwhile also to rewrite the result (26) in the cylindric coordinates:

$$G(Z, \rho) = A \frac{\exp(-\sqrt{Z^2 + \rho^2})}{\sqrt{Z^2 + \rho^2}} A \int_1^{+\infty} \exp(-c|Z|) J_0(\rho\sqrt{c^2 - 1}) dc \quad (28)$$

where $J_0(x)$ is a Bessel function of 0-th order, and the variables $(Z, \rho = \sqrt{x^2 + y^2})$ are the usual cylindric coordinates renormalized by the factor $\frac{\sqrt{6}}{a} \sqrt{\frac{\xi}{1-\xi}}$.

IV. GENERATING FUNCTION t IN A HALF-SPACE

Assume now that our branched polymer is displaced in a semi-space $x \geq 0$. The presence of an impenetrable wall situated at $x = 0$ is described by the potential $\phi(r) \equiv \phi(x, y, z)$, where

$$\phi(x, y, z) = \begin{cases} 0 & \text{for } x \geq 0 \\ \infty & \text{for } x < 0 \end{cases} \quad (29)$$

In this case one can rewrite (14) as follows

$$t(x, y, z, \epsilon) = 1 + \frac{\epsilon}{2} \int_0^\infty dx \int_{-\infty}^\infty dz \int_{-\infty}^\infty dy g(x, y, z; x', y', z') t^2(x', y', z', \epsilon) \quad (30)$$

To solve (30) we suggest the following procedure. First of all we represent (30) in the form:

$$\hat{g}^{-1}(t - 1) = \frac{\epsilon}{2} t^2 \quad (31)$$

where \hat{g}^{-1} is an inverse operator of \hat{g} , the latter being defined as

$$\hat{g}f(r) = \int g(r, r') f(r') dr'$$

Now we expand $(t - 1)$ in (31) in the series[36] up to the second order in $(x - x')$:

$$t(x', y', z') - 1 = t(x, y, z) - 1 + (x - x') \frac{\partial t}{\partial x} + \frac{(x - x')^2}{2} \frac{\partial^2 t}{\partial x^2} + \dots \quad (32)$$

where we took into account that for obvious physical reasons t does not depend either on y or on z . This expansion is valid for sufficiently smooth function $t(r)$. Therefore, in the case under consideration this substitution is acceptable if we are not too close to the surface (the wall). Substituting (32) into (31), we obtain finally

$$\hat{g}^{-1}(t - 1) \simeq t(x, \epsilon) - 1 + \frac{a^2}{6} \frac{\partial^2 t(x, \epsilon)}{\partial x^2} \quad (33)$$

what results in the following differential equation instead of the integral one:

$$t(\tilde{x}, \epsilon) - 1 - \frac{\partial^2 t(\tilde{x}, \epsilon)}{\partial \tilde{x}^2} = \frac{\epsilon}{2} t^2(\tilde{x}, \epsilon) \quad (34)$$

where

$$\tilde{x} = \frac{x\sqrt{6}}{a}$$

is a reduced distance from the surface.

The differential equation (34) can be solved via the substitution $p(t) = \frac{\partial t}{\partial \tilde{x}}$. We get after some algebra:

$$\tilde{x}(\epsilon, t) = \int_{t_0}^t \frac{dy}{\sqrt{-\frac{2\epsilon}{3}y^3 + 2y^2 - 4y + \frac{4}{3}\frac{(1-2\epsilon)^{3/2}-1+3\epsilon}{\epsilon^2}}} \quad (35)$$

where $t_0 = t(0, \epsilon) \geq 1$ is a boundary value of t to be specified later (one could not define this boundary condition *a priori*, as the boundary $x = 0$ does not belong to the region where the substitution (32) is valid; see section VI for the discussion of the proper choice of t_0) and we have already used the boundary conditions at $+\infty$:

$$\left\{ \begin{array}{l} \lim_{x \rightarrow +\infty} t = \frac{1 - \sqrt{1 - 2\epsilon}}{\epsilon} \\ \lim_{x \rightarrow +\infty} \frac{dt}{d\tilde{x}} = 0 \end{array} \right. \quad (36)$$

to define the last term in the denominator in (35).

Performing the substitution

$$\begin{aligned} \xi &= \sqrt{1 - 2\epsilon} \\ s &= 1 + (\epsilon y - 1)\xi^{-1} \end{aligned} \quad (37)$$

we arrive at the simple integral for the function $\tilde{x}(\epsilon, t)$:

$$\tilde{x}(\epsilon, t) = \sqrt{\frac{3}{2\xi}} \int_{1+(\epsilon t_0-1)/\xi}^{1+(\epsilon t-1)/\xi} \frac{ds}{s\sqrt{3-s}} \quad (38)$$

which we can easily evaluate:

$$\tilde{x}(\xi, t) = \frac{2}{\sqrt{\xi}} \left(\operatorname{arctanh} \frac{\sqrt{2+4\xi+t(\xi^2-1)}}{\sqrt{6\xi}} - \operatorname{arctanh} \frac{\sqrt{2+4\xi+t_0(\xi^2-1)}}{\sqrt{6\xi}} \right) \quad (39)$$

Inverting (39) we obtain the desired partition function $t(\tilde{x})$:

$$t(\tilde{x}) = \frac{1}{\epsilon} \left[1 - \xi - 3\xi \sinh^{-2} \frac{\tilde{x}\sqrt{\xi} + \ln g(\xi, t_0)}{2} \right] \quad (40)$$

where the auxiliary function $g(\xi, t_0)$ reads

$$g(\xi, t_0) = \frac{\sqrt{2+4\xi+t_0(\xi^2-1)} + \sqrt{6\xi}}{\sqrt{2+4\xi+t_0(\xi^2-1)} - \sqrt{6\xi}} \quad (41)$$

Note, that as \tilde{x} tends to infinity, the function $\sinh(\dots)$ in (40) does too and, therefore, the function $t(x)$ approaches its bulk value (18).

V. PARTITION FUNCTION OF A RANDOMLY BRANCHED POLYMER NEAR THE SURFACE

To compute the desired partition function $C_N(r)$ of a single randomly branched polymer, consisting of $N + 1$ links, one of which is fixed at a given point r , we should expand the generating function

$$\rho(\lambda, \epsilon, r) = \frac{\lambda t^3(\epsilon, r)}{6} \quad (42)$$

where t is given by (40), in the power series in ϵ . We perform this expansion in two successive steps. First we expand t in the power series in ξ :

$$\begin{aligned} t = & 2(1 - 3x_0^{-2}) - 2 \left(1 - 3x_0^{-2} + \frac{x_0^2}{5} - \frac{3\sqrt{6}}{5} x_0^{-3} \frac{5t_0^2 + 12 - 10t_0}{(2 - t_0)^{5/2}} \right) (1 - 2\epsilon) \\ & + \frac{4}{63} x_0^{-3} \left(x_0^7 + 2 \left(\frac{6}{2 - t_0} \right)^{7/2} \right) (1 - 2\epsilon)^{3/2} + O((1 - 2\epsilon)^2) \end{aligned} \quad (43)$$

where

$$x_0 = \frac{\tilde{x}}{2} + \frac{\sqrt{6}}{\sqrt{2 - t_0}} \sqrt{6} \left(\frac{x}{2a} + \frac{1}{\sqrt{2 - t_0}} \right) \quad (44)$$

is a reduced coordinate, and we have used (37) to replace ξ by ϵ . Thus, the first singular (with respect to ϵ) term in the series expansion of $t(\epsilon, r)$ is proportional to $(1 - 2\epsilon)^{3/2}$ and not to $(1 - 2\epsilon)^{1/2}$ as in the bulk case. Now, the first singular term in the series for $\rho(\lambda, \epsilon, r)$ equals to

$$\rho_{\text{sing}}^{(1)} = \frac{8x_0^{-3}}{63} z(1 - 3x_0^{-2})^2 \left(x_0^7 + 2 \left(\frac{6}{2 - t_0} \right)^{7/2} \right) (1 - 2\epsilon)^{3/2} \quad (45)$$

Now, taking into account that

$$(1 - 2\epsilon)^{3/2} = 1 - 3\epsilon + \frac{3}{2}\epsilon^2 + 3 \sum_{N=3}^{\infty} \frac{(2N - 5)!!}{N!} \epsilon^N$$

and allowing for the asymptotic behavior of the coefficients in the above sum:

$$\frac{(2N - 5)!!}{N!} = 2^N N^{-5/2} (1 + O(N^{-1}))$$

we obtain that the desired partition function $C_n(r)$ for $n \gg 1$ tends to

$$C_N(x_0) = A(x_0) N^{-\theta} \epsilon^N \quad (46)$$

where the function $A(x)$ depends on the microscopic parameters of the model:

$$A(x_0) = \frac{8}{7} x_0^{-3} (1 - 3x_0^{-2})^2 \left(x_0^7 + 2 \left(\frac{6}{2 - t_0} \right)^{7/2} \right) \quad (47)$$

and the exponent $\theta = \frac{5}{2}$ is universal.

If x_0 is large enough (i.e. we are not too close to the surface), one can neglect all the sub-dominant contributions of x_0 and can rewrite (46)–(47) in a simpler form

$$C_N(r) \simeq \frac{2^N}{N^{3/2}} \left(\frac{x^4}{N a^4} \right) \quad (48)$$

Note that the additional (in comparison with the bulk case) factor

$$\frac{x^4}{N a^4} = \left(\frac{\langle x \rangle}{a N^{1/4}} \right)^4$$

is just the 4-th power of the distance from the surface to the gyration radius of the randomly branched polymer (27). Thus, in contrast to the bulk behavior, the partition function of the randomly branched polymer near the surface carries the information about the spatial dimension of the branched polymer.

VI. THE PROBABILITY OF BRANCHING

Our next objective is to calculate the probabilities of f -functional branchings, $p_f(r, N)$ ($f = 1 \dots 3$) in a $N + 1$ -monomer tree. As we are mostly interested in the case of very large trees we restrict ourselves here to calculation of the limiting values $p_f(r) = \lim_{N \rightarrow \infty} p_f(r, N)$. To do that we should find, according to (16), the asymptotic form of the coefficients $C_N(r)$ and $C_N^{(f)}(r)$ in the series expansions of $t^3(r)$ for $C_N(r)$ and of $(t(r) - 1)^3$, $3(t(r) - 1)^2$, $3(t(r) - 1)$ for $C_N^{(1)}(r)$, $C_N^{(2)}(r)$, $C_N^{(3)}(r)$ respectively. Thus, we find in particular for the probability of junctions ($f = 3$)

$$\begin{aligned} C_N(r) &= \frac{4}{7x_0^3} \left(2 - \frac{6}{x_0^2}\right)^2 \left(x_0^7 + 2 \left(\frac{6}{2-t_0}\right)^{7/2}\right) 2^N N^{-5/2} (1 + O(N^{-1})) \\ C_N^{(3)}(r) &= \frac{4}{7x_0^3} \left(1 - \frac{6}{x_0^2}\right)^2 \left(x_0^7 + 2 \left(\frac{6}{2-t_0}\right)^{7/2}\right) 2^N N^{-5/2} (1 + O(N^{-1})) \end{aligned} \quad (49)$$

and therefore

$$p_3(r) = \left(\frac{x_0^2 - 6}{2x_0^2 - 6}\right)^2 \quad (50)$$

Similarly, one easily finds for the probability of dead ends ($f = 1$):

$$p_1(r) = \lim_{N \rightarrow \infty} \frac{C_N^{(1)}(r)}{C_N(r)} = \frac{x_0^4}{(2x_0^2 - 6)^2} \quad (51)$$

In the Fig. 5 we have plotted the dependencies $p_{1,3}(x_0)$. As $x_0 \rightarrow \infty$ these probabilities approach their bulk values given by Eq.(22).

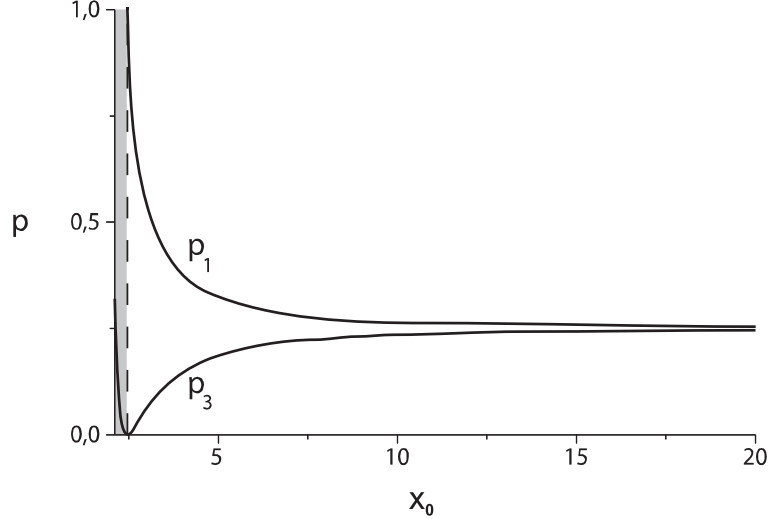


FIG. 5: Profiles of junction points, p_1 , and of dead ends, p_3 . The dashed line corresponds to $x_0 = \sqrt{6}$.

On the other hand, if one chooses t_0 , which is the boundary value of the function $t(x)$ to equal unity ($1 \leq t(x) \leq 2$ for $0 \leq x < \infty$) (see eq.(14)), the value of x_0 approaches $\sqrt{6}$ near the wall and the probabilities of dead ends and junctions tend to unity and zero, respectively. This result seems to be rather natural: as the wall is impenetrable at $x = 0$, there should be mostly dead ends. Therefore we arrive to the conclusion that the choice of $t_0 = 1$ is at least the most natural one thus solving the problem of proper choice of the boundary conditions at $x = 0$ outlined in the discussion after eq. (35). We restrict ourselves to this choice in what follows.

VII. THE CORRELATION FUNCTION IN THE SEMI-SPACE

To find the correlation function $G(r_1, r_2)$ of a randomly branched polymer in a semi-space in 3D we have to solve the equation (17) where the partition function $t(r)$ given by eq. (40). To do that let us multiply (17) by $\epsilon t(r_1)$ and define a new function

$$\Gamma(r_1, r_2) = \epsilon t(r_1)G(r_1, r_2).$$

After such substitution we get

$$\Gamma(r_1, r_2) = \epsilon t(r_1) \left(g(|r_1 - r_2|) + \int g(|r_1 - r_3|) \Gamma(r_3, r_2) d^3 r_3 \right) \quad (52)$$

Similarly to what we have done in the previous sections we substitute $g(|r_1 - r_2|) = \delta(r_1 - r_2)$ into the first term of the r.h.s. of (52) and expand $\Gamma(r_3, r_2)$ up to the second order in $(r_1 - r_3)$. Evaluating the integrals we arrive at the following differential equation

$$\Gamma(u, v, \rho) = \epsilon t(u + v) (\Gamma(u, v, \rho) + \Delta_{u, \rho} \Gamma(u, v, \rho)) \quad (53)$$

where

$$v = \frac{\sqrt{6}x_2}{a}; \quad u = \frac{\sqrt{6}(x_1 - x_2)}{a}; \quad \rho = \frac{\sqrt{6((y_1 - y_2)^2 + (z_1 - z_2)^2)}}{a} \quad (54)$$

In what follows we assume $u > 0$. Such choice does not lead to any loss of generality due to the symmetry of the correlation function: $G(r_1, r_2) = G(r_2, r_1)$ and the case of $u = 0$ is to be taken into account via boundary conditions).

Now we seek for the solution of eq.(53) in the form

$$\Gamma(u, v, \rho) = \int f(c, v) \Gamma_1(c, u) \Gamma_2(c, \rho) dc \quad (55)$$

where the arbitrary function $f(c, v)$ is to be determined later by the boundary conditions. The ansatz (55) allows us to separate the variables in (53). We thus obtain a simple equation for Γ_2

$$\rho^{-1} \frac{\partial}{\partial \rho} \left(\rho \frac{\partial \Gamma_2}{\partial \rho} \right) = c^2 \Gamma_2 \quad (56)$$

the general solution of which is

$$\Gamma_2(c, \rho) = A J_0(c\rho) + B Y_0(c\rho) \quad (57)$$

where J_0 and Y_0 are the Bessel functions of the first and second kind. Due to the boundary condition $\Gamma(c, 0) < \infty$, we set $B = 0$.

The equation for Γ_1 is as follows:

$$\frac{\partial^2 \Gamma_1}{\partial u^2} = \left(c + \frac{1 - \epsilon t(u + v)}{\epsilon t(u + v)} \right) \Gamma_1 \quad (58)$$

If we plug the exact expression (40) for $t(u + v)$ into (58), the resulting equation seems to be not solvable. Since we are interested mainly in the $\xi \rightarrow 0$ limit (i.e. $N \rightarrow \infty$), we can expand the function $t(u + v)$ at small ξ keeping $u + v$ fixed:

$$\varphi(u, v) = \frac{1 - \epsilon t(u + v)}{\epsilon t(u + v)} \simeq \frac{12}{(u + v + a)^2 - 12} \quad (59)$$

where $a = 2\sqrt{6} = \lim_{\xi \rightarrow 0} (\xi^{-1/2} \ln g(\xi))$. The expansion (59) is valid for $(u + v) \lesssim \xi^{-1/2}$. Further simplification of (58) implies the replacement of (58) by the function of the form

$$\tilde{\varphi}(u, v) = \frac{c_1(v)}{(u + c_2(v))^2}$$

to preserve the true limiting behavior of (58) and to make at the same time the equations (58)–(59) solvable. Resolving the set of algebraic equations

$$\begin{cases} \varphi(u=0, v) = \tilde{\varphi}(u=0, v) \\ \left. \frac{\partial \varphi(u, v)}{\partial u} \right|_{u=0} = \left. \frac{\partial \tilde{\varphi}(u, v)}{\partial u} \right|_{u=0} \end{cases}$$

we obtain finally

$$\tilde{\varphi}(u) \simeq \frac{12((a+v)^2 - 12)}{((a+v)(u+a+v) - 12)^2} \quad (60)$$

In the limit of $u \rightarrow \infty$ the function $\varphi(u)$ does not completely vanish but approaches the bulk value $\xi/(1-\xi) \ll 1$. Thus, the function

$$\tilde{\varphi}(u) = \frac{\xi}{1-\xi} + \frac{12((a+v)^2 - 12)}{((a+v)(u+a+v) - 12)^2} \quad (61)$$

seems to be a good approximation of φ in the whole range of parameters. The comparison of the functions $\tilde{\varphi}(u, v)$ and $\varphi(u, v) = \frac{1-\epsilon t(u+v)}{\epsilon t(u+v)}$ for two different values of the parameter v ($v=0$ and $v=3$) is shown in the Fig.6.

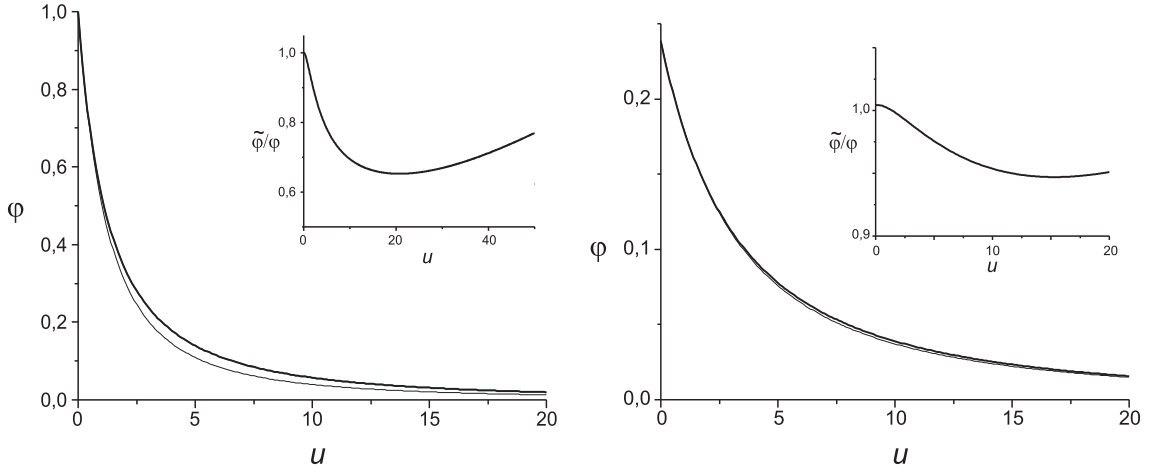


FIG. 6: Plots of the functions $\tilde{\varphi}(u, v)$ (thin line) and $\varphi(u, v) = \frac{1-\beta t(u+v)}{\beta t(u+v)}$ (bold line) for $v=0$ (left) and for $v=3$ (right). The insertions in both plots show the ratio $\tilde{\varphi}/\varphi$.

As one sees, the approximation of the exact function $\varphi(u, v)$ by the function $\tilde{\varphi}(u, v)$ is reasonable for $v=0$ and already very good for $v=3$. Let us recall that the distance from the wall $v=3$ in the non-renormalized (initial) coordinates according to (54) is $x_2 = 3a/\sqrt{6} \approx 1.22a$.

The resulting differential equation

$$\Gamma_1'' = (c^2 + \tilde{\varphi}(u))\Gamma_1$$

is easy to solve. Taking into account the boundary condition $\Gamma_1 \rightarrow 0$ at infinity, one obtains the final result in the following form

$$\Gamma_1 = \sqrt{aw} K_\nu(c'w) \quad (62)$$

where $K_\nu(c'w)$ is a modified Bessel function of 2-nd kind of order ν , and the parameters are as follows:

$$w = u + v + a - \frac{12}{v+a}; \quad \nu = \frac{\sqrt{49(v+a)^2 - 576}}{2(v+a)}; \quad c' = \sqrt{c^2 + \frac{\xi}{1-\xi}} \quad (63)$$

Substituting (57), (62) into (55) we arrive at the desired solution of the equation (53):

$$\Gamma(u, v, \rho) = \int f(c, v) J_0(c\rho) \sqrt{aw} K_\nu(c'w) dc \quad (64)$$

To make this equation comparable with that in the bulk case (28) let us introduce the new variables:

$$C = \sqrt{\frac{c^2(1-\xi)}{\xi} + 1}; \quad \begin{Bmatrix} R \\ U \\ V \\ W \end{Bmatrix} = \sqrt{\frac{\xi}{1-\xi}} \begin{Bmatrix} \rho \\ u \\ v \\ w \end{Bmatrix} \quad (65)$$

After such a substitution the correlation function acquires the form

$$\Gamma(U, V, R) = \int f(C, V) J_0(R\sqrt{C^2-1}) \sqrt{W} K_\nu(CW) dC \quad (66)$$

where we have omitted all the unimportant spatially independent factors. The unknown function $f(C, V)$ is to be determined by the boundary conditions

$$\Gamma(U, V, R) \Big|_{U \gg 1 \text{ or } V \gg 1} \rightarrow \epsilon t_{\text{bulk}} G_{\text{bulk}}(\sqrt{U^2 + R^2}) \quad (67)$$

One thus easily finds

$$f(C, V) \sim \sqrt{C} \exp \left[C \left(V + A - \frac{12}{V + A} \right) \right], \quad C > 1 \quad (68)$$

where we have omitted once again all terms which do not depend on c and v . Let us stress that the condition $C > 1$ ultimately defines the limits of integration in (68). Thus we arrive finally at the following expression for the correlation function

$$G(u, v, \rho) = \int_1^{+\infty} \sqrt{CW} e^{C(V+A-12(V+A)^{-1})} K_\nu(CW) J_0(R\sqrt{C^2-1}) dC \quad (69)$$

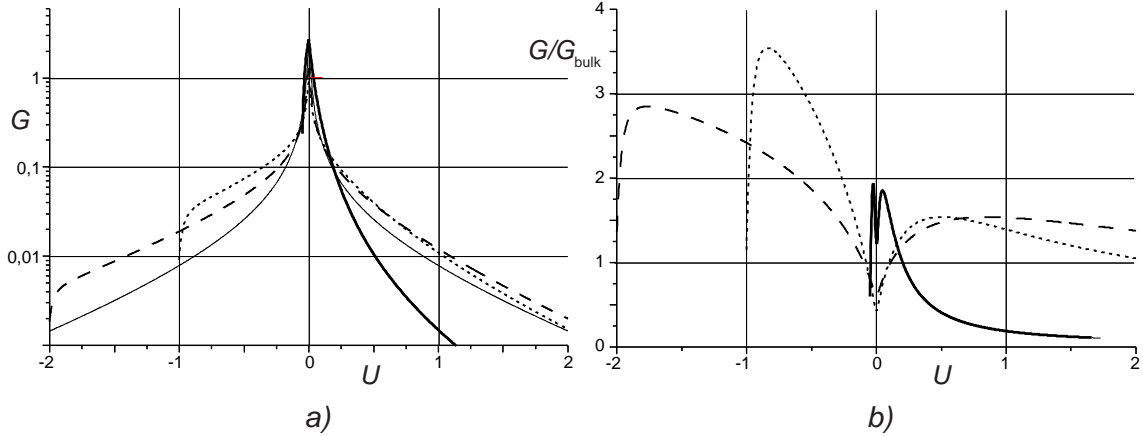


FIG. 7: a) The correlation functions $G(U, V, R)$ for $\xi = 10^{-4}$, $R = 0.01$ and $V = 0.05$ (dotted line), $V = 1$ (dashed line) and $V = 2$ (dot-dashed line) as compared to the bulk correlation function for similar R (bold line). All the curves are normalized by the condition $\int G(U, V, R) dU = 1$; b) The ratios $G(U, V, R)/G_{\text{bulk}}(U, R)$ for values of ξ , R and V similar to that in a).

Figure 7 shows the dependencies $G(U)$ for different values of V as compared with the bulk behavior. One sees easily how the presence of the wall affects the correlation function. In particular, it is interesting to note the increase of the polymer density in the vicinity of the wall, and also the smaller increase of the density in the outer region due to polymer-wall hardcore repulsion. The rapid decrease of the correlation function for $V = 0.05$ with the growth of U is due to the fact that in the system controlled by the fugacity ϵ , the mean size of clusters in the vicinity of the wall is much smaller than that in the bulk (this is clearly outlined by the fact that $t(x) \rightarrow 1$ as $x \rightarrow 0$).

VIII. DISCUSSION

As it is mentioned in the Introduction, the statistics of randomly branched ideal polymer chain near the impenetrable boundary was studied by supersymmetric methods in the work [30], where the authors follow the general scheme of the supersymmetric "dimensional reduction" for branched random walks formulated for the first time in [21] and exploited later in [22, 23]. Let us outline some results on conformational properties of branched polymers without the volume interactions, obtained in [30] and compare these results to the ones computed in our paper.

The authors of the paper [30] have computed many thermodynamic properties of branched polymer chains near the repulsive and the adsorbing impenetrable surfaces in 3D. We would pay the most attention to the "non-adsorbing" (i.e. repulsive) regime, comparing the surface critical exponent θ and the distribution function of [30] to the same values computed in the present work.

Let us recall that the main strategy of the supersymmetric approach for branched polymers consists of the possibility to perform the dimensional reduction and to map the partition function of the d -dimensional branched polymer onto the partition function of the scalar field in $d-2$ dimensions at the Yang-Lee edge singularity [21, 22, 23]. Apparently the presence of the surface in d space breaks the full supersymmetry, however the arguments of [23] allow to conclude that for $d \geq 3$ even the restricted supersymmetry still possess the dimensional reduction. Such construction enables the authors of [30] to map the randomly branched polymers near the surface onto the semi-infinite one-dimensional Ising chain in an imaginary bulk and surface fields.

In [30] the authors have got the following results below the adsorbing transition point for the quantities of our interest:

$$\begin{cases} \theta = \frac{5}{2} \\ G_N(z, z') = \operatorname{erfc}(\zeta - \zeta') + \operatorname{erfc}(\zeta + \zeta') - 2\operatorname{erfc}(\zeta) + 16\Gamma^2 \exp[\Gamma(\Gamma - 2\zeta - 2\zeta')] \end{cases} \quad (70)$$

where

$$\zeta = z\sqrt{N}, \quad \zeta' = z'\sqrt{N}, \quad \Gamma = E\sqrt{N}$$

and E is some constant independent of N .

It seems interesting to compare (70) to the same quantities obtained by the straightforward approach developed in our paper. It can be seen that the surface critical exponents $\theta = \frac{5}{2}$ obtained in our work (eqs. (46), (48)) coincides with the one of [30] (computed also in [29]). The comparison of the correlation functions is a bit cumbersome as the results (70) and (69) are obtained in different spaces (connected by the Laplace transform). However it is rather easy to see that these results are significantly different. Indeed, while (70) suggests the characteristic length scale of the problem to be of order $r \sim \sqrt{N}$, our approach results into $r \sim N^{1/4}$, as the integral in (69) is mostly defined by its lower limit (see also (48), where this characteristic scale is clearly outlined). Let us stress that our result coincides with that obtained for the characteristic scale for the randomly branched polymer in the bulk (compare to [34, 35] and equations (26), (27) in this paper), which make us convinced that it is a genuine one.

Note also that despite we have made the approximation (61) during the evaluation of the correlation function $G(u, v, \rho)$, the equation (53) itself is exact (up to the expansion of the Gaussian kernel $g(|\mathbf{r}, \mathbf{r}'|)$ in the Taylor series) and exactly [37] solves the problem of statistics of branched polymer near the impenetrable boundary in 3D. We see that the results of [30] do not match our solutions. This mismatch can be connected with some hidden approximations in the supersymmetric approach with a broken translational invariance. A presence of different methods allowing to study the statistics of an ideal branched polymer in the 3D semi-space, can be used for deeper understanding of the applicability of the supersymmetric approach for branched polymers.

Acknowledgments

The authors are grateful to J.-F. Joanny for valuable stimulating discussions. M.V.T. thanks the laboratory LPTMS (Université Paris Sud, Orsay) for hearty welcome.

[1] P.J. Flory, *Principles of Polymer Chemistry* (Cornell Univ. Press: New York, 1953)

- [2] P.G. de Gennes, *Scaling Concepts in Polymer Physics*, (Cornell Univ. Press: Ithaca, 1979)
- [3] A.Yu. Grosberg, A.R. Khokhlov, *Statistical Physics of Macromolecules* (AIP Press: New York, 1994)
- [4] P.J. Flory, J. Am. Chem. Soc., **63**, 3083, 3091, 3096, 1941.
- [5] W.H. Stockmayer, J.Chem. Phys., **11** 45 (1943)
- [6] S. Alexander, G.S. Grest, H. Nakanishi and T.A. Witten Jr., J. Phys. A: Math. Gen., **17** L185 (1984)
- [7] C.P. Lusignan, T.H. Mourey, J.C. Wilson, R.H. Colby, Phys. Rev. E, **52** 6271 (1995)
- [8] J.Isaacson, T.C. Lubensky, Phys.Rev.A, **20** 2130 (1979)
- [9] A. Coniglio, H.E. Stanley and W. Klein, Phys. Rev. Lett. **42** 518 (1979)
- [10] S.I. Kuchanov, S.V. Korolev, S.V. Panyukov, Adv. Chem. Phys., **72** 115 (1988)
- [11] P.D. Gujrati, J.Chem. Phys., **98** 1613 (1993)
- [12] I.Ya. Erukhimovich, in Proceedings of the All-Union Conference "Mathematical Methods for Investigation of Polymers", Akad. Nauk SSSR, p. 52 (Puschino, 1982); I.Ya. Erukhimovich, Ph.D. Thesis, Moscow, 1979
- [13] I.Ya. Erukhimovich, JETP, **81** 553 (1995)
- [14] I.Ya. Erukhimovich, M.V. Thamm, A.V. Ermoshkin, Macromolecules, **34** 5653 (2001)
- [15] A.N. Semenov, M. Rubinstein, Macromolecules, **31** 1373 (1997)
- [16] S.V. Panyukov, JETP, **61** 1065 (1985)
- [17] T.E. Harris, *The theory of branching processes*, Die Grundlehren der Mathematischen Wissenschaften, **119** (Springer: Berlin, 1963);
- [18] N. Ikeda, M. Nagasawa, and S. Watanabe, J. Math. Kyoto Univ. **8** 233 (1968) (Part I); **8** 365 (1968) (Part II); **9** 95 (1969) (Part III)
- [19] Dynkin E.B., Ann. Prob., **19** 1157 (1991); **21** 1185 (1993)
- [20] J. Engländer, A. Kyprianou, Markov branching diffusions: Martingales, Girsanov type theorems, and application to the long term behavior, preprint (October, 2001)
- [21] G. Parisi, N. Sourlas, Phys. Rev. Lett., **43** 744 (1979); **46** 871 (1981)
- [22] Y. Shapir, J. Phys. A, **15** L433 (1982); Phys. Rev. A, **28** 1893 (1983)
- [23] J. Cardy, Phys. Lett. B, **125** 470 (1983)
- [24] N. Sourlas, Physica D, **15** 115 (1985); J. Cardy, Physica D, **15** 123 (1985); Y. Shapir, Physica D, **15** 129 (1985)
- [25] D.C. Brydges, J.Z. Imbrie, J. Stat. Phys. **110** 503 (2003); Comm. Math. Phys. **239** 523 (2003)
- [26] J.Z. Imbrie, Ann. Henri Poincaré **4** S445 (2003)
- [27] F. Spitzer, *Principles of Random Walk* 2nd Ed., (Springer: New-York, 1976)
- [28] W. Feller, *An Introduction to Probability Theory and Its Applications*, (Wiley, 1968)
- [29] K. De'Bell, T. Lookman, D. Zhao, Phys. Rev. A, **44** 1390 (1991); T. Lookman, D. Zhao, K. De'Bell, **44** 4814 (1991)
- [30] H.K. Janssen, A. Lyssy, Phys. Rev. E, **50** 3784 (1994)
- [31] I.M. Lifshits, A.Yu. Grosberg, A.R. Khokhlov, Rev. Mod. Phys., **50** 683 (1978)
- [32] G.E. Ulenback and G.W. Ford, *Lectures in Statistical Mechanics* (AMS: Providence, 1963)
- [33] A.M. Gutin, A.Yu. Grosberg, E.I. Shakhnovich, J.Phys. A: Math. Gen., **26** 1037 (1993)
- [34] M. Daoud, J.F. Joanny, J. de Physique, **42** 1359 (1981)
- [35] B. Zimm, W.H. Stockmayer, J. Chem. Phys., **17** 301 (1949)
- [36] This expansion is somewhat similar to that for of the partition function $G_N(x, x')$ in the smoothly changing external field made in [31], where a similar problem for the linear polymers is addressed.
- [37] The approximations made in course of the derivation of Eq.(53) are identical to the ones obtained in the derivation of the diffusion equation for linear polymers in 3D semi-dimensional space with Dirichlet boundary conditions at the wall.