

Equation of state and elastic properties of face-centered-cubic FeMg alloy at ultrahigh pressures from first-principles

C. Asker, U. Kargén, L. Dubrovinsky and I.A. Abrikosov

October 24, 2018

Abstract

We have calculated the equation of state and elastic properties of face-centered cubic Fe and Fe-rich FeMg alloy at ultrahigh pressures from first principles using the Exact Muffin-Tin Orbitals method. The results show that adding Mg into Fe influences strongly the equation of state, and cause a large degree of softening of the elastic constants, even at concentrations as small as 1-2 at. %. Moreover, the elastic anisotropy increases, and the effect is higher at higher pressures.

1 Introduction

The properties of iron at ultrahigh pressure have been studied extensively, both experimentally and theoretically. (Belonoshko et al., 2003, 2008; Dubrovinskaia et al., 2005; Dubrovinsky et al., 2003, 2007; Kuwayama et al., 2008; Lin et al., 2002; Mikhaylushkin et al., 2007; Steinle-Neumann et al., 2001; Vočadlo, 2007; Vočadlo et al., 2003, 2008) Apart from a better understanding of one of our most important metals, one aim is to find the composition and structure of the Earth’s core, which is likely to be made up of iron mixed with lighter elements.

For a light element to be considered as a possible component in the Earth’s core, it should naturally alloy with Fe and be abundant within the Earth. While it is well-known that Mg is abundant (Anderson, 1989), until recently, magnesium was not considered as a possible candidate to be one of the light elements in the core, mainly because iron and magnesium differ too much in size to form alloys. However, it has been shown both theoretically and experimentally that at high pressures, the size mismatch of iron and magnesium has decreased enough so that FeMg alloys can form (Dubrovinskaia et al., 2005; Takafuji et al., 2005). At oxygen fugacity corresponding to Mg-MgO buffer, up to 10 *at.*% of Mg could be dissolved in hcp Fe at about 100 GPa pressure (Dubrovinskaia et al., 2005). In presence of magnesiowüstite (Mg,Fe)O and dense silicate perovskite (Mg,Fe)SiO₃, about 1 *at.*% Mg was observed in hcp Fe (Takafuji et al., 2005).

We acknowledge that the relatively high oxygen fugacity in the Earth interior, makes Mg a somewhat unlikely candidate for the main light element in the core (Dubrovinskaia et al., 2005). Still its presence has not been ruled out, and the study of its effect on the properties of Fe is motivated.

The elastic properties of iron rich FeMg alloys were recently reported for the hexagonal close-packed (hcp) (Kádas et al., 2008) and for body-centered cubic (bcc) (Kádas et al., 2009) structures. However, Mikhaylushkin *et al.* have shown that the fcc phase of Fe can not be ruled out as a possible structure stable at conditions corresponding to the Earth’s core. (Mikhaylushkin et al., 2007) Since the energy difference between the competing phases

of Fe at Earth core conditions is extremely small (Mikhaylushkin et al., 2007), we therefore believe it is important to investigate elastic properties for the face-centered cubic structure (fcc) of Fe rich FeMg alloy. In particular, in a recent study (Asker et al., 2009) we have demonstrated that the elastic anisotropy of fcc Fe, estimated according to Hill’s definition (Grimvall, 1999), is much higher than for hcp Fe, and the effect persists in FeNi alloys.

We report in this letter first-principles calculations of the equation of state and elastic properties of fcc Fe, Fe₉₈Mg₀₂, Fe₉₅Mg₀₅ and Fe₉₀Mg₁₀ at ultrahigh pressures. The calculations have been carried out using the EMTO-CPA method (Vitos et al., 2001) (described below), which is a suitable tool for calculating elastic properties in alloys.

The paper is organized as follows: in Sec. 2 we outline the theory used for calculating elastic properties from first-principles by the EMTO-CPA method together with details of our calculations and in Sec. 3 we present the equation of state, the single crystal and polycrystalline elastic properties of fcc FeMg.

2 Theory

In this work, we first calculated the total energy for a set of atomic volumes between 41.6, and 78.0 *Bohr*³. The results from these calculations were then used to find the equation of state (EOS) through the Birch-Murnaghan scheme (Birch, 1947) (3rd order). The EOS provides a relation between volume and pressure as well as allows us to study the pressure dependence of the bulk modulus.

In cubic structures, there are three independent elastic constants: c_{11} , c_{12} and c_{44} . (Grimvall, 1999) The c' elastic constant (also known as Zener’s elastic constant) can be obtained from the orthorhombic structure with the following deformation (Vitos, 2007):

$$\mathbf{I} + \mathbf{D}_{\mathbf{O}} = \begin{pmatrix} 1 + \delta & 0 & 0 \\ 0 & 1 - \delta & 0 \\ 0 & 0 & \frac{1}{1 - \delta^2} \end{pmatrix} \quad (1)$$

The change in total energy upon distortion is

$$\Delta E = 2V \cdot c' \cdot \delta^2 + \mathcal{O}(\delta^4) \quad (2)$$

Now the c_{11} and c_{12} can be calculated from the relations between c' and the bulk modulus:

$$B = \frac{c_{11} + 2c_{12}}{3} \quad (3)$$

and

$$c' = \frac{c_{11} - c_{12}}{2} \quad (4)$$

From Eqs. (2,3,4) the c_{11} and c_{12} elastic constants can be obtained.

Next, the c_{44} elastic constant can be obtained by performing monoclinic distortion (Vitos, 2007):

$$\mathbf{I} + \mathbf{D}_M = \begin{pmatrix} 1 & \delta & 0 \\ \delta & 1 & 0 \\ 0 & 0 & \frac{1}{1-\delta^2} \end{pmatrix} \quad (5)$$

In this case the change in energy is:

$$\Delta E = 2V \cdot c_{44} \cdot \delta^2 + \mathcal{O}(\delta^4) \quad (6)$$

In the calculations of both c' and c_{44} the distortions used were $\delta = [0.00, 0.01, \dots, 0.05]$. The elastic constants were then obtained from (linear) interpolations of the total energy as function of the *square* of the distortion, $\Delta E_{tot} = \Delta E_{tot}(\delta^2)$. The motivation for this procedure is that it simplifies the choice of suitable distortions, and is numerically preferable over interpolation of distortion. In this work we only do volume-conserving distortions. The reason for this is that we seek to calculate the elastic properties as functions of pressure, but in the computational setup we must use volume (rather than pressure) as input parameter. The EOS can then be used to obtain the elastic constants as functions of pressure. Also, the total energy depends more strongly on volume than on the distortions (Steinle-Neumann et al., 1999), indicating that it should be more stable numerically to do volume-conserving distortions whenever possible.

The elastic constants described above (except B) are single-crystal elastic constants. When doing measurements, one is often dealing with polycrystalline

samples of a material, and hence the single-crystal constants should be averaged in a suitable way to facilitate comparison between experiments and theoretical calculations. The polycrystalline shear moduli defined by Reuss and Voigt are (Grimvall, 1999):

$$G_R = \frac{5(c_{11} - c_{12})c_{44}}{4c_{44} + 3(c_{11} - c_{12})} = \frac{5c'c_{44}}{2c_{44} + 3c'} \quad (7)$$

$$G_V = \frac{c_{11} - c_{12} + 3c_{44}}{5} = \frac{2c' + 3c_{44}}{5}, \quad (8)$$

respectively. In the case of cubic systems, the Reuss and Voigt bulk moduli are equal, and defined in Eq.(3).

Further, the elastic anisotropy according to Hill is the weighted difference between the Voigt and Reuss shear moduli:

$$A_{VRH} = \frac{G_V - G_R}{G_V + G_R}, \quad (9)$$

and hence is called the *Voigt-Reuss-Hill* (VRH) anisotropy (Grimvall, 1999).

All the calculations in this work have been carried out within Density-Functional Theory (Hohenberg and Kohn, 1964; Kohn and Sham, 1965) (DFT) using the *Exact Muffin-tin Orbital Method* (EMTO) (Andersen et al., 1994; Vitos, 1999, 2001). The problem of disorder was treated with the Coherent Potential Approximation (CPA) (Soven, 1967; Velicky et al., 1968), implemented in the EMTO-CPA (Vitos et al., 2001) method. For exchange and correlation the Local-Density approximation (LDA), parametrized by Perdew, Burke and Ernzerhof (Perdew et al., 1996), was used. After self-consistency had been reached in the LDA calculations, the total energy was calculated with Full Charge Density Technique (Vitos, 2007; Vitos et al., 1997) (FCD). In this last step the Generalized Gradient Approximation (GGA) was used. This procedure provides essentially the same materials properties as those of a self-consistent GGA scheme for non-magnetic systems. While calculations are done for $T = 0$ K, the effect of temperature on elastic properties is expected to decrease with increasing pressure (Anderson, 1989).

We have performed the calculations for Fe , $Fe_{98}Mg_{02}$, $Fe_{95}Mg_{05}$ and $Fe_{90}Mg_{10}$ in order to investigate the effects of alloying Mg in Fe at small Mg content.

For the EMTO calculations, the integration in reciprocal space was performed over a grid of $29 \times 29 \times 29$ points, and the Green's function was integrated using 16 points in the complex energy plane. The basis set used s, p, d, f orbitals.

3 Results

The volumes as function of pressure for pure Fe and for $Fe_{90}Mg_{10}$ are shown in Fig. 1. From this figure it is clear that adding Mg to Fe increases the volume corresponding to a certain pressure. This is expected due to the larger atomic size of Mg, and is well-known from earlier work. When the pressure is increased, the difference in volumes decreases, which is due to the fact that Mg has higher compressibility than Fe. (Dubrovinskaia et al., 2005)

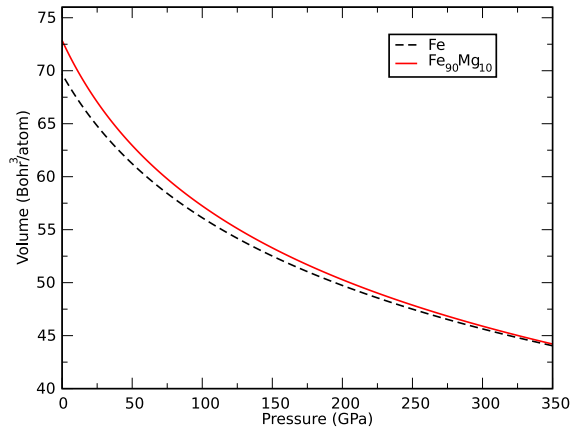


Figure 1: (Color online) Volume as function of pressure in fcc $Fe_{90}Mg_{10}$ (red full line) and pure Fe (black dashed line).

In Fig. 2 we report the density as function of pressure. The results show that adding Mg into Fe decreases the density, which is expected. The results are similar to that reported earlier for hcp Fe-Mg al-

loys (Kádas et al., 2008). The density for $Fe_{90}Mg_{10}$ lies close to those of the Preliminary Reference Earth Model (PREM) (Dziewonski and Anderson, 1981). However, including temperature effects in our calculations is likely to change the agreement. From the inset, showing the concentration dependence at $P = 350$ GPa, we see that adding 2 % Mg causes the density to decrease about 1.5 %.

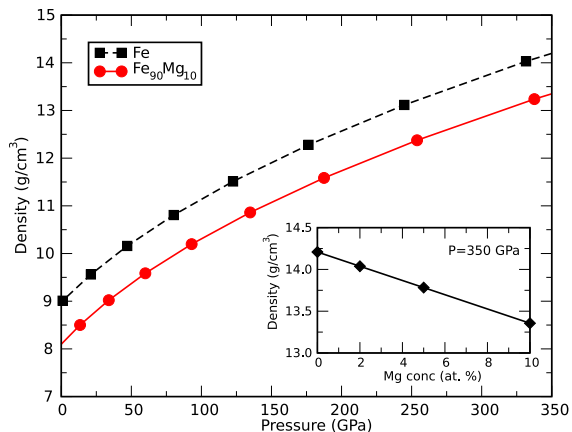


Figure 2: (Color online) Density as function of pressure in fcc $Fe_{90}Mg_{10}$ (red full line) and pure Fe (black dashed line). The inset shows the density as function of Mg content for $P = 350$ GPa.

Next, Fig. 3 shows the bulk modulus as function of pressure. Also here the results are similar to those reported for hcp (Kádas et al., 2008). The bulk modulus is about 55 GPa lower for $Fe_{90}Mg_{10}$ than for pure Fe over the whole pressure range considered here, indicating that the FeMg alloy is indeed softer than pure Fe. Also here we note that the bulk modulus for $Fe_{90}Mg_{10}$ is close to that of the PREM (Dziewonski and Anderson, 1981), but temperature effects may change this, and other elastic properties may not agree to such a large degree. Still, this work aims to show the effects of adding Mg in Fe, which is still likely to be important at elevated temperatures. At 350 GPa, adding 2 % Mg decreases the bulk modulus by about 1.0 %.

The single-crystal elastic constants are shown in Fig. 4. It is interesting to note that both c_{11} and c_{44}

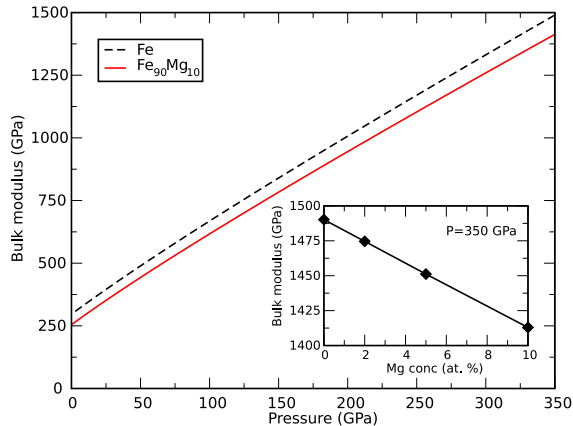


Figure 3: (Color online) Bulk modulus as function of pressure in fcc $Fe_{90}Mg_{10}$ (red full line) and pure Fe (black dashed line). The inset shows the bulk modulus as function of Mg content for $P = 350$ GPa.

show considerable softening when adding Mg . This is also evident for c' , which is shown for comparison. However, the c_{12} elastic constant is almost constant, and for very high pressures it even increases a little when adding Mg . This can be understood from the relations used to obtain c_{11} and c_{12} from c' and the bulk modulus:

$$\begin{aligned} c_{11} &= B + \frac{4}{3}c' \\ c_{12} &= B - \frac{2}{3}c' \end{aligned} \quad (10)$$

Since both the bulk modulus and c' show similar behavior when adding Mg , c_{11} will follow the same trend. However, Eq. (10) suggests that for c_{12} the effect is to some extent canceled out. This can also be seen from the inset for c_{12} in Fig. 4. For $P = 350$ GPa, adding 2 % Mg decreases c' by about 8.2 %, c_{11} by about 2.4 %, c_{12} only 0.1 % and c_{44} by 3.6 %.

The polycrystalline elastic constants are shown in Fig. 5. This figure shows that not just the single-crystal elastic constants change considerably when going from pure Fe to $Fe_{90}Mg_{10}$. A large degree of softening takes place for both G_R and G_V when adding Mg to Fe. For $P = 350$ GPa, adding 2 % Mg

decrease G_V by 4.3 % and G_R by 6.9 %.

Fig. 6 shows the Voigt-Reuss-Hill elastic anisotropy (A_{VRH}) as function of pressure for pure fcc Fe and for fcc $Fe_{90}Mg_{10}$. This graph shows that adding 10% Mg into Fe cause a remarkable increase of the anisotropy. At 300 GPa, the anisotropy is about 40% higher for fcc $Fe_{90}Mg_{10}$ than for pure fcc Fe. The pressure dependence of the anisotropy is also higher for $Fe_{90}Mg_{10}$ than for pure Fe.

4 Conclusion

We have calculated the elastic properties of fcc Fe and $Fe_{90}Mg_{10}$ random alloy up to pressures of the Earth's core from first-principles methods. We show that adding 10 at. % Mg into iron has a substantial effect on the single crystal elastic constants. Moreover, even as small Mg concentrations as 2 % substantially affect some elastic constants, ie c' which decreases by 8.2 % at 350 GPa. Further we find that the effect on the elastic anisotropy is remarkably high and is higher for the fcc FeMg alloy than for pure fcc Fe. We therefore conclude that the possibility of Mg in the Earth's core must be included in models, even though it may not be the dominant light element.

5 Acknowledgments

Useful discussions with L. Vitos are gratefully acknowledged. We are grateful for financial support from the Swedish research council and the Göran Gustafsson Foundation for Research in Natural Sciences and Medicine. The National Supercomputer centre (NSC) and Center for Parallel Computers (PDC) are acknowledged for computer support.

References

Andersen, O. K., Jepsen, O., Krier, G., 1994. Exact Muffin-Tin Orbital Theory. World Science Publishing Co.

- Anderson, D. L., 1989. *Theory of the Earth*. Blackwell Scientific Publications.
- Asker, C., Vitos, L., Abrikosov, I. A., 2009. Elastic constants and anisotropy in feni alloys at high pressures from first-principles calculations. *Physical Review B (Condensed Matter and Materials Physics)* 79 (21), 214112.
- Belonoshko, A. B., Ahuja, R., Johansson, B., August 2003. Stability of the body-centered cubic phase of iron in the Earth's inner core. *Nature* 424, 1032.
- Belonoshko, A. B., Skorodumova, N. V., Rosengren, A., Johansson, B., 2008. Elastic Anisotropy of Earth's Inner Core. *Science* 319 (5864), 797–800.
- Birch, F., Jun 1947. Finite elastic strain of cubic crystals. *Phys. Rev.* 71 (11), 809–824.
- Dubrovinskaia, N., Dubrovinsky, L., Kantor, I., Crichton, W. A., Dmitriev, V., Prakapenka, V., Shen, G., Vitos, L., Ahuja, R., Johansson, B., Abrikosov, I. A., 2005. Beating the miscibility barrier between iron group elements and magnesium by high-pressure alloying. *Physical Review Letters* 95 (24), 245502.
- Dubrovinsky, L., Dubrovinskaia, N., Langenhorst, F., Dobson, D., Rubie, D., Geszmann, C., Abrikosov, I. A., Johansson, B., Baykov, V. I., Vitos, L., Bihan, T. L., Crichton, W. A., Dmitriev, V., Weber, H.-P., Mar. 2003. Iron-silica interaction at extreme conditions and the electrically conducting layer at the base of Earth's mantle. *Nature* 422 (6927), 58–61.
- Dubrovinsky, L., Dubrovinskaia, N., Narygina, O., Kantor, I., Kuznetsov, A., Prakapenka, V. B., Vitos, L., Johansson, B., Mikhaylushkin, A. S., Simak, S. I., Abrikosov, I. A., Jun. 2007. Body-Centered Cubic Iron-Nickel Alloy in Earth's Core. *Science* 316 (5833), 1880–1883.
- Dziewonski, A. M., Anderson, D. L., Jun. 1981. Preliminary reference earth model. *Physics of The Earth and Planetary Interiors* 25 (4), 297–356.
- Grimvall, G., 1999. *Thermophysical Properties of Materials*, 1st Edition. Elsevier.
- Hohenberg, P., Kohn, W., November 1964. Inhomogeneous Electron Gas. *Phys. Rev.* 136 (3B), B864–B871.
- Kádas, K., Vitos, L., Ahuja, R., Jul. 2008. Elastic properties of iron-rich hcp Fe-Mg alloys up to Earth's core pressures. *Earth and Planetary Science Letters* 271 (1-4), 221–225.
- Kádas, K., Vitos, L., Johansson, B., Ahuja, R., 2009. Stability of body-centered cubic iron-magnesium alloys in the Earth's inner core. *Proceedings of the National Academy of Sciences* 106 (37), 15560–15562.
- Kohn, W., Sham, L. J., November 1965. Self-Consistent Equations Including Exchange and Correlation Effects. *Phys. Rev.* 140 (4A), A1133–A1138.
- Kuwayama, Y., Hirose, K., Sata, N., Ohishi, Y., 2008. Phase relations of iron and iron-nickel alloys up to 300 GPa: Implications for composition and structure of the Earth's inner core. *Earth and Planetary Science Letters* 273 (3-4), 379 – 385.
- Lin, J.-F., Heinz, D. L., Campbell, A. J., Devine, J. M., Shen, G., Jan. 2002. Iron-Silicon Alloy in Earth's Core? *Science* 295 (5553), 313–315.
- Mikhaylushkin, A. S., Simak, S. I., Dubrovinsky, L., Dubrovinskaia, N., Johansson, B., Abrikosov, I. A., Oct. 2007. Pure iron compressed and heated to extreme conditions. *Phys. Rev. Lett.* 99 (16), 165505–4.
- Perdew, J. P., Burke, K., Ernzerhof, M., Oct 1996. Generalized gradient approximation made simple. *Phys. Rev. Lett.* 77 (18), 3865–3868.
- Soven, P., April 1967. Coherent-Potential Model of Substitutional Disordered Alloys. *Phys. Rev.* 156 (3), 809–813.
- Steinle-Neumann, G., Stixrude, L., Cohen, R. E., Jul 1999. First-principles elastic constants for the hcp

- transition metals Fe, Co, and Re at high pressure. *Phys. Rev. B* 60 (2), 791–799.
- Steinle-Neumann, G., Stixrude, L., Cohen, R. E., Gulseren, O., Sep. 2001. Elasticity of iron at the temperature of the Earth’s inner core. *Nature* 413 (6851), 57–60.
- Takafuji, N., Hirose, K., Mitome, M., Bando, Y., Mar. 2005. Solubilities of o and si in liquid iron in equilibrium with (mg,fe)sio3 perovskite and the light elements in the core. *Geophys. Res. Lett.* 32, L06313.
- Velicky, B., Kirkpatrick, S., Ehrenreich, H., 1968. Second- and Third- order Elastic Constants of Alkali Metals. *Phys Rev.* 147, 747.
- Vitos, L., November 1999. Application of the exact muffin-tin orbital theory: the spherical cell approximation. *Comp. Mat. Sci.* 18, 24.
- Vitos, L., Jun 2001. Total-energy method based on the exact muffin-tin orbitals theory. *Phys. Rev. B* 64 (1), 014107.
- Vitos, L., 2007. *Computational Quantum Mechanics for Materials Science The EMT0 Method and Applications*, 1st Edition. Springer Verlag.
- Vitos, L., Abrikosov, I. A., Johansson, B., Sep 2001. Anisotropic Lattice Distortions in Random Alloys from First-Principles Theory. *Phys. Rev. Lett.* 87 (15), 156401.
- Vitos, L., Kollár, J., Skriver, H. L., May 1997. Full charge-density scheme with a kinetic-energy correction: Application to ground-state properties of the 4d metals. *Phys. Rev. B* 55 (20), 13521–13527.
- Vočadlo, L., 2007. Ab initio calculations of iron and iron alloys at inner core conditions: Evidence for a partially molten core? *Earth Planet Sci Lett* 254, 227.
- Vočadlo, L., Alfè, D., Gillan, M. J., Wood, I. G., Brodholt, J. P., Price, G. D., July 2003. *Nature* 424, 536.
- Vočadlo, L., Wood, I. G., Alfè, D., Price, G., Apr. 2008. Ab initio calculations on the free energy and high P-T elasticity of face-centred-cubic iron. *Earth and Planetary Science Letters* 268 (3-4), 444–449.

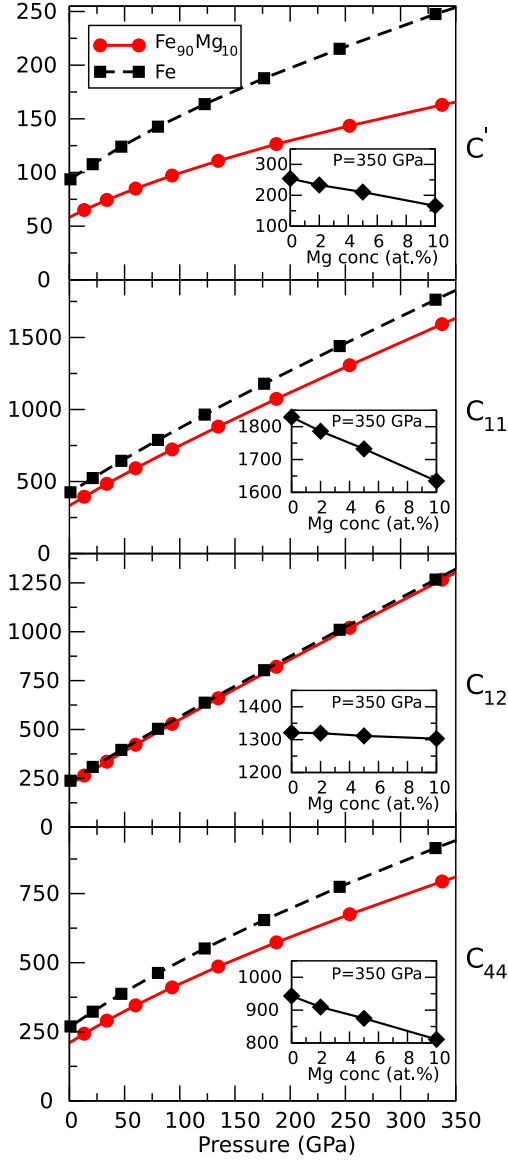


Figure 4: (Color online) Elastic constants as function of pressure in fcc $Fe_{90}Mg_{10}$ (red full line) and pure Fe (black dashed line). All elastic constants are in GPa. The inset in each subfigure show the corresponding elastic constant as function of Mg content for $P = 350$ GPa. Note that all the insets have the same scale (250 GPa).

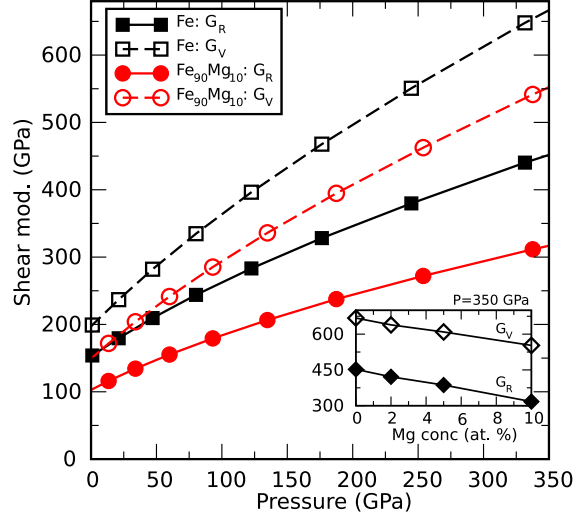


Figure 5: (Color online) Polycrystalline shear modulus as function of pressure. Black lines and squares denote results for fcc Fe, while red lines and circles denote fcc $Fe_{90}Mg_{10}$. Further, full lines and filled symbols denote G_R , while dashed lines and empty symbols denote G_V . The inset shows G_V (open diamonds) and G_R (filled diamonds) as function of Mg content for $P = 350$ GPa.

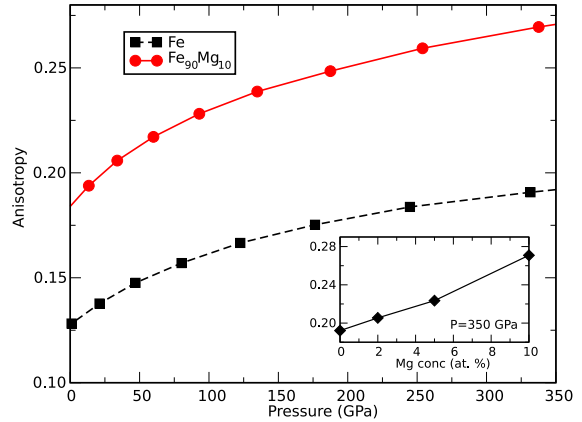


Figure 6: (Color online) Voigt-Reuss-Hill anisotropy as function of pressure in fcc $Fe_{90}Mg_{10}$ (red full line) and pure Fe (black dashed line). The inset shows the anisotropy as function of Mg content for $P = 350$ GPa.