

Luttinger-volume violating Fermi liquid in the cuprates

Jia-Wei Mei,^{1,2} Shinji Kawasaki,³ Guo-Qing Zheng,^{3,4} Zheng-Yu Weng,¹ and Xiao-Gang Wen^{2,1}

¹*Institute for Advanced Study, Tsinghua University, Beijing, 100084, P. R. China*

²*Department of Physics, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, USA*

³*Department of Physics, Okayama University, Okayama 700-8530, Japan*

⁴*Institute of Physics and Beijing National Laboratory for Condensed Matter Physics, Chinese Academy of Sciences, Beijing 100190, China*

(Dated: March 27, 2025)

Based on the detail analysis of the NMR experiments on $\text{Bi}_2\text{Sr}_{2-x}\text{La}_x\text{CuO}_{6+\delta}$ (La-Bi2201), we propose that the non-superconducting pseudogap phase in the cuprates is described as a Luttinger-volume violating Fermi liquid (LvFL). The LvFL is a zero temperature quantum liquid that does not break translational symmetry, and yet, the Fermi surface has an area smaller than the large one given by the Luttinger theorem. In the rigorous sign structure for the t - J model, only the doped holes carry the fermionic statistic signs. So the particle number enclosed by the small Fermi surface in the LvFL equals the doping level p , not the total electron number $n_e = 1 - p$. Both the phase string theory and the dopon theory can capture the sparse fermionic signs. For the dopon theory, we can obtain a semi-quantitative agreement with the NMR experiments.

I. INTRODUCTION

When the high temperature cuprate superconductor was first discovered, everyone knew what is the key issue for solving the high T_c problem: finding a right pairing mechanism that gives rise to high T_c . This point of view is based on the strong belief that the normal metallic state above T_c is described by the Fermi liquid theory¹ and the superconductivity is caused by the pairing instability of the Fermi liquid.

After 25 years of intensive research on high T_c superconductors, we have made a lot of progress. One sign of the progress is that it is no longer clear or people no longer agree on what is the key issue for solving the high T_c problem. This is because for the underdoped cuprates, it is not clear whether the normal metallic state above T_c is described by the Fermi liquid theory. And it is also not clear whether the superconductivity is caused by the pairing instability of the Fermi liquid, since we may not have a Fermi liquid above T_c .

In this paper, we will take a position that the key issue for solving the high T_c problem is not to find a pairing mechanism, but to understand the normal metallic state above T_c . Only after the well understanding of the normal metallic state above T_c , can we start to address the secondary question: what can cause the instability of the the normal metallic state above T_c to give rise to superconducting state.

For overdoped cuprates, it appears that the normal metallic state above T_c is the Fermi liquid. In this case, the key issue is to understand the pairing mechanism of the superconducting instability. For underdoped samples, the normal metallic state is characterized by a pseudo gap (PG) and appears to violate the Luttinger's theorem (a character of the Fermi liquid^{2,3}) in the PG state⁴. So the key issue for underdoped case is to understand such a new normal metallic state, which is called the PG metallic state (PGMS) in this paper.

In the experiment, the robust d -wave superconductiv-

ity conceals the PGMS at low temperatures. The experiments at finite temperatures near T_c contain too many excitations, that also conceal the low energy properties of PGMS, such as if Fermi surface and/or quasiparticles exist or not. We can access the PGMS at zero temperature by applying high magnetic field (up to 44T) on the low T_c cuprate $\text{Bi}_2\text{Sr}_{2-x}\text{La}_x\text{CuO}_{6+\delta}$ (La-Bi2201)^{5,6}. All the experiments are performed under the magnetic field parallel to the c -axis. In $T=0\text{K}$ limit, the PGMS has a reduced finite DOS violating the Luttinger's theorem. And no translational symmetry breaking is found in the PGMS.

Motivated by the experimental facts, in this paper we propose that the PGMS in the underdoped high- T_c cuprates is a metal with properties as follows

- (A) The PGMS has few low energy excitations, as reflected by a low but finite effective "density of states" (DOS) in the $T = 0$ limit.
 - (B) The PGMS is a quantum liquid at zero temperature.
 - (C) The PGMS does not break the translation symmetry.
 - (D) The Fermi surface associated with the small DOS in the PGMS is not large enough to enclose large Fermi volume and the Luttinger's theorem breaks down.
- We call such a new quantum metallic state of electrons a Luttinger-volume violating Fermi liquid (LvFL).

The underdoped cuprate is described as the dopping Mott insulator⁴. Different from the Fermi liquid, the Mottness leads to the sparse fermionic sign structure in the t - J model⁷: only the doped holes carry the fermionic statistics and these fermions occupy small Fermi pockets resulting small DOS in the NMR experiments. In this paper we employ two different theories (the phase string theory^{8,9} and the dopon theory^{10,11}) to capture the sparse fermionic signs of the LvFL in the PGMS. For the dopon theory, a semi-quantitative result is obtained in a good agreement with the NMR experiment.

II. EXPERIMENTAL ASPECTS

A. The PGMS has few low energy excitations

The doping regime for the PG state in La-Bi2201 is $0.10 < p < 0.21$ with the corresponding La concentration $0.2 < x < 0.95^{5,6}$. The large pseudo gap in the single particle spectrum in the PGMS is also confirmed in the ARPES^{12,13} and STM/STS¹⁴ experiments. The resistivity for PG regime is measured under high pulsed magnetic field 60T when the superconductivity is completely suppressed¹⁵. A crossover from metal to an “insulating” state is found near $p_c = 1/8$ ($x = 0.65$): for the large doping $p > p_c$, the in-plane resistivity remains finite (mΩcm) in $T = 0$ limit and this metallic behavior changes to $\log(1/T)$ T-dependence insulating behavior for the low doping regime $p < p_c$. Here the insulating behavior is not due to a full gap opening in the DOS, but some peculiar charge localization. So we will use the term “PGMS” for the whole PG regime.

The optimal La-Bi2201 ($p = 0.16$ with $x = 0.4$ and $T_c = 32$ K) has a PG temperature $T^* \sim 150$ K. Below T^* , the Knight shift (proportional to the DOS) starts to decrease, see Fig. 4(c). The PG behavior in DOS is independent on the magnetic field before entering the superconducting state ($T < T_c(H)$). When the magnetic field increases above $H_{c2} \simeq 26$ T, the superconductivity is killed and PGMS is realized in $T = 0$ limit. The finite DOS in PGMS declares the existence of the few low energy excitations at zero temperature.

The hyperfine coupling constant in the optimal sample is $A_{hf} = 194$ KOe/ μ_B ¹⁶. In $T=0$ limit, the Knight shift in PGMS (when $H > H_{c2}$) is $K_c = 1.36\%$ and the orbit contribution in the shift is $K_{orb} = 1.21\%$. Therefore, the residual finite DOS is given as

$$\frac{dn}{d\epsilon} = \frac{K_c - K_{orb}}{A_{hf}a^2\mu_B^2} \quad (1)$$

In the electromagnetic unit, the lattice constant in the CuO₂ plane is $a = 3.8 \times 10^{-8}$ cm and $\mu_B = 9.27 \times 10^{-21}$ emu. Thus we have $\frac{dn}{d\epsilon} = 5.78 \times 10^{26}$ erg⁻¹cm⁻² = 5.78×10^{37} J⁻¹m⁻². For the Fermi pocket scenario in this paper, we can also estimate the DOS $\frac{dn}{d\epsilon} = \frac{1}{2\pi^2} \frac{L_k}{\hbar v_F}$ where the Fermi velocity v_F can be obtained in ARPES¹³ $v_F = 1.75$ eV·Å and the Fermi surface length has the approximate value $L_k = 2\pi\sqrt{2\pi n_{fp}p}/a$ with n_{fp} the number of the Fermi pockets in the first Brillouin zone. In the dopon theory, $n_{fp} = 4$. So we can estimate the DOS as $\frac{dn}{d\epsilon} = 5.9 \times 10^{37}$ J⁻¹m⁻² very close to the experimental value.

B. The PGMS is a quantum liquid

Firstly, we can rule out the “ d -wave superconductor+thermal fluctuation” (dSC+TF) scenario. In

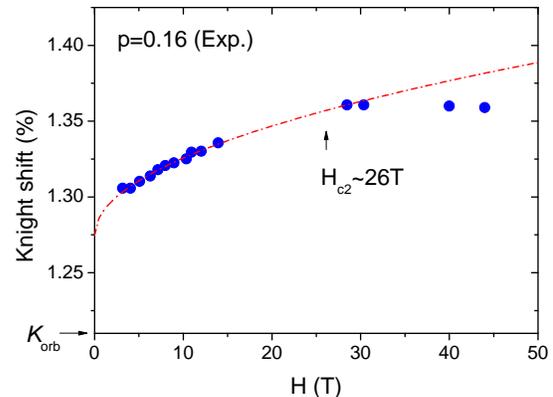


FIG. 1. [Color online] H -dependence of the Knight shift for the optimal La-Bi2201. The dash line is the fitting curve $K_c = 1.27 + 0.016\sqrt{H}$ at $T = 4.2$ K. The square-root behavior breaks down when $H > H_{c2}$. The orbit contribution to the Knight shift is $K_{orb} = 1.21\%$.

dSC+TF scenario, the d -wave superconducting gap remains finite in the PG state and the thermal fluctuations release the DOS near the nodal lines on the Fermi surface. In this picture, the PG phase is a disorder dSC state. It is a thermal liquid in contradiction to the quantum propose in this paper.

Due to the Volovik effect¹⁷, the DOS has a square-root behavior $\frac{dn}{d\epsilon} \propto \sqrt{H}$ when the d -wave superconducting gap remains finite. In other words, the square-root behavior is a signal for dSC. For optimal doped La-Bi2201, the square-root behavior has been observed in the Knight shift measurement when $H < H_{c2}$ in $T=0$ limit. However, the DOS doesn’t increase any more and is independent on the magnetic field for $H > H_{c2}$, see Fig. 1. The fact of the breaking down of the square-root behavior indicates the vanishing of the dSC gap in the PG state and can be used to determine the upper critical field H_{c2} in NMR measurement. The optimal doped La-Bi2201 has $H_{c2} \simeq 26$ T in our NMR measurement which is close the melting field $H_m(T) \simeq 25$ T and much smaller than the “upper critical field H_{c2} ” $\simeq 50$ T in the Nernst measurement^{18,19}.

Our second concern is the vortex issue in the PG state. In the superconducting state, the applied magnetic field will create vortices. These vortices leads to square-root behavior in the DOS when $H < H_{c2}$, see Fig. 1. We are concerned about whether the vortices, if any, form a thermal or quantum liquid in PG state. In Ref. 20, the vortex thermal dynamics with slow thermal motion was observed in the transverse nuclear magnetic relaxation rate $1/T_2$ in YBa₂Cu₃O₇. The T-dependent $1/T_2$ under different magnetic fields was also measured on ⁶³Cu in the optimal La-Bi2201. The PG behavior is independent on the magnetic fields, see Fig. 2 (a). When $H < H_{c2}$, there is some signal associated with sc at low temperatures. $1/T_2$ has a clear enhancement in the sc state. The

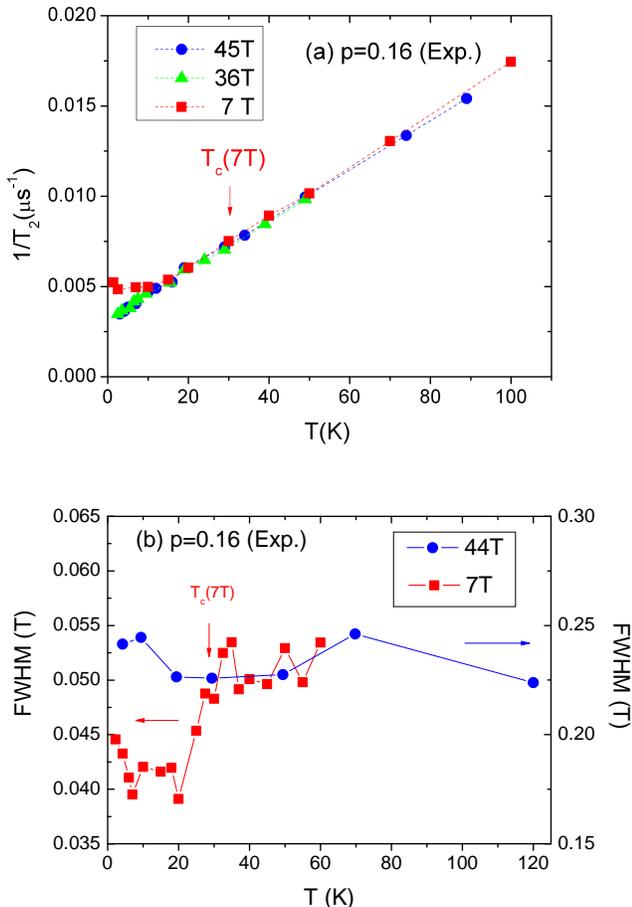


FIG. 2. [Color online] (a) T -dependent $1/T_2$ on ^{63}Cu under different magnetic fields for the optimal La-Bi2201; (b) T -dependent FWHM for the optimal La-Bi2201 under the magnetic field 7T under H_{c2} and 44T above H_{c2} . A clear SC drop is shown in FWHM under 7T.

vortex is possible. However, more careful data is needed to settle down this vortex issue. The low temperature SC behavior is also observed in the full width at half maximum (FWHM) of the intensity on ^{63}Cu . It has a clear drop below $T_c(7\text{T})$ at 7T as shown in Fig.2 (b). At 44T, there is no such a superconducting drop in FWHM indicating that the superconductivity is killed completely under strong magnetic field.

From the data shown in Fig. 2, we cannot settle down the issue whether the vortices, if any, are thermal or quantum objects in PG state in $T=0$ limit. In this paper, we adopt the quantum idea: the PGMS near $T=0$ above H_{c2} is a quantum state of matter (the finite DOS is not a thermal effect). The vortices, if any, form a quantum liquid. The normal metallic state described by the quantum liquid of vortices is nothing but the PGMS with a reduced number of low energy excitations described by a small length of Fermi surface as discussed below.

The last concern is how we should view such a metallic

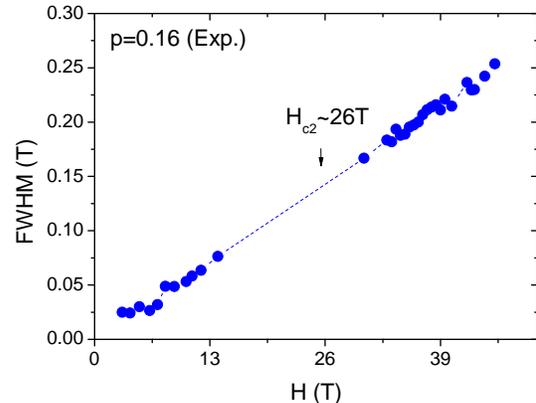


FIG. 3. [Color online] H -dependent FWHM in optimal La-Bi2201 at $T=4.2\text{K}$.

state in the presence of magnetic field. We like to argue that, due to impurities, such a state is very different from the quantum Hall states. The optimal La-Bi2201 has a resistivity $\rho = 0.12 \text{ m}\Omega\text{cm}$ when the superconductivity is killed at 0K. Then the mean free path is around $l = \frac{\hbar l_c}{e^2 \rho} / 4\Delta k_F = 13a$, a and l_c are the in-plane and c -axis lattice constant, respectively; the Fermi vector $\Delta k_F = \sqrt{\pi p}/2$. At 30T magnetic field, the magnetic length $l_B = \sqrt{2\pi\hbar/eB} = 31a$. The mean distance between doped holes is $a\sqrt{1/p} = 2.5a$. We see that $a\sqrt{1/p} < l < l_B$. The mean free path is long enough to have a well-defined wave vector of the electrons and also short enough to suppress the orbit effect of the magnetic field. So we should view PGMS in the presence of magnetic field as a dirty metal. There is no quantum Hall effect since $l < l_B$.

C. The PGMS doesn't break translational symmetry

The NMR/NQR experiment^{5,6} is desired to investigate whether there is a translational symmetry breaking associated with the PG state. When the translational symmetry breaks, there is an internal field on Cu local environment. In the heavily underdoped samples ($x = 0.90$ and 0.80), this internal magnetic field (H_{int}) at Cu site is observed and is very large around $H_{\text{int}} = 7.2\text{T}$ ⁶.

For optimal La-Bi2201, we note that there is no internal magnetic field in the PGMS due to the translational symmetry breaking. Fig. 3 shows the NMR full width at half maximum (FWHM) as a function of field. The FWHM increases linearly with increasing H , indicating that the FWHM is due only to the electronic inhomogeneity that gives a distribution of the spin susceptibility (Knight shift), which is a quite typical behavior seen in cuprates. Namely, the good linearity indicates that there is no additional broadening due to the internal magnetic field associated with the ordered moment. We can es-

timate an upper limit for the ordered moment, if any. At $H=30$ T, the FWHM is 0.16 T. With reasonable assumption that we can detect an additional broadening of 1/10 FWHM, and with the knowledge of the hyperfine coupling constant, we conclude that the magnetic field-induced moment, if any, should be less than $1 \text{ m}\mu_B$. Likewise, we can conclude that there is no charge order which would give rise to a quadrupole splitting for the first satellites of the spectrum since the distance between the two satellites is proportional to the charge state of Cu. With a conservative assumption that we can detect a splitting that is 1/2 FWHM, then we can rule out a charge order that gives rise to a splitting of $\gamma \times 0.08 \text{ T} = 0.9 \text{ MHz}$. This is equivalent to saying that there is no field-induced charge disproportion of 0.0075 hole or 1% of the Cu charge state at zero magnetic field, since one Cu-3d hole would give rise to 117 MHz of the nuclear quadrupole frequency²².

Although the conventional translational symmetry breaking (SDW or CDW) can be ruled out by our NMR measurement, the staggered flux issue²³ remains unsolved in our NMR experiments. The internal field on the Cu sites is always zero regardless of the existence of the staggered flux in the PG state.

D. The PGMS has the small Fermi surface

Generally, the small DOS indicates the small Fermi surface. However, we should be careful to make this conclusion.

Since dSC gap vanishes in PGMS, the nodal metal scenario should be discarded. Also we should rule out the large Fermi surface scenario. Within the large Fermi surface scenario, the reduced DOS in PGMS should be caused by the Fermi velocity anomaly ($\frac{dn}{d\epsilon} = \frac{1}{2\pi^2} \frac{L_k}{\hbar v_F}$). However, the increasing Fermi velocity in PGMS with decreasing the temperature is not observed in optimal La-Bi2201. The Fermi velocity at high T can be obtained from ARPES¹³, $v_F = 1.75 \text{ eV} \cdot \text{\AA}$. In T=0 limit, the gap slope is $v_\Delta = 0.028 \text{ eV} \cdot \text{\AA}$ extracted from specific heat²⁴. The ratio v_F/v_Δ can be extracted from the thermal conductivity measurement²⁵, $v_F/v_\Delta = 33$. Thus the Fermi velocity is $v_F = 0.93 \text{ eV} \cdot \text{\AA}$ at low temperature. No Fermi velocity increasing is found with decreasing the temperature.

In the Sec. II A, we extracted the reduced DOS in PGMS at T=0K from the Knight shift in optimal La-Bi2201. To obtain a value in an agreement with the experiment, the PGMS has four small Fermi pockets in the first Brillouin zone.

E. Experimental conclusions

The PG behavior is confirmed in optimal La-Bi2201 in the Knight shift, $1/T_1T$ and $1/T_2$. The key feature is the loss of DOS in the PG state. However, the loss of DOS

is not complete. We can apply the high static magnetic field to kill superconductivity and realize the PGMS in T=0K limit. The PGMS has few low energy excitations. The PGMS is not a disorder dSC state since the volovik square-root behavior breaks down in PGMS. We measure $1/T_2$ to address the issue whether the vortices in PGMS, if any, form a thermal or quantum liquid. The data here still cannot clear this issue. However, in this paper we propose that the vortices in PGMS are quantum objects and such a quantum PGMS has a reduced number of low energy excitations described by a small length of Fermi surface. It should be emphasized that PGMS has no SDW or CDW order. Although we cannot rule out the staggered-flux state, we propose in this paper that PGMS is still a translational invariant system. Since there is no Fermi velocity increasing with decreasing the temperature, the small DOS in PGMS comes from small Fermi surface. No microscopic theory that we have known up to now can explain the Fermi arc²¹ and so we adopt the Fermi pocket scenario in this paper. The scenario that the PGMS has four small Fermi pockets in the first Brillouin zone works very well and gives a close value of DOS to the experimental data. The small Fermi pocket in PGMS does not enclose the volume determined by the Luttinger's theorem. So we call the PGMS a Luttinger-volume violating Fermi liquid (LvFL).

III. THEORETICAL DESCRIPTIONS

A. Sparse fermionic signs and small Luttinger's volume

For the overdoped samples, the normal metallic state in La-Bi2201 is the Fermi liquid. As the Fermi gas, the Fermi liquid has the full fermionic statistics: when two of the electrons exchange with each other, there is a negative sign in the partition function

$$Z_{\text{FL}} = \sum_{\{c\}} (-1)^{N_{\text{ex}}[c]} Z_0[c] \quad (2)$$

where $\{c\}$ contains all the closed loops of the spatial trajectories of the fermions and $Z_0[c] > 0$ is the classical partition function on the loop c . The fermionic statistics is determined by the total number of electron exchanges $N_{\text{ex}}[c]$. Owing to the Pauli exclusion principle for the fermionic statistics, every electron with the fermionic statistics occupies a quantum state. The space for each state is quantized and stable against the interaction resulting in the Luttinger's theorem^{2,3}

$$2 \frac{V_F}{(2\pi)^2} = n_e \pmod{2} \quad (3)$$

where V_F is the Fermi volume occupied by the electrons in the \mathbf{k} space.

However, the Luttinger's theorem breaks down in the LvFL. The small DOS in LvFL indicates the sparse

fermionic statistics in LvvFL. Based on the t - J model, Wu *et al* describe the sparse fermionic statistics for the LvvFL as follows⁷

$$Z_{t-J} = \sum_{\{c\}} \tau_c \mathcal{Z}[c] \quad (4)$$

where $\mathcal{Z}[c] > 0$. For a given closed loop c , the sign structure is now written as

$$\tau_c = \tau_{\text{ps}} \times \tau_h \quad (5)$$

with the phase string sign $\tau_{\text{ps}} = (-1)^{N_h^\downarrow[c]}$ and the fermionic sign $\tau_h = (-1)^{N_{\text{ex}}^h[c]}$. Here $N_h^\downarrow[c]$ is the total number of exchanges between the doped holes and down spins and $N_{\text{ex}}^h[c]$ denotes the total number of exchanges between doped holes.

The phase string sign τ_{ps} is the dynamical frustration which turns the long range antiferromagnetic state into short range spin liquid state⁸. The sparse fermionic statistics in τ_h is only activated for the doped holes. Each fermionic hole occupies a quantum state and have a small Luttinger's volume

$$-2 \frac{V_F}{(2\pi)^2} = n_e - 1 \pmod{2} \quad (6)$$

The minus sign on the left represents the hole pockets. This modified Luttinger theorem is also obtained by using the elegant Oshikawa argument³ in Ref. 27.

B. The phase string theory for the LvvFL

To capture the sign structure, the phase string theory describe LvvFL as a projected product state⁹

$$|\text{LvvFL}\rangle_{\text{ps}} = \mathcal{P} \left(|\widetilde{\text{RVB}}\rangle_b \otimes |\Phi\rangle_a \right) \quad (7)$$

Here the phase string sign τ_{ps} is embedded in the half-filled ($n = 1$) bosonic resonant-valence-bond state $|\widetilde{\text{RVB}}\rangle_b$ described by the mutual Chern-Simons theory²⁸. The spare fermionic signs ($n = p$) are carried by the Fermi pockets described by $|\Phi\rangle_a$. The phase string theory captures very rich physics in the doped Mott insulator. For the details, see Ref. 9.

C. The dopon theory for the LvvFL

The dopon theory developed in Ref. 10 and 11 can also describe the LvvFL. In the dopon theory, the LvvFL is described by the following many-body trial wave function

$$|\text{LvvFL}\rangle_{\text{dopon}} = \mathcal{P} \left(|\text{RVB}\rangle_f \otimes |\Phi\rangle_d \right) \quad (8)$$

Here $|\text{RVB}\rangle_f$ is the half-filled ($n = 1$) fermionic RVB state and $|\Phi\rangle_d$ describes the Fermi pockets ($n = p$). In the dopon theory, the phase string signs are simply treated by

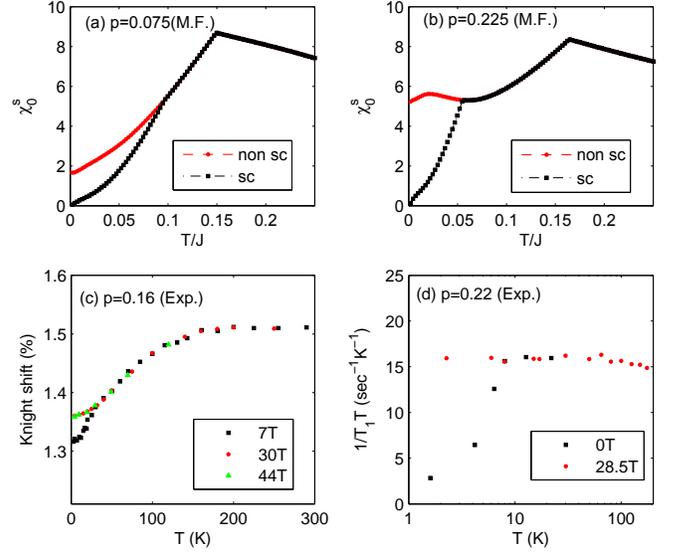


FIG. 4. [Color online] The mean field T -dependence of the uniform spin susceptibilities from the dopon theory in superconducting (SC) and non-superconducting (non SC) states, for (a) underdoped case $x = 0.075$ and (b) overdoped one $x = 0.225$. (c) The experimental Knight shift for optimal La-Bi2201 under different magnetic fields; (d) The experimental $1/T_1T$ for overdoped Bi-La2201 $p = 0.22$. The experimental data under strong magnetic fields above 26T are for non-superconducting (non SC) states.

the projected short range spin liquid. The dopon theory has a simpler mean field Hamiltonian^{10,11}

$$H_{\text{MF}} = \begin{pmatrix} f_{\mathbf{k}}^\dagger & d_{\mathbf{k}}^\dagger \end{pmatrix} \begin{pmatrix} \alpha_{\mathbf{k}}^z \sigma_z + \alpha_{\mathbf{k}}^x \sigma_x & \beta_{\mathbf{k}} \sigma_z \\ \beta_{\mathbf{k}} \sigma_z & \gamma_{\mathbf{k}} \sigma_z \end{pmatrix} \begin{pmatrix} f_{\mathbf{k}} \\ d_{\mathbf{k}} \end{pmatrix} + \frac{3J_{\text{eff}}}{4} N(\chi^2 + \Delta^2) - N\mu_d(1-p) - 2Nb_0b_1(9)$$

where $\alpha_{\mathbf{k}}^z = -\left(\frac{3J_{\text{eff}}}{4}\chi - t_1p\right)(\cos k_x + \cos k_y) - \mu_f$, $\alpha_{\mathbf{k}}^x = -\frac{3J_{\text{eff}}}{4}\Delta(\cos k_x - \cos k_y)$, $\gamma_{\mathbf{k}} = 2t_2 \cos k_x \cos k_y + t_3(\cos 2k_x + \cos 2k_y) - \mu_d$ and $\beta_{\mathbf{k}} = \frac{3b_0}{8}[t_1(\cos k_x + \cos k_y) + 2t_2 \cos k_x \cos k_y + t_3(\cos 2k_x + \cos 2k_y)] + b_1$. $f_{\mathbf{k}}^\dagger = \begin{pmatrix} f_{\mathbf{k}\uparrow}^\dagger & f_{-\mathbf{k}\downarrow}^\dagger \end{pmatrix}$, $d_{\mathbf{k}}^\dagger = \begin{pmatrix} d_{\mathbf{k}\uparrow}^\dagger & d_{-\mathbf{k}\downarrow}^\dagger \end{pmatrix}$ and σ_z, σ_x are the pauli matrices.

To obtain the proper phase diagram, the parameters in the dopon theory are tuned as follows: $J_{\text{eff}} = (1-p)^2J$, $t_1 = 1.5J$, $t_2 = \frac{p}{0.3}J$ and $t_3 = J - \frac{p}{0.6}J$. The order parameters χ , Δ , b_0 , b_1 , μ_f and μ_d are determined by minimizing the free energy. There are two different normal states above the sc transition temperature T_c : the LvvFL in the upderdoped regime and the Fermi liquid in the overdoped regime.

The mean field results of T -dependent uniform spin susceptibility χ_0^s for $p = 0.075$ (underdoped) and $p = 0.225$ (overdoped) are shown in Fig. 4 (a) and (b). We also plot the T -dependent Knight shift K_c for the optimal sample ($p = 0.16$) and $1/T_1T$ for the overdoped sample ($p = 0.22$) in Fig. 4 (c) and (d). The mean field results

coincide semi-quantitatively with the experimental data. Also, the LvFL described by the dopon theory has four Fermi pockets.

IV. SUMMARY

We study the normal metallic state in the underdoped cuprates which we call the PGMS in this paper. Although the data is not enough, we prefer the quantum picture for the PGMS. The PGMS has four small Fermi pockets in the first Brillouin zone and violates the Luttinger's theorem. No translational symmetry breaking is found in the PGMS. The particle number enclosing in the small Fermi pockets equals to the doping level p , not the total number of the electrons $n_e = 1 - p$. The PGMS

has more sparse fermionic statistics than the Fermi liquid which can be captured by the sign structure of the t - J model. Both the phase string theory and the dopon theory work well with the sparse fermionic statics. The theory is in a good agreement with the NMR measurements.

V. ACKNOWLEDGMENT

J. W. Mei thanks Lu Li, Hai-Hu Wen, Yao-Min Dai, Jian-Qiao Meng and Xin-Jiang Zhou for useful discussions. JWM and ZYW are supported by NSFC grant No. 10834003 and National Program for Basic Research of MOST Nos. 2009CB929402 and 2010CB923003. XGW is supported by NSF Grant No. DMR-1005541 and NSFC 11074140.

-
- ¹ See the classic book A. A. Abrikosov, L. P. Gor'kov, and I. E. Dzyaloshinski, *Methods of quantum field theory in statistical physics* (Prentice-Hall, Inc., 1963).
- ² J. M. Luttinger, Phys. Rev. **119**, 1153 (1960).
- ³ M. Oshikawa, Phys. Rev. Lett. **84**, 3370 (2000).
- ⁴ For a review P. A. Lee, N. Nagaosa, and X.-G. Wen, Rev. Mod. Phys. **78**, 17 (2006).
- ⁵ G.-q. Zheng, P. L. Kuhns, A. P. Reyes, B. Liang, and C. T. Lin, Phys. Rev. Lett. **94**, 047006 (2005).
- ⁶ S. Kawasaki, C. Lin, P. L. Kuhns, A. P. Reyes, and G.-q. Zheng, Phys. Rev. Lett. **105**, 137002 (2010).
- ⁷ K. Wu, Z. Y. Weng, and J. Zaanen, Phys. Rev. B **77**, 155102 (2008).
- ⁸ Z.-y. Weng, International Journal of Modern Physics B **21**, 773 (2007).
- ⁹ Z.-Y. Weng, ArXiv e-prints (2011), arXiv:1105.3027 [cond-mat.supr-con].
- ¹⁰ T. C. Ribeiro and X.-G. Wen, Phys. Rev. Lett. **95**, 057001 (2005).
- ¹¹ T. C. Ribeiro and X.-G. Wen, Phys. Rev. B **74**, 155113 (2006).
- ¹² J. Meng, G. Liu, W. Zhang, L. Zhao, H. Liu, X. Jia, D. Mu, S. Liu, X. Dong, J. Zhang, W. Lu, G. Wang, Y. Zhou, Y. Zhu, X. Wang, Z. Xu, C. Chen, and X. J. Zhou, Nature **462**, 335 (2009).
- ¹³ J. Meng, W. Zhang, G. Liu, L. Zhao, H. Liu, X. Jia, W. Lu, X. Dong, G. Wang, H. Zhang, Y. Zhou, Y. Zhu, X. Wang, Z. Zhao, Z. Xu, C. Chen, and X. J. Zhou, Phys. Rev. B **79**, 024514 (2009).
- ¹⁴ A. Sugimoto, S. Kashiwaya, H. Eisaki, H. Kashiwaya, H. Tsuchiura, Y. Tanaka, K. Fujita, and S. Uchida, Phys. Rev. B **74**, 094503 (2006).
- ¹⁵ S. Ono, Y. Ando, T. Murayama, F. F. Balakirev, J. B. Betts, and G. S. Boebinger, Phys. Rev. Lett. **85**, 638 (2000).
- ¹⁶ S. Kawasaki, unpublished.
- ¹⁷ G. Volovik, JETP Letters **58**, 469 (1993).
- ¹⁸ Y. Wang, L. Li, and N. P. Ong, Phys. Rev. B **73**, 024510 (2006).
- ¹⁹ L. Li, Y. Wang, S. Komiya, S. Ono, Y. Ando, G. D. Gu, and N. P. Ong, Phys. Rev. B **81**, 054510 (2010).
- ²⁰ C. H. Recchia, J. A. Martindale, C. H. Pennington, W. L. Hults, and J. L. Smith, Phys. Rev. Lett. **78**, 3543 (1997).
- ²¹ S. Kawasaki, unpublished.
- ²² G. qing Zheng, Y. Kitaoka, K. Ishida, and K. Asayama, Journal of the Physical Society of Japan **64**, 2524 (1995).
- ²³ T. C. Hsu, J. B. Marston, and I. Affleck, Phys. Rev. B **43**, 2866 (1991).
- ²⁴ Y. Wang, Z.-Y. Liu, C. T. Lin, and H.-H. Wen, Phys. Rev. B **83**, 054509 (2011).
- ²⁵ Y. Ando, S. Ono, X. F. Sun, J. Takeya, F. F. Balakirev, J. B. Betts, and G. S. Boebinger, Phys. Rev. Lett. **92**, 247004 (2004).
- ²⁶ At high temperature, the dSC+TF scenario was used to explain the Fermi arc in Ref. 29 and 30. However, this scenario is not consistent with PGMS in T=0 limit, see Fig.1.
- ²⁷ T. Senthil, M. Vojta, and S. Sachdev, Phys. Rev. B **69**, 035111 (2004).
- ²⁸ S.-P. Kou, X.-L. Qi, and Z.-Y. Weng, Physical Review B **71**, 1 (2005).
- ²⁹ E. Berg and E. Altman, Phys. Rev. Lett. **99**, 247001 (2007).
- ³⁰ Q. Han, T. Li, and Z. D. Wang, Phys. Rev. B **82**, 052503 (2010).