

Electronic Raman scattering in metals: effects of electron-phonon coupling

Yu. S. Ponosov¹ and S. V. Streltsov^{1,2}

¹*Institute of Metal Physics UD RAS, 620990, S. Kovalevskaya str. 18, Ekaterinburg, Russia*

²*Ural Federal University, Mira str. 19, Ekaterinburg, Russia*

We report the first systematic measurements of the Raman scattering by electrons in elemental metals of Al, Mo, Nb, Os, Pb, Re, Ta, Ti, V, W and metallic compound LaB_6 . Experimental spectra are modelled on the base of the band structures, calculated within the density functional theory, taking properly into account the effects of electron-phonon scattering. The agreement between our measured and calculated spectra is excellent for the variety of metals, thus providing estimates for the electron-phonon coupling constants and temperature-dependent relaxation rates. The method can be applied for other metallic materials to evaluate an electron-phonon coupling as an alternative to the transport and optical measurements.

PACS numbers: 78.30.-j, 74.25.nd, 74.70.Ad, 71.38.Cn

After the discovery of high-temperature superconductors (HTSC) the electronic Raman scattering (ERS) has been widely used to study electronic excitations both in superconducting and normal state of a variety of compounds.[1] The ERS provides information on the two-particle correlation function, which is in close correspondence to transport properties. In addition to studies of the magnitude and symmetry properties of the superconducting gap, many investigations of the ERS have been devoted to the problem of many-body interactions. Since clear understanding of the electron self-energy origin may shed light on the leading mechanism of unusual superconductivity, the ERS has become an important complementary tool for the electron-dynamics investigations.[1] Thus, the observation of a flat, nearly frequency-independent, electronic Raman response in the normal state of cuprates [2–4] has become the basis of a marginal Fermi liquid concept.[5] Models, incorporating different electron interactions, like nested Fermi liquid [6] or antiferromagnetic spin fluctuations [7, 8], have been proposed to explain the unusual ERS spectra of HTSC. The phonon origin of the electron self-energy in cuprates is still debated. [9] Broad Raman spectra very similar to a marginal Fermi liquid behavior have been simulated for strongly coupled electron-phonon systems. [10–12] However, no experimental evidence for such behavior has been presented in early studies of the strongly-coupled conventional superconductors. Moreover, no normal-state spectra have been measured for Nb,[13, 14] and the origin of the broad continuum in A-15 compounds, which is evolved in superconducting state, is still not fully understood. [13–16] Thus, the investigations of the ERS spectra in the normal state of conventional metals and compounds, where an electron-phonon interaction seems to be the main contribution to the electron self-energy, and of their evolution upon the change of coupling strength and temperature are actually lacking.

The first unsuccessful attempts to observe the Raman scattering from electronic excitations in conventional metals were performed more than sixty years ago.[17, 18]

The following calculation of the Raman response [19] has shown that the sensitivity in these measurements was by 5 or 6 orders of magnitude low. In spite of the substantial advances of the Raman technique nowadays, the widespread opinion consist in that the measurements of the Raman effect from electrons in conventional metals is a difficult challenge. It is because the charge-density fluctuations are largely screened by conducting electrons and the $q \rightarrow 0$ limit, usually used in the experiment treatment, implies the smallness of electronic scattering cross section which is proportional to q^2 at low frequencies.

In the elemental metals, however, the values of the wave vector transfer q corresponding to the exciting laser energies in the visible range are usually in the range $(5-15) \times 10^5 \text{ cm}^{-1}$. With electron velocities v_f being as high as 10^8 cm/sec , the electronic excitation's energies $\omega = qv_f$ in the Raman spectra can spread up to 1000 cm^{-1} . The multisheeted Fermi surfaces and their anisotropy[20] together with the found resonance effects[21] are the factors assisting the observation ERS spectra in metals.

In this report we present the first systematic investigations of the temperature-dependent ERS spectra in the normal state of elemental metals and metallic compounds. The obtained spectra have been compared with those simulated based on the band structures, calculated within the density functional theory, taking into account the electron-phonon interaction. The groups of metals with weak and strong electron-phonon interaction were found to have strongly distinct Raman spectra and their temperature dependences. The results of the measurements and their analysis provided independent estimations of the electron-phonon coupling constants and electron relaxation rates.

For temperature-dependent measurements (10-300K), electropolished plates of single crystals (residual resistance ratio ≥ 50) were placed into an Oxford optical cryostat. The Raman spectra were excited by low-power laser radiation (up to 3 mW) at wavelengths of 514 nm and 633 nm, and they were recorded by a single-stage Renishaw

microscope spectrometer providing a focal spot on the samples of $2 \div 10 \mu\text{m}$ diameter. The represented spectra were corrected for the Bose factor, spectral response of the spectrometer, and transmission and absorption coefficients in the frequency range of the scattered light.

The cross section for the ERS by the intraband excitations is determined via integrating the electron susceptibility $\chi(q, \omega)$ over the distribution of excited wave vectors $U^2(q)$ [22, 23]:

$$\frac{d^2\sigma}{d\omega d\Omega} \propto \frac{1}{1 - \exp^{-\hbar\omega/kT}} \int_0^\infty dq \cdot U^2(q) \cdot \chi(q, \omega) \quad (1)$$

When the interaction between electrons is taken into account, the susceptibility $\chi(q, \omega)$ can be written in the form of the integral of the imaginary part of the q -dependent polarization operator over the Fermi surface [22, 23]:

$$\chi(q, \omega) = \oint \frac{ds_f}{v_f} \bar{\gamma}^2(k_f, q, \omega) \int_{-\infty}^{\infty} d\epsilon [f(\epsilon) - f(\epsilon + \omega)] \times \Im \frac{1}{\omega - qv_z - \Sigma(\epsilon) + \Sigma(\epsilon + \omega)} \quad (2)$$

The similar formalism has been previously used in the calculations of the nonadiabatic effects in the phonon self-energy[24] and the ERS spectra in the $q \rightarrow 0$ limit. [10–12] Here, $\bar{\gamma}_{\alpha\beta}(k_f, q, \omega) = \gamma_{\alpha\beta}(k_f, q, \omega) - \langle \gamma_{\alpha\beta}(k_f, q, \omega) \rangle$ is the matrix element of the electron-photon interaction with account of the Coulomb interaction, angular brackets denote the averaging over the Fermi surface, $f(\epsilon)$ is the Fermi function, and z denotes the normal to the sample surface. The retarded and advanced quasi-particle electron self-energies $\Sigma\epsilon$ and $\Sigma(\epsilon + \omega)$ determine the electron spectrum renormalization near the Fermi level due to different interactions. In the case of electron-phonon scattering, their real and imaginary parts are [25]

$$\Sigma'(\epsilon) = \int d\Omega \alpha^2 F(\Omega) \times \Re \left[\psi \left(\frac{1}{2} + i \frac{\omega + \Omega}{2T} \right) - \psi \left(\frac{1}{2} + i \frac{\omega - \Omega}{2T} \right) \right] \quad (3)$$

$$\Sigma''(\epsilon) = 2\pi \int d\Omega \alpha^2 F(\Omega) \times [2n_B(\omega) - f(\epsilon + \omega) + f(\epsilon - \omega)] + \nu. \quad (4)$$

Here, ν is the impurity relaxation rate, taken equal 10 cm^{-1} in all calculations (this value is the upper limit for used pure samples), Ψ is the digamma function, Ω is the phonon energy, $\alpha^2 F(\Omega)$ is the Eliashberg spectral function for the electron-phonon interaction, and n_B is the

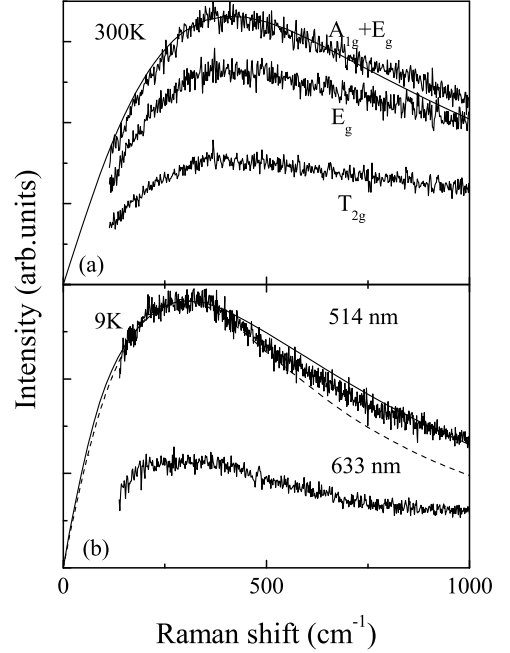


FIG. 1: Raman spectra for W, measured in different polarization geometries with 514 nm excitation at 300K -(a) and using different exciting energies at 9K -(b). Calculated spectra are shown by solid line for $\lambda=0.13$ and dashed-for $\lambda=0$.

Bose function. The literature data on the phonon densities of states $F(\Omega)$ [26] and optical constants [27] for the calculation of the function $U^2(q)$, taken in the form, [28] were used. In this work, we assume the Raman vertex $\bar{\gamma}_{\alpha\beta}(k_f, q, \omega)$ to be a constant. This simplification is justified, since the continua shapes in the spectra measured with different excitation energies are quite similar. In addition, the shapes for the spectra measured in different polarization geometries are nearly the same, suggesting a slight effect of screening on the frequency dependence of the Raman response in different symmetries. The electron velocities on the Fermi surface have been obtained within the band-structure calculations using the linearized muffin-tin orbital method (TB-LMTO-ASA)[29] in the local density approximation. Integration over the Fermi surface was performed with a fine mesh of 125,000 k-points in the full Brillouin zone.

At first sight, all spectra, shown in Figs.1-3, look very similar. They contain broad continua with linearly increased intensity at small frequencies and a characteristic position of maximum. The spectra measured with different excitation energies have similar forms, as it is shown for W in Fig.1(b), where broad peaks with the energy of maximum near 300 cm^{-1} are observed at the low temperature for both exciting laser lines - 514 and

633 nm. The first-order Raman scattering by phonons for all investigated elemental cubic metals is forbidden and the upper limit of possible second-order spectra in W is limited by 400 cm^{-1} . Hence, the broad spectra observed indicate their electronic origin. The continuum frequency increases to 400 cm^{-1} at room temperature. We calculated the ERS spectra for W using (Eq.2) with the electron-phonon constant $\lambda = 2 \int d\Omega \alpha^2 F(\Omega)/\Omega = 0$. In such case of noninteracting electrons the spectra maximum should be found at the energy $\omega = qv_z$, which is determined by the average Fermi velocity v_z and wave vector q , corresponding to the maximum in the momentum transfer distribution $U^2(q)$. One can see (dashed line in Fig.1(b)) that the energies of the calculated low-temperature continua are very close to the experimental ones. Together with the moderate frequency hardening upon increasing temperature this evidences rather weak electron interactions. In fact, both low- and room-temperature spectra can be fitted well using $\lambda=0.13$ (Fig.1). Thus, the obtained ERS results demonstrate that the source of the observed ERS are intraband electronic excitations. They also confirm the conservation of the electron momentum transfer q in the course of the scattering process. Obviously, in the case of W the qv_z term can not be neglected even at room temperature. The shapes of the observed continua are quite similar for different polarization geometries ($A_{1g}+E_g$), E_g and T_{2g} (Fig.1(a)) indicating the same quasiparticle lifetimes for different symmetry channels.

Next case when the qv_z term determines the continua energies in the ERS spectra is shown in Fig.2(a). Though Pb is a strongly coupled superconductor, its low-temperature ERS spectrum is very close to the calculated spectrum for noninteracting electrons (dashed line in Fig.2(a)). This is due to a large value of the qv_z term (both Fermi velocity and q are large) and the smallness of the phonon-induced electron self-energies at low temperatures. The effect of temperature on the quasiparticle damping is large: the fit of the temperature-dependent Raman spectra with Eq.2 shows the increase of the electron relaxation rate $\Gamma \approx 2 \cdot \Sigma''(\omega)$ from 150 cm^{-1} at 10K to 1500 cm^{-1} at room temperature. At high temperatures this rate becomes frequency-independent and exceeds the contribution of the term with $qv_z \approx 600 \text{ cm}^{-1}$. In this case, the qv_z term can be neglected and a Drude-like expression for the electron response $\chi(q, \omega)$ can be used in the $q \rightarrow 0$ limit [30]:

$$\chi(\omega) \propto N_f \frac{\omega \Gamma(\omega)}{\omega^2 + \Gamma(\omega)^2} \quad (5)$$

where N_f is the density of states at the Fermi level. The continuum energy then should be observed at the frequency $\omega \approx \Gamma$, which accounts for the large shift of the ERS spectra toward higher energies when temperature increases. The experimental spectra at all tem-

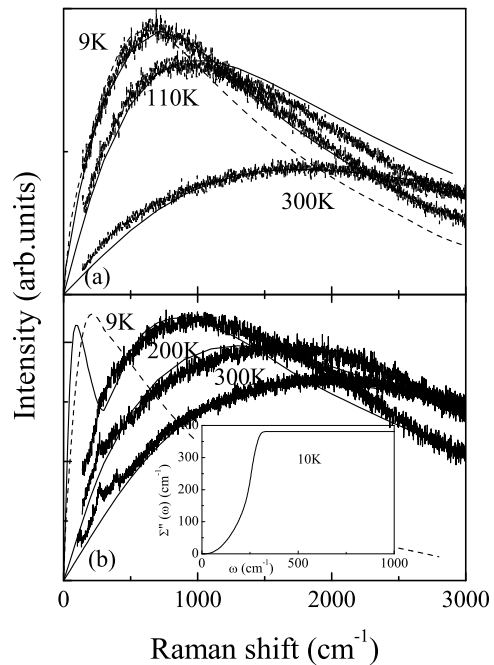


FIG. 2: Raman spectra for Pb (a) and Nb (b) at different temperatures, measured with 633 nm excitation. Calculated spectra are shown by solid line for $\lambda=1.04$ and dashed for $\lambda=0$. Inset in (b) - energy dependence of the quasiparticle damping for Nb at 10K, calculated with Eq. 4.

peratures were well reproduced in our calculations with $\lambda=1.04$ (Fig.2(a)). As in case of W, only small part of the spectral intensity in Pb is redistributed to the high-energy range at low temperatures, indicating small deviations from the Fermi-liquid behavior. At high temperatures, a large incoherent part appears over a high-energy scale that reminds the situation in the high-temperature superconductors.

In another strongly coupled superconductor Nb non-Fermi liquid behavior can be observed already at low temperatures. While the position of maximum in the calculated ERS spectra for noninteracting electrons is 210 cm^{-1} , the experimental value $\omega \approx 1000 \text{ cm}^{-1}$, i.e. five times larger (Fig.2(b)). For Nb, both the real and imaginary parts of the electron self-energy have large values already at low temperatures. This results in the appearance of a low-frequency feature in our calculation (Fig.2(b)). This quasiparticle peak arises due to a large mass renormalization and can be still observed if the quasiparticle damping is small in this energy range, as our calculation shows (inset in Fig.2(b)). The same result was found for other strongly coupled metals Ta and V. However, we did not observe signatures of these features up to the detection limit of our spectrometer ($\approx 100 \text{ cm}^{-1}$). Possibly, this indicates an increase of coupling at low frequencies as compared with the calculation, which

can lead to suppression of the low-frequency peaks. The large quasiparticle damping (inset in Fig.2(b)), which becomes frequency-independent at high temperatures, determines the appearance of broad relaxation peaks at higher energies at all temperatures, which were well reproduced in the calculations (Fig.2(b)). Thus, we firstly report the observation of the normal-state intraband electronic continuum in Nb, the redistribution of which has been evidenced earlier.[16] The electron-phonon coupling constant in Nb was estimated to be $\lambda=1.27$.

The room temperature spectra for a number of metals are shown in Fig.3. As in the abovementioned examples the spectra contain the broad continua sometimes with superimposed peaks arising from the first- and second-order phonon scattering. All spectra show rather strong temperature dependences which will be reported elsewhere. The comparison with the calculation helps to explain the energy positions of the experimental peaks for each metal. For example, the ERS spectra for Al and V looks very similar but their continua energies are governed by different processes. In Al the spectrum position is determined by the qv_z term because its room-temperature relaxation rate $\Gamma \approx 400 \text{ cm}^{-1}$ is much lower than $qv_z \approx 1200 \text{ cm}^{-1}$. For V the situation is quite contrary and the spectral weight is transferred to high en-

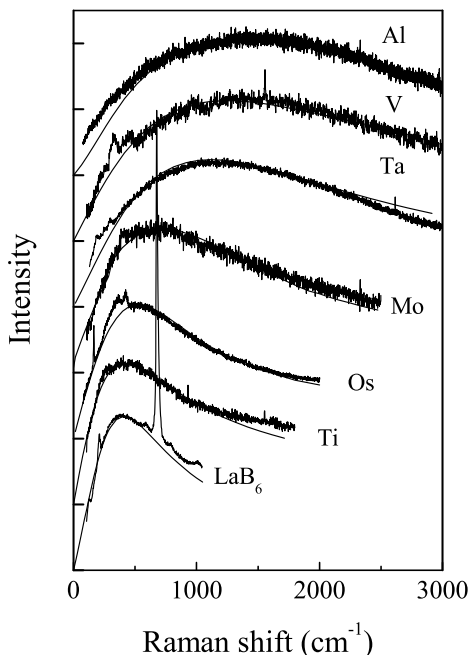


FIG. 3: Raman spectra for a number of metals taken at 300K. Narrow lines in some spectra are the first- and second-order phonon scattering. Calculated spectra are shown by solid lines.

TABLE I: Experimental values for the electron-phonon coupling λ_{exp} and relaxation frequency Γ_{exp} (in cm^{-1}). Literature data of the transport λ_{tr} [32, 33], calculated by McMillan[31, 34] λ_{McM} and Γ_{opt} from optical experiments [35–37] are shown for comparison

	λ_{exp}	λ_{tr}	λ_{McM}	Γ_{exp}	Γ_{opt}
Al	0.26	0.39	0.38	375	557
Mo	0.33	0.32	0.41	450	446
Nb	1.15	1.06	0.82	1500	1210
Os	0.3	0.54	0.39	360	530
Pb	1.04	1.48	1.12	1290	1625
Re	0.77	0.76	0.46	1010	585
Ta	0.83	0.87	0.65	1080	616
Ti	0.31	0.54	0.38	430	400
V	0.87	1.09	0.6	1140	637
W	0.13	0.26	0.28	175	265
LaB ₆	0.19		0.33	270	160

ergies due the strong electron-phonon scattering. The frequency dependences of the ERS peaks and their temperature dependences are satisfactorily fitted by (Eq.2) and magnitudes of the electron-coupling constant λ are estimated from these fits (Fig.3). The derived values of λ and relaxation rates Γ are given in Table I for all investigated metals together with available data from literature. We should note a rather good coincidence between the derived and literature λ for strongly coupled metals (having superconducting temperatures $T_c \geq 1^\circ\text{K}$) while for the low T_c metals, our constants are, as a rule, smaller than the literature ones. The frequency dependence of the ERS spectra results from both the scattering processes of carriers due to interaction with phonons and Coulomb repulsion. It may be suggested that the experiment measures the effective coupling constant which is renormalized by the Coulomb interaction. It is such effective coupling constant that determines transition temperature for weakly coupled systems.[31]

In summary, we presented convincing evidence for the ERS observation in metals, which is, indeed, attributed to intraband electronic excitations. An account of finite q effects when calculating the ERS spectra is important, especially for metals with the weak electron-phonon coupling even at high temperatures. In the strongly coupled systems the relaxation rate for electrons usually overcomes the qv_z term that allows one to obtain a good description using the Drude-like expression in the collision limited regime. The electron-phonon interaction becomes apparent in the ERS spectra of metals owing to transfer of the spectral intensity to the high frequency range. It is found to be the leading channel of the electron self-energy renormalization in the investigated metals. The relaxation rates for electrons Γ and electron-phonon coupling constants λ are estimated from the comparison of

the experimental spectra with the calculated ones. The agreement between the obtained λ values and those available in literature is fairly good. Thus, the ERS is shown to be an alternative to the transport and optical measurements to estimate the strength of the electron-phonon interaction.

This research was partly supported by RFBR grants No. 11-02-00306 and 10-02-96011 and by UD RAS program for young scientists. Authors acknowledge A.A. Eliseev for help in dealing with low temperature measurements.

-
- [1] T. P. Devereaux and R. Hackl, *Rev. Mod. Phys.* **79**, 175 (2007).
 - [2] I. Bozovic, , D. Kirillov, A. Kapitulnik, K. Char, M. R. Hahn, M. R. Beasley, T. H. Geballe, Y. H. Kim, and A. J. Heeger, *Phys. Rev. Lett.* **59**, 2219 (1987).
 - [3] Cooper, S. L., M. V. Klein, B. G. Pazol, J. P. Rice, and D. M. Ginsberg, 1988, *Phys. Rev. B* **37**, 5920.
 - [4] Cooper, S. L., F. Slakey, M. V. Klein, J. P. Rice, E. D. Bukowski, and D. M. Ginsberg, 1988, *Phys. Rev. B* **38**, 11934.
 - [5] Varma, C. M., *Physica C* **162-164**, 303, (1989).
 - [6] A. Virosztek, and J. Ruvalds, *Phys. Rev. Lett.* **67**, 1657 (1991); *Phys. Rev. B* **45**, 347 (1992)
 - [7] A. P. Kampf, and W. Brenig, *Z. Phys. B: Condens. Matter* **89**, 313 (1992).
 - [8] T. P. Devereaux, and A. P. Kampf, *Phys. Rev. B* **59**, 6411 (1999).
 - [9] E. G. Maksimov, M. L. Kulic, and O. V. Dolgov, *Advances in Condensed Matter Physics* **2012**, ID 423725 (2010).
 - [10] V. N. Kostur and G. M. Eliashberg, *JETP Letters*, **53**, 391 (1991)
 - [11] K. Itai, *Phys. Rev. B* **45**, 707 (1992).
 - [12] S. N. Rashkeev and G. Wendin, *Z. Phys. B* **93**, 33 (1993).
 - [13] M. V. Klein, and S. B. Dierker, *Phys. Rev. B* **29**, 4976 (1984).
 - [14] M. V. Klein, in *Light Scattering in Solids III*, edited by M. Cardona and G. Guntherodt Springer-Verlag, Berlin, 1982, p. 121.
 - [15] R. Hackl, R. Kaiser, and S. Schick Tanz, *J. Phys. C* **16**, 1729 (1983)
 - [16] S. B. Dierker, , M. V. Klein, G. W. Webb, and Z. Fisk, *Phys. Rev. Lett.* **50**, 853 (1983).
 - [17] B. I. Verkin and B. G. Lazarev, *Izv. Akad. Nauk SSSR, Ser. Fiz.* **12**, 598 (1948)
 - [18] M. S. Khakin and V. P. Bykov, *Sov. Phys. JETP* **3**, 119 (1956))
 - [19] A. A. Abrikosov and L. A. Falkovski, *Sov. Phys. JETP* **13**, 179 (1961)
 - [20] A. A. Abrikosov, and V. M. Genkin, *Sov. Phys. JETP* **38**, 417 (1974).
 - [21] Yu. S. Ponomov, G. A. Bolotin, C. Thomsen, and M. Cardona, *Phys. Status Solidi B* **208**, 257 (1998).
 - [22] I. P. Ipatova, M. I. Kaganov, and A. V. Subashiev, *Sov. Phys. JETP* **57**, 1066 (1983).
 - [23] L. A. Falkovskii, *Sov. Phys. JETP* **76**, 331 (1993).
 - [24] E. G. Maksimov and S. V. Shulga, *Solid State Commun.* **97**, 553 (1996).
 - [25] S.V. Shulga, O.V. Dolgov, and E.G. Maksimov, *Phys. C* **178**, 266 (1991)
 - [26] Landolt-Bornstein, New Series III/13a (1981)
 - [27] Landolt-Bornstein, New Series III/15b (1985)
 - [28] A. Dervisch and R. Loudon, *J. Phys. C* **9**, L669 (1976). M.M. Kirillova, L.V. Nomerovannaya, *Sov. Phys. Solid State* **20**, 984 (1978)
 - [29] O.K. Andersen and O. Jepsen, *Phys. Rev. Lett.* **53**, 2571 (1984)
 - [30] A. Zawadowski, and M. Cardona, *Phys. Rev. B* **42**, 10732(1990)
 - [31] W. L. McMillan, *Phys. Rev.* **167**, 331(1968)
 - [32] B. A. Sanborn, P. B. Allen, and D. A. Papaconstantopoulos, *Phys. Rev. B* **40**, 6037 (1989)
 - [33] P. B. Allen, *Phys. Rev. B* **36**, 2920 (1987)
 - [34] G. Schell, H. Winter, H. Rietschel, and F. Gompf, *Phys. Rev. B* **25**, 1589 (1982)
 - [35] M.M. Kirillova, L.V. Nomerovannaya and M. M. Noskov, *Sov. Phys. Solid State* **16**, 1425 (1974)
 - [36] G. P. Motulevich , *Sov. Phys. Usp.* **12**, 80 (1969)
 - [37] Shin-ichi Kimura, Takao Nanba, Satoru Kunii and Tadao Kasuya, *Phys. Rev. B* **50**, 1406 (1994)