

# Car-Parrinello Simulation of the Reaction of Aluminium with Oxygen

Marius Schulte<sup>†</sup> and Irmgard Frank<sup>\*,‡</sup>

*Ludwig-Maximilians-Universität München, Department Chemie, Butenandtstr. 11, 81377 München, Germany, and Leibniz Universität Hannover, Institut für Physikalische Chemie und Elektrochemie, Callinstr. 3A, 30167 Hannover, Germany*

E-mail: irmgard.frank(at)theochem.uni-hannover.de

## Abstract

We present Car-Parrinello molecular dynamics simulations of the initial reaction steps leading to an inert oxide layer on aluminium. The mechanism of the reaction of the aluminium surface with single oxygen molecules is analysed. After adsorption at the surface the oxygen molecules dissociate at a femtosecond timescale and the atoms are chemisorbed at the surface at a distance of several angstrom. When the aluminium surface is exposed to higher oxygen pressure, a surface layer essentially consisting of threefold coordinated oxygen atoms starts to form.

---

\*To whom correspondence should be addressed

<sup>†</sup>Ludwig-Maximilians-Universität München

<sup>‡</sup>Leibniz Universität Hannover

## Introduction

Aluminium as a base metal gains its corrosion resistance from a thin layer consisting of a mixture of aluminium oxide and aluminium hydroxide which forms immediately when a clean aluminium surface is exposed to air.<sup>1</sup> The composition, thickness and properties of this chemically passivating layer depend on the particular conditions of formation. Spontaneous self-passivation leads to layers of a few nanometers thickness. Significantly thicker and harder layers essentially consisting of well-ordered  $\alpha$ -Al<sub>2</sub>O<sub>3</sub> can be obtained electrochemically. Like for bulk aluminium oxide, the surface of passivated aluminium is covered with OH groups with different coordination to the bulk.<sup>2</sup> The reaction of oxygen with aluminium was investigated in detail with STM experiments as early as 1992 emphasizing the role of 'hot adatoms'.<sup>3,4</sup> The oxygen atoms were found to be at an average distance of 8 nm after dissociation. Theoretical studies yielded lower separations.<sup>5,6</sup> A subsequent experimental study<sup>7</sup> measured a much lower transient mobility of the adsorbed oxygen atoms (oxygen-oxygen separation of 0.5 nm on average) which is in way better agreement with the high oxygen affinity of aluminium. The subject continued to be investigated in experimental and theoretical studies. A recent HRTEM study investigates the growth of an aluminium oxide layer in contact with the melt.<sup>8</sup>

In the present study we want to simulate, at first-principles level, the initial steps of the formation of such layers. Previous theoretical investigations using density functional theory (DFT) focussed on alumina surfaces and their reactivity.<sup>9-14</sup> Early work confirmed the experimental finding that the (0001) surface is most stable.<sup>9,10</sup> First-principles molecular dynamics simulations<sup>13,14</sup> showed the facile reaction of the oxide surface with water molecules leading to OH coverage. In a study of the reaction of oxygen with aluminium<sup>15,16</sup> the authors induced an artificial barrier to chemisorption in order to explain the results by Brune et al.<sup>3</sup> This barrier was constructed by claiming the relevance of 'non-adiabatic effects' when the triplet oxygen molecule chemisorbs at the surface. However, the proper treatment of non-adiabatic effects with density functional theory in the Kohn-Sham approximation is unclear at best. On top, it is not at all clear how any non-adiabatic calculation should help to describe an intersystem crossing as it does not include

spin terms in the Hamiltonian. Also in view of the more recent experiments which indicate a much lower transient mobility and faster chemisorption,<sup>7</sup> an artificial extension of DFT might not be necessary to model the system. To analyse the mechanism and to elucidate the influence of the multiplicity we investigate the reaction of an aluminium surface with one oxygen molecule simulating the gas-phase situation as well as the reaction with liquid oxygen.

## Results and discussion

A series of simulations with one attacking oxygen only was performed at a temperature of 300 K using different initial orientations of the oxygen molecule relative to the surface. The incident oxygen molecule is moving towards the surface with a velocity of 400 m/s which leads to a reaction within a few hundred femtoseconds in all ten simulation runs. In each case, the oxygen molecule binds to the surface and dissociates. 1 illustrates the motion of the two oxygen atoms for one of the simulation runs. The molecule hits the surface 120 fs after the end of the equilibration. At this point it is accelerated to a velocity of roughly 1300 m/s by the attraction of the surface. The distance plot shows that it starts to dissociate but 100 fs later. Soon after the first oxygen atom (red graph in 1, lower plot) contacts the surface, the second atom (black graph) is bound to a second surface aluminium atom. In this particular simulation run the aluminium layer is strongly disturbed immediately upon the oxygen impact: During the bond dissociation the first atom is pushed over the bound aluminium atom to its new position while the aluminium atom itself is pulled out of the surface to another position leading to a relatively large aluminium displacement (1). Apart from this special feature of this particular MD run, the reaction follows always the same scheme: adsorption of one oxygen atom, adsorption of the second, dissociation and relaxation at distant lattice sites.

2 shows the increase in temperature (blue graph) of the total system. Both the adsorption and the consecutive dissociative reaction lead to a significant increase in temperature. From the comparison with 1 it is obvious that initially the oxygen atoms gain kinetic energy, while in the

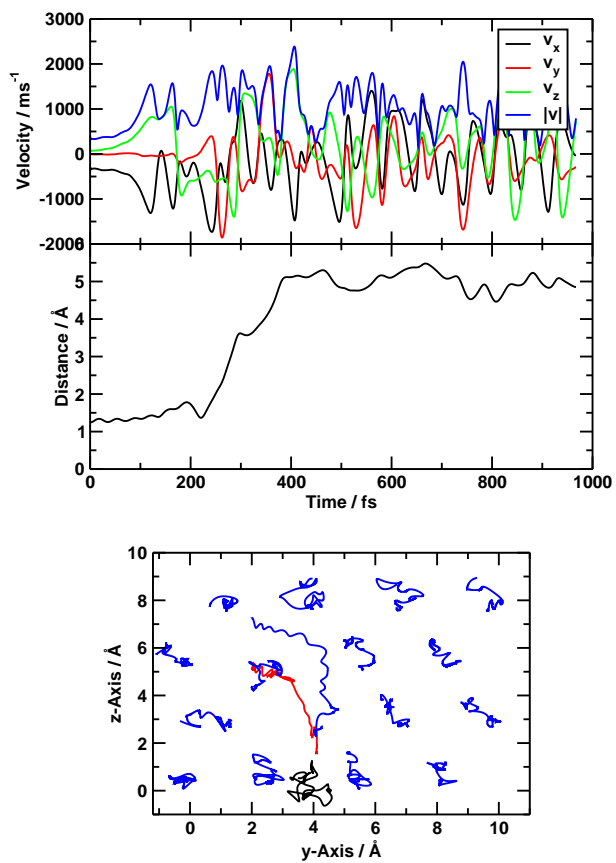


Figure 1: Reaction of an oxygen molecule with an aluminium surface as observed in one of the simulation runs. The upper plot shows the velocities of the center of mass of the two oxygen atoms and their distance. In the lower plot the motion of the oxygen atoms on the aluminium surface are depicted (black and red). One of the surface atoms (blue) is moved to another lattice site as a consequence of the impact.

further course of the reaction the increase of the kinetic energy is taken up by the surface. The Kohn-Sham energy is lowered by roughly 0.14 a.u. (370 kJ/mol). Since no thermostats were used in the simulation, the electronic system heats up quite a bit and gains kinetic energy. The single reaction steps can be followed from the graphs of the charge and the spin charge (2). During the first reaction step, which is the adsorption to the surface, the charge of the oxygen molecule changes only partially. The spin charge is transferred to the surface within 160 fs while the oxygen atoms are fully ionized after about 400 fs.

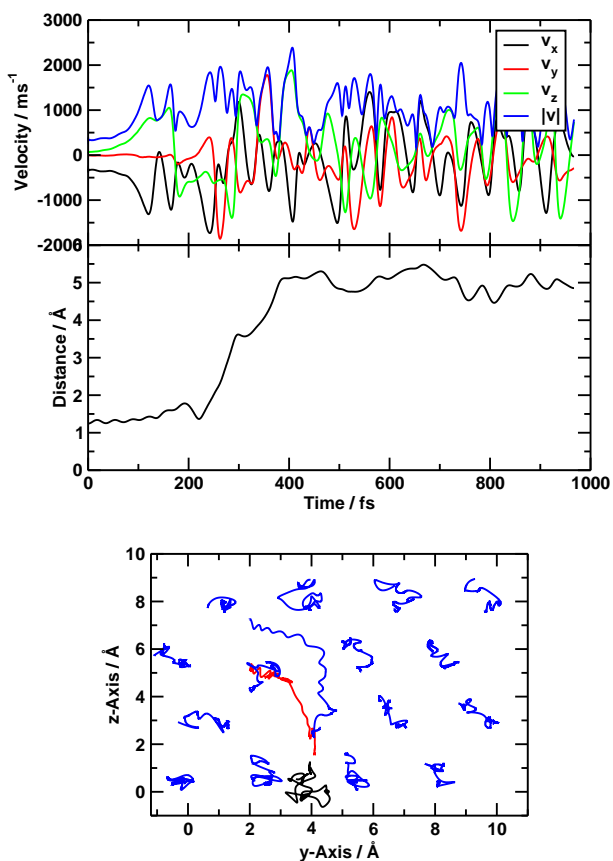


Figure 2: Change of energy, temperature, charge and spin charge during the strongly exothermic reaction of a single oxygen molecule with the surface. Top graph: Kohn-Sham energy (black), classical energy (red), total energy of the Car-Parrinello Lagrangian (green), and temperature (blue). The temperature is proportional to the kinetic energy of the ions and hence to the difference between the black and the red curve, while the difference between the red and the green curve corresponds to the fictitious kinetic energy of the orbitals in Car-Parrinello theory. The two lower graphs show the charges and spin charges of the two oxygen atoms. While the spin charge at the oxygen atoms decreases during adsorption and is transferred to the surface, the charge of the oxygen atoms is increased during the full reaction including dissociation and relaxation.

3 shows some snapshots of this simulation run. Before the start of the reaction, the oxygen molecule is in its triplet ground state which is reflected by a high spin density. The spin density is transferred to the surface while the molecule binds to the surface and forms a three-membered ring with an aluminium atom. (The total spin of the system stays 1). After the spin charge of the oxygen atoms has decayed to zero, they dissociate (fourth snapshot in 3). Some 30 fs later there is again a certain accumulation of spin density at the oxygen atoms which is obvious also from the peak in the graph of the spin charge (2) about 270 fs after the end of the equilibration. After this oscillation the oxygen atoms relax in surface lattice sites whereby an aluminium atom is strongly disturbed and dislocated from its lattice site to another one (3, last snapshot). From following the behaviour of the spin charge, it is obvious that the surface can easily swallow the spin. The two unpaired spins avoid each other within the electron gas of the metal resulting in a vanishing exchange interaction. This finding is trivial: There is nothing like an aluminium triplet state which could energetically be discriminated from the singlet state.

4 shows the variance of the O-O distances during the reaction. The motion of the oxygen atoms ends up at distances of about  $1 a_s$ ,  $\sqrt{3} a_s$ ,  $2 a_s$ , and  $\sqrt{7} a_s$  with  $a_s = 2.86 \text{ \AA}$  being the nearest neighbour spacing. The distribution agrees excellently with experiment.<sup>7</sup> Note, however, that the attribution of a certain distance to a certain channel is not a hundred percent reliable as is illustrated by the exemplary simulation run discussed above (1): Due to the strong disturbance of the surface layer, a final distance of  $5 \text{ \AA}$  is reached, while from the distance of the relevant lattice sites a distance of  $7.6 \text{ \AA}$  would be computed.

The average distance obtained in the ten simulation runs is 0.4 nm. This result is in nice agreement with the publication by Schmid et al.<sup>7</sup> who report a mean interatomic distance after adsorption of 0.5 nm. The deviation of the numerical value is within the error which stems from the limitations in statistics, simulation time and simulation cell size. The computed value certainly does not agree, however, with the value of 8 nm reported in the work by Brune et al.<sup>3,4</sup> Due to the lower resolution of these early STM pictures adatom pairs were obviously interpreted as single atoms.

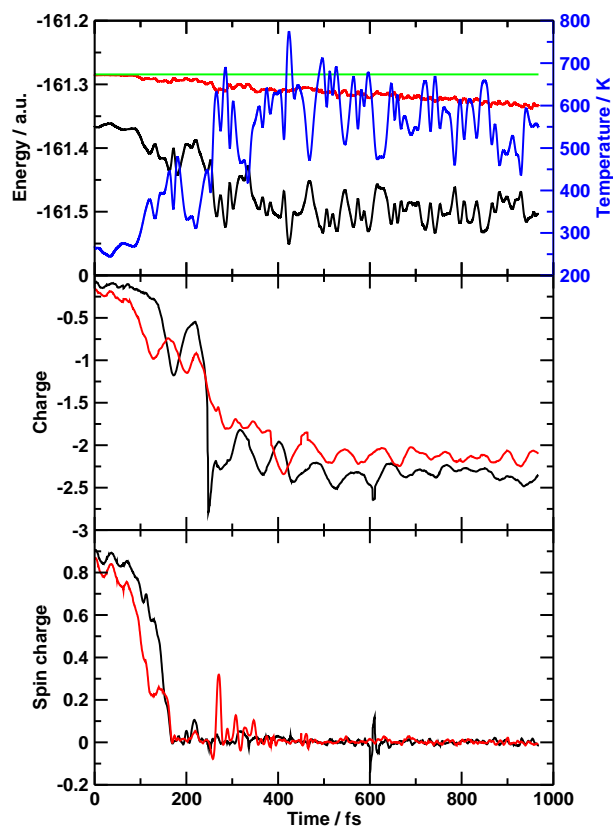


Figure 3: Snapshots from a simulation run showing a single oxygen molecule reacting with the surface. The oxygen molecule (red) approaches the surface and dissociates. The spin densities are shown in orange.

Experimentally, the distribution of the adatoms (or rather adatom pairs) was found to be random at low oxygen pressure while at higher oxygen pressure the formation of islands was observed.<sup>4</sup> Also increasing the temperature supports this island formation.<sup>17</sup> From these experimental observations and from our results, island formation is less due to the initial motion of the oxygen atoms till they are chemisorbed, than to the strong increase of kinetic energy in the upper aluminium layer leading to partial melting of the metal. In our picture it is not single oxygen atoms which move on the surface to form large islands, but small and hard aluminium oxide islands which float on a soft metal surface.

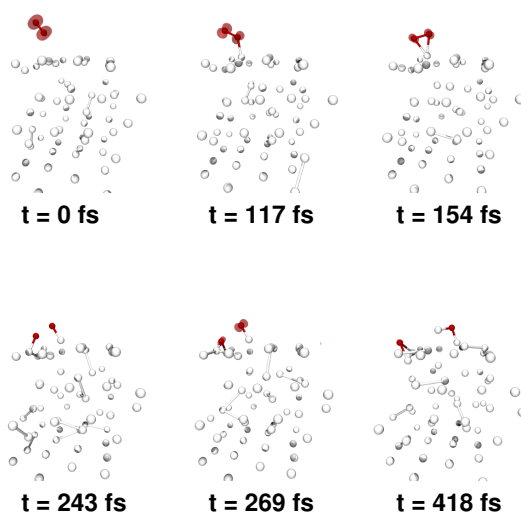


Figure 4: Change of the distance of the two oxygen atoms in the ten simulations and average value. The average distance after dissociation and relaxation (0.4 nm) agrees well with the experimental value (0.5 nm).

The beginning of a surface layer formation was studied in an additional simulation with liquid oxygen simulated by 24 oxygen molecules inbetween the aluminium layers. 5 shows some snapshots from a molecular dynamics simulation at 300 K. After the equilibration, the distance between the nearest oxygen atoms and the surface is about 2.3 to 2.4 Å. Nine out of 24 oxygen molecules in the simulation cell react during the first 10000 steps (484 fs), four of them at the slab surface shown in the figure. A thermostat was used which strongly reduces the kinetic energy set free in this extremely exothermic surface reaction. Nevertheless, the strong disorder of the top-most



aluminium layer is obvious. Statistically, similar numbers of oxygen atoms with two up spins and two down spins hit the surface, so a large spin accumulation never happens. Upon adsorption and dissociation, the oxygen atoms start to form a rigid surface layer of triply coordinated adatoms illustrating the beginning of  $\text{Al}_2\text{O}_3$  formation.

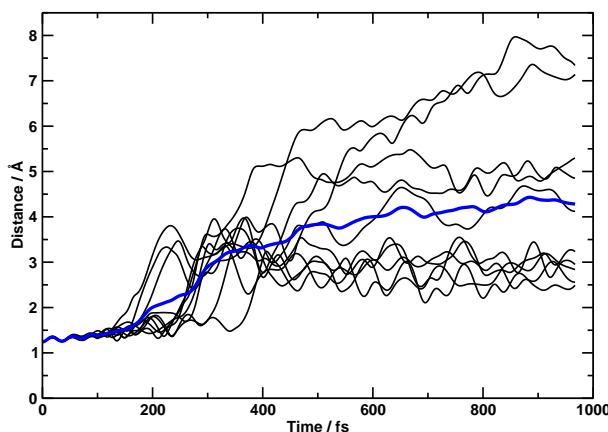


Figure 5: Snapshots from the molecular dynamics simulation of the reaction of the aluminium surface with molecular oxygen.

## Conclusions

In conclusion, Car-Parrinello molecular dynamics simulations of the reaction of molecular oxygen with aluminium show that the oxygen molecules are chemisorbed immediately upon contact with the surface. Dissociation leads to adatoms which are separated by 0.4 nm on average in very good agreement with experiment.<sup>7</sup> The mechanism is best described as an adsorption-dissociation mechanism: the oxygen atoms are chemisorbed, dissociate within a few 100 fs and relax within about a picosecond at lattice sites close-by. Mechanistically this is inbetween a dissociative chemisorption and a 'hot adatom' mechanism. The resulting oxygen atoms are not necessarily located at neighbouring sites, but, on the other hand, do not move freely over the surface before relaxing. Extensions of density functional theory are not necessary to explain this reaction. The spin density of the triplet oxygen molecule is simply transferred to the surface during the reaction. Density functional theory within the BLYP approximation turns out to be very well suited to describe this

surface reaction. The approach may serve to investigate many more experiments in this field.

## Methods

For our molecular dynamics simulations we used the implementation of the Car–Parrinello molecular dynamics (CPMD) scheme<sup>18</sup> in the CPMD code.<sup>19</sup> This scheme uses density functional theory (DFT)<sup>20,21</sup> for the description of the electronic structure. The unrestricted formulation of the Becke–Lee–Yang–Parr (BLYP)<sup>22,23</sup> generalized gradient approximation (GGA) functional was used. In the plane wave code CPMD, pseudopotentials are used for the description of the core electrons. The separable dual space Gaussian pseudopotentials by Goedecker, Teter and Hutter (GTH)<sup>24,25</sup> were used with a plane–wave cutoff of 90 Rydberg. The fictitious electronic mass was set to the default value of 400 atomic units (a.u.). A small time step of 2 a.u. (0.048 fs) was chosen. The temperature of the nuclei was set to 300 K. The model system consists of four layers of 16 aluminium atoms stacked in an ABCA order in an orthorhombic simulation cell describing a (111)–surface of fcc aluminium. Previous test calculations showed that four layers are sufficient to describe the chemistry of the system. A lattice constant of  $a_0 = 4.04959 \text{ \AA}$  was used for calculating the cell parameters, corresponding to a fcc nearest neighbour distance of  $a_s = a_0/\sqrt{2} = 2.86349$ . Between the layers a spacing of approximately  $12.0 \text{ \AA}$  is introduced. The resulting cell parameters are  $21.35213 \text{ \AA}$  ( $4\sqrt{3}/3 a_0 + 12.0$ ),  $11.45396 \text{ \AA}$  ( $4\sqrt{2}/2 a_0$ ) and  $9.91942 \text{ \AA}$  ( $2\sqrt{3}/2 a_0$ ). For the simulation of liquid oxygen, the spacing between the layers is filled with 24 oxygen molecules corresponding to a density of approximately  $935 \frac{\text{kg}}{\text{m}^3}$ , which is a bit lower than that of liquid oxygen ( $1120 \frac{\text{kg}}{\text{m}^3}$ ). As liquid oxygen is highly reactive and would react immediately, it was replaced by unreactive nitrogen molecules during the equilibration. The temperature of the reacting system would rise rapidly in the liquid oxygen simulation, hence Nosé–Hoover thermostats<sup>26–28</sup> were used to control the temperature of the nuclei as well as the fictitious kinetic energy of the electrons. As thermostat parameters we use a frequency of  $3000 \text{ cm}^{-1}$  for coupling the nuclei to the bath and a frequency of  $10000 \text{ cm}^{-1}$  for the electrons. The fictitious kinetic energy of the electrons was chosen to be 0.07

a.u. The charges and spin charges were calculated by integrating the densities and spin densities, respectively, using Bader analysis to determine the integration range.<sup>29</sup>

## References

- (1) Holleman, A. F.; Wiberg, E. *Lehrbuch der Anorganischen Chemie*, 101st ed.; de Gruyter: Berlin, New York, 1995.
- (2) Knözinger, H.; Ratnasamy, P. *Catal. Rev. Sci. Eng.* **1978**, *17*, 31–70.
- (3) Brune, H.; Wintterlin, J.; Behm, R. J.; Ertl, G. *Phys. Rev. Lett.* **1992**, *68*, 624–626.
- (4) Brune, H.; Wintterlin, J.; Trost, J.; Ertl, G.; Wiechers, J.; Behm, R. J. *J. Chem. Phys.* **1993**, *99*, 2128.
- (5) Engdahl, C.; Wahnström, G. *Surf. Sci.* **1994**, *312*, 429–440.
- (6) Wahnström, G.; Lee, A. B.; Strömquist, J. *J. Chem. Phys.* **1996**, *105*, 326–336.
- (7) Schmid, M.; Leonardelli, G.; Tscheließnig, R.; Biedermann, A.; Varga, P. *Surface Science Letters* **2001**, *478*, 355–362.
- (8) Oh, S. H.; Chisholm, M. F.; Kauffmann, Y.; Kaplan, W. D.; Luo, W.; Rühle, M.; Scheu, C. *Science* **2010**, *330*, 489–493.
- (9) Causa, M.; Dovesi, R.; Pisani, C.; Roetti, C. *Surf. Sci.* **1989**, *215*, 259.
- (10) Manassidis, I.; Vita, A. D.; Gillan, M. J. *Surf. Sci. Lett.* **1993**, *285*, 517–521.
- (11) Frank, I.; Marx, D.; Parrinello, M. *J. Am. Chem. Soc.* **1995**, *117*, 8037.
- (12) Frank, I.; Marx, D.; Parrinello, M. *J. Chem. Phys.* **1996**, *104*, 8143.
- (13) Hass, K. C.; Schneider, W. F.; Curioni, A.; Andreoni, W. *Science* **1998**, *282*, 265–268.

- (14) Hass, K. C.; Schneider, W. F.; Curioni, A.; Andreoni, W. *J. Phys. Chem. B* **2000**, *104*, 5527–5540.
- (15) Behler, J.; Delley, B.; Lorenz, S.; Reuter, K.; Scheffler, M. *Phys. Rev. Lett.* **2005**, *94*, 036104.
- (16) Behler, J.; Reuter, K.; Scheffler, M. *Phys. Rev. B* **2008**, *77*, 115421.
- (17) Trost, J.; Brune, H.; Wintterlin, J.; Behm, R. J.; Ertl, G. *J. Chem. Phys.* **1998**, *108*, 1740.
- (18) Car, R.; Parrinello, M. *Phys. Rev. Lett.* **1985**, *55*, 2471–2474.
- (19) CPMD, Version 3.15, J. Hutter et al., <http://www.cpmid.org/>, Copyright IBM Corp 1990-2008, Copyright MPI für Festkörperforschung Stuttgart 1997-2001.
- (20) Hohenberg, P.; Kohn, W. *Phys. Rev. B* **1964**, *136*, 864–871.
- (21) Kohn, W.; Sham, L. J. *Phys. Rev. A* **1965**, *140*, 1133–1138.
- (22) Becke, A. *Phys. Rev. A* **1988**, *38*, 3098–3100.
- (23) Lee, C.; Yang, W.; Parr, R. G. *Phys. Rev. B* **1988**, *37*, 785–789.
- (24) Goedecker, S.; Teter, M.; Hutter, J. *Phys. Rev. B* **1996**, *54*, 1703–1710.
- (25) Hartwigsen, C.; Goedecker, S.; Hutter, J. *Phys. Rev. B* **1998**, *58*, 3641–3662.
- (26) Nosé, S. *Mol. Phys.* **1984**, *52*, 255.
- (27) Nosé, S. *J. Chem. Phys.* **1984**, *81*, 511.
- (28) Hoover, W. G. *Phys. Rev. A* **1985**, *31*, 1695.
- (29) Bader, R. F. W. *Atoms in molecules: A quantum theory*; Oxford University Press: New York, 1990.