

Scintillation properties of pure and Ce³⁺-doped SrF₂ crystals

R. Shendrik^{a,b,*}, E. A. Radzhabov^{a,b}, A. I. Nepomnyashchikh^{a,b}

^aVinogradov Institute of geochemistry SB RAS, Favorskogo 1a, Irkutsk, Russia, 664033

^bPhysics department of Irkutsk state university, Gagarina blvd 20, Irkutsk, Russia, 664003

Abstract

In this paper results of scintillation properties measurements of pure and Ce³⁺-doped strontium fluoride crystals are presented. We measure light output, scintillation decay time profile and temperature stability of light output. X-ray excited luminescence outputs corrected for spectral response of monochromator and photomultiplier for pure SrF₂ and SrF₂-0.3 mol.% Ce³⁺ are approximately 95% and 115% of NaI-Tl emission output, respectively. A photopeak with a 10% full width at half maximum is observed at approximately 84% the light output of a NaI-Tl crystal after correction for spectral response of photomultiplier, when sample 10x10 mm of pure SrF₂ crystal is excited with 662 KeV photons. Corrected light output of SrF₂-0.3 mol.% Ce³⁺ under 662 KeV photon excitation is found at approximately 64% the light output of the NaI-Tl crystal.

Keywords: scintillator, well-logging, alkali-earth fluorides, cerium doped crystals

1. Introduction

The interest in new scintillation materials is promoted by increasing number of new applications in medicine, science, and homeland security, which require ramp-up of material production. The most perspective scintillators are bromides and iodides doped with Ce³⁺ and Eu²⁺ ions, such as SrI₂-Eu and LaBr₃-Ce. These crystals have high light outputs (up to 100000 photons/MeV for SrI₂-Eu), good energy resolution, and high proportionality (Dorenbos, 2010). Disadvantages of these scintillators are high hygroscopic and price. In addition, SrI₂-Eu has temperature instability of light output observed by Alekhin et al., 2011.

For the most applications a cheaper NaI-Tl scintillator has quite properties (light output about 45000 photons/MeV cited in Derenzo, 2012). Therefore, one of the way in development of new scintillators is to find new materials with similar to NaI-Tl properties but no hygroscopic. In this way advanced materials for new scintillators are alkali-earth fluorides doped with rare earth ions. Theoretical limit of light output for them is up to 50000 photons/MeV (Dorenbos, 2010). If an efficient energy transfer is provided then alkali-earth fluorides will be promising scintillators. A real light output of CaF₂-Eu is 18000-22000 photons/MeV, but BaF₂ and BaF₂-Ce crystals demonstrate lower light output at about 10000 photons/MeV (Visser et al., 1991). Scintillation properties of SrF₂ crystals are almost not investigated. Light output of SrF₂ was estimated about 10000-12000 photons/MeV by Schotanus et al., 1987. However, potential light output of SrF₂ will be higher. Also SrF₂ crystals doped with Ce³⁺ and Pr³⁺ have a temperature stability

of light output in wide range (20 °C to 200 °C) (Shendrik and Radzhabov, 2010). Therefore, SrF₂ can be high-potential scintillator for well-logging. So, scintillator properties of strontium fluoride crystals are among the least studied of fluorides crystals, but these crystals have potential applications. Thus, the investigations of scintillation properties of strontium fluorides are topical today. This paper describes the scintillation properties of pure and cerium doped strontium fluorides crystals, a newly discovered inorganic scintillator.

2. Experimental methodology

Growing with addition of CdF₂ as an oxygen scavenger, oxygen-free crystals of pure SrF₂ and doped with different concentrations of Ce³⁺ ions were grown in a graphite crucible by the Stockbarger method. We applied several experimental techniques in measurement of scintillation properties of the crystals. To determine light output, pulsed-height spectra under ¹³⁷Cs 662 KeV gamma source excitation were measured with PMT FEU-39A, a homemade preamplifier and an Ortec 570A spectrometric amplifier. The crystals of 10x10 mm dimensions were polished and then covered with several layers of ultraviolet reflecting Teflon tape (PTFE tape). The shaping time of Ortec 570 spectrometric amplifier was set at 10 μs to collect much light from scintillator.

X-ray excited luminescence was performed using x-ray tube with Pd anode operating at 35 kV and 0.8 mA. The spectra were recorded at photon-counting regime using PMT FEU-39A and vacuum grating monochromator VM-4.

Scintillation decay time profiles under ¹³⁷Cs E=662 KeV gamma source excitation were recorded by 200 MHz oscilloscope Rigol DS-1202CA. To register decay curves in wide time interval, we used oscilloscope input resistance set (50 Ω and 2.8 kΩ).

*Corresponding author: Vinogradov Institute of geochemistry SB RAS, Favorskogo 1a, Irkutsk, Russia, 664033

Email address: shendrik@iee.org (R. Shendrik)

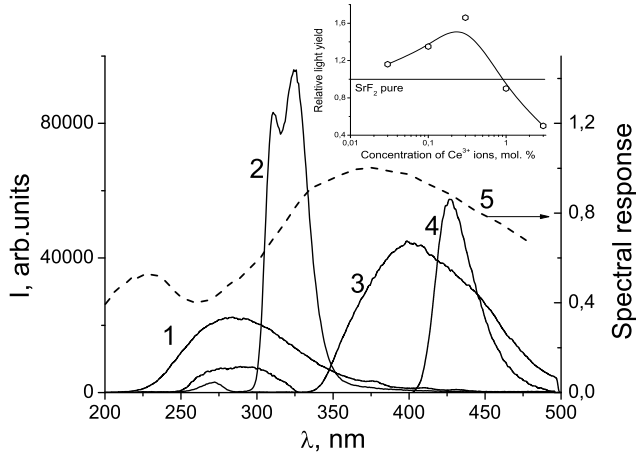


Figure 1: Luminescence spectra of SrF₂ (curve 1), SrF₂-0.3 mol.% Ce³⁺ (curve 2), NaI-Tl (curve 3), and CaF₂-0.1 mol.% Eu²⁺ (curve 4) under x-ray excitation. Dashed curve 5 is spectral sensitivity of the grating monochromator and PMT registration channel. In the inset dependence of integral intensity of emission bands of Ce³⁺ ions versus Ce concentration is presented.

3. Experimental results and discussion

Figure 1 shows spectra of x-ray luminescence of pure SrF₂, NaI-Tl, SrF₂-0.3 mol.% Ce³⁺, and CaF₂-0.1 mol.% Eu²⁺. In the spectrum of SrF₂ a wide band at 280 nm is attributed to self-trapped exciton (STE) emission. In SrF₂ doped with Ce³⁺ ions STE luminescence is quenched and vanished at concentrations Ce³⁺ ions higher than 1 mol. %. The most intense bands in x-ray luminescence spectra of SrF₂-Ce³⁺ crystal at 310 and 325 nm correspond to 5d-4f emission of Ce³⁺ ions.

Luminescence spectrum of CaF₂-Eu²⁺ is shown in Fig. 1, curve 4. Its emission band is centered at 425 nm. This luminescence is due to 4f⁶5d¹-4f⁷ transitions in the Eu²⁺ ion (Kobayasi et al., 1980).

Dependence of integral intensity of Ce³⁺ ions emission bands on Ce concentration is shown in the inset to Figure 1. The highest light output is demonstrated by SrF₂-0.3 mol.% Ce³⁺.

X-ray excited luminescence output measured by integral intensity is compared with the one of NaI-Tl crystal (Table 1). Light output of NaI-Tl crystals is approximately 43000 photons/MeV. Therefore, light output of the measured samples can be estimated. The data are shown in Table 1. Light output of CaF₂-0.1 mol.% Eu²⁺ is about 21500 photons/MeV that is in accordance with known data for CaF₂-Eu crystals given by Derenzo, 2012. Pure SrF₂ has light output about 20640 photons/MeV, doped with 0.3 mol.% and 1 mol.% crystals have the ones about 34000 photons/MeV and 18500 photons/MeV, respectively.

All integral intensities and light outputs are presented without correction for spectral response of registration channel. The spectral response curve is shown in Figure 1, dashed line. The sensitivity of the PMT and monochromator system in SrF₂ and SrF₂-Ce luminescence spectral range is lower than in NaI-Tl and CaF₂-Eu emission region. After the correction, light output of pure SrF₂ luminescence is about 40000 photons/MeV, and SrF₂ doped with 0.3 mol. % and 1 mol. % crystals have light

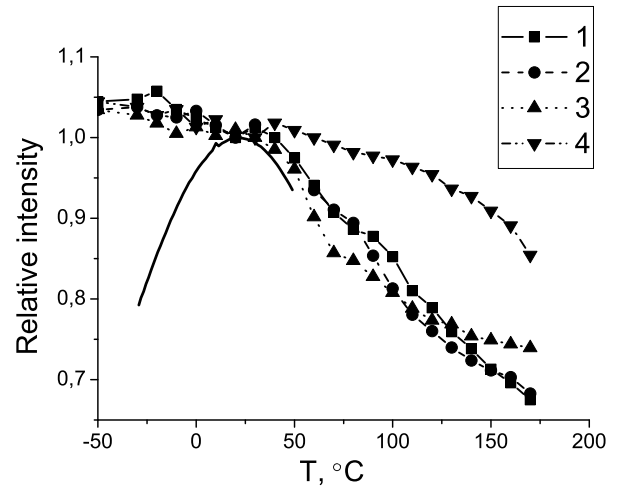


Figure 2: Temperature dependences of relative light output of SrF₂ crystals doped with 0.01 mol. % Ce³⁺ (curve 1); 0.1 mol. % Ce³⁺ (curve 2); 0.3 mol. % Ce³⁺ (curve 3) and 1 mol. % Ce³⁺ (curve 4) in comparison with NaI-Tl (solid line) measured by Moszynski et al., 2006.

outputs about 50000 photons/MeV and 28000 photons/MeV, respectively.

Temperature dependences of x-ray excited luminescence intensity of SrF₂-Ce are given in Figure 2. Emission intensity does not depend on temperature in the range between -50 °C and +50 °C. At higher temperatures decrease of 5d-4f luminescence intensity is observed. At 170 °C temperature light output of SrF₂ doped with 0.01 mol.% and 0.1 mol.% of Ce³⁺ ions decreases to 30 %. 25 % and 15 % decreases in integral emission are found in the SrF₂ crystals doped with 0.3 mol. % Ce³⁺ and 1 mol. %, respectively. Crystals of SrF₂-0.3 mol. % Ce³⁺ and SrF₂-1 mol. % Ce³⁺ demonstrate high temperature stability of light output in the region between -50 °C and 170 °C in comparison with NaI-Tl (see Fig. 2, solid line). For this reason, the SrF₂-Ce³⁺ crystals would be perspective scintillators for well-logging applications.

Figure 3 shows pulse height spectra of SrF₂, SrF₂-0.3 mol. % Ce³⁺ and NaI-Tl. The photopeak corresponding to the ¹³⁷Cs energy photon is seen in each curve in the Figure 3. Light output of SrF₂ and SrF₂-Ce crystals was measured by comparing these response to 662 KeV energy to the response of NaI-Tl crystal with known characteristics under the same conditions. The photopeak in pure SrF₂ is centered at a pulse height that is 42% of the 662 keV photopeak pulse height in NaI-Tl. Using the NaI-Tl light output of 43000 photons/MeV, this implies that the light output of pure SrF₂ is approximately 18000 photons/MeV that is similar to x-ray emission light output (see Table 1). The full width at half maximum (FWHM) in pure SrF₂ of the 662 keV photopeak is 10 %. FWHM of NaI-Tl is 6.7 %, which is consistent with known results given by scintillators database of Derenzo, 2012.

Dependence of SrF₂-Ce relative light output versus concentration is demonstrated in the inset to Figure 3. Best light out-

Table 1: Light output of SrF₂, SrF₂-Ce³⁺, NaI-Tl and CaF₂-0.1 mol.% Eu²⁺ crystals measured under gamma and x-ray excitation.

Crystal	Light output of x-ray excited luminescence spectra		Light output measured by pulse height spectra	
	rel.units	photons/MeV	rel.units	photons/MeV
NaI-Tl	1	43000	1	43000
CaF ₂ -0.1 mol.% Eu ²⁺	0.5	21500	0.44	18920
SrF ₂	0.48	20640	0.42	18060
SrF ₂ -0.3 mol.% Ce ³⁺	0.79	33970	0.32	13760
SrF ₂ -1 mol.% Ce ³⁺	0.43	18490	0.2	8600

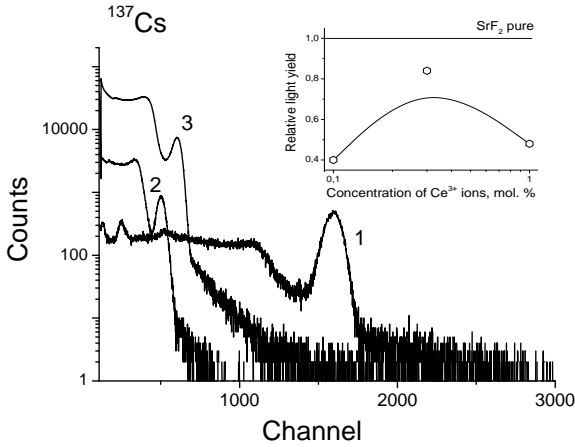


Figure 3: Pulse height spectra of NaI-Tl (curve 1), SrF₂-0.3 mol.% Ce³⁺ (curve 2) and SrF₂ (curve 3) under gamma-source ¹³⁷Cs (E=662 KeV) excitation. In the inset dependence of relative light outputs of SrF₂-Ce crystals versus Ce concentration is presented.

put of the Ce-doped crystals is found for SrF₂-0.3 mol. % Ce³⁺. Its photopeak is centered at a pulse height that is 32 % of the 662 keV photopeak pulse height in NaI-Tl, this implies that the light output of SrF₂-0.3 mol.% Ce³⁺ is approximately 14000 photons/MeV. FWHM of the SrF₂-0.3 mol.% Ce³⁺ is approximately 9.3 %, which is lower than FWHM of pure SrF₂. This fact means that in spite of worse light output SrF₂-0.3 mol.% Ce³⁺ crystal has better energy resolution in comparison with pure strontium fluoride.

All light outputs without any corrections are given in Table 1. Bearing in mind that spectral sensitivity of S20 photocathode (PMT FEU 39A) is higher at CaF₂-Eu and NaI-Tl emission bands than in SrF₂ and SrF₂-Ce luminescence region (Flyckt and Marmonier, 2002). Corrected light outputs of pure SrF₂ is about 80% (36000 photons/MeV) of NaI-Tl and SrF₂-0.3 mol. % of Ce³⁺ – about 60% (26000 photons/MeV) of NaI-Tl.

Scintillation decay time profile of SrF₂-0.3 mol.% Ce³⁺ is shown in Figure 4. Resistance of oscilloscope input was 2.6 KΩ for registration long time decay components in Ce³⁺ emission. The decay time is described by a sum of exponents. First component (2.8 μs) in Ce³⁺ decay is integrated short components. Lifetime of the shortest one equals 130 ns at 50 Ω input resistance in SrF₂-0.3 mol.% Ce³⁺ and it becomes longer with

decrease of Ce concentration. Decay constants of this component in dependence on Ce concentration are presented in the inset of the Figure 4.

Contribution of slow components to scintillation time profile is estimated. In the figure 4 exponential components of total decay curve are shown separately. There are two long time components in SrF₂-0.3 mol.% Ce³⁺ emission. 20% of the light is emitted with a 9 μs time constant, and 25% of the light is emitted with a 280 μs time constant.

Emission decay time of cerium doped alkaline-earth fluorides under optical excitation at lowest energy absorption bands is estimated about 30 ns (Visser et al., 1993; Radzhabov and Kurobori, 2004; Wojtowicz et al., 2000). Under vacuum ultraviolet excitation at exciton and higher energies regions the decay of Ce-doped fluorides became nonexponential (Wojtowicz et al., 2000). Under x-ray excitation the decay curves is also nonexponential (Fig. 4).

Whole decay curve can be described by several processes. Fast stage could be ascribed to resonance energy transition in nearest pairs of exciton and cerium ion. In the inset of the figure 4 concentration dependence of these decay constants is presented. Note that the decay becomes shorter with increasing Ce³⁺ ions concentration due to reduction of distance between exciton and activator ion with increase of cerium ions concentration.

In SrF₂-Ce crystals thermoluminescence glow peaks at 200-250 K were found (Radzhabov, 2001; Maghrabi and Townsend, 2001). Broad glow peaks at higher temperatures are shifted to lower temperature with increasing concentration of Ce³⁺ ions in the SrF₂ crystal (Maghrabi and Townsend, 2001). Long stages in scintillation time profile can be attributed to thermoactivated processes related to electron or hole delayed transfer to the activator ion. A similar energy transfer mechanism has been observed in SrF₂ doped with Pr (Shendrik and Radzhabov, 2012).

Therefore, the difference in light outputs measured from x-ray luminescence and pulse height spectra is explained by presence of intensive slow components in cerium ions luminescence (see Fig. 4). They give a large contribution to total light output. Shaping time of pulse height spectrum measurement is 10 μs, and a large part of emitted light is not registered whereas a rate of x-ray excited luminescence spectra registration is amount about 1 s⁻¹ that leads to much more light registration.

Light output of SrF₂-Ce³⁺ samples can be increased by de-

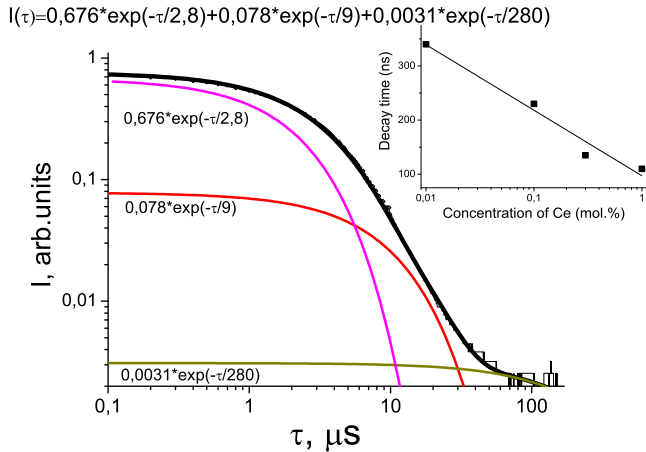


Figure 4: Scintillation decay time profile of $\text{SrF}_2\text{-}0.3 \text{ Ce}^{3+}$ crystal measured under gamma-source ^{137}Cs excitation ($E=662 \text{ KeV}$). Exponential components of total decay curve are presented separately. In the inset dependence of shortest decay time component on Ce^{3+} ions concentration is shown.

creasing of slow component contribution in Ce^{3+} luminescence. It might be possible by co-doping these crystals with Ga^{3+} , In^{3+} or Cd^{2+} ions to change band gap in $\text{SrF}_2\text{-Ce}$ crystal and, thence, reducing the role of traps in scintillation energy transfer. This idea has been made in garnets by Fasoli et al., 2011. However, Cd^{2+} ions bring to STE suppressing in alkali-earth fluorides (Radzhabov and Kirm, 2005; Radzhabov et al., 2005). Consequently, Cd^{2+} co-doping leads to suppression of efficient resonance exciton energy transfer mechanism and following light output reducing. Therefore, Cd^{2+} co-doping is not eligible way for increasing light output of $\text{SrF}_2\text{-Ce}$ scintillator. A role of Ga^{3+} and In^{3+} impurities in STE suppressing has not yet been investigated and follow-up study of the crystals doped with Ga^{3+} and In^{3+} ions is required.

4. Conclusion

The SrF_2 crystal are well suited for use as gamma radiation detector. It has a higher (4.18 g/cm^3) than NaI-Tl (3.67 g/cm^3) density, comparable light output, and it is no hygroscopic. Taking into account that crystals $\text{SrF}_2 - 0.3 \text{ mol.}\% \text{ Ce}^{3+}$ and $\text{SrF}_2 - 1 \text{ mol.}\% \text{ Ce}^{3+}$ have a high temperature stability of light output in the temperature interval from $-50 \text{ }^\circ\text{C}$ to $200 \text{ }^\circ\text{C}$, these materials can be applied in well-logging scintillation detectors. Summarizing the experimental results we conclude that strontium fluoride crystals would be useful as newly perspective scintillator.

Acknowledgement

This work was partially supported by Federal Target Program "Scientific and scientific-pedagogical personnel of innovative Russia" in 2009-2013 and Russian Foundation for Basic Research (RFBR).

Authors are thankful to V. Kozlovskii for growing the crystals investigated in this work.

References

- Alekhin, M., de Haas, J., Kramer, K., Dorenbos, P., 2011. Scintillation properties of and self absorption in $\text{SrF}_2\text{-Eu}^{2+}$. Nuclear Science, IEEE Transactions on 58 (5), 2519–2527.
- Derenzo, S. E., 2012. Scintillation properties database. <http://scintillator.lbl.gov>.
- Dorenbos, P., 2010. Fundamental limitations in the performance of Ce^{3+} and Pr^{3+} and Eu^{2+} activated scintillators. Nuclear Science, IEEE Transactions on 57, 1162–1167.
- Fasoli, M., Vedda, A., Nikl, M., Jiang, C., Uberuaga, B. P., Andersson, D. A., McClellan, K. J., Stanek, C. R., Aug 2011. Band-gap engineering for removing shallow traps in rare-earth $\text{Lu}_3\text{Al}_5\text{O}_{12}$ garnet scintillators using Ga^{3+} doping. Phys. Rev. B 84, 081102.
- Flyckt, S.-O., Marmonier, C., 2002. Photomultiplier tubes. Principles and applications. Photonis, France.
- Kobayashi, T., Mroczkowski, S., Owen, J. F., Brixner, L. H., 1980. Fluorescence lifetime and quantum efficiency for $5d \rightarrow 4f$ transitions in Eu^{2+} doped chloride and fluoride crystals. Journal of Luminescence 21 (3), 247–257.
- Maghrabi, M., Townsend, P., 2001. Thermoluminescence spectra of rare earth doped *Ca*, *Sr* and *Ba* fluorides. Journal of physics: Condensed matter 13, 2211–2224.
- Moszynski, M., Nassalski, A., Syntfeld-Kazuch, A., Szczesniak, T., Czarnacki, W., Wolski, D., Pausch, G., Stein, J., 2006. Temperature dependences of $\text{LaBr}_3(\text{Ce})$, $\text{LaCl}_3(\text{Ce})$ and $\text{NaI}(\text{Tl})$ scintillators. Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment 568 (2), 739–751.
- Radzhabov, E., 2001. Creation of trapped electrons and holes in alkaline-earth fluoride crystals doped by rareearth ions. J.Phys.: Condens.Matter 13, 10955.
- Radzhabov, E., Kirm, M., 2005. Triplet luminescence of cadmium centres in alkaline-earth fluoride crystals. Journal of Physics: Condensed Matter 17 (37), 5821.
- Radzhabov, E., Kurobori, T., 2004. Cubic and tetragonal Ce^{3+} ions in strontium fluoride. Journal of Physics: Condensed Matter 16 (10), 1871.
- Radzhabov, E., Mysovsky, A., Egranov, A., Nepomnyashikh, A., Kurobori, T., 2005. Cadmium centres in alkaline-earth fluoride crystals. Physica Status Solidi C Current Topics 2, 388–391.
- Schotanus, P., van Eijk, C. W. E., Hollander, R. W., Pijpelink, J., 1987. Development study of a new gamma camera. Nuclear Science, IEEE Transactions on 34 (1), 271–276.
- Shendrik, R., Radzhabov, E., 2010. Temperature dependence of Ce^{3+} and Pr^{3+} emission in CaF_2 , SrF_2 , BaF_2 . Nuclear Science, IEEE Transactions on 57, 1295–1299.
- Shendrik, R., Radzhabov, E., 2012. Energy transfer mechanism in Pr -Doped SrF_2 crystals. Nuclear Science, IEEE Transactions on 59 (5), 2089–2094.
- Visser, R., Dorenbos, P., van Eijk, C., 1993. Ce^{n+} energy levels in alkaline-earth fluorides and cerium-electron, cerium-hole interactions. J.Phys.: Condens Matter 5, 5887–5910.
- Visser, R., Dorenbos, P., van Eijk, C., Hollander, R., Schotanus, P., 1991. Scintillation properties of Ce^{3+} doped BaF_2 crystals. Nuclear Science, IEEE Transactions on 38 (2), 178–183.
- Wojtowicz, A., Szupryczynski, P., Glodo, J., Drozdowski, W., Wisniewski, D., 2000. Radioluminescence and recombination processes in $\text{BaF}_2\text{:Ce}$. J.Phys.Condens.Matter 12, 4097–4124.