

Conventional superconductivity at 190 K at high pressures

A.P. Drozdov, M. I. Erements*, I. A. Troyan

Max-Planck Institut für Chemie, Chemistry and Physics at High Pressures Group

Postfach 3060, 55020 Mainz, Germany

*e-mail: m.eremets@mpic.de

The highest critical temperature of superconductivity T_c has been achieved in cuprates¹: 133 K² at ambient pressure and 164 K at high pressures³. As the nature of superconductivity in these materials is still not disclosed, the prospects for a higher T_c are not clear. In contrast the Bardeen–Cooper–Schrieffer (BCS) theory gives a clear guide for achieving high T_c : it should be a favorable combination of high frequency phonons, strong coupling between electrons and phonons, and high density of states. These conditions can be fulfilled for metallic hydrogen and covalent hydrogen dominant compounds^{4,5}. Numerous followed calculations supported this idea^{6,7} and predicted $T_c=100-235$ K for many hydrides⁶ but only moderate $T_c\sim 17$ K has been observed experimentally⁸. Here we found that sulfur hydride transforms at $P\sim 90$ GPa to metal and superconductor with T_c increasing with pressure to 150 K at ≈ 200 GPa. This is in general agreement with recent calculations of $T_c\sim 80$ K for H_2S ⁷. Moreover we found superconductivity with $T_c\approx 190$ K in a H_2S sample pressurized to $P>\sim 150$ GPa at $T>220$ K. This superconductivity likely associates with the dissociation of H_2S , and formation of SH_n ($n>2$) hydrides. We proved occurrence of superconductivity by the drop of the resistivity at least 50 times lower than the copper resistivity, the decrease of T_c with magnetic field, and the strong isotope shift of T_c in D_2S which evidences a major role of phonons in the superconductivity. H_2S is a substance with a moderate content of hydrogen therefore high T_c can be expected in a wide range of hydrogen–contain materials. Hydrogen atoms seem to be essential to provide the high frequency modes in the phonon spectrum and the strong electron-phonon coupling.

A room temperature superconductor probably is the most desired system in solid state physics¹⁰. So far the greatest advances, cuprates¹, pnictides¹¹ and number of others were obtained in a serendipitous way. As there is no clear theory for these superconductors, it is difficult to predict where progress will be made. Another, distinct way is the BCS theory described by the pairing of electrons mediated by phonon lattice vibrations. The Eliashberg formulation of this theory puts no apparent bounds on T_c ¹². In practice, however BCS theory does not have a predictive power to calculate material-specific properties¹² but it serves as a guide for the search for superconductors. Materials with light elements are especially favorable as they provide high frequencies in the phonon spectrum. Indeed many superconductive materials have been found in this way, but with a disappointing moderately high T_c of about 10 K. The highest $T_c=39$ K that has been found in this search is in MgB_2 . There is still frequent preconception that $T_c\sim 30$ K is the maximum what can be achieved in conventional superconductors.

N. Ashcroft⁴ turned attention to hydrogen as the lightest element for which high T_c can be expected, because of the very high vibrational frequencies due to the light hydrogen atom, a strong electron-phonon interaction, and covalent bonding. Further calculations showed that metallic hydrogen should be a superconductor with a very high critical temperature $T_c \sim 100-240$ K¹³⁻¹⁵ for molecular hydrogen, and $T_c = 300-350$ K in the atomic phase at 500 GPa¹⁶. However superconductivity in pure hydrogen has not yet been found while the conductive and likely semimetallic state of hydrogen has been recently achieved¹⁷. Hydrogen dominate materials such as covalent hydrides SiH_4 , SnH_4 etc. might also be good candidates for high T_c superconductivity⁵. Similar to pure hydrogen, they have a high Debye temperature. Moreover, heavier elements might be beneficial as they contribute to the low frequencies that enhance electron phonon coupling. Lower pressures are required to metallize these hydrides in comparison to pure hydrogen. Ashcroft's general idea was supported in numerous calculations for T_c of different hydrogen containing materials. The key in this new approach of searching for new superconductors is the prediction of structures from *ab-initio* calculations^{6,18,19}. As soon as the structure is known, the electronic phonon spectra can be calculated and T_c estimated by solving the Eliashberg equations. However, the theoretical search for structures at present cannot

guarantee the most stable structure. Regularly new theoretical results are published where the predicted structures are revised and lower energy structures are found^{6,7}. It can only be determined experimentally if the calculated T_c s are correct and give prospects for high T_c in the hydrogen dominate materials. However, experimental progress is much slower^{8,20} apparently because the majority of the theoretically studied materials are difficult to access, and high pressure studies are difficult and challenging, especially electrical measurements. For the present study we selected H_2S because it is relatively easy to handle, transforms to metal at a low pressure of ≈ 100 GPa, and the calculated $T_c=80$ K⁷ is high.

H_2S is known as a typical molecule substance with a rich phase diagram²¹. At about 96 GPa hydrogen sulfide transforms to metal²². The transformation is complicated by the partial dissociation of H_2S and the appearance of elemental sulfur at $P>27$ GPa at room temperature, and higher pressures for lower temperatures²¹. Therefore, the metallization of hydrogen sulfide can be explained by elemental sulfur which is known to become metallic above 95 GPa²³. No experimental studies on hydrogen sulfide are known above 100 GPa. Recent theoretical work⁷ revised the phase diagram of H_2S , and a number of new stable structures were found. At $P>130$ GPa – higher pressures than experimentally observed – hydrogen sulfide was predicted to become a metal and a superconductor with a maximal transition temperature of ~ 80 K at 160 GPa. Precipitation of sulfur has been found to be very unlikely, in apparent contradiction to the experiments^{21,24}.

In our typical experiments the Raman spectra for H_2S and D_2S measured during the pressure increase are in general agreement with the literature data^{25,26} (see Extended Data Fig. 1). In electrical measurements, H_2S starts to conduct at $P\sim 50$ GPa. At this pressure it is a semiconductor as follows from the temperature dependence of resistance and a pronounced photoconductivity. At 90-100 GPa resistance further drops, and the temperature dependence becomes metallic. No photoconductive response is observed in this state, or the resistance increases under illumination. H_2S is a poor metal – its resistivity at ~ 100 K is $\rho\approx 3 \cdot 10^{-5}$ Ohm m at 110 GPa and $\rho\approx 3 \cdot 10^{-7}$ Ohm m at ~ 200 GPa.

During cooling of the metal phase to 4K at pressures of about 100 GPa (Fig. 1a) resistance abruptly drops three to four orders of magnitude at $T_c \approx 23$ K. After warming to $T \sim 100$ K, pressure was increased to the next value and the sample was cooled. The next loadings were performed at 100-150 K (Fig. 1a, see Extended Data Fig. 2). T_c increased with pressure (Fig. 2a) with sharp growth when pressure approached 200 GPa. We found a route to another superconductive state with $T_c \approx 190$ K by application of pressure $P > \sim 150$ GPa but at significantly higher temperatures of 220-300 K (Fig. 2b). This T_c has weak pressure dependence (Fig. 2b) – very different from the T_c obtained at low temperatures (Fig. 2a). Frequently the 190 K step is accompanied with a step with $T_c \sim 30$ K which disappears with time ($> \sim 1$ day) or further application of pressure while the 190 K step sharpens (see Extended Data Fig.3). There are some oscillations on the $R(T)$ with period of 25-30 K clearly seen in a number of runs (see Extended Data Fig. 3). The accumulated data reveal a quite complex P - T_c diagram and we separate it for two parts: Fig. 2a and Fig.2b according to the different routes of achieving T_c s.

We conclude that for both the routes the observed steps at the temperature dependence of resistance (Figs 1, 3.4) represent a transition to the superconducting state for the following arguments:

- (1) The measured minimum resistance is at least as low $\approx 10^{-11}$ Ohm m – about two orders of magnitude less than for pure copper (Figs 1, see Extended Data Figs. 2,3) measured at the same temperature²⁷.
- (2) T_c shift to lower temperatures with the available magnetic field up to 7 Tesla (Fig.3). Much higher fields are required to destroy the superconductivity: extrapolation of $T_c(B)$ gives an estimation of critical magnetic field at ~ 25 T and 70 T for two critical temperatures (Fig. 3).
- (3) A strong isotopic effect: T_c shifts to lower temperatures for D_2S (Figs 1,2, see Extended Data Fig. 4).
- (4) For the phonon mechanism of the pairing of electrons in the BCS superconductivity the critical temperature depends on the square root of the mass: $T_c \sim M^{-\alpha}$ where $\alpha_H \approx 0.5$. For both superconducting states of sulfur hydride with $T_c \approx 60$ K and $T_c \approx 185$ K (Fig 2) we observe a critical temperature of the corresponding isotope at 30 K and 90 K indicating phonon assisted superconductivity.

The behavior of T_c with pressure (Fig. 2a) reasonably agrees with the calculations for H_2S ⁷: the experimental values of T_c s are comparable with the predicted $T_c \approx 80$ K which is apparently conventional superconductivity. The pressure dependence is different, however, there is no predicted drop of T_c at 160 GPa⁷, or this drop might be at $P > \sim 200$ GPa instead.

The superconductivity at $T_c \sim 190$ K shown in the Fig. 2b is not seen or missed in the calculation for H_2S ⁷. High temperatures of $T > 220$ K are required to reach the $T_c \sim 190$ K therefore decomposition of H_2S can be involved. While precipitation of elemental sulfur can be expected, which is well known at low pressures of $P > 27$ GPa²¹, the superconductivity of sulfur alone is too low (Fig. 2a, see Extended Data Fig. 5). Precipitation of sulfur might be of particular interest as likely, sulfur forms impurities or clusters in a host lattice which can promote an increase of T_c through interface effects, instabilities, and disproportionation which are common features of high temperature superconductors³. The sharp increase of T_c at $P > \sim 200$ GPa (Fig. 2a) can probably be explained by an increase of electron density of states due to impurities of sulfur. The effect of precipitation on superconductivity might be interesting to study in other systems too³.

Another expected product of decomposition of H_2S is hydrogen. However the strong characteristic vibron from H_2 molecule was never observed in the Raman spectra in spite of using a sensitive spectrometer and ultralow luminescence synthetic diamond anvils. No H_2 vibron has been found in Ref. ²¹ either even after 1 hour of accumulation. We suppose therefore that the dissociation of H_2S might go differently: $2H_2S \rightarrow H_4S + S$, or $3H_2S \rightarrow H_6S + S$. It is natural to expect these reactions as the valency of sulfur is 2, 4, and 6. The molecules H_4S and H_6S are known to be thermodynamically unstable, but kinetically stable at ambient pressure⁸, and high pressure might stabilize them. In fact calculations⁷ indirectly support this hypothesis as the dissociation $H_2S \rightarrow H_2 + S$ was shown to be energetically very unfavorable. We found further theoretical support for our hypothesis on the dissociation of H_2S to H_nS ($n > 2$) and sulfur in Ref ⁹. In this work the van der Waals compound²⁸

$(\text{H}_2\text{S})_2\text{H}_2$ has been considered and it has been shown that at pressures above 111 GPa H_3S molecular unit is built, and that above 180 GPa, sulfur and hydrogen form a lattice with coordination number of the S atom is six. The predicted $T_{c,s} \sim 160$ K and 190 K for these two phases are close to our experimental values and T_c also decreases with pressure above 180 GPa (Fig. 2b). Moreover, our Raman measurements of the sample with $T_c \sim 190$ K showed a phase transformation at 180 GPa (see Extended Data Fig. 5). Thus $T_c \sim 190$ K (Fig. 2b) might be related to superconductivity of H_3S obtained as a result of the dissociation of H_2S . Further theoretical and experimental studies of H_2S and higher hydrides H_nS , $n > 2$ are apparently needed.

We have found high T_c superconductivity in H_2S – material with low fraction of hydrogen. This probably will give a prospect to find high T_c in other hydrogen contain materials first of all various carbon-based materials: fullerenes, aromatic hydrocarbon, graphanes etc. Instead of application of pressure they can be turned to superconducting state by doping or gating.

Methods Summary

A diamond anvil cell (DAC) was placed into a cryostat and cooled down to ≈ 200 K (within the temperature range of liquid H_2S) and then H_2S gas was put through a capillary into a rim around diamond anvil where it liquidified. H_2S of 99,5% and D_2S of 97% purity have been used. Liquid H_2S was clamped in a gasket hole. After the clamping, DAC was heated to ~ 220 K to evaporate the rest of the H_2S , and the pressure was further increased at this temperature. A metallic gasket of DAC was separated from the electrodes with an insulating layer made of Teflon or NaCl as these materials do not react with H_2S . Typical dimensions of the sample are a diameter ≈ 10 μm and a thickness of ≈ 1 μm . The material of electrodes was Ti covered by Au to protect Ti from oxidation. Four electrodes were sputtered on the anvil. To check a possible contribution of the diamond surface to conductivity we prepared a different configuration of electrodes: two electrodes were sputtered on one anvil and another two on another anvil similar to Ref. ¹⁷. Electrical and Raman measurements were done in the same cryostat. Resistance was measured by using the four-probe Van der Pauw method (Fig. 1 and see

Extended Data Fig. 3) with a current of 10 -10000 μ A. The dependence of superconducting transitions on the magnetic field has been measured with a small nonmagnetic DAC in a Quantum Design physical property measurement system (PPMS6000) in a 4-300 K temperature range up to 7 Tesla. Pressure was determined by a diamond edge scale²⁹. For optical measurements a Raman spectrometer was equipped with a nitrogen-cooled CCD and notch filters. The 632.8 nm line of a He-Ne laser was used to excite the Raman spectra and to determine pressure.

Acknowledgments. Support provided by the European Research Council under the 2010-Advanced Grant 267777 is gratefully acknowledged. We appreciate support provided by Prof. U.Pöschl. The authors are thankful for V. Ksenofontov and B. Balke for generous help with measurements at PPMS and useful discussions.

Author contributions: A. D. performed the whole experiment and contributed to the data interpretation and writing the manuscript. M.E. designed the study, wrote the manuscript and participated in the experiments. I.T. participated in experiments and discussions. M.E., and A. D. contributed equally to this paper.

References

- 1 Bednorz, J. G. & Mueller, K. A. Possible high TC superconductivity in the Ba-La-Cu-O system. *Zeitschrift für Physik B* **64**, 189–193 (1986).
- 2 Sun, G. F., Wong, K. W., Xu, B. R., Xin, Y. & Lu, D. F. Tc enhancement of HgBa₂Ca₂Cu₃O₈ by Tl substitution *Physics Letters A* **192**, 122-124 (1994).
- 3 Chu, C. W. A Possible Path to RTS. *AAPPS Bulletin* **18**, 9-21 (2008).
- 4 Ashcroft, N. W. Metallic hydrogen: A high-temperature superconductor? *Phys. Rev. Lett.* **21**, 1748-1750 (1968).
- 5 Ashcroft, N. W. Hydrogen Dominant Metallic Alloys: High Temperature Superconductors? *Phys. Rev. Lett.* **92**, 187002 (2004).
- 6 Wang, Y. & Ma, Y. Perspective: Crystal structure prediction at high pressures. *J. Chem. Phys.* **140**, 402616 (2014).
- 7 Li, Y., J. Hao, Li, Y. & Ma, Y. The metallization and superconductivity of dense hydrogen sulfide. *J. Chem. Phys.* **140**, 040901 (2014).
- 8 Eremets, M. I., Trojan, I. A., Medvedev, S. A., Tse, J. S. & Yao, Y. Superconductivity in Hydrogen Dominant Materials: Silane. *Science* **319**, 1506-1509 (2008).
- 9 Duan, D. *et al.* Pressure-induced metallization of dense (H₂S)₂H₂ with high-Tc superconductivity. *Sci. Reports* **4**, 6968 (2014).

- 10 P. Cudazzo *et al.* Electron-phonon interaction and superconductivity in metallic molecular hydrogen. II. Superconductivity under pressure. *Phys. Rev. B* **81**, 134506 (2010).
- 11 Jie Yang *et al.* Superconductivity at 53.5 K in GdFeAsO_{1- δ} . *Supercond. Sci. Technol.* **21**, 082001 (2008).
- 12 Cohen, M. L. in *BCS: 50 years* (ed Leon N. Cooper; Dmitri Feldman) 375-389 (2011).
- 13 Barbee, T. W., Garcia, A., Cohen, M. L. & Martins, J. L. Theory of High-Pressure Phases of Hydrogen. *Phys. Rev. Lett.* **62**, 1150 (1989).
- 14 Zhang, L. *et al.* Ab initio prediction of superconductivity in molecular metallic hydrogen under high pressure. *Sol. St. Comm.* **141**, 610-614 (2007).
- 15 Cudazzo, P. *et al.* Ab Initio Description of High-Temperature Superconductivity in Dense Molecular Hydrogen. *Phys. Rev Lett.* **100**, 257001 (2008).
- 16 McMahon, J. M., Morales, M. A., C, P. & Ceperley, D. M. The properties of hydrogen and helium under extreme conditions. *Rev. Mod. Phys.* **84**, 1607-1653 (2012).
- 17 Eremets, M. I. & Troyan, I. A. Conductive dense hydrogen. *Nature Materials* **10**, 927-931 (2011).
- 18 Glass, C. W., Oganov, A. R. & Hansen, N. USPEX - Evolutionary crystal structure prediction. *Comp. Phys. Comm.* **241**, 95-103 (2006).
- 19 Pickard, C. J. & Needs, R. J. Ab initio random structure searching. *Journal of Physics: Condensed Matter* **23**, 053201 (2011).
- 20 Goncharenko, I. *et al.* Pressure-Induced Hydrogen-Dominant Metallic State in Aluminum Hydride. *Phys. Rev. Lett.* **100**, 045504 (2008).
- 21 Fujihisa, H. *et al.* Molecular dissociation and two low-temperature high-pressure phases of H₂S. *69*, 214102 (2004).
- 22 M. Sakashita *et al.* Pressure-Induced Molecular Dissociation and Metallization in Hydrogen-Bonded H₂S Solid. *Phys. Rev. Lett.* **79**, 1082-1085 (1997).
- 23 Kometani, S., Eremets, M., K.Shimizu, Kobayashi, M. & Amaya, K. Observation of pressure-induced superconductivity of sulfur. *J. Phys. Soc. Japan.* **66**, 818-819 (1997).
- 24 Endo, S. *et al.* High-pressure phase of solid hydrogen sulfide. *Phys. Rev. B* **54**, R717-R719 (1996).
- 25 H. Shimizu *et al.* Pressure-temperature phase diagram of solid hydrogen sulfide determined by Raman spectroscopy. *Phys. Rev. B* **51**, 9391-9394 (1995).
- 26 H. Shimizu, H. Murashima & Sasaki, S. High-pressure Raman study of solid deuterium sulfide up to 17 GPa. *J. Chem. Phys.* **97**, 7137-7139 (1992).
- 27 Matula, R. A. Electrical resistivity of copper, gold, palladium, and silver. *J. Phys. Chem. Refer.* **8**, 1147-1298 (1979).
- 28 Strobel, T. A., Ganesh, P., Somayazulu, M., Kent, P. R. C. & Hemley, R. J. Novel Cooperative Interactions and Structural Ordering in H₂S-H₂. *Phys. Rev. Lett.* **107**, 255503 (2011).
- 29 Eremets, M. I. Megabar high-pressure cells for Raman measurements. *J. Raman Spectroscopy* **34**, 515-518 (2003).

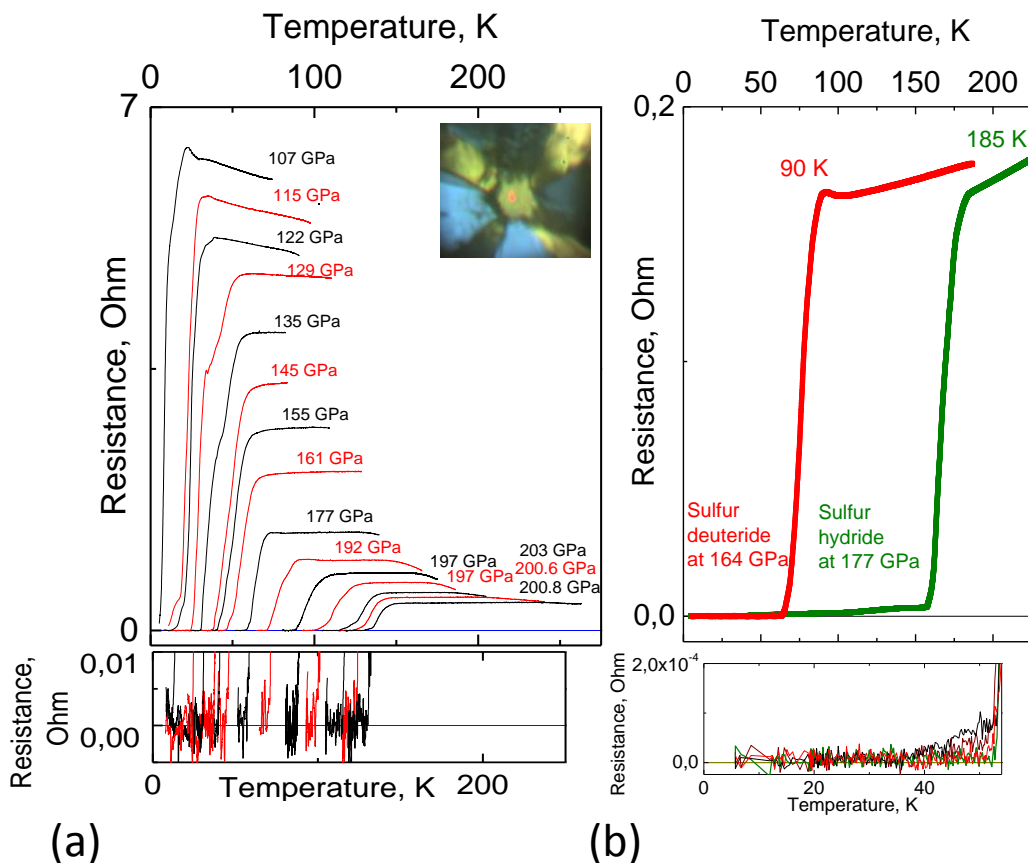


Fig. 1. Temperature dependence of resistance of sulfur hydride and sulfur deuteride measured at different pressures. The pressures did not change during the cooling (within ≈ 5 GPa). Resistance was measured with four electrodes deposited on a diamond anvil touched the sample (photo). Diameter of the samples was $\sim 25 \mu\text{m}$ and the thickness $\sim 1 \mu\text{m}$.

(a) Sulfur hydride as measured at the growing pressures, the values are indicated near the corresponding plot. Plots at pressures < 135 GPa were scaled (reduced in 5-10 times) for easier comparison with the higher pressure steps. The resistance was measured with current of $10 \mu\text{A}$. Bottom: the resistance plots near zero. (b) Comparison of the superconducting steps of sulfur deuteride and hydride at similar pressures. Bottom: resistance measured near zero. Resistance was measured in four channels with van der Pauw method (SI Fig. 4) with current of 10 mA .

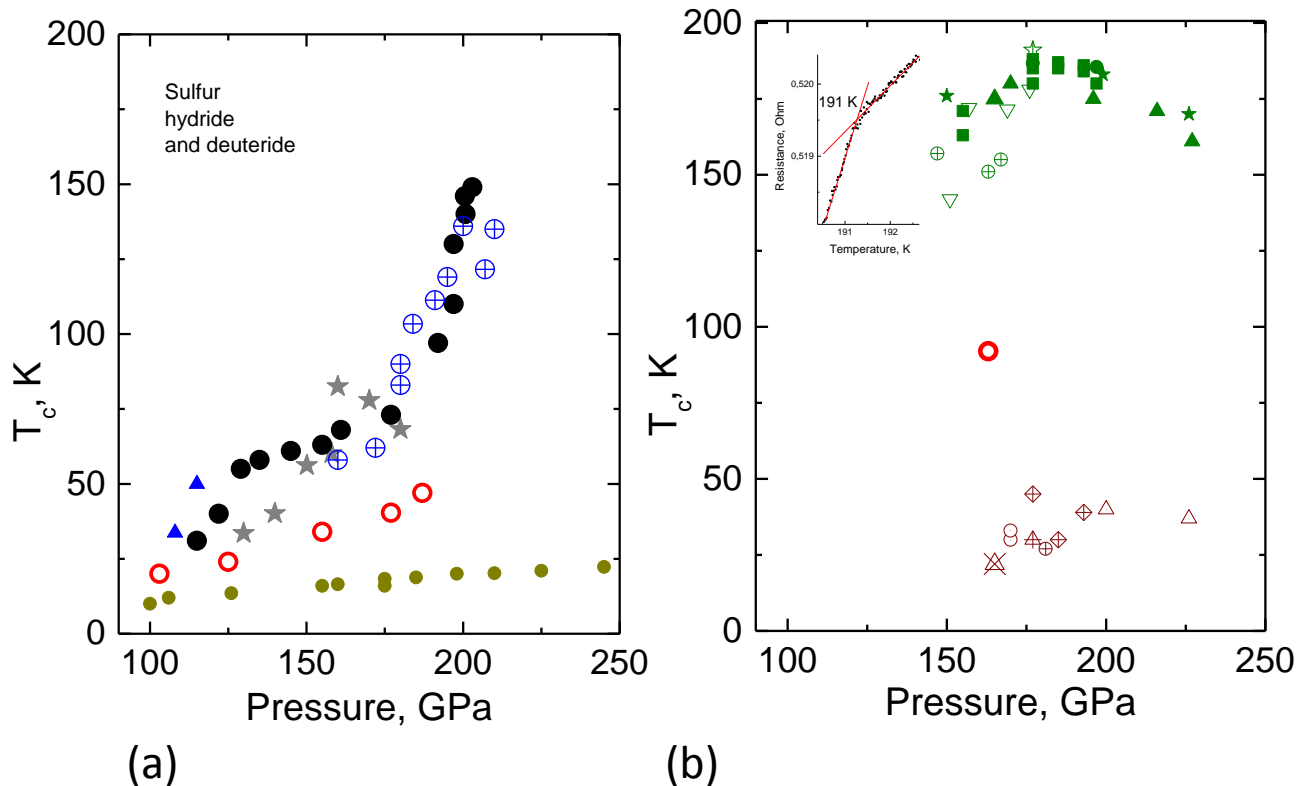


Fig. 2. Pressure dependence of critical superconducting temperature T_c on pressure. Only four probe electrical measurements in van der Pauw geometry are presented in both panels. Critical superconducting temperature T_c was determined as a point where resistance starts to sharply decrease with cooling from the plateau at the $R(T)$ plot (inset in (b)).

(a) Data were obtained when pressure was applied in the 100-190 GPa pressure range at 100-150 K, and higher temperatures at $P \sim 200$ GPa when T_c sharply increased. Black points are data from Fig. 1a. Blue points - other runs. Red points are measurements of D_2S . Dark yellow points are T_c s of pure sulfur. Grey stars are calculations from Ref. 7.

(b) Higher $T_c \sim 190$ K found when pressure $P > 150$ GPa was applied in combination with 220-300 K temperatures. The 190 K step is accompanied with another step with $T_c \sim 30$ K (wine points). It is shown in SI Fig. 3. The red point is T_c for D_2S sample (Fig. 1b).

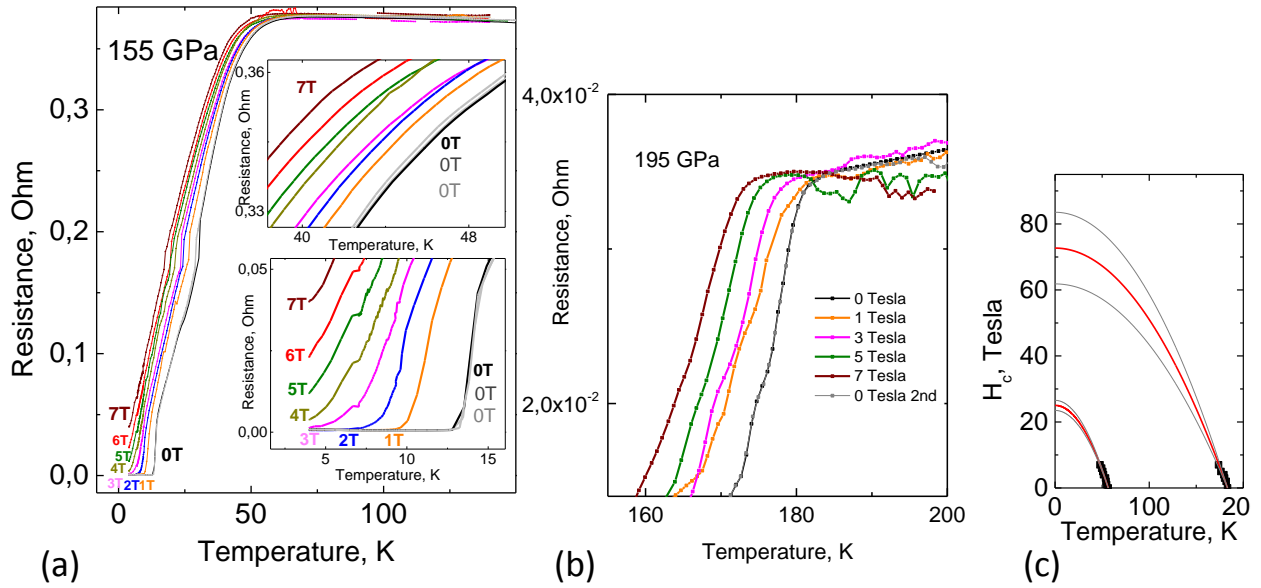


Fig. 3. Temperature dependence of resistance of sulfur hydride at different magnetic fields. (a) The shift of the ~ 60 K superconducting step in the 0-7 T magnetic fields. The upper and low parts of the step are enlarged in the insets. Temperature dependence of resistance without magnetic field was measured three times: before applying a field, after applying 1,3,5,7 Teslas and at the end of measurements (black, grey and dark grey colors). (b) The same measurements but with the 185 K step. (c) The shift of critical temperature of superconducting transition T_c with magnetic field. The plots were extrapolated to high magnetic fields with $H_c(T) = H_{c0}(1 - (T/T_c)^2)$ formula to estimate the critical magnetic field H_c . The extrapolation has been done with 95% confidence band (grey lines).

Supplementary information

Conventional superconductivity at 190 K at high pressures

A. P. Drozdov, M. I. Erements*, I. A. Troyan

Max-Planck Institut für Chemie, Chemistry and Physics at High Pressures Group

Postfach 3060, 55020 Mainz, Germany

*e-mail: m.eremets@mpic.de

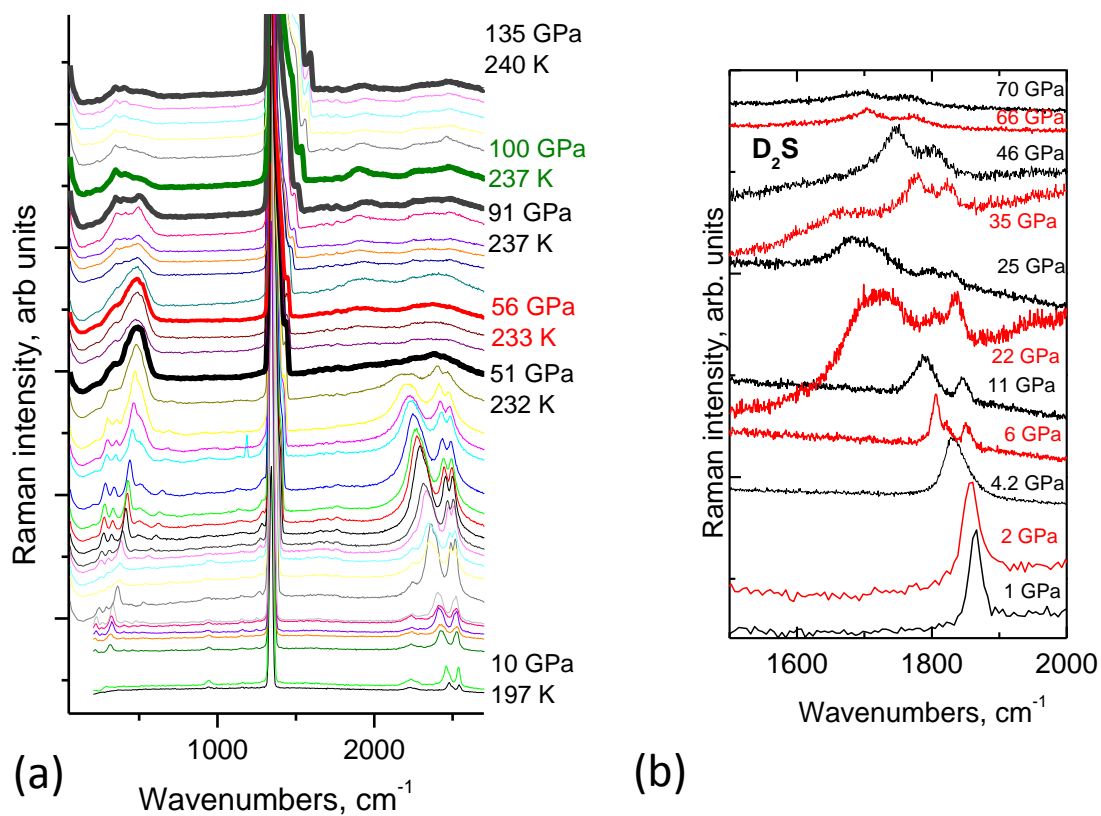


Fig. 1. Raman spectra of sulfur hydride at different pressures. (a) Spectra at increasing pressure at ~ 230 K. The spectra are shifted each other. The temperature of the measurement is also indicated. (b) Raman spectra of D_2S measured at $T \sim 170$ K.

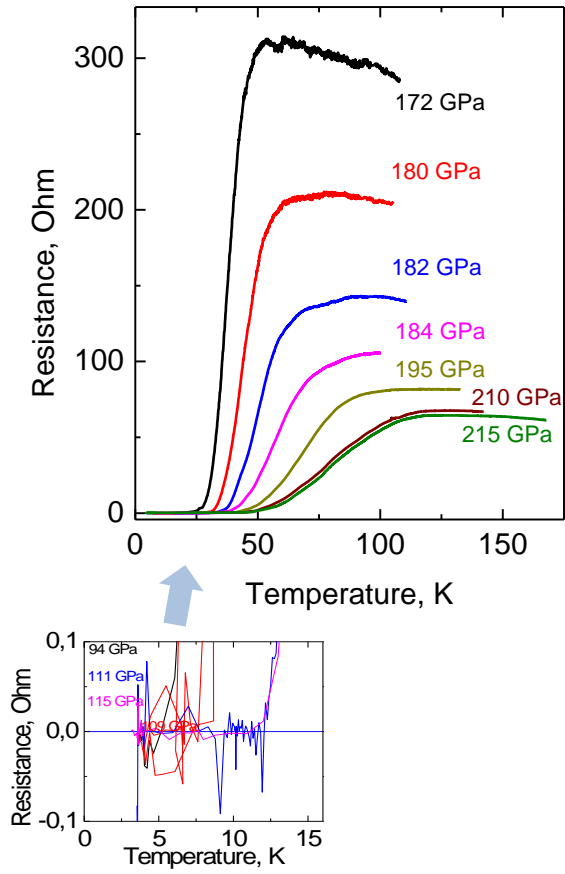


Fig. 2 . Temperature dependence of resistance (superconducting steps). Corresponding T_c s are shown by blue points in Fig. 2. Left figure demonstrates minimum resistance measured in this run with current of $10 \mu\text{A}$.

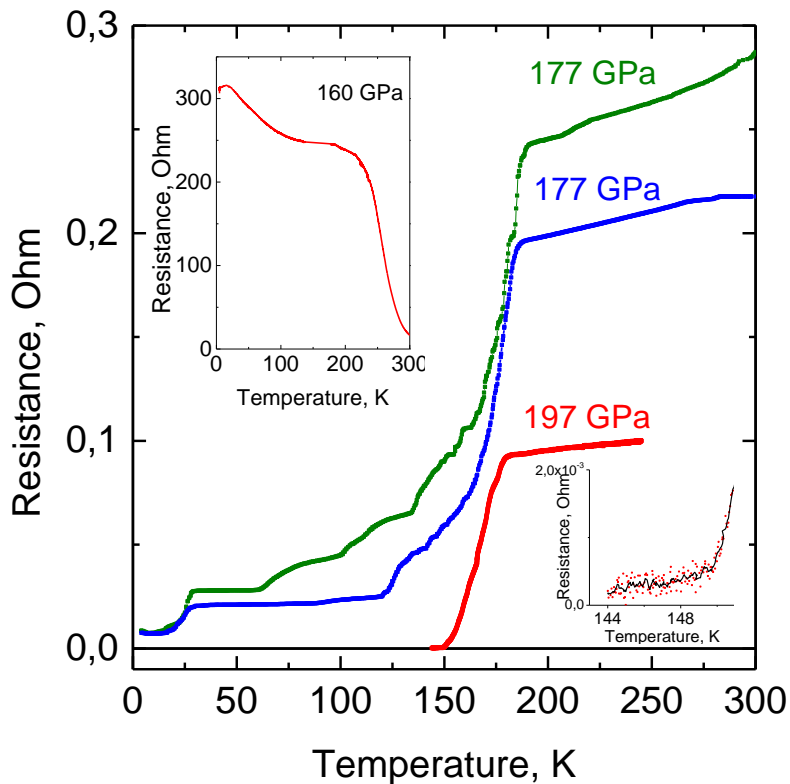


Fig. 3. Transformation of the superconducting state in the H_2S sample with pressure, temperature and time. At pressures up to 155 GPa there is only one SC step at ~ 60 K. After warming to 300 K at this pressure the resistance dropped to ~ 5 Ohm and then below 1 Ohm at pressurizing to 177 GPa. The step at ~ 180 K developed at the cooling (olive line). It became more pronounced (blue line) with time (15 hours). After pressurizing to 197 GPa at 300 K and next cooling the minimum resistance reached $R = 1.7 \cdot 10^{-4}$ Ohm at 144 K (inset). Corresponding resistivity $\rho \sim 1.7 \cdot 10^{-10}$ Ohm m ~ 50 times lower than for copper (at 150 K $\rho = 70 \cdot 10^{-10}$ Ohm m, Ref. 27). There are notable oscillations on the $R(T)$ pronounced at the olive curve. We observed these oscillations with period of 25-30 K in a number of runs. The resistance plots (olive and blue lines) taken in PPMS were averaged from the measurements with increasing and decreasing of temperature. The rest of the plots are measurements in optical cryostat at slow (about 5 hours) warming so the temperature was close to equilibrium.

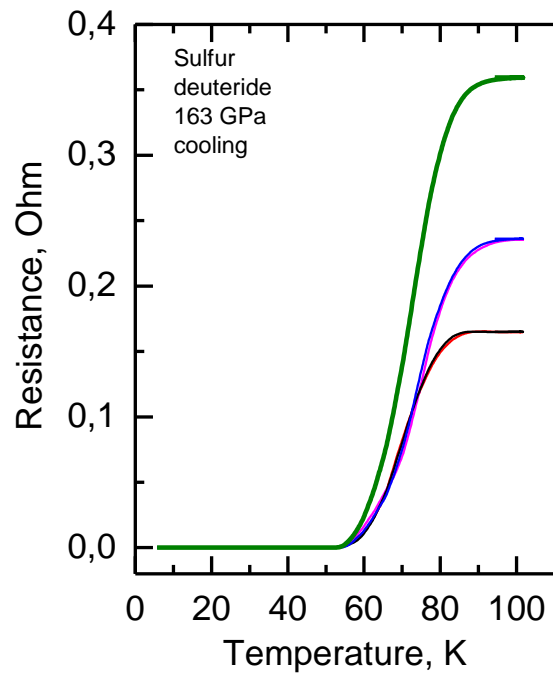


Fig. 4. Electrical measurements of sulfur deuteride at 163 GPa. The sample was pressurized to 163 GPa at 200 K. $R(T)$ measured with current of 10 mA at decreasing of temperature. Color lines – measurements on four channels, and olive line – the resistance calculated from these data with the van der Pauw method.

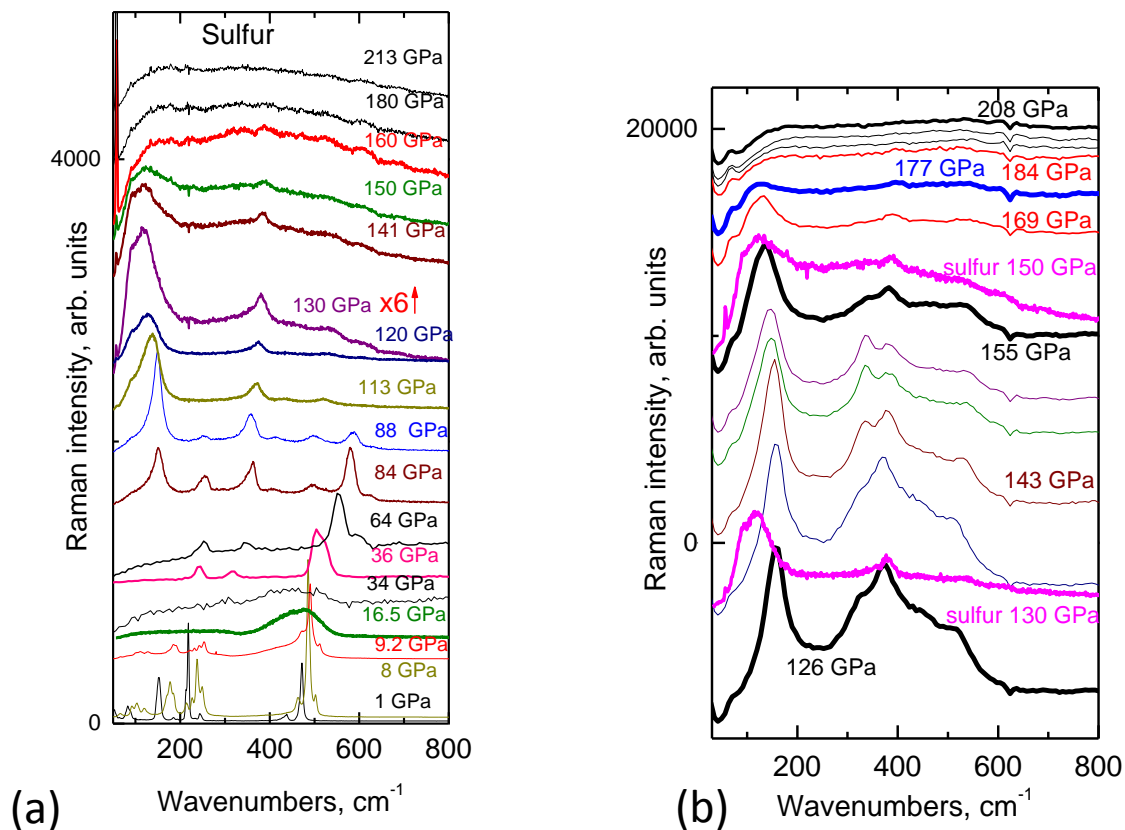


Fig. 5. Raman spectra of sulfur hydride compared with elemental sulfur. Ultralow luminescence synthetic diamond anvils allowed us to record the Raman spectra at high pressures in the metallic state.

- (a) Raman spectra of elemental sulfur at different pressures measured at room temperature in the wide pressure range. At small pressures Raman signal is very strong but above ~ 10 GPa the intensity dramatically decreases, some reflectivity appears. Above 80 GPa a new phase appeared which persists to 150 GPa in the metallic state. At 160 GPa Raman disappears, likely because of transformation to the β -Po phase. The pressure of the transformation is in a good agreement with our four probe electrical measurements of T_c (Fig. 2a). The electrical measurements in turn are in good agreement with the susceptibility measurements (Gregoryanz *et al*, Phys. Rev. B **65**, 064504) but we obtained noticeable higher $T_{c,s}$ at $P > 200$ GPa (to be published).
- (b) Raman spectra of sulfur hydride at releasing pressure from 208 GPa at room temperature. The spectra are much stronger than those from sulfur in the metallic state at high pressures. There is apparent phase transition at ≈ 180 GPa.

There is apparent difference in the Raman spectra of sulfur hydride (a) and sulfur (b): the peaks at ~ 100 cm^{-1} shift each other, phase transformation are at different pressures: 160 GPa for sulfur and 180 GPa for sulfur hydride. Finally, Raman spectra of sulfur hydride are significantly stronger.