

Negative thermal expansion near two structural quantum phase transitions

Connor A. Occhialini¹, Sahan U. Handunkanda^{1,2}, Ayman Said³,
Sudhir Trivedi⁴, G. G. Guzmán-Verri^{5,6}, and Jason N. Hancock^{1,2}

¹*Department of Physics, University of Connecticut, Storrs, Connecticut 06269 USA*

²*Institute for Materials Science, University of Connecticut, Storrs, Connecticut 06269 USA*

³*Advanced Photon Source, Argonne National Laboratory, Argonne, Illinois 60349, USA*

⁴*Brimrose Technology Corporation, Sparks, MD 21152-9201, USA*

⁵*Centro de Investigación en Ciencia e Ingeniería de Materiales and Escuela de Física,*

Universidad de Costa Rica, San José, Costa Rica 11501 and

⁶*Materials Science Division, Argonne National Laboratory, Argonne, Illinois, USA 60439*

(Dated: December 6, 2017)

Recent experimental work has revealed that the unusually strong, isotropic structural negative thermal expansion in cubic perovskite ionic insulator ScF_3 occurs in excited states above a ground state tuned very near a structural quantum phase transition, posing a question of fundamental interest as to whether this special circumstance is related to the anomalous behavior. To test this hypothesis, we report an elastic and inelastic X-ray scattering study of a second system Hg_2I_2 also tuned near a structural quantum phase transition while retaining stoichiometric composition and high crystallinity. We find similar behavior and significant negative thermal expansion below 100K for dimensions along the body-centered-tetragonal c axis, bolstering the connection between negative thermal expansion and zero temperature structural transitions. We identify the common traits between these systems and propose a set of materials design principles that can guide discovery of new materials exhibiting negative thermal expansion.

Negative thermal expansion (NTE) is an emerging area of material behavior discussed in chemistry, engineering, and physics which challenges conventional notions of lattice dynamics. Two routes to realizing NTE have been realized: one recipe is via a *broadened phase transition* from some high-temperature phase to a higher-volume, lower temperature phase. Treatment with quenched disorder can smear the transition and achieve a gradual and tunable NTE evolution of lattice parameters. Examples of this type of NTE are found in InVar[1], anti-perovskites[2, 3], ruthenates[4], and charge-transfer insulators[5, 6]. In contrast, a second type of NTE is realized from *intrinsic dynamical origins*, also referred to as structural NTE (SNTE)[7], which is not obviously resultant from phase competition and does not require quenched disorder but seems to arise from intrinsic geometrical modes with tendencies to draw in the lattice dimensions when thermally activated. Unlike the broadened phase transition type, SNTE appears in a wide variety of lattice systems[8, 9] without necessarily constraining the magnetic or electronic phase diagram. This freedom allows one to envisage new multifunctional materials with diverse mechanical, spin, orbital, thermal, electronic, superconducting, and more exotic order co-existing with NTE, potentially enabling the benefits of strain control to enable new types of order.

ScF_3 is prominent among SNTE systems, forming in the so-called “open” perovskite (ReO_3 -type) structure with a small, four-atom unit cell and cubic symmetry at all temperatures below the high melting point of 1800K (Fig 1a)[10–16]. The linear coefficient of thermal expansion (CTE) of this material is isotropic, strongly negative, and persistent over 1000K temperature window[10]. Combined computational and inelastic

scattering work[11] has described the configurational potential for R point distortions as having a nearly quartic form at small displacement, presenting an interesting limit of lattice dynamics. Further inelastic scattering investigations on single crystals aimed at exploring the consequences of this unusual situation discovered an incipient soft-mode instability[12] implying the development of a structural instability with a small extrapolated critical temperature $T_c < 0$. This result implies that while similar compounds like TiF_3 realize a cubic-to-rhombohedral structural phase transition, the transition is never realized in ScF_3 , except under an extremely small $< 1\text{kbar}$ hydrostatic pressure at cryogenic temperatures. These special circumstances are contextualized in Figure 1a, which shows the global structural phase diagram of 3d transition metal trifluorides BF_3 as a function of the B^{+3} ionic radius, r_B . The occurrence of the endpoint of a structural phase boundary so near the ground state of a stoichiometric compound is extremely rare, as is the pronounced SNTE property of ScF_3 . The confluence of these unusual circumstances raises the broad question of whether SNTE can arise as unusual behavior above structural quantum phase transitions (SQPTs) associated with transverse shifts of linking units between volume-defining vertices. To directly address this issue, we have explored the thermal expansion behavior and lattice fluctuation spectra in optical/detector quality single crystals of a second stoichiometric SQPT material Hg_2I_2 , known colloquially as protiodide[17].

Figure 1b summarizes the known structural phase diagram of the mercurous halides Hg_2X_2 ($\text{X}=\text{Cl}, \text{Br}, \text{I}$) as a function of the X^- ionic radius[17], r_X . The high symmetry structure in this case is body-centered tetragonal (BCT; Fig 1e) and can be described as a dense packing

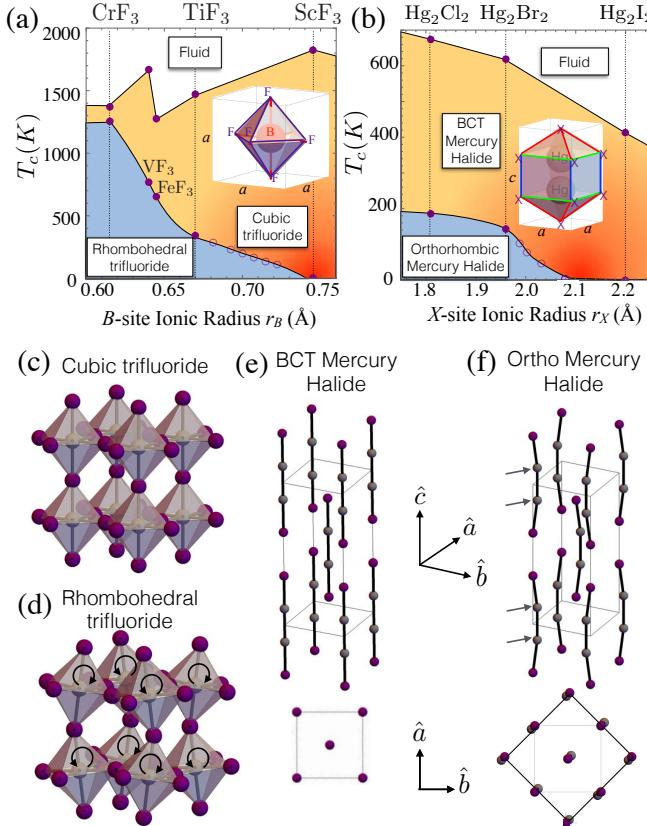


FIG. 1: Structural phase diagrams of (a) 3d transition metal trifluorides BF₃ and (b) mercurous halides Hg₂X₂. Open circles represent solid solutions Sc_{1-x}TixF₃[18] and Hg₂(Br_{1-x}I_x)₂[19], respectively. Insets show the basic volume-defining polyhedral units: (a) the BF₆ octahedron and (b) the elongated square dipyramid (ESD). (c-f) Schematic structures of the (c) cubic trifluoride (d) rhombohedral trifluoride (e) body-centered tetragonal mercury halide, and (f) orthorhombic mercury halide. The lower panels in (e) and (f) show views down the 001 axis, showing the shift pattern of the Hg dimer across the structural transition and gray line show the BCT unit cell and the black diamond in (f) shows the orthorhombic unit cell.

of X-Hg-Hg-X linear molecules oriented along the tetragonal c axis[20]. The basic structural unit that defines the high-temperature unit cell is an elongated square dipyramid (ESD) formed as a cage with parts of 10 X⁻ ions surrounding a Hg dimer oriented along c , shown in Figure 1b inset and Figure 4b. The structural transition to the orthorhombic phase can be described as a freezing of the Hg dimer transverse fluctuation in a staggered pattern (Fig. 1f) at the X point of the BCT Brillouin zone.

Single crystals of Hg₂I₂ and Hg₂Br₂ were prepared from purified materials using physical vapor deposition as previously reported[17]. Diffraction and inelastic X-ray scattering (IXS) data were collected using the HERIX spectrometer in sector 30 of the Advanced Photo-

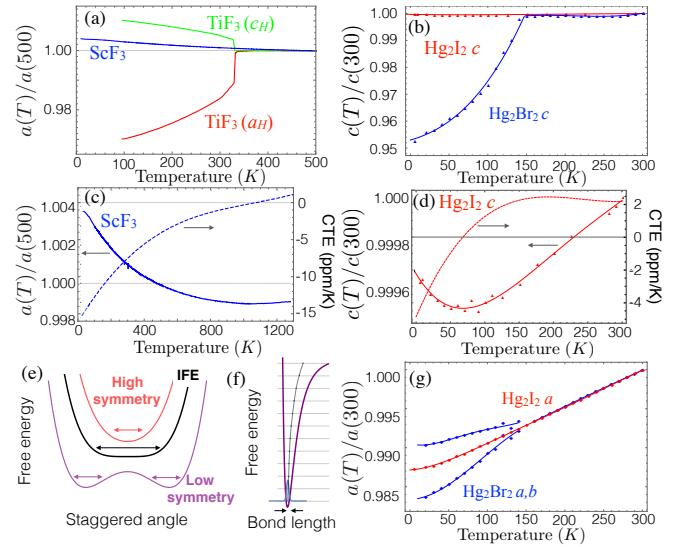


FIG. 2: Temperature-dependent lattice parameters of (a,c) ScF₃ and TiF₃ from references [10, 12, 21], and (b,d,f) Hg₂I₂, and Hg₂Br₂. The mercurous halide c axis parameters were collected from the 004 and 008 reflections and the a,b parameters are derived from the 300 and 030 twin reflections. The panel (e) shows a schematic free energy landscape of high, low, and transitioning systems near the SQPT. (f) Shows an intermolecular potential appropriate for bond-stretch coordinates. The mean separation is indicated by a dashed curve, illustrating the positive thermal expansion effect of this type of excitation. Horizontal arrows in (e) and (f) show the fluctuation domain in each case. (g) Planar lattice parameters for Hg₂Br₂ and Hg₂I₂.

ton Source, Argonne National Laboratory. Figure 2 shows the lattice parameters of ScF₃[10] and Hg₂I₂ along with data from their nearest realized structural transitions in TiF₃[18] and Hg₂Br₂, respectively, for comparison. In the case of TiF₃ (Fig 2a), the cubic-to-rhombohedral transition has profound effects on the lattice dimensions, showing a signature step of a first order transition and subsequent continuous order parameter development, shrinking ~3% between the structural transition temperature T_c and base temperature[21]. The hexagonal c axis on the other hand displays SNTE similar in magnitude to the negative CTE observed along the cubic a axis of ScF₃ in the same temperature range. The lattice expansion of the realized transition in Hg₂Br₂ bears remarkable resemblance, with a significant reduction in tetragonal c axis lattice parameter below the transition, changing 4.5% between 150K and base temperature. The transition appears to be nearly continuous, consistent with prior work[22]. The c axis of Hg₂I₂ however shows a strongly negative CTE below 100K shown in Figure 2d, reaching a significant low-temperature value of -5ppm/K. While negative values of the c -axis compressibility have been noted in mercurous halides[23], SNTE in Hg₂I₂ has not been reported to our knowledge.

The similarities to the fluorides are striking - both real-

ized transitions TiF_3 and Hg_2Br_2 show a strong positive CTE below their respective transitions while the systems tuned near SQPTs show SNTE in high symmetry directions aligned with a linkage undergoing strong transverse fluctuations at the lowest temperatures. Beyond the phase diagram and structural motifs, we note other gross similarities between these two material classes: they are ionic insulators with no reported magnetism or free carriers and retain high symmetry structures at all temperatures below their respective melting temperatures. Furthermore, both systems are driven to lower symmetry phases at modest pressure and ambient temperature (ScF_3 cubic-to-rhombohedral at $p_c=7\text{kbar}$ and 300K[10]; Hg_2I_2 body-center-tetragonal-to-orthorhombic at $p_c=9\text{kbar}$ and 300K[24]) or very low pressure at cryogenic temperatures (estimated $p_c \sim 1\text{kbar}$ for both systems at 4K[10, 25]). We note also analogous structural motifs: the bridging F ion in ScF_3 , which occurs in all three spatial directions and the bridging Hg dimer, which is oriented along the c axis in the mercurous halides.

Figs 2c,d show remarkable similarities in the functional form of the CTE of Hg_2I_2 and ScF_3 , which strengthen significantly at low temperature, implying the relevant lattice modes lie at extremely low energy. Apart from exceptional cases[26, 27], the influence of higher-energy bond-stretch excitations are expected to provide positive thermal expansion influences which generically compete with SNTE due to the short-range hardening and long-range softening of central force interionic potentials (Fig. 2f)[28, 29], which explains the overwhelming prevalence of positive thermal expansion in materials at ambient temperature. For Hg_2I_2 , the magnitude of the c -CTE (-5ppm/K) is about one third of the maximum a -CTE in ScF_3 (-14ppm/K) and the range of thermal persistence is also reduced about 10-fold. This suppression can be partially explained by the much larger mass in the iodide case (ScF_3 density 2.53g/cm^3 ; Hg_2I_2 density 7.7g/cm^3), which significantly reduces the phonon bandwidth ($\sim 140\text{meV}$ in ScF_3 [15] and $\sim 25\text{meV}$ in Hg_2I_2 [24]) and activation energy for bond-stretch dynamics which compete with and ultimately overtake the SNTE effect. We point out further that quenched disorder is known to compete with SNTE[30], and while we have restricted our attention to pure stoichiometric systems, the halide system is likely more disordered than the fluoride based on comparison of the rocking curve width (0.002° for ScF_3 and 0.13° for Hg_2I_2 ; see Supplemental Materials). A recent study of a SQPT achieved through chemical substitution shows prominent elastic and thermodynamic anomalies near the SQPT in solid solution $\text{LaCu}_{6-x}\text{Au}_x$ [31] but does not report SNTE near the critical composition. In contrast, both ScF_3 and Hg_2I_2 lie very close to the critical endpoint of a structural phase boundary without the additional detrimental effects of quenched disorder.

Figure 3 provides an experimental basis to demonstrate proximities to SQPTs in ScF_3 and Hg_2I_2 , showing inelastic X-ray scattering spectra at the momentum

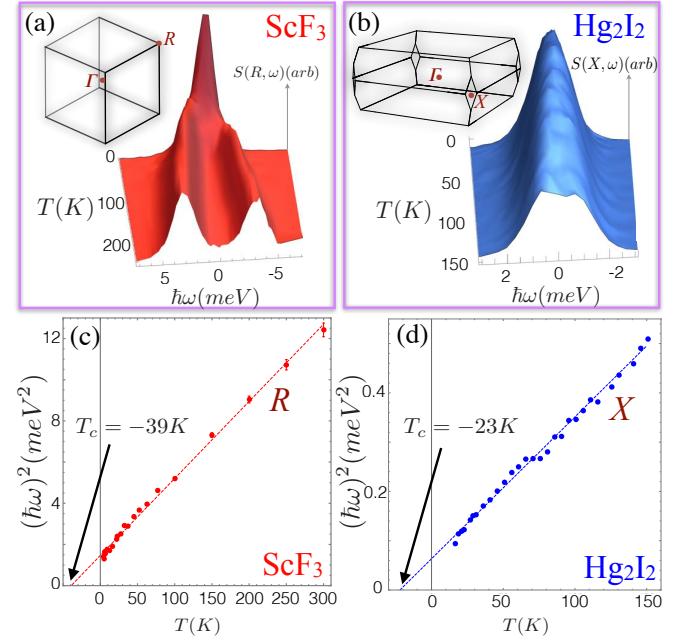


FIG. 3: (a) Dynamical structure factor for ScF_3 collected using inelastic X-ray scattering at the $(2.5,3.5,0.5)$ reciprocal vector, corresponding to the R point of the simple cubic Brillouin zone, shown as an inset. (b) Dynamical structure factor for Hg_2I_2 collected using inelastic X-ray scattering at the $(2.5,3.5,0)$ reciprocal vector, corresponding to the X point of the body-centered tetragonal Brillouin zone, shown as an inset. (c) Soft mode frequency squared determined from fits to the data in (a), showing the incipient ferroelastic state underlies the SNTE effect in ScF_3 . (d) (d) Soft mode frequency squared determined from fits to the data in (b), showing the incipient ferroelastic state also underlies the SNTE effect in Hg_2I_2 .

points corresponding to the soft mode instabilities. The trifluoride low-temperature phase can be described as a staggered tilt of octahedra around the 111 axis (Figure 1f). This fluctuation has the (π,π,π) spatial texture of the R point in the simple cubic Brillouin zone, shown in Figure 3a. Also shown is a surface plot of the dynamical structure factor $S(R, \omega)$ obtained using IXS[12]. At high temperature, a Stokes and anti-Stokes mode at low frequency of 3.4 meV softens considerably, approaching an extrapolated transition temperature $T_c \simeq -39\text{ K}$, as shown in Figure 3c. This singular point in the response function is suggestive of a flattening of the free energy landscape in an approach to an unrealized structural phase transition and strongly supports our identification of ScF_3 as near a SQPT.

In the halide case, starting from the BCT phase, the relevant distortion to the low-temperature orthorhombic phase is a staggered shift of the Hg-Hg dimer from the ESD central axis in the 110 direction of the basal plane (Figure 1f) and the structural transition then corresponds to condensation of the transverse acoustic wave at the X point of the BCT Brillouin zone[22, 32, 33].

Figure 3b,d shows the evolution of $S(X, \omega)$ with temperature and an avoided condensation of a soft mode at the X point of the body-centered tetragonal Brillouin zone in Hg_2I_2 . $S(X, \omega)$ also shows Stokes/anti-Stokes mode pairs that imply a putative transition at $T_c \approx -23$ K. This is fully consistent with previous studies on single crystals using energy-integrated diffuse X-ray scattering showing $T_c \sim 20$ K[34]. We explore more detailed analysis of the influences driving these incipient structural transitions in each case below.

For the realized structural transitions in the mercurous halides $X=\text{Cl}, \text{Br}$ [22, 34] $T_c > 0$ and the $T=0$ energy landscape consists of four minima corresponding to the possible saturated shifts of the Hg dimers (Fig 4d). For larger ionic radius $X=\text{I}$, these minima flatten and coalesce to the central axis, as no symmetry breaking is observed. The flattening of the energetic landscape however induces strong temperature-dependent fluctuations of the staggered shift, as is observed experimentally from X-ray diffraction data as large transverse dimensions of the Hg thermal ellipsoids, approaching $2\sqrt{U_{11}}=0.38\text{\AA}$ at $T=150$ K for Hg_2I_2 [35].

To gain further insight into the origin of the avoided transition in Hg_2I_2 , we analyze trends among the bond lengths of the ESD, which is not regular, but rather compressed (Fig 1b inset), defined by X-X bond lengths of three varieties: the long X-X bonds (green) lying in the basal plane, the short X-X bonds (blue) oriented along the tetragonal c axis, and apical X-X bonds (red). Figure 4b shows reported literature values of the lengths of the three types of X-X bond distance[20, 35–39]. The basal planar (green) X-X bonds cluster well[62] with a clear trend far in excess of the diagonal dashed line that indicates simplest expectation based on sphere packing. The apical (red) bonds trend with ionic radius and stay near the X ionic diameter, indicating the apical half octahedron is flattened relative to a regular ESD but roughly satisfies simple packing conditions. On the contrary, the c -oriented (blue) X-X bond is near the ionic diameter only for $X=\text{Cl}$ (calomel) and deviates significantly for $X=\text{Br}$ and even more so for the SQPT material $X=\text{I}$, suggestive that the compression of the X-X bond plays a role in the energy flattening behind the SQPT and the NTE we report here. These short halide-halide bonds along c are in a state of compression due to forces provided by the rest of the framework[63]. The natural source of this compression is a net tension in the X-Hg-Hg-X linear molecule along the c axis through the ESD center. We propose that the origin of the coalescing energy minima can be viewed as an effect of two competing forces: the compressive stress on the c -oriented X-X bonds and the tensile stress on the X-Hg-Hg-X linear molecule by its environment. For $X=\text{I}$, these forces have a near-canceling effect which stabilizes the high-symmetry BCT structure with large transverse dimer fluctuations inside the ESD and the corresponding c -axis SNTE. Our identification of the compressive/tensile balance in Hg_2X_2 constitutes a context for the 1D “tension effect”[8, 14, 40, 41], which

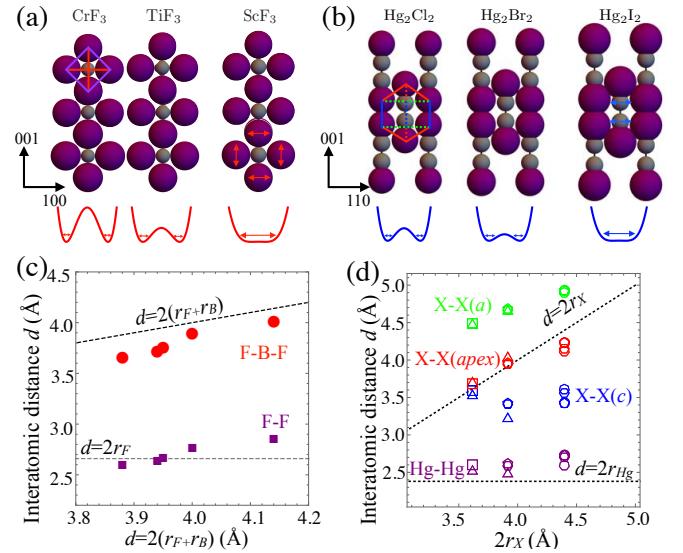


FIG. 4: (a) Development of the structures of the transition metal trifluorides, with purple spheres representing F^- and silver spheres representing B^{3+} ions. (b) Development of the structures of the mercurous halides with purple spheres representing X^- and silver spheres representing Hg^{2+} ions. B^{3+} or X^- ionic radius increases from left to right in (a) and (b) respectively. Overlayed lines show the ESD of Figure 1b inset, where solid lines lie in the plane of the page and dashed lines show bonds that protrude out of the plane. (c,d) Comparison of the observed bond distances and expectations based on hard sphere packing (dashed lines) for (c) transition metal trifluorides in the cubic phase[49] and (d) mercurous halides in the BCT phase. Symbols in (d) are from corresponding references: triangles[38], squares[39], pentagons[37], hexagons[36], septagons[50], and circles[35].

has been observed in cyanides[42, 43] in 1D and 2D. The Hg linking dimer is distinct from the linking CN complex in that it does not set up orientational order known to exist in a broad class of cyanides[44].

Crossing the SQPT from the high symmetry side can be viewed as an increase in the number of zero modes as the potential landscape flattens in certain directions. In the language of structural mechanics, a change in zero mode count must be accompanied by a reduction in the number of states of self stress (SSS) in the ESD polyhedral unit[45–47], a condition which increases its stability against deformation[48]. For the critical composition $X=\text{I}$, a critically-tensioned linear molecule inside the ESD unit exhibits large transverse fluctuations of the Hg dimer which exert tension on all bonds in the c direction and leads to the observed negative thermal expansion along this axis which increases as the temperature is lowered (Fig. 2d). This size-induced stiffening is also apparent in the lowering of the melting temperature and triple points as the X ion grows, since the entropy of the BCT phase is reduced by the stiffening of the ESD, enabling the fluid phase to persist at lower temperature.

In a similar set of considerations, we analyze the evolution of the basic trifluoride octahedral subunit with r_B , used as a baseline for comparison of relative size effects. Figure 4a shows that to a good approximation, the unit cell dimension F-B-F ionic distance (a lattice parameter) trends with r_F+r_B while the nearest F-F distance grows to values significantly in excess of $2r_F$. We note further that for $r_B > 0.75\text{\AA}$ in the rare-earth class and beyond, trifluorides take on other crystal structures with B site coordination larger than $n=6$ in the orthorhombic tysonite ($n=8$), and hexagonal ($n=9$)[51] structures. Together, these observations suggest an effective reduction of the overall stiffness of the BF_6 octahedron for large B ions through reduced interaction of the anions situated at the octahedral vertices. In this case, a large number of SSSs are removed as the octahedral unit loses integrity with increasing r_B . Notably, fluctuations of the F^- position transverse to the B-F-B bond are very large in ScF_3 , approaching $2\sqrt{U_{33}}=0.24\text{\AA}$ [11, 14, 15] at $T=150\text{ K}$, consistent with this picture. In contrast to the mechanism in the mercurous iodide, we expect that the onset of pliancy of octahedral molecules stabilizes the cubic phase, as many states are available with the average cubic structure. This situation is also manifest in the high melting point of ScF_3 , where the high entropy of transverse bond fluctuation competes with the fluid phase as high as 1800K.

We note that incipient lattice instabilities and broadly systems tuned near SQPTs have recently attracted renewed interest[52] in light of their use to develop a 50% increase[53] in superconducting transition temperature of Nb-doped SrTiO_3 in an exceptional limit of the strong coupling theory[54], while the recent observation of electronic coupling to a substrate phonon in FeSe films raises questions regarding the possible role of substrate lattice fluctuations in stabilizing film superconductivity[55]. The common appearance of incipient soft modes also in SNTE materials potentially opens promising areas for future work combining SNTE and superconductivity to realize new emergent phases enabled by extremal strain conditions. Our results here suggest renewed importance of spectroscopic studies of known high-symmetry NTE materials such as ZrW_2O_8 [56, 57], $\text{Zn}(\text{CN})_2$ [58, 59], and $\text{Ag}_3[\text{Co}(\text{CN})_6]$ [60].

The transition metal trifluoride and mercurous halide

materials bear strong similarities besides the unusual strengthening of the SNTE effect at low temperature. In both cases, molecular units form a high-symmetry structure whose bonds are on average straight and are situated so as to define the linear dimensions of the crystal, a in ScF_3 and c in Hg_2I_2 . On approach to zero temperature, high-energy bond-stretch excitations become frozen out quickly according to the Bose factor, while the soft mode angular fluctuations reduce more gradually due to the observed $\omega \propto \sqrt{T}$ dependence. These competing influences lead to trend of NTE strengthening at the lowest temperatures and conventional expansion at elevated temperatures and the soft mode is crucial to boost the weak NTE influence. From this point of view, ScF_3 has extremely strong and thermally-persistent NTE behavior due both to the stiff bond-stretch, three dimensional lattice system, and proximity to the SQPT. The incipient nature of the transition is vital to this condition to avoid a staggered strain symmetry breaking which disrupts the coupling of angle to dimension. We generalize this understanding in a proposal that candidate SNTE materials may be identified in systems which have (i) structural instability associated with a transverse linkage shift between-volume-defining vertices, (ii) soft modes and large fluctuations of the near the SQPT, (iii) low quenched disorder and stoichiometric composition, and (iv) relatively stiff bond-stretch excitations.

Acknowledgments

Work at the University of Connecticut was provided by National Science Foundation Award No. DMR-1506825 with additional support from the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, under Award No. de-sc0016481. C.A.O. acknowledges support from the Treibick family scholarship, managed by the Office of Undergraduate Research at the University of Connecticut. Work at the University of Costa Rica is supported by the Vice-rectory for Research under the project no. 816-B7-601 and work at Argonne National Laboratory is supported by the U.S. Department of Energy, Office of Basic Energy Sciences under contract no. DE-AC02-06CH11357.

-
- [1] C. E. Guillaume, Stockholm, Sweden: Royal Swedish Academy of Sciences pp. 1–16 (1920), URL [#1.](http://scholar.google.com/scholar?hl=en&btnG=Search&q=intitle:The+Nobel+Prize+in+Chemistry++2000:+Conductive+polymers)
 - [2] K. Takenaka and H. Takagi, Applied Physics Letters **87**, 261902 (2005), ISSN 00036951, URL <http://link.aip.org/link/APPLAB/v87/i26/p261902/s1&Agg=doi>.
 - [3] B. Qu, H. He, and B. Pan, Advances in Condensed Matter Physics **2012**, 4903 (2012), URL <http://www.hindawi.com/journals/acmp/2012/913168/abs/>.
 - [4] K. Takenaka, Y. Okamoto, T. Shinoda, N. Katayama, Y. Sakai, C. N. Chu, N. Saka, N. P. Suh, A. W. Sleight, G. D. Barrera, et al., Nature Communications **8**, 14102 (2017), ISSN 2041-1723, URL <http://www.nature.com/doifinder/10.1038/ncomms14102>.
 - [5] M. Azuma, W.-t. Chen, H. Seki, M. Czapski, S. Olga, K. Oka, M. Mizumaki, T. Watanuki, N. Ishimatsu, N. Kawamura, et al., Nature communications **2**, 347 (2011), ISSN 2041-1723, URL <http://www.nature.com/doifinder/10.1038/ncomms14102>.

- //www.ncbi.nlm.nih.gov/articlerender.fcgi?artid=3156814&tool=pmcentrez&rendertype=abstracthttp://www.nature.com/ncomms/journal/v2/n6/abs/ncomms1361.html.
- [6] J. Chen, L. Fan, Y. Ren, Z. Pan, J. Deng, R. Yu, and X. Xing, Physical Review Letters **110**, 115901 (2013), ISSN 0031-9007, URL <http://link.aps.org/doi/10.1103/PhysRevLett.110.115901>http://prl.aps.org/abstract/PRL/v110/i11/e115901.
- [7] C. A. Occhialini, S. U. Handunkanda, E. B. Curry, and J. N. Hancock, Physical Review B **95**, 094106 (2017), ISSN 2469-9950, URL <https://link.aps.org/doi/10.1103/PhysRevB.95.094106>.
- [8] M. T. Dove and H. Fang, Reports on Progress in Physics **79**, 066503 (2016), ISSN 0034-4885, URL <http://stacks.iop.org/0034-4885/79/i=6/a=066503?key=crossref.65f05914eba7be083272c39a81151ff6>.
- [9] R. Mittal, M. Gupta, and S. Chaplot, Progress in Materials Science **92**, 360 (2018), ISSN 00796425, URL <https://www.sciencedirect.com/science/article/pii/S0079642517301184>http://linkinghub.elsevier.com/retrieve/pii/S0079642517301184.
- [10] B. K. Greve, K. L. Martin, P. L. Lee, P. J. Chupas, K. W. Chapman, and A. P. Wilkinson, Journal of the American Chemical Society **132**, 15496 (2010), ISSN 1520-5126, URL <http://dx.doi.org/10.1021/ja106711v>http://www.ncbi.nlm.nih.gov/pubmed/20958035.
- [11] C. W. Li, X. Tang, J. A. Muñoz, J. B. Keith, S. J. Tracy, D. L. Abernathy, and B. Fultz, Physical Review Letters **107**, 195504 (2011), ISSN 0031-9007, URL <http://link.aps.org/doi/10.1103/PhysRevLett.107.195504>http://prl.aps.org/abstract/PRL/v107/i19/e195504.
- [12] S. U. Handunkanda, E. B. Curry, V. Voronov, A. H. Said, G. G. Guzmán-Verri, R. T. Brierley, P. B. Littlewood, and J. N. Hancock, Physical Review B **92**, 134101 (2015), ISSN 1098-0121, URL <http://link.aps.org/doi/10.1103/PhysRevB.92.134101>https://link.aps.org/doi/10.1103/PhysRevB.92.134101.
- [13] S. U. Handunkanda, C. A. Occhialini, A. H. Said, and J. N. Hancock, Physical Review B **94**, 214102 (2016), ISSN 2469-9950, URL <https://link.aps.org/doi/10.1103/PhysRevB.94.214102>.
- [14] L. Hu, J. Chen, A. Sanson, H. Wu, C. Guglieri Rodriguez, L. Olivi, Y. Ren, L. Fan, J. Deng, and X. Xing, Journal of the American Chemical Society **138**, 8320 (2016), ISSN 0002-7863, URL <http://pubs.acs.org/doi/abs/10.1021/jacs.6b02370>.
- [15] S. Piskunov, P. A. Žguns, D. Bocharov, A. Kuzmin, J. Purans, A. Kalinko, R. A. Evarestov, S. E. Ali, and F. Rocca, Physical Review B **93**, 214101 (2016), ISSN 2469-9950, URL <http://link.aps.org/doi/10.1103/PhysRevB.93.214101>.
- [16] A. van Roekeghem, J. Carrete, and N. Mingo, Physical Review B **94**, 020303 (2016), ISSN 2469-9950, URL <http://link.aps.org/doi/10.1103/PhysRevB.94.020303>.
- [17] P. M. Amarasinghe, J.-S. Kim, H. Chen, S. Trivedi, S. B. Qadri, J. Soos, M. Diestler, D. Zhang, N. Gupta, J. L. Jensen, et al., Journal of Crystal Growth **450**, 96 (2016), ISSN 00220248, URL <https://www.sciencedirect.com/science/article/pii/S0022024816303165>http://linkinghub.elsevier.com/retrieve/pii/S0022024816303165.
- [18] C. R. Morelock, L. C. Gallington, and A. P. Wilkinson, Chemistry of Materials **26**, 1936 (2014), ISSN 0897-4756, URL <http://dx.doi.org/10.1021/cm5002048>.
- [19] Y. F. Markov, K. Knorr, and E. M. Roginskii, Ferroelectrics **359**, 82 (2007), ISSN 0015-0193, URL <http://www.tandfonline.com/doi/abs/10.1080/00150190701514850>.
- [20] R. J. Havighurst, American Journal of Science **10**, 15 (1925), ISSN 0002-9599, URL <http://geoscienceworld.org/georef/2006-056970>http://www.ajsonline.org/cgi/doi/10.2475/ajs.s5-10.55.15.
- [21] C. R. Morelock, L. C. Gallington, and A. P. Wilkinson, Journal of Solid State Chemistry **222**, 96 (2015), ISSN 00224596, URL <http://www.sciencedirect.com/science/article/pii/S0022459614004861>.
- [22] M. E. Boiko, Y. Markov, V. S. Vikhmin, A. S. Yurkov, and B. S. Zadokhin, Ferroelectrics **130**, 263 (1992), ISSN 0015-0193, URL <http://www.informaworld.com/openurl?genre=article&doi=10.1080/00150199208008969&magic=crossref%7C%7CD404A21C5BB053405B1A640AFFD44AE3>.
- [23] R. H. Baughman, S. Stafström, C. Cui, and S. O. Dantas, Science **279** (1998), URL <http://science.sciencemag.org/content/279/5356/1522>.
- [24] Y. F. Markov, V. Y. Mirovitskii, and E. M. Roginskii, Physics of the Solid State **57**, 480 (2015), ISSN 1063-7834, URL <http://link.springer.com/10.1134/S1063783415030130>.
- [25] E. Rehbar, H. Fischer, and W. Dultz, Physical Review B **25**, 5889 (1982), ISSN 0163-1829, URL <https://link.aps.org/doi/10.1103/PhysRevB.25.5889>.
- [26] M. C. Rechtsman, F. H. Stillinger, and S. Torquato, The journal of physical chemistry. A **111**, 12816 (2007), ISSN 1089-5639, URL <http://dx.doi.org/10.1021/jp0768591>.
- [27] V. A. Kuzkin, The journal of physical chemistry. A **118**, 9793 (2014), ISSN 1520-5215, URL <http://dx.doi.org/10.1021/jp509140n>http://www.ncbi.nlm.nih.gov/pubmed/25245826.
- [28] G. D. Barrera, J. A. O. Bruno, T. H. K. Barron, and N. L. Allan, Journal of Physics: Condensed Matter **17**, R217 (2005), ISSN 0953-8984, URL <http://stacks.iop.org/0953-8984/17/i=4/a=R03?key=crossref.163695459dc29d5c53bc358b51e1ddcc>.
- [29] K. Takenaka, T. Hamada, D. Kasugai, and N. Sugimoto, Journal of Applied Physics **112**, 083517 (2012), ISSN 00218979, URL [http://apps.webofknowledge.com/full{_}record.do?product=UA&search{_}mode=GeneralSearch&qid=40&{SID=2Fv4pNcCJ8qjseiAchW&page=10&{doc=100}](http://apps.webofknowledge.com/full{_}record.do?product=UA&search{_}mode=GeneralSearch&qid=40&{SID=2Fv4pNcCJ8qjseiAchW&page=10&{doc=100).
- [30] E. E. Rodriguez, A. Llobet, T. Proffen, B. C. Melot, R. Seshadri, P. B. Littlewood, and A. K. Cheetham, Journal of Applied Physics **105**, 114901 (2009), ISSN 00218979, URL <http://scitation.aip.org/content/aip/journal/jap/105/11/10.1063/1.3120783>.
- [31] L. Poudel, A. F. May, M. R. Koehler, M. A. McGuire, S. Mukhopadhyay, S. Calder, R. E. Baumback, R. Mukherjee, D. Sapkota, C. de la Cruz, et al., Physical Review Letters **117**, 235701 (2016), ISSN 0031-9007, URL <https://link.aps.org/doi/10.1103/PhysRevLett.117.235701>.
- [32] Č. Barta, A. A. Kaplyanski, V. V. Kulakov, and Y. F. Markov, Journal of Experimental and Theoretical Physics Letters **21**, 54 (1975).

- [33] J. P. Benoit, G. Hauret, Y. Luspin, C. X. An, and J. Lefebvre, *Ferroelectrics* **25**, 569 (1980), ISSN 0015-0193, URL <http://www.tandfonline.com/doi/abs/10.1080/00150198008207072>.
- [34] Y. F. Markov, K. Knorr, and E. M. Rognskii, *Ferroelectrics* **265**, 67 (2002), ISSN 0015-0193, URL <http://www.tandfonline.com/doi/abs/10.1080/00150190208260606>.
- [35] M. Kars, T. Roisnel, V. Dorcet, A. Rebbah, and O.-D. L. Carlos, *Acta Crystallographica Section E Structure Reports Online* **68**, i11 (2012), ISSN 1600-5368, URL <http://www.ncbi.nlm.nih.gov/pubmed/22346788http://www.pubmedcentral.nih.gov/articlerender.fcgi?artid=PMC3274835http://scripts.iucr.org/cgi-bin/paper?S1600536811056339>.
- [36] R. J. Havighurst, *Journal of the American Chemical Society* **48**, 2113 (1926), ISSN 0002-7863, URL <http://pubs.acs.org/doi/abs/10.1021/ja01419a016>.
- [37] E. Hylleraas, *Zeitschrift fur Physik* **36**, 859 (1927).
- [38] E. Dorm, *Journal of the Chemical Society D: Chemical Communications* p. 466 (1971), ISSN 0577-6171, URL <http://xlink.rsc.org/?DOI=c29710000466>.
- [39] N. J. Calos, C. H. L. Kennard, and R. L. Davis, *Zeitschrift für Kristallographie - Crystalline Materials* **187**, 305 (1989), ISSN 2196-7105, URL <http://www.degruyter.com/view/j/zkri.1989.187.issue-1-4/zkri.1989.187.14.305/zkri.1989.187.14.305.xml>.
- [40] Z. Schlesinger, J. A. Rosen, J. N. Hancock, and A. P. Ramirez, *Physical Review Letters* **101**, 015501 (2008), ISSN 0031-9007, URL <http://link.aps.org/doi/10.1103/PhysRevLett.101.015501http://prl.aps.org/abstract/PRL/v101/i1/e015501>.
- [41] A. Sanson, *Chemistry of Materials* **26**, 3716 (2014), ISSN 0897-4756, URL <http://dx.doi.org/10.1021/cm501107w>.
- [42] S. J. Hibble, A. M. Chippindale, A. H. Pohl, and A. C. Hannon, *Angewandte Chemie International Edition* **46**, 7116 (2007), ISSN 14337851, URL <http://doi.wiley.com/10.1002/anie.200701246>.
- [43] S. J. Hibble, G. B. Wood, E. J. Bilbé, A. H. Pohl, M. G. Tucker, A. C. Hannon, and A. M. Chippindale, in *Zeitschrift fur Kristallographie* (2010), vol. 225, pp. 457–462, ISBN 2194-4946, ISSN 00442968.
- [44] U. T. Höchli, K. Knorr, and A. Loidl, *Advances in Physics* **51**, 589 (1990), ISSN 0001-8732, URL <http://dx.doi.org/10.1080/00018730110117442>.
- [45] J. C. Maxwell, *Philosophical Magazine Series 4* **27**, 294 (1864), ISSN 1941-5982, URL <http://www.tandfonline.com/doi/abs/10.1080/14786446408643668>.
- [46] C. Calladine, *International Journal of Solids and Structures* **14**, 161 (1978), ISSN 00207683, URL <http://linkinghub.elsevier.com/retrieve/pii/0020768378900525>.
- [47] C. L. Kane and T. C. Lubensky, *Nature Physics* **10**, 39 (2013), ISSN 1745-2473, URL http://www.nature.com/nphys/journal/v10/n1/full/nphys2835.html?WT.ecf{_}id=NPHYS-201401.
- [48] R. B. Fuller, *Synergetics: Explorations in the Geometry of Thinking* (MacMillan, 1975).
- [49] P. Daniel, A. Bulou, M. Rousseau, J. Nouet, and M. Leblanc, *Physical Review B* **42**, 10545 (1990), ISSN 0163-1829, URL <http://link.aps.org/doi/10.1103/PhysRevB.42.10545>.
- [50] M. L. Huggins and P. L. Magill, *Journal of the American Chemical Society* **49**, 2357 (1927), ISSN 0002-7863, URL <http://pubs.acs.org/doi/abs/10.1021/ja01409a003>.
- [51] D. N. Khitarov, B. P. Sobolev, and I. V. Alexeeva, *The Rare Earth Trifluorides* (Institut d'Estudis Catalans, Barcelona, 2001), URL https://books.google.com/books?id=IvD-PAvUuWkC{&}pg=PA406{&}dq=fluoride+chemistry+rare+earth{&}hl=en{&}sa=X{&}ved=OahUKEwix5bfat4bUAhUh{_{}}IMKHb-6B-UQ6AEIIzAA{#}v=onepage{&}q=fluoridechemistryrareearth{&}f=false.
- [52] H. Takahashi, T. Akiba, K. Imura, T. Shiino, K. Deguchi, N. K. Sato, H. Sakai, M. S. Bahramy, and S. Ishiwata, *Physical Review B* **95**, 100501 (2017), ISSN 2469-9950, URL <https://link.aps.org/doi/10.1103/PhysRevB.95.100501>.
- [53] A. Stucky, G. W. Scheerer, Z. Ren, D. Jaccard, J.-M. Poumirol, C. Barreteau, E. Giannini, and D. van der Marel, *Scientific Reports* **6**, 37582 (2016), ISSN 2045-2322, URL <http://www.nature.com/articles/srep37582>.
- [54] J. M. Edge, Y. Kedem, U. Aschauer, N. A. Spaldin, and A. V. Balatsky, *Physical Review Letters* **115**, 247002 (2015), ISSN 0031-9007, URL <https://link.aps.org/doi/10.1103/PhysRevLett.115.247002>.
- [55] J. J. Lee, F. T. Schmitt, R. G. Moore, S. Johnston, Y.-T. Cui, W. Li, M. Yi, Z. K. Liu, M. Hashimoto, Y. Zhang, et al., *Nature* **515**, 245 (2014), ISSN 0028-0836, URL [http://dx.doi.org/10.1038/nature13894http://www.nature.com/nature/journal/v515/n7526/abs/nature13894.html{#}supplementary-information](http://dx.doi.org/10.1038/nature13894http://10.0.4.14/nature13894http://www.nature.com/nature/journal/v515/n7526/abs/nature13894.html{#}supplementary-information).
- [56] J. Hancock, Ph.D. thesis, University of California (2004).
- [57] F. Bridges, T. Keiber, P. Juhas, S. J. L. Billinge, L. Sutton, J. Wilde, and G. R. Kowach, *Physical Review Letters* **112**, 045505 (2014), ISSN 0031-9007, URL <http://link.aps.org/doi/10.1103/PhysRevLett.112.045505>.
- [58] K. W. Chapman, P. J. Chupas, and C. J. Kepert, *Journal of the American Chemical Society* **127**, 15630 (2005), ISSN 0002-7863, URL <http://dx.doi.org/10.1021/ja055197f>.
- [59] R. Mittal, S. L. Chaplot, and H. Schober, *Applied Physics Letters* **95**, 201901 (2009), ISSN 00036951, URL <http://scitation.aip.org/content/aip/journal/apl/95/20/10.1063/1.3264963>.
- [60] A. L. Goodwin, M. Calleja, M. J. Conterio, M. T. Dove, J. S. O. Evans, D. A. Keen, L. Peters, and M. G. Tucker, *Science (New York, N.Y.)* **319**, 794 (2008), ISSN 1095-9203, URL http://apps.webofknowledge.com/full{_}record.do?product=UA{&}search{_}mode=GeneralSearch{&}qid=36{&}SID=2Fv4pNcCJ8qjseiAchW{&}page=1{&}doc=8.
- [61] A. Belsky, M. Hellenbrandt, V. L. Karen, and P. Luksch, *Acta Crystallographica Section B Structural Science* **58**, 364 (2002), ISSN 0108-7681, URL <http://scripts.iucr.org/cgi-bin/paper?S0108768102006948>.
- [62] The tight clustering for the X-X (a) bonds is due to the simple relation to structure - this bond distance is simply the a lattice parameter and can be determined from a single reflection and Bragg's law. The distances for the trifluoride show little scatter for the same reasons. The other internal distances require refinement of many allowed Bragg reflections over a larger angular range so show more scatter between reports.

- [63] This distance is much shorter than typical X-X distances obtained through searches of the international crystal database[61].