

Shear flow of non-Brownian rod-sphere mixtures near jamming

Carmine Anzivino,^{1,*} Christopher Ness,^{2,†} Amgad Salah Moussa,³ and Alessio Zaccone^{1,‡}

¹*Department of Physics “A. Pontremoli”, University of Milan, via Celoria 16, 20133 Milan, Italy*

²*School of Engineering, University of Edinburgh, Edinburgh, EH9 3JL, United Kingdom*

³*Syngenta AG, 4058 Basel, Switzerland*

Varying particle shape provides a route to rationally design the viscosity and jamming of complex fluids. The underlying physical mechanisms, however, remain unexplored. Here we use the discrete element method, taking particle contact and hydrodynamic lubrication into account, to unveil the shear rheology of mixtures of frictionless non-Brownian spheres and rod-like (spherocylinders) particles in the dense regime of packing fraction. By increasing the aspect ratio of the rods, while keeping constant either the total (rods plus spheres) particle packing fraction and the rod-sphere mixing ratio, the viscosity η of the mixture is observed to vary in a non-monotonical fashion. An initial decrease of viscosity with increasing aspect ratio is followed by a subsequent increase after that a minimum is reached when the rods have an aspect ratio of approximately 1.5. This minimum represents the absolute one, in the particular case of no spheres present in the system. A mechanistic interpretation of this discovery is provided in terms of packing and excluded-volume arguments.

Suspensions of non-Brownian, i. e. micron-sized, particles dispersed in a Newtonian fluid are ubiquitous in nature and have widespread application in industry, especially when considered in the *dense* regime where solid and fluid are mixed in roughly equal proportion [1–3]. These systems are well-known to undergo a *jamming* transition upon increasing the solid packing fraction ϕ towards a so-called jamming point ϕ_J [4]. While a dense non-Brownian suspension can flow under an external shear stress for $\phi < \phi_J$, the viscosity η of the suspension increases dramatically when $\phi \rightarrow \phi_J$, and the system eventually develops a solid-like behavior, with a finite yield stress, at $\phi \geq \phi_J$. Even if the mechanism underlying this flow arrest is not yet fully understood, the jamming transition is commonly believed to influence the shear rheology of dense non-Brownian suspensions in a crucial way [2, 5, 6].

When the dispersed micron-sized particles are frictionless and spherically-shaped, the viscosity η of the (resulting) suspension is empirically believed to exhibit a power law divergence $\eta(\phi) \approx (\phi_J - \phi)^{-\beta}$, where $\beta \approx 2$ and the jamming packing fraction ϕ_J coincides with the *random close packing* volume fraction, ϕ_{RCP} , of a collection of hard spheres, i. e. $\phi_J \approx \phi_{RCP} \approx 0.64$ [4]. This is in agreement with the picture, introduced for frictionless particles, according to which the jamming transition coincides with the isostatic threshold and the flow properties can be related to the geometry of the contact network [7].

Much research in the last decades has concerned how the maximum density reachable by a random packing of hard spheres is affected by a perturbation of the particle shape from spherical towards rod-like. Both Donev et al. [8] and Philipse and collaborators [9–11], have found the densest packing of a monodisperse collection of rod-like particles to exhibit an intriguing non-monotonic dependence of on the particle aspect ratio L/D . Upon increasing L/D , the packing density increases until a maximum

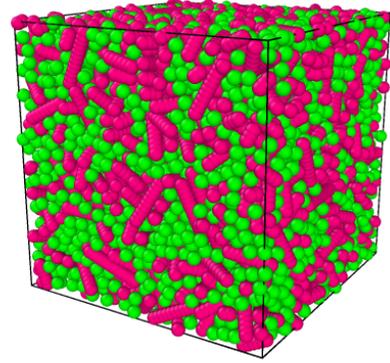


FIG. 1: Randomly packed rod-sphere mixture. The spheres have diameter a , while the rods (spherocylinders formed from glued spheres of diameter $D = a$) have aspect ratio $L/D = 5$.

is reached at approximately $L/D = 1.5$. Further particle elongation results in a decrease in packing volume fraction. Philipse and co-workers have discovered that the density maximum is also present in randomly packed rod-sphere mixtures [12–14]. Despite the large effort on optimal packings, a systematic investigation of how non-sphericity affects the functional dependence of the shear rheology of a non-Brownian suspension of frictionless particles has not yet been performed. Besides theoretical interest, a similar study could have crucial relevance in many applications where reducing the viscosity at fixed packing fraction is important, e.g. for optimal fluidization of complex fluids and for reducing energy consumption in stirred tanks and flow-reactors. Furthermore, this problem has a direct application to biology where optimal viscosity is achieved in crowded environments populated by non-Brownian particles such as the cell or blood

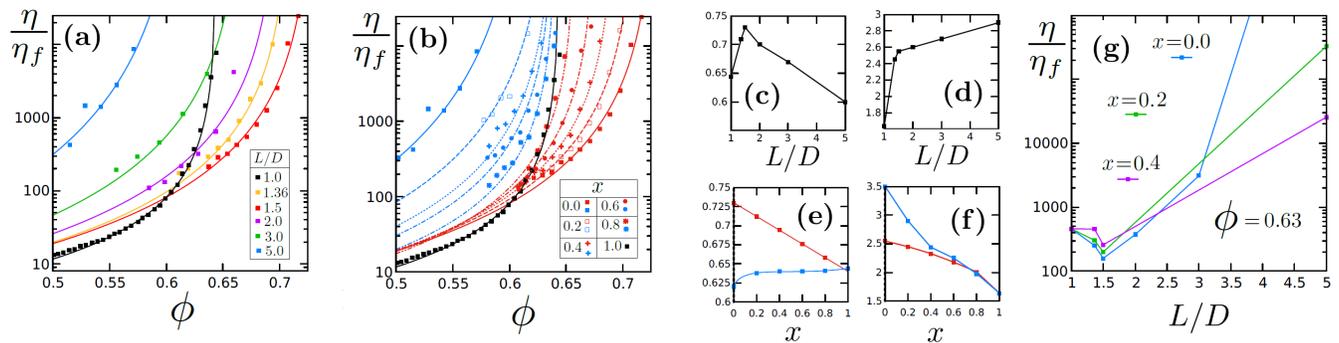


FIG. 2: Dimensionless (shear) viscosity η of a rod-sphere mixture as a function of the total (rods plus spheres) particle concentration, for several values of the rods aspect ratio L/D at fixed concentration of the spheres $x = 0$ (a), and for several values of x at fixed $L/D = 1.5$ and $L/D = 5$ (b). All data can be fitted to the KD relation (see Eq. (1) in the main text). The ϕ_J and β coefficients of the curves in Fig. (a) are plotted in Figs. (c) and (d), respectively. The ϕ_J and β coefficients of the curves in Fig. (b), i. e. at fixed $L/D = 1.5$ (red) and $L/D = 5$ (blue), are plotted in Figs. (e) and (f), respectively. In (g) η is plotted as a function of L/D at fixed $\phi = 0.63$ for several values of x .

plasma.

To fill this gap, in the present Letter we consider a sheared mixture of spheres and rods (spherocylinders), for which we compute the viscosity η as a function of either the aspect ratio L/D of the rods and the relative concentration x of the rods in the mixture. To this aim, we employ a recently introduced numerical method [15], which is based on an analogy between dense non-Brownian suspensions and dry granular matter. This analogy exploits the fact that, by contrast with dilute regimes where hydrodynamic interactions or lubrication forces are important, particle contact interactions and random packing dominate the dynamics in the dense regime near jamming [2].

Our main finding is that the effect of adding rods on the viscosity η of the rod-sphere mixture strongly depends, in a non-monotonic fashion, on the rods' aspect ratio L/D . Adding rods to frictionless spheres reduces the viscosity of the suspension as long as the rods have aspect ratio $L/D < 3$, with a minimum value of viscosity η found at $L/D = 1.5$. When rods with $L/D > 3$ are added, instead, the viscosity dramatically increases.

We employ a recently introduced [15] simulation technique based on LAMMPS, which has been widely used in the past years to perform numerical rheological measurements of frictionless and frictional spheres under simple and extensional flows. While sharing many details with traditional molecular dynamics, the method is more commonly labelled as “discrete element method” due to its similarity to approaches used in granular physics (specifically the absence of thermal forces and the inclusion of particle-particle friction). To obtain a (single) numerical measurement, a multiple-step approach is followed. First a set of non-overlapping particles of desired shape and size distribution are initialised in a simulation box. For a fixed particle shape, the packing fraction ϕ can be set by

fixing the number of particles and the volume of the box. The box is then subjected to an external deformation, which results in a background fluid velocity gradient and causes the particles to interact through a set of pairwise hydrodynamic and contact interactions. These include Stokes drag, pairwise lubrication and pairwise contact. The trajectory of each particle is then evaluated over a series of timesteps by numerically solving Newton's second law, and the bulk stress tensor Σ is computed from the interaction forces and particle positions. The rheology of the system can be fully characterized by computing Σ as a function of deformation rate $E \equiv \frac{1}{2}(\nabla \mathbf{u}^\infty + \nabla \mathbf{u}^{\infty T})$ and the packing fraction ϕ .

In this Letter, we consider a binary mixture of N_S spheres and N_R rods, placed randomly in a simulation cubic box of side L^B under a uniform flow with imposed deformation rate. As showed in Fig. 1, the spheres have diameter a and the rods are composed of glued spheres resulting in an aspect ratio $L/D \geq 1$. For the sake of simplicity we assume $D = a$. The total packing fraction of non-Brownian suspended particles is $\phi = \phi_S + \phi_R$, where $\phi_S = (4/3)\pi a^3 \rho_S$ and $\phi_R = (4/3)\pi a^3 \rho_R + \pi a^2 \rho_R L$ are the packing fraction of the spheres and the rods, respectively. Moreover $x \equiv \phi_S / \phi$ is the relative component of spheres in the mixture. Of course $\phi_R / \phi = 1 - x$.

To ensure bulk conditions, we assume $L^B \gg \sigma$ and $L^B \gg L$. We assume the spheres and the rods to be buoyant and to have the same density ρ , the same particle normal stiffness k_n and to be frictionless (i.e. they have friction coefficient $\mu = 0$). We assume the background fluid to be characterized by a velocity field \mathbf{u}^∞ with gradient (a tensor) $\nabla \mathbf{u}^\infty$, and to be applied for a time t . Here we consider suspensions under the action of a simple shear flow directed along the x axis with gradient along the y axis. Thus by indicating with $\dot{\gamma}$ the shear rate, we have $\mathbf{u}^\infty = (\dot{\gamma}y, 0, 0)$ such that $\dot{\gamma} = \partial u_x / \partial y$. To

simulate simple shear we use a triclinic periodic box with a tilt length L_{xy}^B that is incrementally increased linearly in time as $L_{xy}^B(t) = L_{xy}^B(t_0) + L_y^B \dot{\gamma} t$, giving a deformation that is entirely equivalent to that obtained using a Lee-Edwards boundary conditions. Under these conditions, the viscosity of the mixture can be written as $\eta = \Sigma_{xy}/(\dot{\gamma}\eta_f)$, where Σ_{xy} is the xy component of Σ .

By using the method described above, we compute the viscosity η of a mixture of spheres and rods, for several combinations of the total (spheres plus rods) particle packing fraction $\phi \equiv \phi_S + \phi_R$, the relative concentration of the spheres $x (\equiv \phi_S/\phi)$, and the aspect ratio of the rods L/D . In all cases, both spheres and spherocylinders form an amorphous packing with no crystal or liquid-crystalline ordering like nematic or columnar phase, something that we checked also quantitatively by means of the standard nematic order parameter in our simulations.

We start from the case $x = 0$, corresponding to the absence of any sphere in the mixture that consequently reduces to a monodisperse ensemble of rod-like particles (for which $\phi_S = 0$ and $\phi \equiv \phi_R$, respectively). For several fixed values of $L/D \in [1, 5]$, we plot the viscosity η of this system as a function of ϕ , with symbols in Fig. 2(a). In all cases, we express η in units of the viscosity of the hosting fluid η_f . In the figure, black points represent the limiting case $L/D = 1$, which corresponds to a monodisperse suspension of non-Brownian frictionless spheres. As stated, the rheology of this model system has attracted a great deal of attention in the past years and will be used as a reference state throughout this Letter. The black points in Fig. 2(a) can be fitted to the widely used Krieger-Dougherty (KD) relation

$$\eta/\eta_f = \alpha(1 - \phi/\phi_J)^{-\beta}, \quad (1)$$

with fitting parameters $\alpha = 1$, $\beta = 1.6$ and $\phi_J = 0.644$, respectively. Moreover we show that, besides the case $L/D = 1$, all the numerical data plotted in Fig. 2(a) can be fitted to the KD relation (1), once the values of β and ϕ_J are properly fitted. All the fitted curves are plotted with full lines in Fig. 2(a) and Fig. 2(b). The values of β and ϕ_J are plotted as a function of L/D in Figs. 2(c) and 2(d), respectively. In agreement with Donev et al. [8], we find ϕ_J to vary in a non-monotonic fashion as a function of L/D , with a maximum reached at $L/D = 1.5$.

Figure 2(a) allows us to extract the functional dependence of the viscosity η of a monodisperse system of rods on the rods aspect ratio L/D , at fixed values of the total particle packing fraction ϕ . In Fig. 2(f) we use blue points to plot η as a function of L/D , for fixed $\phi = 0.63$ and $x = 0$. We observe η to monotonically decrease upon increasing L/D . However, after a minimum is reached at $L/D = 1.5$, the viscosity η starts to monotonically increase as a function of L/D . This crucial result establishes that, analogously to what happens for the static

random close packing fraction with no flow [8–11, 13], also the viscosity of a monodisperse ensemble of (frictionless) rods can be optimized when the rods have aspect ratio $L/D = 1.5$.

After having fully explored the case $x = 0$, corresponding (for $L/D > 1$) to the absence of spheres in the system, we consider a more complex situation in which both rods and spheres are present in the sample, i. e. we consider the case $x \neq 0$. As for the case of monodisperse rods, also for rod-sphere binary mixtures it results convenient to use a collection of frictionless spheres as a reference state to orient our investigation. The latter situation can be obtained in two distinct ways: either (i) choosing the value of spheres concentration $x = 1$ independently of the aspect ratio of the rods, or (ii) fixing $L/D = 1$ independently of the spheres concentration x . In both cases, the functional dependence of the viscosity η on the packing fraction ϕ is given by the black curve depicted in Fig. 2(a). To explore other non-trivial situations, while keeping the aspect ratio L/D of the rods fixed, we compute the viscosity η of the mixture as a function of ϕ , for several values of $x \in [0, 1]$. We repeat this protocol for (almost) the same values of aspect ratio considered in Fig. 2(a), for $L/D \in [1, 5]$. The results of this analysis could be already guessed from data reported in Fig. 2(b). Each of the curve plotted in this figure, indeed, represents the case $x = 0$ at fixed L/D . The black curve, instead, represents the case $x = 1$ for any value of L/D . It follows that all the “colored” curves must collapse on the black one by increasing the relative concentration x of the spheres in the mixture.

So, by adding rod-like particles to spherical ones, the existence of two different opposite behaviors can be detected depending on L/D . While addition of “short” rods, having $L/D \leq 3$ results in a decrease of the viscosity of the system at fixed ϕ , addition of “long” rods, having $L/D > 3$ results in an increase of the viscosity of the mixture at fixed ϕ . This scenario is depicted in Fig. 2(b), illustratively for the case of rods with aspect ratio $L/D = 1.5$ and $L/D = 5$, respectively.

This result can be interpreted in terms of the average number of permanent contacts per particle required for a rod-sphere mixture to be mechanically stable at jamming. Again it is instructive to start from a purely rod-like system, i. e. from the case $x = 0$.

As it is well-known [8, 16], the average contact number z in a monodisperse system of jammed rods having aspect ratio L/D increases from the value $z = 6$ at $L/D = 1$ until a value $z \approx 10$ is reached at approximately $L/D = 1.5$ and then remains constant upon further increment of L/D . As argued by Donev et al. [8], the way z varies as a function of L/D provides an explanation for the non-monotonic variation (shown in Fig. 2(c)) of ϕ_J on L/D , which is confirmed here for jamming under shear flow. More specifically, the number of degrees of freedom per particle in the system increases upon increasing L/D

as rotational degrees of freedom add to the translational ones when rods replace spheres [17]. The increase in the number of degrees of freedom per particle results in the increase of the number of particle contacts z required to mechanically stabilize the packing. In turn, an increase of z , at the onset of mechanical stability, is consequently associated with an increase of the corresponding ϕ_J [16, 18]. After a certain threshold ($L/D \approx 1.5$) is reached, the number of degrees of freedom does not depend on L/D anymore, then z remains constant after the value $z = 10$ has been reached. In this situation, the decrease of ϕ_J for markedly aspherical particles in orientationally disordered packings is explained by strong excluded-volume effects à la Onsager [19].

A quantitative explanation of the dependence (observed in this Letter for the first time) of the viscosity η of the system on L/D follows from ϕ_J being the point at which η diverges (from Eq. (1) and as numerically shown in the above). In particular, in the first regime where ϕ_J increases with increasing L/D , the viscosity decreases because the viscosity is always lower when ϕ_J is larger, cfr. also Eq. (1). Conversely, when ϕ_J decreases with increasing L/D , for the reasons explained above, then the viscosity increases with further increasing L/D .

To summarize, for a system of pure rods there are two different mechanisms which determine the location of the jamming point ϕ_J as a function of the aspect ratio L/D . As for short rods excluded-volume effects à la Onsager are not dominant, the increase of ϕ_J as a function of L/D is caused by the increase of z due to the emergence of additional rotational degrees of freedom. Excluded-volume effects à la Onsager instead dominate in orientationally disordered packings of long rods [16], from which a decrease of ϕ_J in the region $L/D \geq 1.5$ results. The trend of ϕ_J then determines the trend of the viscosity versus L/D , which will be opposite, i.e. anti-correlated, to that of ϕ_J , according to Eq. (1).

This scenario can be generalized to the case of a rod-sphere mixture. When spheres are added to a system of randomly jammed long rods, they mainly act as to fill the large voids between the rods. As a consequence, the jamming point ϕ_J , at which the viscosity diverges, increases upon increasing the fraction of spheres, and the viscosity decreases. By contrast, when spheres are added to a system of randomly jammed short rods with $L/D \leq 1.5$, they mainly act as to reduce the number of degrees of freedoms in the system, by effectively “killing” rotational degrees of freedom. As a consequence, the jamming point ϕ_J decreases with the addition of spheres, in this regime, and the viscosity increases.

In summary, we have investigated the sheared rheology of a binary mixture of spheres and rods (spherocylinders) by means of the discrete element method. Our main finding is that the effect of adding rods on the viscosity η of the mixture strongly depends, in a non-monotonic fashion, on the rods’ aspect ratio L/D .

Adding rods to frictionless spheres reduces the viscosity of the suspension as long as the rods have aspect ratio $L/D < 3$, with a minimum value of zero-shear viscosity η found at $L/D = 1.5$. When rods with $L/D > 3$ are added, instead, the viscosity dramatically increases. Our findings could have crucial relevance in application where reducing the viscosity at fixed packing fraction is important.

* Electronic mail: carmine.anzivino@unimi.it,

† Electronic mail: chris.ness@ed.ac.uk,

‡ Electronic mail: alessio.zaccone@unimi.it

- [1] E. Guazzelli and O. Pouliquen, *Journal of Fluid Mechanics* **852**, P1 (2018).
- [2] C. Ness, R. Seto, and R. Mari, *Annual Review of Condensed Matter Physics* **13**, 97 (2022), <https://doi.org/10.1146/annurev-conmatphys-031620-105938>, URL <https://doi.org/10.1146/annurev-conmatphys-031620-105938>.
- [3] D. Pan, Y. Wang, H. Yoshino, J. Zhang, and Y. Jin, *A review on shear jamming* (2023), 2306.13416.
- [4] P. Olsson and S. Teitel, *Phys. Rev. Lett.* **99**, 178001 (2007).
- [5] C. Heussinger and J.-L. Barrat, *Phys. Rev. Lett.* **102**, 218303 (2009).
- [6] B. Andreotti, J.-L. Barrat, and C. Heussinger, *Phys. Rev. Lett.* **109**, 105901 (2012).
- [7] E. Lerner, G. Düring, and M. Wyart, *Proceedings of the National Academy of Sciences* **109**, 4798 (2012).
- [8] A. Donev, I. Cisse, D. Sachs, E. A. Variano, F. H. Stillinger, R. Connelly, S. Torquato, and P. M. Chaikin, *Science* **303**, 990 (2004).
- [9] S. R. Williams and A. P. Philipse, *Phys. Rev. E* **67**, 051301 (2003).
- [10] A. V. Kyrylyuk and A. P. Philipse, *physica status solidi (a)* **208**, 2299 (2011).
- [11] S. Sacanna, L. Rossi, A. Wouterse, and A. P. Philipse, *Journal of Physics: Condensed Matter* **19**, 376108 (2007).
- [12] A. V. Kyrylyuk, A. Wouterse, and A. P. Philipse, *AIP Conference Proceedings* **1145**, 211 (2009).
- [13] A. V. Kyrylyuk, A. Wouterse, and A. P. Philipse, in *Trends in Colloid and Interface Science XXIII* (Springer Berlin Heidelberg, Berlin, Heidelberg, 2010), pp. 29–33.
- [14] A. V. Kyrylyuk, M. Anne van de Haar, L. Rossi, A. Wouterse, and A. P. Philipse, *Soft Matter* **7**, 1671 (2011).
- [15] O. Cheal and C. Ness, *Journal of Rheology* **62**, 501 (2018), ISSN 0148-6055.
- [16] S. Rocks and R. S. Hoy, *Soft Matter* **19**, 5701 (2023), URL <http://dx.doi.org/10.1039/D3SM00705G>.
- [17] A. Zaccone, *Theory of Disordered Solids* (Springer, Heidelberg, 2023).
- [18] A. Zaccone, *Phys. Rev. Lett.* **128**, 028002 (2022).
- [19] L. Onsager, *Annals of the New York Academy of Sciences* **51**, 627 (1949), <https://nyaspubs.onlinelibrary.wiley.com/doi/pdf/10.1111/j.1749-6632.1949.tb27296.x>, URL <https://nyaspubs.onlinelibrary.wiley.com/doi/abs/10.1111/j.1749-6632.1949.tb27296.x>.

1749-6632.1949.tb27296.x.

- [20] C. Anzivino, M. Casiulis, T. Zhang, A. S. Moussa, S. Martiniani, and A. Zaccone, *The Journal of Chemi-*

cal Physics **158** (2023), ISSN 0021-9606, 044901.