

Generic statistical and spatial properties of low-energy excitations in computer glasses

Edan Lerner¹ and Eran Bouchbinder²

¹*Institute of Theoretical Physics, University of Amsterdam,
Science Park 904, 1098 XH Amsterdam, the Netherlands*

²*Chemical and Biological Physics Department, Weizmann Institute of Science, Rehovot 7610001, Israel*

Following advances initiated almost four decades ago (e.g., [1]), it is now well established that structural glasses feature quasilocalized, nonphononic low-energy (soft) excitations. These are manifested at low frequencies ω in the vibrational density of states (VDoS) $\mathcal{D}(\omega)$ of glasses, once hybridization with phonons is properly accounted for [2–4], taking the form $\mathcal{D}(\omega) \sim \omega^\beta$ for $\omega \rightarrow 0$. The nature and statistical properties of these nonphononic excitations are currently extensively investigated. A large body of evidence suggests that $\beta = 4$, independently of glass composition, interatomic interactions, thermal history and space dimensionality [5].

Schirmacher et al. [6] aim at addressing the nature of nonphononic excitations in computer glasses and make several claims, the most notable ones are listed here:

- (i) The nonphononic (non-Debye) VDoS of computer glasses quenched from high parent-temperature liquid states follows $\mathcal{D}(\omega) \sim \omega^2$.
- (ii) Under the above-stated conditions, the VDoS is populated by random-matrix-like excitations that are spatially extended [7], which Schirmacher et al. term ‘type-I’ nonphononic excitations.
- (iii) The nonphononic VDoS of computer glasses quenched from low parent temperatures (‘more stable’ in the terminology of Schirmacher et al.) is populated by other excitations termed ‘type-II’ excitations, whose VDoS follow $\mathcal{D}(\omega) \sim \omega^\beta$. Here, $\beta = 5 - 2\alpha$, with α being the scaling exponent characterizing the distribution of small local stresses σ , i.e., $p(\sigma) \sim \sigma^{-\alpha}$. Moreover, the power-law exponent β is also claimed to depend on the *tapering function* of the interaction potential based on the relation $\alpha = 1 - 1/m$ (valid for purely repulsive potentials). Here, m corresponds to the number of derivatives that are continuous at a cutoff distance at which the interaction is tailored to vanish. That is, α can be varied by controlling m in purely repulsive glasses, and consequently it is claimed that $\beta = 3 + 2/m$. Finally, it is further argued that computer glasses employing attractive pairwise interactions correspond to $m = 1$, i.e., should feature $\beta = 5$.
- (iv) The so-called ‘type-II’ excitations feature ‘non-irrotational’, vortex-like displacement fields.

Here, we demonstrate that assertions (i)-(iv) above are not generally valid. This is achieved by providing counterexamples emerging from careful computer simulations and based on analyzing data presented by Schirmacher et al. [6].

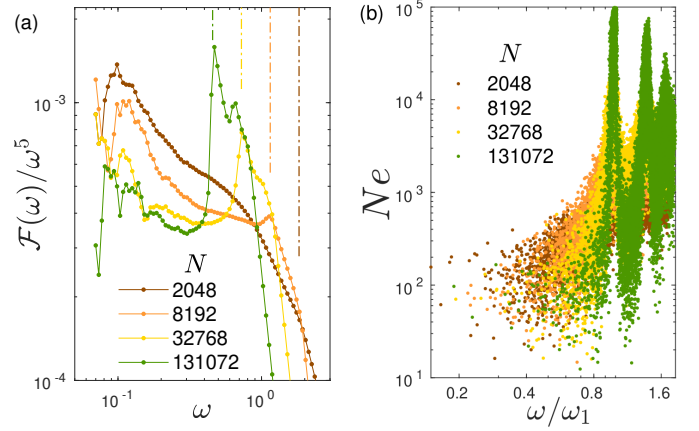


FIG. 1. (a) $\mathcal{F}(\omega)/\omega^5$ for IPL glasses of size N (see legend) quenched instantaneously from high-temperature equilibrium states, see text for discussion. The vertical dashed lines mark the lowest phonon frequency ω_1 for each N . (b) The scaled participation ratio Ne (see text for definition) scatter-plotted against ω/ω_1 .

We first address claims (i)-(ii). To this aim, we prepared computer glasses quenched from high parent-temperature liquid states using a canonical 3D computer glass-former, known as the inverse-power-law (IPL) model, see details in [8]. The system is first equilibrated at a high temperature of $T = 2.0$ (in simulation units [8]), which is roughly 4 times larger than the glass transition temperature, followed by an instantaneous quench to zero temperature by minimizing the potential energy using a standard conjugate gradient algorithm. We then calculated the low-frequency spectrum of ensembles of glasses with different system sizes N , and measured the participation ratio $e \equiv [N \sum_i (\Psi_i \cdot \Psi_i)^2]^{-1}$ (i denotes particle indices) of each individual vibrational mode Ψ .

In Fig. 1a, we present the cumulative VDoS $\mathcal{F}(\omega) \equiv \int_0^\omega \mathcal{D}(\omega') d\omega'$, rescaled by ω^5 , for various N 's (see legend). If the nonphononic spectrum follows $\mathcal{D}(\omega) \sim \omega^4$, one expects $\mathcal{F}(\omega)/\omega^5$ to be constant as $\omega \rightarrow 0$ (below the first phonon band [2, 5], marked in the figure). It is observed that deviations from the universal quartic law (i.e., from a constant in this presentation) appear to be larger for smaller N . Consequently, claim (i) simply reflects finite-size effects. In Fig. 1b, we scatter-plot $Ne(\omega)$ for the glasses used in panel (a). For localized modes, one has $Ne \sim \mathcal{O}(100)$ independently of N , for $\omega \rightarrow 0$ [9], as indeed observed, in contrast to claim (ii) that low-frequency nonphononic modes in glasses quenched from high parent temperatures are spatially extended (and hence that $Ne \sim \mathcal{O}(N)$).

We next address claims (iii)-(iv). First, we employ the same IPL model as above (with $N \approx 8000$ particles), but this time generate glassy states corresponding to low parent temperatures ('more stable' glasses) by performing a continuous quench at a rate $\dot{T} = 10^{-3}$ (in simulational units [8]) and set $m=6$ in the tapering function. According to claim (iii), one expects $\mathcal{D}(\omega) \sim \omega^{10/3}$. In contrast, we show in Fig. 2a that the nonphononic VDoS follows the universal quartic scaling, $\mathcal{D}(\omega) \sim \omega^4$, in agreement with a large body of existing evidence [5].

Second, we consider a bead-spring model of glass elasticity (see [10] for details) that is regarded as a 'stable glass' [11], in which there is no interaction cutoff and beads experience both repulsive and attractive forces. According to claim (iii), the latter corresponds to $m=1$ and hence one expects $\mathcal{D}(\omega) \sim \omega^5$. However, we show in Fig. 2a that also here $\mathcal{D}(\omega) \sim \omega^4$.

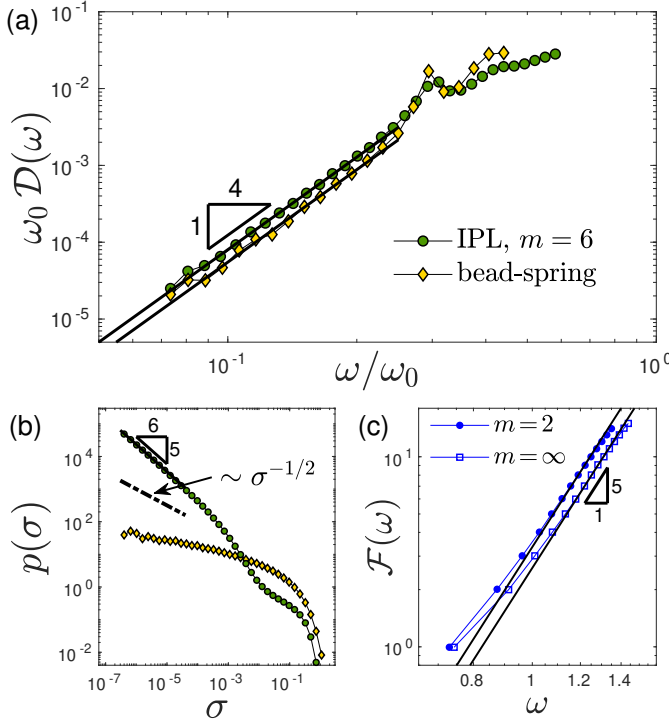


FIG. 2. (a) $\mathcal{D}(\omega)$ for the IPL (circles) and bead-spring (diamonds) models (see text), corresponding to $m=6$ and $m=1$, respectively. Here, $\omega_0 \equiv c_s/a_0$, where a_0 is an interatomic distance. (b) $p(\sigma)$, where $\sigma \equiv \bar{\sigma}/G$ (G is the shear modulus), measured in the bead-spring and IPL models, see legend of panel (a). The dash-dotted line corresponds to $p(\sigma) \sim \sigma^{-1/2}$, see text for discussion. (c) Digitized data from Fig. 4b of [6] for two cumulative VDoSs $\mathcal{F}(\omega) \equiv \int_0^\omega \mathcal{D}(\omega') d\omega'$, both consistent with $\mathcal{D}(\omega) \sim \omega^4$ (black lines), see text for discussion.

Since $\beta=4$ in both datasets in Fig. 2a, the relation $\beta=5-2\alpha$ in claim (iii) suggests that the distribution of weak local stresses σ should follow $p(\sigma) \sim \sigma^{-1/2}$. In Fig. 2b, we plot $p(\sigma)$ for the two datasets presented in Fig. 2a, revealing that none of them follow $p(\sigma) \sim \sigma^{-1/2}$. Note that for the IPL model we find $p(\sigma) \sim \sigma^{-5/6}$ at small σ , as anticipated by the relation $\alpha=1-1/m$ with

$m=6$ [6], yet the $\beta=5-2\alpha$ prediction is strongly violated.

In an attempt to support claim (iii), Fig. 4 in [6] presents results of 3D computer simulations with $N=1000$ particles; no tests for finite-size effects were reported, despite that it has been repeatedly shown [12–15] that finite-size deviations from the $\sim \omega^4$ law generally exist, cf. Fig. 1a. These finite-size effects can persist up to $N \sim 10^5$ [12], and are more pronounced in systems cooled quickly from higher equilibrium parent temperatures [13, 15]. In Fig. 2c, we show digitized two dataset (for two m values, see legend) from Fig. 4b of [6] for the cumulative VDoS $\mathcal{F}(\omega)$; in [6] it is argued that the $m=\infty$ dataset features $\beta=3$ (thus $\mathcal{F}(\omega) \sim \omega^4$). However, we show here that both the $m=2$ and $m=\infty$ dataset are consistent with $\mathcal{F}(\omega) \sim \omega^5$ (black lines). The deviations seen in the lowest frequencies are known finite-size effects [14, 15], as also shown in Fig. 1a.

In [6], the ‘non-irrotational’, vortex-like real-space structure of ‘type-II’ nonphononic excitations, i.e., claim (iv) above, is extensively discussed. Yet — and unfortunately — the actual spatial structures are not presented therein. However, an example [16] is presented in Fig. 1 of the Peer Review File of [6], which is reproduced here in Fig. 3a. Such vortex-like displacement fields generally emerge from a superposition of *phonons*, as demonstrated in Fig. 3b-d. The same vortex-like patterns are observed in vibrational excitations up to and in the vicinity of the boson-peak frequency, as demonstrated recently in [17]. Consequently, we strongly suspect that the object claimed in [6] to be a ‘non-irrotational’ *nonphononic* excitation is, in fact, of *phononic* nature and hence that claim (iv) is a serious misinterpretation.

To conclude, we showed that the nonphononic VDoS of computer glasses follows the universal $\sim \omega^4$ quartic law, independently of the form of the tapering function of the pairwise potential, of glass formation history, and of the form of the distribution at local, small stresses — all at odds with the claims of [6]. We also showed that nonphononic excitations in glasses quenched from high parent temperatures are (quasi)localized [9], and that the vortex-like patterns seen in low-frequency modes naturally correspond to a superpositions of phonons, again at odds with the claims of [6].

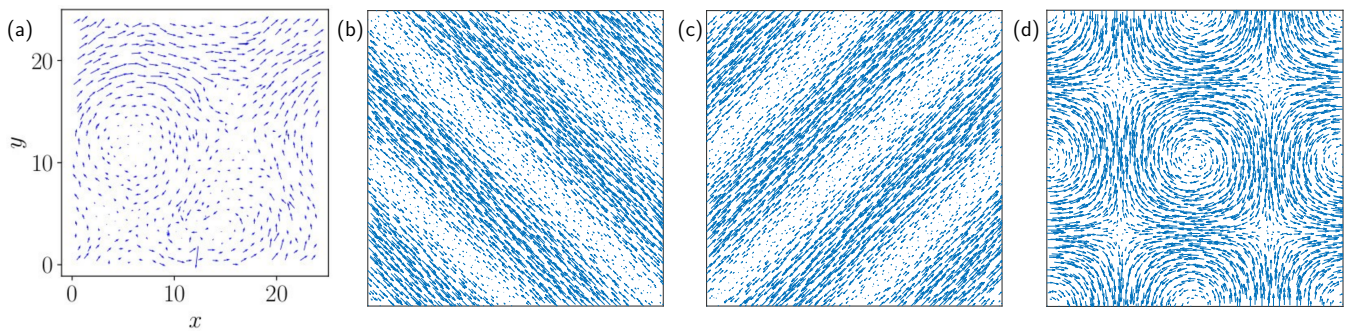


FIG. 3. (a) Reproduction of Fig. 1 of the [Peer Review File](#) of [6] (see also [16]), showing a 2D slice of a ‘Type-II’ nonphononic excitation in a computer glass. Panels (b) and (c) show 2D transverse phonons of identical wavelength, but orthogonal wave-vectors. The superposition of these phonons is shown in panel (d). See text for discussion.

Data availability All data generated or analysed during this study are included in the published article. All relevant processed data are available from the authors upon reasonable request.

Acknowledgements

We thank Francesco Zamponi and Walter Schirmacher for open and useful discussions. E.B. is supported by the Ben May Center for Chemical Theory and Computation,

and the Harold Perlman Family.

Author contributions

Both authors conceived of the project. E.L. performed all simulations, analyzed the results and generated the figure. Both authors wrote the final manuscript.

Competing interests

The authors declare no competing interests.

-
- [1] M. Il'in, V. Karpov, and D. Parshin, Parameters of soft atomic potentials in glasses, *Zh. Eksp. Teor. Fiz.* **92**, 291 (1987).
 - [2] E. Bouchbinder and E. Lerner, Universal disorder-induced broadening of phonon bands: from disordered lattices to glasses, *New J. Phys.* **20**, 073022 (2018).
 - [3] E. Lerner, A. Moriel, and E. Bouchbinder, Enumerating low-frequency nonphononic vibrations in computer glasses, *arXiv preprint arXiv:2404.12735* (2024).
 - [4] A. Moriel, E. Lerner, and E. Bouchbinder, Experimental evidence for the ω^4 tail of the nonphononic spectra of glasses, *arXiv preprint arXiv:2404.16996* (2024).
 - [5] E. Lerner and E. Bouchbinder, Low-energy quasilocalized excitations in structural glasses, *J. Chem. Phys.* **155**, 200901 (2021).
 - [6] W. Schirmacher, M. Paoluzzi, F. C. Mocanu, D. Khomenko, G. Szamel, F. Zamponi, and G. Ruocco, The nature of non-phononic excitations in disordered systems, *Nat. Commun.* **15**, 3107 (2024).
 - [7] Y. M. Beltukov and D. A. Parshin, Theory of sparse random matrices and vibrational spectra of amorphous solids, *Phys. Solid State* **53**, 151 (2011).
 - [8] E. Lerner and E. Bouchbinder, A characteristic energy scale in glasses, *J. Chem. Phys.* **148**, 214502 (2018).
 - [9] Nonphononic modes were shown [5] to be *quasilocalized*, i.e., they feature a disordered core of about 100 particles (cf. Fig. 1), decorated by far fields that decay as r^{-2} at distance r from the core.
 - [10] T. Pettinari, G. Düring, and E. Lerner, Elasticity of self-organized frustrated disordered spring networks, *arXiv preprint arXiv:2401.11996* (2024).
 - [11] We study bead-spring networks with mean connectivity $z = 6.2$ and structural-frustration parameter $w = 0.2$ (see [10] for details), for which we measure the mechanical disorder quantifier $\chi \simeq 2.1$, which corresponds to stable computer glasses, see [18].
 - [12] E. Lerner, Finite-size effects in the nonphononic density of states in computer glasses, *Phys. Rev. E* **101**, 032120 (2020).
 - [13] E. Lerner and E. Bouchbinder, Nonphononic spectrum of two-dimensional structural glasses, *J. Chem. Phys.* **157**, 166101 (2022).
 - [14] D. Richard, G. Kapteijns, and E. Lerner, Detecting low-energy quasilocalized excitations in computer glasses, *Phys. Rev. E* **108**, 044124 (2023).
 - [15] D. Xu, S. Zhang, H. Tong, L. Wang, and N. Xu, Low-frequency vibrational density of states of ordinary and ultra-stable glasses, *Nat. Comm.* **15**, 1424 (2024).
 - [16] Plotted is a 2D slice of the 12th vibrational mode (ordered by frequency), which is almost always a (hybridized) phonon in computer glasses – since the lowest-frequency phonon-band consists of 12 modes.
 - [17] E. Lerner and E. Bouchbinder, Boson-peak vibrational modes in glasses feature hybridized phononic and quasilocalized excitations, *J. Chem. Phys.* **158**, 194503 (2023).
 - [18] K. González-López, E. Bouchbinder, and E. Lerner, Variability of mesoscopic mechanical disorder in disordered solids, *J. Non-Cryst. Solids* **604**, 122137 (2023).