

# Mechanics of elliptical JKR-type adhesive contact

Andrea Giudici, Dominic Vella, Ian Griffiths

Mathematical Institute, University of Oxford, Woodstock Rd, Oxford, OX2 6GG,  
UK

E-mail: giudici@maths.ox.ac.uk

## Abstract.

The classic Johnson Kendall Roberts (JKR) theory describes the short-ranged adhesive contact of elastic bodies, but is only valid for axisymmetric contact. A theory for non-axisymmetric contact, which relies on approximating the contact region as an ellipse, was proposed by Johnson and Greenwood (JG). The theory includes the effects of adhesion via Griffith's criterion applied *only* at the semi-major and semi-minor axes of the contact ellipse. Although JG's work is in good agreement with numerical and experimental results for quasi-circular contacts, the agreement worsens as the eccentricity of the contact region increases. In this paper, we show that including the effects of adhesion by instead minimizing the sum of elastic and surface energy yields results that are in excellent agreement with previous numerical simulations over the full range of contact eccentricities.

## 1. Introduction

The classic Johnson Kendall Roberts (JKR) theory describes the adhesive contact between elastic bodies [1]. It accounts for adhesive interactions via surface energy and is thus only appropriate when the interaction length is small compared to other length-scales in the problem. Nevertheless, short-range interactions are common, making the JKR theory extremely useful. For example, JKR is used in the study of adhesion in microelectromechanical systems (MEMS) [2, 3] and biological tissues [4, 5, 6].


Despite its success, however, the JKR theory only describes axisymmetric contact, and thus cannot describe the general adhesive contact between two bodies — for example the contact between a cylinder and a sphere. To resolve this limitation, Johnson and Greenwood (JG) [7] proposed a JKR-type theory (i.e. for short-range interactions) valid for non-axisymmetric contact. To do so, they noted that, for small-displacements and in the absence of adhesion, the general problem may be reduced to finding the contact region between an ellipsoid and an elastic half-space [8]. Since analytical results exist for an elliptical contact region, JG assumed that the contact

region remains elliptical even in the presence of adhesion and is entirely specified by the values of the semi-major and semi-minor axes (giving only two degrees of freedom for the solution). To determine these, they then applied Griffith's criterion [9] at the boundary of the semi-major and semi-minor axis of the ellipse including the effects of adhesion. This allowed them to obtain analytical results that describe the evolution of the indentation, size and shape of the contact ellipse as a function of the applied load.

Although JG's theory is in excellent agreement with numerics and simulations in the case of weakly elliptical contacts (small eccentricity), numerical studies have shown that the theory underestimates the magnitude of the pull-off force as well as the size of the contact region when the contact ellipse becomes slender (eccentricity close to one) [10, 11]. One may attribute the relatively large error to the incorrect assumption that the contact region remains elliptical even in the presence of adhesion — something that was well understood by the authors and was later confirmed both numerically and experimentally [10, 11, 12]. However, the contact region is very close to being elliptical, suggesting that this erroneous assumption may not entirely account for the disagreement.

Alternative theories and extensions have been proposed to improve upon JG's work. Zini *et al.* [13] derived a theory using the double-Hertz model [14], in which the indenting and adhesive Hertzian pressures act on elliptical domains of different size (but with the same eccentricity), to account for the effects of long-range interactions. However, despite this being a useful model, both the authors of the paper and Greenwood [15] have expressed worry about the validity of some of the assumptions made. In particular, the authors assume that the eccentricity of the contact region is independent of the load, which appears to be incorrect even for long-ranged interactions. An alternative approach has been proposed by Li and Popov [10], who obtained an approximation for the adhesive elliptical contact by fitting a curve to their numerical simulation data. Their work is useful, but their model lacks a formal physical basis and does not predict the change of eccentricity as a function of load — something important for applications.

In this paper, we revisit the problem of elliptical adhesive contact maintaining JG's assumption of an elliptical contact region. However, instead of applying Griffith's criterion at isolated points, we introduce the effect of adhesion by minimizing the sum of the elastic and surface energy of the system. This approach yields results that are in excellent agreement with numerical simulations at various values of eccentricity. Our work indicates that the error in JG's theory arises mostly from the choice of satisfying Griffith's criterion locally, and not on the assumption of an elliptical contact *per se*. In particular, JG's approach leads them to overestimate the magnitude of the stress singularity at the boundary of contact, thereby underestimating the contact size and the magnitude of the pull-off force.

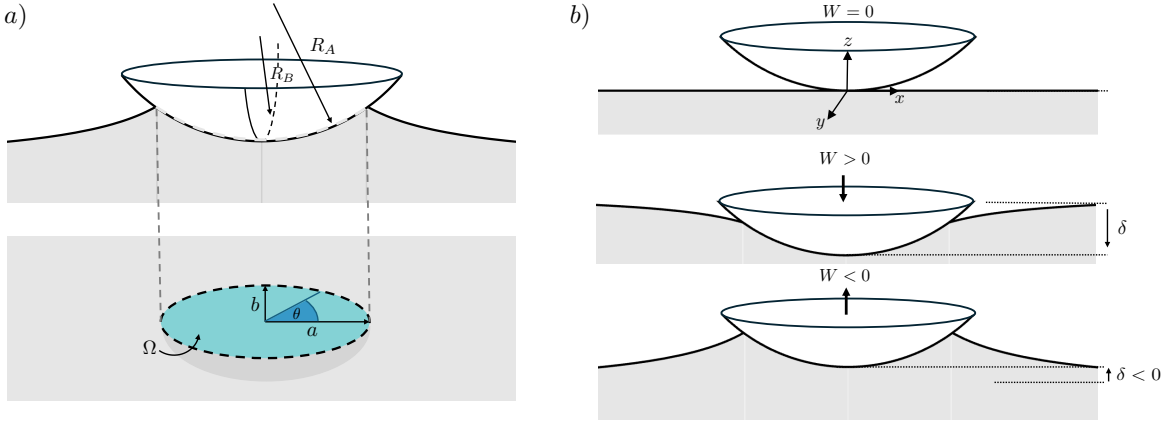

**Figure 1.** a) A sketch of the contact geometry, showing the radii of curvature of the ellipsoid and the contact region. b) Sketch of the hysteric behaviour of a rigid ellipsoid as it is loaded and unloaded in contact with an elastic half-space. In the top panel, the ellipsoid comes in contact with the half-space (top) at zero load. It then indents the half-space as it is loaded (middle panel) with depth  $\delta$ . Finally, even with negative loads the contact is maintained due to adhesive forces, and negative indentations are obtained before the bodies detach (at the pull-off force,  $W_{\text{pull off}}$ ).

## 2. Theory

We study the adhesive contact between two smooth elastic bodies. When the contact region between the two bodies is small compared to their radii of curvature — i.e. the strains and displacements are small — the problem is equivalent to studying the contact between a stiff (undeformable) ellipsoid coming into adhesive contact with an elastic half-space with given effective stiffness [8]. Therefore, without loss of generality, we follow JG’s approach and consider an ellipsoid with radii of curvature  $R_A$  and  $R_B < R_A$  that indents an elastic half-space whose surface lies on the  $x$ - $y$  plane. (Coordinates are chosen such that contact first occurs at the point  $x = y = z = 0$ .) The contact region, which we denote  $\Omega$ , is assumed to be elliptical with semi-major and semi-minor axes  $a$  and  $b$ , respectively. A sketch of the contact geometry is shown in figure 1(a). The load required to push the ellipsoid a depth  $\delta$  into the half-space is denoted  $W$ , while adhesion originates from a surface energy  $\Delta\gamma$ .

Solving the adhesive contact problem requires us to find the relationship between the load  $W$ , the surface energy  $\Delta\gamma$ , the contacting geometry  $R_A, R_B$ , the indentation depth  $\delta$ , and the size of the contact region (parametrized by  $a$  and  $b$ ). As a first step, we note that, within the contact region, the vertical displacement,  $u(x, y)$ , at the surface of the elastic half-space caused by the indenting body can be approximated as parabolic,

i.e.

$$u(x, y) = \delta + \frac{1}{2R_A}x^2 + \frac{1}{2R_B}y^2. \quad (1)$$

From Hertzian contact mechanics [8], it is known that a parabolic indentation is caused by the general pressure distribution

$$p(x, y) = \frac{p_0 - \alpha x^2 - \beta y^2}{\sqrt{1 - (x/a)^2 - (y/b)^2}}, \quad (2)$$

where  $p_0$ ,  $\alpha$  and  $\beta$  are all constants that need to be determined.

Our task is to find  $p_0$ ,  $\alpha$ ,  $\beta$ ,  $a$ ,  $b$ , and  $\delta$  as functions of  $W$ ,  $R_A$ ,  $R_B$  and  $\Delta\gamma$ . This requires six equations, one of which may be obtained by deriving the relationship between indentation and total load  $W$  via

$$W = \int_{\Omega} p(x, y) \, dx \, dy = 2\pi c^2 p_0 - \frac{2\pi c^4 (\alpha + \beta g^2)}{3g}. \quad (3)$$

Three further equations come from relating the pressure in eqn (2) to the indentation  $u$  in eqn (1) and the effective stiffness of the elastic half-space,  $E^*$ . To write these equations as neatly as possible, and remove any dependence on the stiffness  $E^*$ , we non-dimensionalize by making the substitutions:

$$p_0 = \bar{p}_0 \frac{E^*}{2bR}, \quad \alpha = \bar{\alpha} \frac{E^*}{2bR}, \quad \beta = \bar{\beta} \frac{E^*}{2bR}. \quad (4)$$

It is also convenient to characterize the contact geometry using  $\lambda = \sqrt{R_B/R_A}$  and  $R = \sqrt{R_A R_B}$  while characterizing the contact region using its slenderness  $g = b/a$  and the effective contact radius  $c = \sqrt{ab}$ . Making these substitutions, the relationship between pressure and displacement can be written [7] as

$$\begin{bmatrix} \delta \\ \lambda/(2R) \\ 1/(2\lambda R) \end{bmatrix} = \left( \frac{1}{2R} \right) \begin{bmatrix} 2\mathbf{K}(e) & c^2/g\mathbf{E}(e) & c^2g\mathbf{D}(e) \\ 0 & \mathbf{D}(e) + \mathbf{C}(e) & -g^2\mathbf{C}(e) \\ 0 & -\mathbf{C}(e) & \mathbf{B}(e) + g^2\mathbf{C}(e) \end{bmatrix} \cdot \begin{bmatrix} \bar{p}_0 \\ \bar{\alpha} \\ \bar{\beta} \end{bmatrix}. \quad (5)$$

where  $\mathbf{K}$  and  $\mathbf{E}$  are elliptic integrals of the first and second kind respectively,  $e = \sqrt{1 - g^2}$  is the eccentricity, and we define the functions

$$\mathbf{D}(e) \equiv e^{-2} [\mathbf{K}(e) - \mathbf{E}(e)], \quad (6)$$

$$\mathbf{B}(e) \equiv \mathbf{K}(e) - \mathbf{D}(e), \quad (7)$$


$$\mathbf{C}(e) \equiv e^{-2} [\mathbf{D}(e) - \mathbf{B}(e)]. \quad (8)$$

Solving eqn (5) for  $\delta$ ,  $\bar{\alpha}$  and  $\bar{\beta}$ , we obtain

$$\delta = \frac{\bar{p}_0 \mathbf{K}(e)}{R} - \frac{c^2 \bar{\alpha} \mathbf{B}(e)}{2gR} - \frac{c^2 g \bar{\beta} \mathbf{D}(e)}{2R}, \quad (9)$$

$$\bar{\alpha} = \frac{\lambda^2 \mathbf{B}(e) + \lambda^2 g^2 \mathbf{C}(e) + g^2 \mathbf{C}(e)}{\lambda \sqrt{g} [\mathbf{B}(e) \mathbf{C}(e) + \mathbf{B}(e) \mathbf{D}(e) + g^2 \mathbf{C}(e) \mathbf{D}(e)]}, \quad (10)$$

$$\bar{\beta} = \frac{\lambda^2 \mathbf{C}(e) + \mathbf{C}(e) + \mathbf{D}(e)}{\lambda \sqrt{g} [\mathbf{B}(e) \mathbf{C}(e) + \mathbf{B}(e) \mathbf{D}(e) + g^2 \mathbf{C}(e) \mathbf{D}(e)]}. \quad (11)$$

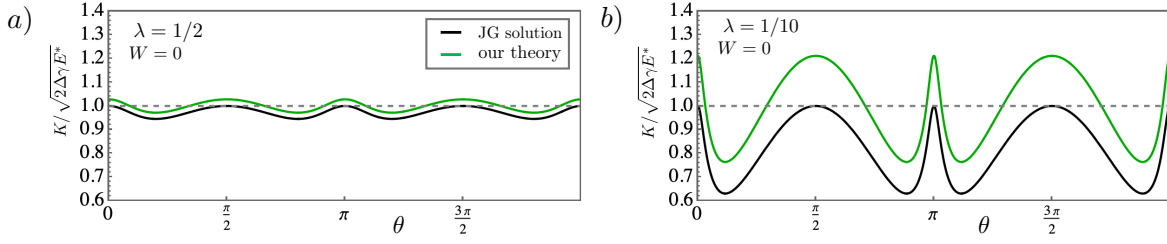

**Figure 2.** The angular distribution of the normalized stress intensity factor  $K/\sqrt{2E^*\Delta\gamma}$  around the edge of the contact ellipse obtained by JG and our theory. The dashed line shows the magnitude of the stress intensity factor predicted using Griffith's criterion, i.e. the stress intensity factor obtained at the boundary of contact if the contact shape was correct. Our theory predicts a very similar stress intensity factor distribution as the JG theory, but offset to be slightly larger, and hence on average closer to the dashed line.

In this way, we have now expressed three of the original six unknowns in terms of the remaining three ( $c$ ,  $g$  and  $\bar{p}_0$ ). We can readily find  $\bar{p}_0$  by solving equation (3), giving

$$\bar{p}_0 = \frac{c^2 (\bar{\alpha} + g^2 \bar{\beta})}{3g} + \frac{\sqrt{g}RW}{\pi c E^*}, \quad (12)$$

leaving us only with  $c$  and  $g$  to be determined.

A further condition is derived following JG's work and equating the (mode I) stress intensity factor  $K$  at the ends of the semi-major and semi-minor axes of contact. The mode I stress intensity factor describes the strength of the tensile stress singularity at the boundary of a crack or, as in our case, at the boundary of the adhesive contact region [16]. It is defined as  $K = \sqrt{2\pi} \lim_{r \rightarrow 0} \sigma \sqrt{r}$  where  $\sigma$  is the stress and  $r$  the distance from the boundary. For the correct contact set,  $K$  is constant along the boundary. However, the elliptical contact assumption we (and others) have made is only an approximation chosen to facilitate analytical progress; meaning  $K$  now varies along the boundary. Using the pressure in (2) and defining a vector normal to the ellipse boundary, we can calculate that the stress intensity factor as a function of angular position  $\theta$  is

$$K(\theta) = \frac{E^* \sqrt{\pi}}{2bR} \frac{(\bar{\alpha} a^2 \cos^2 \theta + \bar{\beta} b^2 \sin^2 \theta - \bar{p}_0)}{(\cos^2 \theta / a^2 + \sin^2 \theta / b^2)^{1/4}}, \quad (13)$$

where we remind the reader that  $\bar{\alpha} = \alpha(g, \lambda)$ ,  $\bar{\beta} = \beta(g, \lambda)$ . JG determined the two unknown parameters  $g$  and  $c$  by equating the values of  $K$  at  $\theta = 0$  and  $\theta = \pi/2$  and, further, by equating this value to that given by Griffith's criterion. Here, we follow the first of these steps, setting  $K(0) = K(\pi/2)$  to give

$$(\bar{\alpha} a^2 - \bar{p}_0) \sqrt{a} = (\bar{\beta} b^2 - \bar{p}_0) \sqrt{b}. \quad (14)$$

We can now substitute the expressions for  $\bar{\alpha}$  and  $\bar{\beta}$ , given in eqns (10) and (11), in (14)

to obtain the relationship:

$$W = \frac{\pi E^*}{3} c^3 \frac{(2\sqrt{g} + 1) g^2 \bar{\beta} - (\sqrt{g} + 2) \bar{\alpha}}{(\sqrt{g} - 1) g^{3/2} R}. \quad (15)$$

Note that we have conveniently expressed  $W$  as a function of  $g$ . Since  $W$  (the load) is the relevant control parameter,  $g$  will be used as a parameter to plot the behaviour of the system.

So far, we have followed the steps from JG's work. To complete their derivation and find the size of the effective contact radius  $c$ , JG use Griffith's criterion, which predicts delamination occurs when  $K$  is larger than the critical value  $K_c = \sqrt{2E^* \Delta \gamma}$ . Since the stress intensity factor is not constant, JG choose to impose Griffith's criterion at the semi-major and semi-minor axis, so that  $K(0) = K(\pi/2) = \sqrt{2E^* \Delta \gamma}$ . However, as shown by the black curves in figure 2, at these locations the stress intensity factor takes its largest value. This means that JG's theory overestimates  $K$  and therefore underestimates the size of the contact radius.

We would instead like to satisfy Griffith's criterion in some global or 'average' sense over the whole boundary. In our view, the natural way to do this is to determine the size of the effective contact radius  $c$  by minimising the total energy of the system, given by the sum of elastic and surface energy. The green curves in figure 2 show the stress intensity factor (rescaled by the critical value) predicted by this energetic approach. The shape of the curves are similar to those from JG's theory, but they are shifted upwards. This shift means that our theory accepts a larger stress intensity factor at the boundary, whose average is closer (albeit not identical) to the critical value. As a result, our theory predicts a larger contact radius, which is in better agreement with the numerical simulations obtained in [10].

Our last step is therefore different from JG's work. We complete our derivation by determining the size of the effective contact radius  $c$  using an energetic approach. In particular, we want to write the total energy of the system — equal to the sum of the elastic energy of the deformation  $U_{\text{el}}$  and the energy saved by surface tension via contact  $U_{\Delta \gamma}$  — as a function of the contact radius, i.e.  $U_{\text{tot}}(c) = U_{\text{el}}(c) + U_{\Delta \gamma}(c)$ . We then find out the size of the contact by minimising the total energy, meaning we need to solve  $U'_{\text{tot}}(c) = 0$ .

To evaluate the energy stored in the elastic half-space, we parameterise the pressure and indentation displacement using a parameter  $\xi$ . We let  $\tilde{p}(x, y) = \xi p(x, y)$  and  $\tilde{u}(x, y) = -\xi u(x, y)$  where  $u$  and  $p$  are defined in equations (1) and (2), respectively. Note that the minus sign in the latter equation has been added so that positive pressures correspond to displacements *into* the half-space. This parametrisation means that when  $\xi = 0$  no displacement occurs, while as  $\xi$  increases, so does the deformation of the system until we obtain the final contact deformation at  $\xi = 1$ . By the principle of virtual work,

the energy of the deformation is given by

$$\begin{aligned}
 U_{\text{el}} &= \int_{\Omega} \int p(x, y) \, du(x, y) \, dA \\
 &= \int_{\Omega} \int_0^1 \tilde{p}(x, y) \frac{d\tilde{u}(x, y)}{d\xi} \, d\xi \, dA \\
 &= - \int_{\Omega} \int_0^1 \tilde{p}(x, y) (\delta + Ax^2 + By^2) \, d\xi \, dA \\
 &= \frac{\pi c^5 E^* (2\lambda^2 \bar{\alpha} + 2g^4 \bar{\beta} - g^2 (\bar{\alpha} + \lambda^2 \bar{\beta}))}{90g^{5/2} \lambda R^2} - \frac{c^2 W (g^2 + \lambda^2)}{12g\lambda R} - \frac{W\delta}{2}, \quad (16)
 \end{aligned}$$

where in the second step we have used eqn (1), while in the third step we have evaluated the remaining integral, substituted  $A$  and  $B$  for  $\lambda$  and  $R$ , and used equation (5). Note that we have written the dependence of  $\delta$  on  $c$  arising from equation (9) explicitly since this is important later in the minimization. Similarly, we have also had to capture the  $W$  dependence explicitly since this is an independent variable.

The final ingredient is the surface energy saved by contact,  $U_{\Delta\gamma} = -\Delta\gamma\pi c^2$  where  $\pi c^2$  is the contact area of the ellipse. The total energy,  $U_{\text{tot}} = U_{\text{el}} + U_{\Delta\gamma}$  is minimized with respect to variations in  $c$ , ( $U'_{\text{tot}}(c) = 0$ ), and gives

$$c \left( \frac{E^*}{\Delta\gamma R^2} \right)^{1/3} = \left( \frac{12 (\sqrt{g} - 1)^2 g^{5/2} \lambda}{f(\lambda, g) - (g - \sqrt{g}) (g^{3/2} + \lambda^2) (\bar{\beta} g^2 - \bar{\alpha})} \right)^{1/3}, \quad (17)$$

where


$$f(\lambda, g) = \frac{\lambda [(\sqrt{g} - 1) (\bar{\alpha} \mathbf{B}(e) + \bar{\beta} g^2 \mathbf{D}(e)) + \mathbf{K}(e) (\bar{\beta} g^2 - \bar{\alpha} \sqrt{g})]}{[\bar{\beta} (2\sqrt{g} + 1) g^2 - \bar{\alpha} (\sqrt{g} + 2)]^{-1}}. \quad (18)$$

Equations (10)-(12) with (15) and (17) represent the solution of the problem and allow us to express all quantities relevant to the problem as a function of the load  $W$  (recalling that we use the contact slenderness  $g$  as a parameter to facilitate plots). We now proceed to study their behaviour and compare with previous results.

### 3. Results

We compare our theory with the results presented by JG as well as recent numerical simulations for elliptical contact obtained in [10]. To make the comparison, we express our quantities in dimensionless form following the original work by Johnson Kendall and Roberts [1], so that:

$$\begin{aligned}
 c_r &= \left( \frac{9\pi R^2 \Delta\gamma}{4E^*} \right)^{1/3}, & \bar{W} &= \frac{W}{3\pi R \Delta\gamma}, \\
 \bar{c} &= \frac{c}{c_r}, & \delta &= \bar{\delta} \frac{c_r^2}{R}. \quad (19)
 \end{aligned}$$

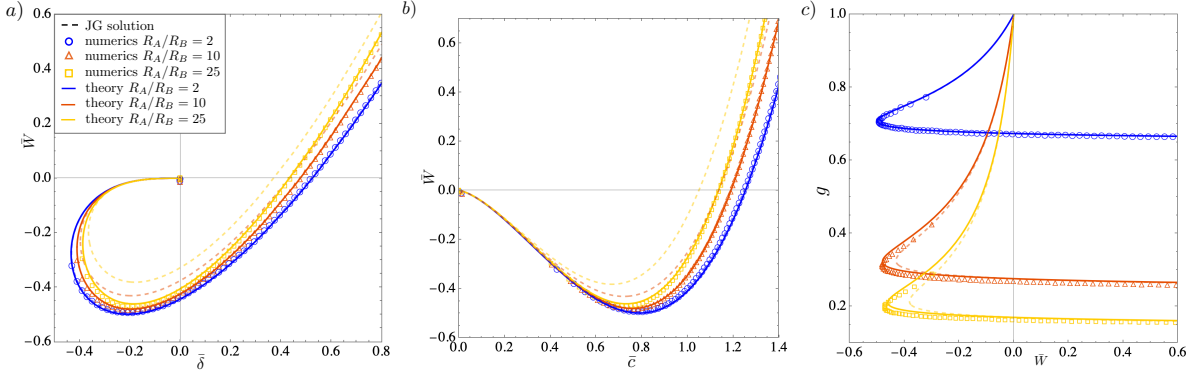

**Figure 3.** Comparison between the present theory (solid curves), the predictions of JG (dashed curves) and recent numerical simulations (points) [10]. Plots show (a) the load versus displacement, (b) load versus contact radius, and (c) contact aspect ratio  $g$  versus load for a range of values of  $\lambda^2 = R_B/R_A$ . Since the contact region is not perfectly elliptical in numerical simulations, the aspect ratio  $g$  is calculated by dividing the largest distance on the boundary from the centre (equivalent to the semi-major axis) by the smallest distance (equivalent to the semi-minor axis). Our approximate theory agrees very well with the numerical results and is also able to predict the eccentricity of the contact boundary.

Applying these rescalings, all our equations in the previous section become independent of the parameters  $E^*$ ,  $W$ ,  $R$  and  $\delta$ , and our results can be neatly presented. Our results are shown in figure 3. The energy minimization approach used here leads to analytical results that are in very good agreement with numerical simulations, even for very slender contact ellipses; this good agreement is observed despite the (erroneous) assumption of an elliptical contact region. Note that the numerical simulations make no assumptions about the shape of the contact set, which is close to being elliptical, but slightly ‘squared-out’ near the semi-major axis, as shown in figure 3 of [10].

#### 4. Conclusion

In this paper, we have revisited the seminal work by Johnson and Greenwood [7] on non-axisymmetric adhesive contact. To derive our approximate theory, we maintained JG’s simplifying assumption that the contact region is elliptical. However, instead of using Griffith’s criterion locally to establish the effect of adhesion, we minimized the sum of the elastic and surface energies to find the size of the contact region. The results of our theory are in good agreement with numerical simulations and offer a considerable improvement on JG’s theory.

The reason for the improvement can be understood by considering the stress intensity factor at the boundary of contact. Due to the approximation of an elliptical



contact, the stress intensity factor is not constant on the contact boundary. JG choose to satisfy Griffith's criterion locally, at the ends of the semi-major and semi-minor axis, where the stress intensity factor is, in fact, maximal. As a result, they underestimate the size of the contact radius and the magnitude of the pull-off force. Conversely, our energetic approach is global and satisfies Griffith's criterion in an average sense. This means that, despite predicting the contact shape incorrectly, the contact area is well approximated, leading to good and robust predictions.

Using a global energetic approach instead of a local application of Griffith's criterion may help smear out errors in other problems in adhesion and contact mechanics. For example, Zini *et al.* [13] have proposed a double-Hertz model to describe elliptical contact and capture effects of adhesion also in the case of long-ranged interactions. Similarly to Johnson and Greenwood, they made a series of assumptions about the shape of the contact and cohesive region to simplify the problem—leading to a non-constant stress singularity at the boundary—and included the effects of adhesion via Griffith's criterion applied to the semi-major axis. It is likely that a part of the observed error in their theory is a result of the local application of Griffith's criterion, and we therefore anticipate that a global energetic approach may lead to more accurate results.

## Acknowledgements

A.G. is grateful to the Royal Society for funding. The project was partially supported by the UK Engineering and Physical Sciences Research Council via grant EP/W016249/1 (D.V.).

## References

- [1] Johnson K L, Kendall K and Roberts A 1971 *Proceedings of the royal society of London. A. mathematical and physical sciences* **324** 301–313
- [2] Rusu F, Pustan M, Birleanu C, Müller R, Voicu R and Baracu A 2015 *Applied Surface Science* **358** 634–640
- [3] Joulaei M, Kolahdoozan M, Salehi M, Zadsar M and Vahabi M 2020 *Surface and Interface Analysis* **52** 34–41
- [4] Spolenak R, Gorb S, Gao H and Arzt E 2005 *Proceedings of the Royal Society A: Mathematical, Physical and Engineering Sciences* **461** 305–319
- [5] Chu Y S, Dufour S, Thierry J P, Perez E and Pincet F 2005 *Physical review letters* **94** 028102
- [6] Ciavarella M, Joe J, Papangelo A and Barber J 2019 *Journal of the Royal Society Interface* **16** 20180738
- [7] Johnson K and Greenwood J 2005 *Journal of Physics D: Applied Physics* **38** 1042
- [8] Barber J R and Ciavarella M 2000 *International Journal of solids and structures* **37** 29–43
- [9] Gdoutos E E 2020 *Fracture mechanics: an introduction* vol 263 (Springer Nature)

- [10] Li Q and Popov V L 2020 *Journal of Physics D: Applied Physics* **53** 335303
- [11] Jin C, Jagota A and Hui C Y 2011 *Journal of Physics D: Applied Physics* **44** 405303
- [12] Sümer B, Onal C D, Aksak B and Sitti M 2010 *Journal of Applied Physics* **107**
- [13] Zini N, De Rooij M, Bazr Afshan Fadafan M, Ismail N and Schipper D 2018 *Tribology letters* **66** 1–13
- [14] Greenwood J and Johnson K 1998 *Journal of Physics D: Applied Physics* **31** 3279
- [15] Greenwood J A 2018 *Tribology letters* **66**
- [16] Gdoutos E E 2020 *Fracture mechanics: an introduction* vol 263 (Springer Nature)