

Interplay of d - and p -States in RbTi_3Bi_5 and CsTi_3Bi_5 Flat-Band Kagome Metals

M. Wenzel,^{1,*} E. Uykur,² A. A. Tsirlin,³ A. N. Capa Salinas,⁴ B. R. Ortiz,⁵ S. D. Wilson,⁴ and M. Dressel¹

¹*Physikalisches Institut, Universität Stuttgart, 70569 Stuttgart, Germany*

²*Helmholtz-Zentrum Dresden-Rossendorf, Institute of Ion Beam Physics and Materials Research, 01328 Dresden, Germany*

³*Felix Bloch Institute for Solid-State Physics, Leipzig University, 04103 Leipzig, Germany*

⁴*Materials Department and California Nanosystems Institute,*

University of California Santa Barbara, Santa Barbara, CA, 93106, USA

⁵*Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831, USA*

(Dated: January 31, 2025)

Shifting the Fermi level of the celebrated AM_3X_5 (135) compounds into proximity of flat bands strongly enhances electronic correlations and severely affects the formation of density waves and superconductivity. Our broadband infrared spectroscopy measurements of RbTi_3Bi_5 and CsTi_3Bi_5 combined with density-functional band-structure calculations reveal that the correlated Ti d -states are intricately coupled with the Bi p -states that form a tilted Dirac crossing. Electron-phonon coupling manifests itself in the strong damping of itinerant carriers and in the anomalous shape of the phonon line in RbTi_3Bi_5 . An anomaly in these spectral features around 150 K can be paralleled to the onset of nematicity detected by low-temperature probes. Our findings show that the materials with low band filling open unexplored directions in the physics of kagome metals and involve electronic states of different nature strongly coupled with lattice dynamics.

Kagome 135-compounds have been the focal point of studying charge ordering, superconductivity, and electronic nematicity, among other exotic quantum phenomena in correlated electronic systems, over the last five years [1–4]. Rooted in the presence of flat bands, saddle points (van Hove singularities), and Dirac bands, the rich electronic phase diagram of kagome metals is highly sensitive to the band filling level [5–9]. Building on the broad interest in the $AV_3\text{Sb}_5$ ($A = \text{K}, \text{Rb}, \text{Cs}$) series, new materials maintaining the pristine 135-kagome lattice structure have recently been proposed [1, 10–14]. Among these, the $ATi_3\text{Bi}_5$ ($A = \text{Rb}, \text{Cs}$) compounds stand out as one of the few synthesized materials with a significantly lower band filling level compared to $AV_3\text{Sb}_5$ compounds, according to the reduced number of valence electrons. Here, kagome-Ti planes stabilized by Bi1 atoms are stacked along the c -axis and separated by alkali ion layers and Bi2 honeycomb nets as sketched in Fig. S1 [15]

Magnetic susceptibility, dc resistivity, and specific heat studies [13, 16] indicate the absence of a charge-density-wave (CDW) state in $ATi_3\text{Bi}_5$, a finding that is further corroborated by first-principle calculations [17]. Some dc resistivity and magnetic susceptibility data report traces of a superconducting transition near 4 K [13, 18, 19]. However, this observation remains contentious, as the transition temperature coincides with the T_c of possible RbBi_2 and CsBi_2 impurities [13, 20, 21]. For CsTi_3Bi_5 , superconductivity emerges under external pressure, exhibiting a characteristic double-dome feature in T_c , similar to $AV_3\text{Sb}_5$ compounds, but with the second dome terminating at 35 GPa [22, 23].

Scanning tunneling microscopy (STM) and angle-resolved photoemission spectroscopy (ARPES) studies reveal a reduction in the C_6 lattice symmetry to C_2 at low temperatures, without breaking the translational symme-

try [18, 19, 24, 25]. This rotational symmetry breaking, without the formation of a CDW state, has been identified as a Pomeranchuk instability [26] and provides a path to explore purely electronic nematic order in nonmagnetic kagome metals. However, the exact temperature of this nematic transition and its occurrence in the bulk remain to be established, because the nematicity has been so far detected with surface-sensitive techniques and at low temperatures only.

In this work, we present a broadband optical spectroscopic study of RbTi_3Bi_5 and CsTi_3Bi_5 , probing the temperature-dependent evolution of the bulk electronic structure above and below the Fermi level. Aided by density functional theory (DFT) calculations, we demonstrate that the low-energy optical response is predominantly governed by interband transitions involving linearly dispersing Ti-kagome bands, with significant contributions from Bi2 p_z states. Our findings highlight the enhancement of correlation effects in $ATi_3\text{Bi}_5$ compared to CsV_3Sb_5 and elucidate the role of Ti-flat bands in the vicinity of the Fermi level. Finally, we identify signatures of the nematic phase transition in the optical spectra of RbTi_3Bi_5 , pinpointing the transition temperature just below 150 K.

High-quality single crystals were synthesized using a self-flux method [13]. Reflectivity measurements were performed in the ab -plane on as-grown single crystals in a broad frequency range (50 - 18000 cm^{-1}) at different temperatures down to 10 K. The optical conductivity was obtained by Kramers-Kronig analysis as explained in the Supplemental Material [15]. Fig. 1(a) shows the calculated real part of the optical conductivity of RbTi_3Bi_5 at selected temperatures. The raw data as well as the spectra of CsTi_3Bi_5 can be found in the Supplemental Material [15].

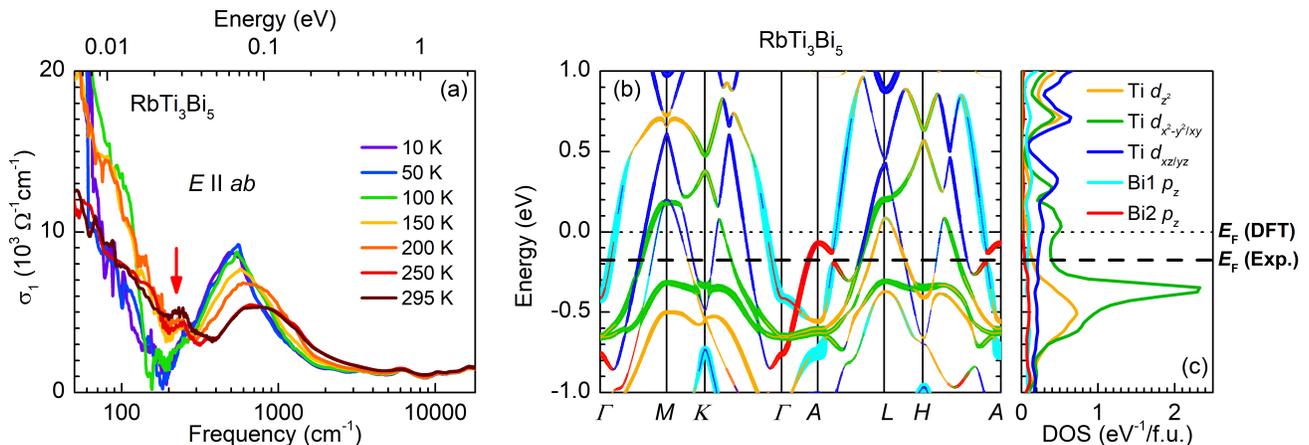


FIG. 1. (a) Temperature-dependent real part of the in-plane optical conductivity of RbTi_3Bi_5 calculated from the measured reflectivity. The red arrow marks the Fano resonance around 200 cm^{-1} . (b) Band structure of RbTi_3Bi_5 with different colors representing contributions from different atomic orbitals as labeled in panel (c) showing the corresponding density of states (DOS). The short-dashed line shows the Fermi level obtained from DFT, whereas the long-dashed line is the position of the Fermi level adjusted using the experimental optical conductivity.

Band structure and optical conductivity calculations were performed in the *Wien2K* code [27, 28] using the experimental crystal structures from Ref. [13] and the Perdew-Burke-Ernzerhof (PBE) exchange-correlation potential [29]. Spin-orbit coupling was included in all calculations. The optical conductivity was obtained using the *OPTIC* module of *Wien2K* [30].

Fig. 1(b) displays the calculated band structure of RbTi_3Bi_5 highlighting the different orbital contributions. The low-energy band structure is dominated by linearly dispersing Ti d - and Bi1 p_z -states crossing the Fermi level. Band saddle points, comprised mainly of Ti $d_{x^2-y^2/xy}$ states, are located above the Fermi level at the M - and L -points. Additionally, flat bands with a large density of Ti $d_{x^2-y^2/xy}$ and d_{z^2} states [see panel (b)] are present below the Fermi level.

Experimental optical conductivities are analyzed by modeling the different contributions to the total optical spectra using the Drude-Lorentz approach as presented in Figs. 2(a) and (b) for the 10 K data. In addition to the classical Lorentzian (interband) and Drude (intraband) contributions, a strong, temperature-dependent absorption peak is observed at low energies (blue), which is attributed to the intraband signature of localized electrons [31–35]. The spectra of RbTi_3Bi_5 further reveal a rather broad Fano-shaped phonon mode around 200 cm^{-1} , marked by the red arrow in Fig. 1(a), signaling the presence of strong electron-phonon coupling. The total complex optical conductivity [$\tilde{\sigma} = \sigma_1 + i\sigma_2$] then takes the form

$$\tilde{\sigma}(\omega) = \tilde{\sigma}_{\text{intraband}} + \tilde{\sigma}_{\text{phonon}} + \tilde{\sigma}_{\text{interband}}. \quad (1)$$

The experimental interband optical transitions are obtained by subtracting the intraband contributions, i.e.,

Drude and localization peaks, and the Fano resonance from the optical conductivity. Figs. 2(c) and (d) show the experimental and DFT-based interband optical conductivity of RbTi_3Bi_5 and CsTi_3Bi_5 , respectively. Stoichiometric calculations predict a sharp absorption feature around 1500 cm^{-1} , which deviates from the experimental data, indicating the need for band energy renormalization. A better agreement between experiment and theory is achieved by a downward shift of the Fermi level by 177 meV for RbTi_3Bi_5 and 179 meV for CsTi_3Bi_5 . This adjustment reproduces the experimental low-energy absorption observed near 1000 cm^{-1} . Notably, a similar downward shift of the Fermi level has also been reported in ARPES measurements for the Cs compound [36].

Interestingly, this substantial downward shift of the Fermi level has minuscule impact on the bands crossing E_F along Γ - M - K - Γ , as outlined in Fig. 1(a). Therefore, the Fermi surface at $k_z = 0$ [see Fig. 3(a)] is largely unchanged and consistent with those obtained from ARPES and quantum oscillation studies [25, 36–38]. The primary effect of the Fermi level shift is the emergence of Bi2 p_z states at the Fermi level around the A point, as illustrated in Fig. 1(a). This leads to the formation of two new Fermi surface sheets around the A point, depicted in Fig. 3(a) for RbTi_3Bi_5 .

To further investigate the contributions of different electronic bands to the interband conductivity, we perform band-resolved calculations, presented in Fig. 3(c) for RbTi_3Bi_5 . The interband absorption at the lowest energies arises purely from (i) transitions between the linearly dispersing Ti d bands C and D, as labeled in Fig. 3(b), and (ii) transitions between the bands E and F. The latter transitions resemble a sharp Pauli edge and can be attributed to the tilted Dirac-like bands along

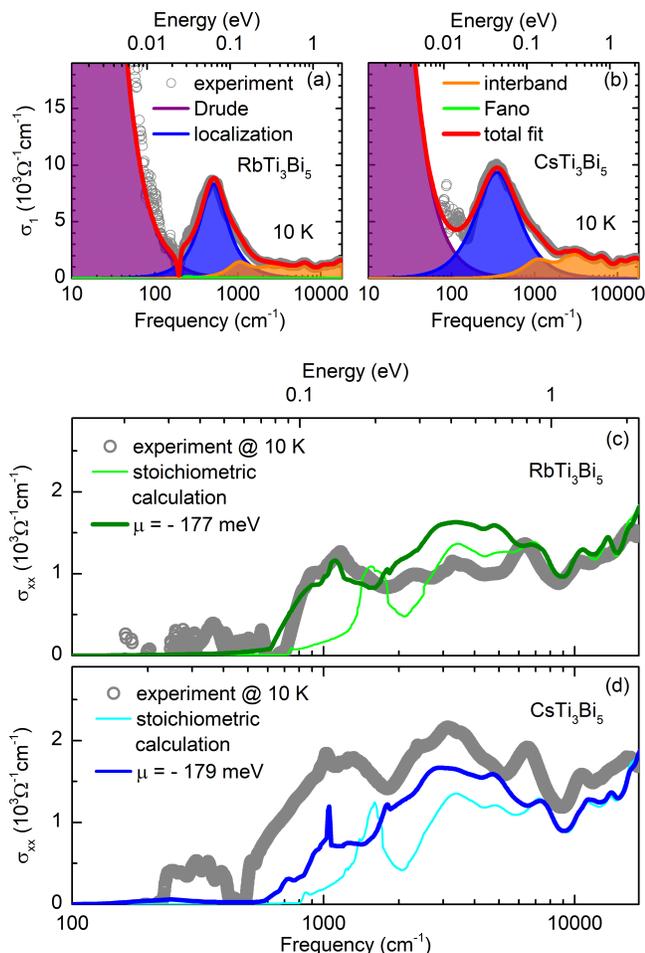


FIG. 2. Comparison of the optical response of RbTi_3Bi_5 and CsTi_3Bi_5 . (a) and (b) Decomposed optical conductivities at 10 K, consisting of a Drude peak (purple), a localization peak (blue), several interband transitions (orange), and a Fano resonance (green) in the case of RbTi_3Bi_5 . (c) and (d) Experimental and DFT-based in-plane interband optical conductivities of RbTi_3Bi_5 and CsTi_3Bi_5 , respectively. Above 2500 cm^{-1} , a broadening of 0.05 eV is applied to the calculated spectra. The shift of the Fermi level necessary to reproduce the experimental results is expressed by the chemical potential μ .

A-L and *H-A*, predominantly involving Bi1 and Bi2 p_z orbitals [see Figs. 1(b) and (c)]. Previous studies highlighted such tilted linear crossings of d -bands along Γ - M and A - L [25, 36]. Our band-resolved calculations, however, reveal that these type-II Dirac crossings of the bands D and E do not contribute to the low-energy optical response, which is dominated by the $E \rightarrow F$ transitions. The replacement of the alkali ion does not change this scenario [see Fig. S9 [15]] but essentially only shifts the tilted Dirac bands of Bi relative to the Fermi energy as highlighted in Fig. S8 [15]. Consequently, band E forms hole pockets in the Fermi surface of RbTi_3Bi_5 at $k_z = 0.5$, while the respective pockets in CsTi_3Bi_5 are

instead created by band F and exhibit electron character.

The large shift of the Fermi level required to reproduce the experimental optical conductivity moves the Ti flat bands closer to the Fermi level, positioning them at approximately -0.2 eV and -0.4 eV , in good agreement with ARPES measurements [25, 36]. Similarly close flat bands, though located above the Fermi energy, have also been reported in CsCr_3Sb_5 , where the Cr- d bands exhibit strong orbital-selective renormalization effects [39–41]. The treatment of correlation effects in ATi_3Bi_5 within the DFT+ U framework is discussed in the Supplemental Material [15]. However, adding a Hubbard U term to the Ti- d orbitals pushes the flat bands farther away from the Fermi energy and induces modifications in the Fermi surface, failing to reproduce both the electronic band structure observed in ARPES studies and the optical response. This suggests more complex, orbital-selective correlation effects similar to the ones observed in CsCr_3Sb_5 that cannot be captured within the mean-field DFT+ U approach.

Significant electronic correlations in ATi_3Bi_5 are clearly witnessed by our optical data. Not only must the band energy be renormalized by the downward shift of the Fermi level to align with the experimental interband transitions, but also the calculated plasma frequencies of 4.02 eV and 3.98 eV for RbTi_3Bi_5 and CsTi_3Bi_5 , respectively, are much higher than the experimental values of 2.50 eV (Rb) and 2.52 eV (Cs). This discrepancy indicates that DFT overestimates the spectral weight of itinerant charge carriers. The strength of the electronic correlations can be gauged by the ratio of the experimental to DFT-based intraband spectral weights [43, 44], as outlined in the Supplemental Material [15]. This ratio is approximately 0.40 for both RbTi_3Bi_5 and CsTi_3Bi_5 in stark contrast to CsV_3Sb_5 , which is almost uncorrelated as illustrated in Fig. 4(a). Interestingly, though, KV_3Sb_5 and RbV_3Sb_5 also show enhanced correlations.

The experimental optical spectra of RbTi_3Bi_5 reveal a relatively broad phonon mode around 200 cm^{-1} , displaying Fano-like behavior, a hallmark of electron-phonon coupling. Such phonon modes are relatively common in kagome metals and have been observed, albeit at higher energies, in other 135-compounds as well [31, 33]. According to our DFT calculations outlined in the Supplemental Material [15], the mode in RbTi_3Bi_5 can be assigned to the infrared-active E_{1u} phonon mainly involving in-plane atomic displacements within the Ti-Bi1 kagome net.

Below 150 K , the phonon spectrum evolves into a pronounced anti-resonance seen in Fig. S6 [15], which corresponds to a drastic change in the Fano coupling parameter q^2 plotted in Fig. 4(b) (orange). Simultaneously, a sudden shift in the phonon frequency to lower energies is observed [Fig. 4(b) (green)]. While changes in phonon spectra are often associated with structural phase transitions, no alterations in the interband optical absorption are observed across the entire temperature

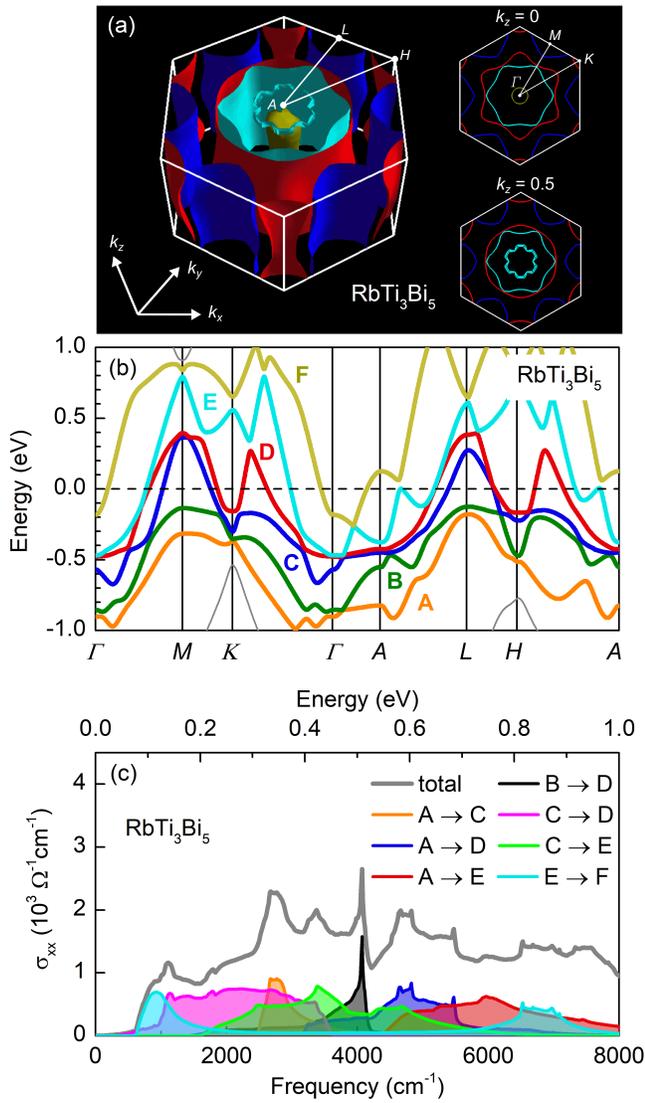


FIG. 3. (a) Fermi surface of RbTi₃Bi₅ constructed from the calculated band structure with the Fermi level shifted down by 177 meV to match the experimental data. **FermiSurfer** program was used for the visualization [42]. (b) Calculated band structure of RbTi₃Bi₅ with the experimentally determined position of the Fermi level. (c) Band-resolved in-plane optical conductivity with different colors representing contributions from interband optical transitions between different bands following the labeling in panel (b). Note that no broadening is introduced to the calculations.

range [see Fig. S4 for the decomposed spectra at different temperatures [15]]. Combined with the absence of a low-temperature anomaly in dc transport, magnetic susceptibility, or specific heat [13, 16], these findings make structural changes unlikely. Additionally, we observe an anomaly in the position of the localization peak around the same temperature of 150 K [Fig. 4(c)]. The localization peaks are typically caused by electron-boson interactions [45–47]. Therefore, we interpret the changes in the

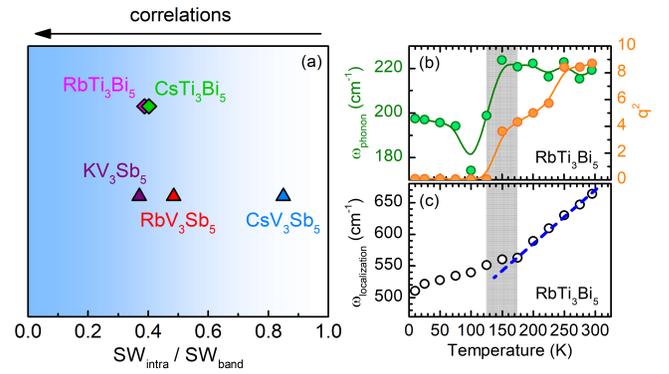


FIG. 4. (a) Ratio of the experimental and DFT-based intraband spectral weights serving as a gauge of the strength of electronic correlations. Values of the vanadium-based 135-compounds are taken from previous studies [31–33]. (b) Temperature evolution of the phonon frequency observed in the optical spectra of RbTi₃Bi₅ (green) and the Fano coupling parameter q^2 (orange). (c) Position of the localization peak in RbTi₃Bi₅ as a function of temperature. Grey shaded areas highlight the changes in the phonon and localization peak parameters attributed to the nematic phase transition just below 150 K.

phonon line and the anomaly in the position of the localization peak as a sign of sudden changes in the electron-phonon coupling upon entering the nematic phase at low temperatures. Consequently, our data provide evidence for a bulk nematic phase transition in RbTi₃Bi₅ just below 150 K. We note that the absence of similar signatures in the data of CsTi₃Bi₅ does not imply the absence of a nematic phase transition at comparable temperatures, but rather may be explained by the phonon mode being screened by conduction electrons.

Overall, the significantly reduced band filling level in the ATi₃Bi₅ compounds compared to the AV₃Sb₅ strongly modifies the nature of low-energy optical excitations. In the case of the AV₃Sb₅, the low-energy electrodynamics are dominated by charge carriers around the M point, which arise from vanadium 3d kagome states [31–33, 48–50]. In contrast, non-kagome Bi p_z states forming a tilted Dirac crossing play a substantial role in ATi₃Bi₅. These states are witnessed by the low-energy spectral weight observed in our measurements. Additionally, the presence of flat bands can be inferred from the significant band renormalization and the reduced intraband spectral weight, both indicative of the sizable electronic correlations in ATi₃Bi₅.

The proximity of the Fermi level to the flat bands seems crucial for the ATi₃Bi₅ physics that entails orbital-selective correlations leading to the d -wave Pomeranchuk instability and a purely electronic nematic phase [26]. Our results extend this picture in two aspects. First, we demonstrate the presence of electron-phonon coupling evidenced by the anomalous phonon mode and the promi-

ment localization peak of the intraband carriers. Second, we show that both of these features reveal an anomaly around 150 K, which is likely associated with the nematic transition. Our observations suggest that phonons can serve as useful fingerprints of electronic instabilities and call for momentum-dependent phonon studies on ATi_3Bi_5 .

Our findings underscore the prominent role of linear and flat Ti $3d$ as well as Bi p_z states in shaping the low-energy electronic structure of the ATi_3Bi_5 compounds. Especially the presence of Bi $2p_z$ Fermi surface pockets clearly distinguishes these compounds from their AV_3Sb_5 counterparts. Simultaneously, the effects of electronic correlations are amplified due to the proximity of Ti flat bands to the Fermi level. The temperature evolution of the optical spectra reveals bulk signatures of a nematic phase transition in $RbTi_3Bi_5$ just below 150 K, accompanied by changes in electron-phonon coupling.

Note added. During the completion of this work, an independent infrared spectroscopy study [51] reported optical signatures of flat bands in $CsTi_3Bi_5$ similar to our work, but neither the low-energy features presented here nor the correlation strength could be resolved in that study.

We are grateful to Gabriele Untereiner for preparing single crystals and assisting in the optical measurements. M.W. is supported by Center for Integrated Quantum Science and Technology (IQST) Stuttgart/Ulm via a project funded by the Carl Zeiss Stiftung. Work by B.R.O. was supported by the U.S. Department of Energy, Office of Science, Basic Energy Sciences, Materials Sciences and Engineering Division. S.D.W gratefully acknowledges support via the UC Santa Barbara NSF Quantum Foundry funded via the Q-AMASE-i program under award DMR-1906325. The work has been supported by the Deutsche Forschungsgemeinschaft (DFG) via DR228/51-3, DR228/68-1, and UY63/2-1.

* maxim.wenzel@pi1.physik.uni-stuttgart.de

- [1] S. D. Wilson and B. R. Ortiz, AV_3Sb_5 kagome superconductors, *Nat. Rev. Mater.* **9**, 420 (2024).
- [2] T. Nguyen and M. Li, Electronic properties of correlated kagomé metals AV_3Sb_5 ($A = K, Rb,$ and Cs): A perspective, *J. Appl. Phys.* **131**, 060901 (2022).
- [3] K. Jiang, T. Wu, J.-X. Yin, Z. Wang, M. Z. Hasan, S. D. Wilson, X. Chen, and J. Hu, Kagome superconductors AV_3Sb_5 ($A = K, Rb, Cs$), *Natl. Sci. Rev.* **10**, nwac199 (2022).
- [4] T. Neupert, M. M. Denner, J.-X. Yin, R. Thomale, and M. Z. Hasan, Charge order and superconductivity in kagome materials, *Nat. Phys.* **18**, 137 (2022).
- [5] M. M. Denner, R. Thomale, and T. Neupert, Analysis of Charge Order in the Kagome Metal AV_3Sb_5 ($A = K, Rb, Cs$), *Phys. Rev. Lett.* **127**, 217601 (2021).
- [6] M. L. Kiesel, C. Platt, and R. Thomale, Unconventional Fermi Surface Instabilities in the Kagome Hubbard Model, *Phys. Rev. Lett.* **110**, 126405 (2013).
- [7] T. Park, M. Ye, and L. Balents, Electronic instabilities of kagome metals: Saddle points and Landau theory, *Phys. Rev. B* **104**, 035142 (2021).
- [8] W.-S. Wang, Z.-Z. Li, Y.-Y. Xiang, and Q.-H. Wang, Competing electronic orders on kagome lattices at van Hove filling, *Phys. Rev. B* **87**, 115135 (2013).
- [9] J. B. Profeta, L. Klebl, F. Grandi, H. Hohmann, M. Dürrnagel, T. Schwemmer, R. Thomale, and D. M. Kennes, Kagome Hubbard model from a functional renormalization group perspective, *Phys. Rev. Res.* **6**, 043078 (2024).
- [10] X.-W. Yi, X.-Y. Ma, Z. Zhang, Z.-W. Liao, J.-Y. You, and G. Su, Large kagome family candidates with topological superconductivity and charge density waves, *Phys. Rev. B* **106**, L220505 (2022).
- [11] J. Si, L. Shi, B. Chen, H. Yang, J. Xu, M. Liu, and S. Meng, Coexistence of superconductivity and topological phase in kagome metals ANb_3Bi_5 ($A = K, Rb, Cs$), *npj Comput. Mater.* **10**, 96 (2024).
- [12] Y. Liu, Z.-Y. Liu, J.-K. Bao, P.-T. Yang, L.-W. Ji, S.-Q. Wu, Q.-X. Shen, J. Luo, J. Yang, J.-Y. Liu, C.-C. Xu, W.-Z. Yang, W.-L. Chai, J.-Y. Lu, C.-C. Liu, B.-S. Wang, H. Jiang, Q. Tao, Z. Ren, X.-F. Xu, C. Cao, Z.-A. Xu, R. Zhou, J.-G. Cheng, and G.-H. Cao, Superconductivity under pressure in a chromium-based kagome metal, *Nature* **632**, 1032 (2024).
- [13] D. Werhahn, B. R. Ortiz, A. K. Hay, S. D. Wilson, R. Seshadri, and D. Johrendt, The kagomé metals $RbTi_3Bi_5$ and $CsTi_3Bi_5$, *Z. Naturforsch. B* **77**, 757 (2022).
- [14] Y. Hu, C. Le, X. Wu, and M. Shi, Topological electronic structure and electronic nematicity in candidate kagome superconductors, ATi_3Bi_5 ($A = Rb, Cs$), *Supercond. Sci. Technol.* **37**, 123004 (2024).
- [15] See Supplemental Material at for experimental details, data analysis, and additional computational results (see, also, references [52–58] therein).
- [16] Y. Wang, Y. Liu, Z. Hao, W. Cheng, J. Deng, Y. Wang, Y. Gu, X.-M. Ma, H. Rong, F. Zhang, S. Guo, C. Zhang, Z. Jiang, Y. Yang, W. Liu, Q. Jiang, Z. Liu, M. Ye, D. Shen, Y. Liu, S. Cui, L. Wang, C. Liu, J. Lin, Y. Liu, Y. Cai, J. Zhu, C. Chen, and J.-W. Mei, Flat Band and Z_2 Topology of Kagome Metal $CsTi_3Bi_5$, *Chin. Phys. Lett.* **40**, 037102 (2023).
- [17] B. Liu, M.-Q. Kuang, Y. Luo, Y. Li, C. Hu, J. Liu, Q. Xiao, X. Zheng, L. Huai, S. Peng, Z. Wei, J. Shen, B. Wang, Y. Miao, X. Sun, Z. Ou, S. Cui, Z. Sun, M. Hashimoto, D. Lu, C. Jozwiak, A. Bostwick, E. Rotenberg, L. Moreschini, A. Lanzara, Y. Wang, Y. Peng, Y. Yao, Z. Wang, and J. He, Tunable Van Hove Singularity without Structural Instability in Kagome Metal $CsTi_3Bi_5$, *Phys. Rev. Lett.* **131**, 026701 (2023).
- [18] H. Yang, Y. Ye, Z. Zhao, J. Liu, X.-W. Yi, Y. Zhang, H. Xiao, J. Shi, J.-Y. You, Z. Huang, B. Wang, J. Wang, H. Guo, X. Lin, C. Shen, W. Zhou, H. Chen, X. Dong, G. Su, Z. Wang, and H.-J. Gao, Superconductivity and nematic order in a new titanium-based kagome metal $CsTi_3Bi_5$ without charge density wave order, *Nat. Commun.* **15**, 9626 (2024).
- [19] Y. Hu, C. Le, Y. Zhang, Z. Zhao, J. Liu, J. Ma, N. C. Plumb, M. Radovic, H. Chen, A. P. Schnyder, X. Wu, X. Dong, J. Hu, H. Yang, H.-J. Gao, and M. Shi, Non-trivial band topology and orbital-selective electronic ne-

- maticity in a titanium-based kagome superconductor, *Nat. Phys.* **19**, 1827 (2023).
- [20] H. Li, M. Ikeda, A. Suzuki, T. Taguchi, Y. Zhang, H. Goto, R. Eguchi, Y.-F. Liao, H. Ishii, and Y. Kubozono, Pressure dependence of superconductivity in alkali-Bi compounds KBi_2 and RbBi_2 , *Phys. Chem. Chem. Phys.* **24**, 7185 (2022).
- [21] S. Sankaralingam, S. M. Jaya, and R. Asokamani, Studies on the electronic structure and superconducting behavior of the intermetallic compounds ABi_2 ($A = \text{K}, \text{Rb}, \text{Cs}$), *J. Low Temp. Phys.* **88**, 1 (1992).
- [22] W. Wu, X. Bai, X. Wang, D. Liu, Z. Zeng, and L. Zou, Pressure-tuning topological phase transitions in Kagome superconductor CsTi_3Bi_5 (2024), [arXiv:2403.16119](https://arxiv.org/abs/2403.16119).
- [23] J. Y. Nie, X. F. Yang, X. Zhang, X. Q. Liu, W. Xia, D. Z. Dai, C. C. Zhao, C. P. Tu, X. M. Kong, X. B. Jin, Y. F. Guo, and S. Y. Li, Pressure-induced double-dome superconductivity in kagome metal CsTi_3Bi_5 (2023), [arXiv:2308.10129](https://arxiv.org/abs/2308.10129).
- [24] H. Li, S. Cheng, B. R. Ortiz, H. Tan, D. Werhahn, K. Zeng, D. Johrendt, B. Yan, Z. Wang, S. D. Wilson, and I. Zeljkovic, Electronic nematicity without charge density waves in titanium-based kagome metal, *Nat. Phys.* **19**, 1591 (2023).
- [25] Z. Jiang, Z. Liu, H. Ma, W. Xia, Z. Liu, J. Liu, S. Cho, Y. Yang, J. Ding, J. Liu, Z. Huang, Y. Qiao, J. Shen, W. Jing, X. Liu, J. Liu, Y. Guo, and D. Shen, Flat bands, non-trivial band topology and rotation symmetry breaking in layered kagome-lattice RbTi_3Bi_5 , *Nat. Commun.* **14**, 4892 (2023).
- [26] C. Bigi, M. Dürnagel, L. Klebl, A. Consiglio, G. Pokharel, F. Bertran, P. L. Fèvre, T. Jaouen, H. C. Tchouekem, P. Turban, A. D. Vita, J. A. Miwa, J. W. Wells, D. Oh, R. Comin, R. Thomale, I. Zeljkovic, B. R. Ortiz, S. D. Wilson, G. Sangiovanni, F. Mazzola, and D. D. Sante, Pomeranchuk instability from electronic correlations in CsTi_3Bi_5 kagome metal (2024), [arXiv:2410.22929](https://arxiv.org/abs/2410.22929).
- [27] P. Blaha, K. Schwarz, G. Madsen, D. Kvasnicka, J. Luitz, R. Laskowski, F. Tran, and L. Marks, WIEN2k, An Augmented Plane Wave + Local Orbitals Program for Calculating Crystal Properties (Karlheinz Schwarz, Techn. Universität Wien, Austria), 2018. ISBN 3-9501031-1-2.
- [28] P. Blaha, K. Schwarz, F. Tran, R. Laskowski, G. K. H. Madsen, and L. D. Marks, WIEN2k: An APW+lo program for calculating the properties of solids, *J. Chem. Phys.* **152**, 074101 (2020).
- [29] J. P. Perdew, K. Burke, and M. Ernzerhof, Generalized Gradient Approximation Made Simple, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [30] C. Ambrosch-Draxl and J. O. Sofo, Linear optical properties of solids within the full-potential linearized augmented planewave method, *Comput. Phys. Commun.* **175**, 1 (2006).
- [31] M. Wenzel, B. R. Ortiz, S. D. Wilson, M. Dressel, A. A. Tsirlin, and E. Uykur, Optical study of RbV_3Sb_5 : Multiple density-wave gaps and phonon anomalies, *Phys. Rev. B* **105**, 245123 (2022).
- [32] E. Uykur, B. R. Ortiz, O. Iakutkina, M. Wenzel, S. D. Wilson, M. Dressel, and A. A. Tsirlin, Low-energy optical properties of the nonmagnetic kagome metal CsV_3Sb_5 , *Phys. Rev. B* **104**, 045130 (2021).
- [33] E. Uykur, B. R. Ortiz, S. D. Wilson, M. Dressel, and A. A. Tsirlin, Optical detection of the density-wave instability in the kagome metal KV_3Sb_5 , *npj Quantum Mater.* **7**, 16 (2022).
- [34] S. Fratini, S. Ciuchi, and D. Mayou, Phenomenological model for charge dynamics and optical response of disordered systems: Application to organic semiconductors, *Phys. Rev. B* **89**, 235201 (2014).
- [35] S. Fratini and S. Ciuchi, Displaced Drude peak and bad metal from the interaction with slow fluctuations., *SciPost Phys.* **11**, 039 (2021).
- [36] J. Yang, X. Yi, Z. Zhao, Y. Xie, T. Miao, H. Luo, H. Chen, B. Liang, W. Zhu, Y. Ye, J.-Y. You, B. Gu, S. Zhang, F. Zhang, F. Yang, Z. Wang, Q. Peng, H. Mao, G. Liu, Z. Xu, H. Chen, H. Yang, G. Su, H. Gao, L. Zhao, and X. J. Zhou, Observation of flat band, Dirac nodal lines and topological surface states in Kagome superconductor CsTi_3Bi_5 , *Nat. Commun.* **14**, 4089 (2023).
- [37] Z. Dong, L. Shi, B. Wang, M. Huo, X. Huang, C. Huang, P. Ma, Y. Zhang, B. Shen, and M. Wang, The de Haas-van Alphen quantum oscillations in the kagome metal RbTi_3Bi_5 , *Chin. Phys. B* **33**, 107102 (2024).
- [38] Z. Rehfuss, C. Broyles, D. Graf, Y. Li, H. Tan, Z. Zhao, J. Liu, Y. Zhang, X. Dong, H. Yang, H. Gao, B. Yan, and S. Ran, Quantum oscillations in kagome metals CsTi_3Bi_5 and RbTi_3Bi_5 , *Phys. Rev. Mater.* **8**, 024003 (2024).
- [39] F. Xie, Y. Fang, Y. Li, Y. Huang, L. Chen, C. Setty, S. Sur, B. Yakobson, R. Valentí, and Q. Si, Electron correlations in the kagome flat band metal CsCr_3Sb_5 (2024), [arXiv:2403.03911](https://arxiv.org/abs/2403.03911).
- [40] Y. Guo, Z. Wang, F. Xie, Y. Huang, B. Gao, J. S. Oh, H. Wu, Z. Liu, Z. Ren, Y. Fang, A. Biswas, Y. Zhang, Z. Yue, C. Hu, C. Jozwiak, A. Bostwick, E. Rotenberg, M. Hashimoto, D. Lu, J. Kono, J.-H. Chu, B. I. Yakobson, R. J. Birgeneau, Q. Si, P. Dai, and M. Yi, Ubiquitous Flat Bands in a Cr-based Kagome Superconductor (2024), [arXiv:2406.05293](https://arxiv.org/abs/2406.05293).
- [41] Y. Li, Y. Liu, X. Du, S. Wu, W. Zhao, K. Zhai, Y. Hu, S. Zhang, H. Chen, J. Liu, Y. Yang, C. Peng, M. Hashimoto, D. Lu, Z. Liu, Y. Wang, Y. Chen, G. Cao, and L. Yang, Correlated Electronic Structure and Incipient Flat Bands of the Kagome Superconductor CsCr_3Sb_5 (2024), [arXiv:2406.03740](https://arxiv.org/abs/2406.03740).
- [42] M. Kawamura, FermiSurfer: Fermi-surface viewer providing multiple representation schemes, *Comput. Phys. Commun.* **239**, 197 (2019).
- [43] Y. Shao, A. N. Rudenko, J. Hu, Z. Sun, Y. Zhu, S. Moon, A. J. Millis, S. Yuan, A. I. Lichtenstein, D. Smirnov, Z. Q. Mao, M. I. Katsnelson, and D. N. Basov, Electronic correlations in nodal-line semimetals, *Nat. Phys.* **16**, 636 (2020).
- [44] M. M. Qazilbash, J. J. Hamlin, R. E. Baumbach, L. Zhang, D. J. Singh, M. B. Maple, and D. N. Basov, Electronic correlations in the iron pnictides, *Nat. Phys.* **5**, 647 (2009).
- [45] H. Rammal, A. Ralko, S. Ciuchi, and S. Fratini, Transient Localization from the Interaction with Quantum Bosons, *Phys. Rev. Lett.* **132**, 266502 (2024).
- [46] A. Biswas, O. Iakutkina, Q. Wang, H. C. Lei, M. Dressel, and E. Uykur, Spin-Reorientation-Induced Band Gap in Fe_3Sn_2 : Optical Signatures of Weyl Nodes, *Phys. Rev. Lett.* **125**, 076403 (2020).
- [47] M. Wenzel, A. A. Tsirlin, F. Capitani, Y. T. Chan, B. R. Ortiz, S. D. Wilson, M. Dressel, and E. Uykur, Pressure evolution of electron dynamics in the superconducting kagome metal CsV_3Sb_5 , *npj Quantum Mater.* **8**, 45

- (2023).
- [48] A. A. Tsirlin, P. Fertey, B. R. Ortiz, B. Klis, V. Merkl, M. Dressel, S. D. Wilson, and E. Uykur, Role of Sb in the superconducting kagome metal CsV_3Sb_5 revealed by its anisotropic compression, *SciPost Phys.* **12**, 049 (2022).
- [49] S. Mozaffari, W. R. Meier, R. P. Madhugaria, N. Peshcherenko, S.-H. Kang, J. W. Villanova, H. W. S. Arachchige, G. Zheng, Y. Zhu, K.-W. Chen, K. Jenkins, D. Zhang, A. Chan, L. Li, M. Yoon, Y. Zhang, and D. G. Mandrus, Universal sublinear resistivity in vanadium kagome materials hosting charge density waves, *Phys. Rev. B* **110**, 035135 (2024).
- [50] N. Peshcherenko, N. Mao, C. Felser, and Y. Zhang, Sublinear transport in Kagome metals: Interplay of Dirac cones and Van Hove singularities (2024), [arXiv:2404.11612](https://arxiv.org/abs/2404.11612).
- [51] L. Cao, X. Liu, J. Cheng, B. Gao, X. Zhang, Y. Guo, F. Ma, and R. Chen, Infrared spectroscopy study of kagome material CsTi_3Bi_5 (2024), [arXiv:2409.03688](https://arxiv.org/abs/2409.03688).
- [52] D. B. Tanner, Use of x-ray scattering functions in Kramers-Kronig analysis of reflectance, *Phys. Rev. B* **91**, 035123 (2015).
- [53] K. Momma and F. Izumi, *VESTA*: a three-dimensional visualization system for electronic and structural analysis, *J. Appl. Crystallogr.* **41**, 653 (2008).
- [54] C. C. Homes, M. Reedyk, D. A. Cradles, and T. Timusk, Technique for measuring the reflectance of irregular, submillimeter-sized samples, *Appl. Opt.* **32**, 2976 (1993).
- [55] M. Dressel and G. Grüner, *Electrodynamics of Solids: Optical Properties of Electrons in Matter* (Cambridge University Press, 2002).
- [56] U. Fano, Effects of Configuration Interaction on Intensities and Phase Shifts, *Phys. Rev.* **124**, 1866 (1961).
- [57] M. Wenzel, A. A. Tsirlin, O. Iakutkina, Q. Yin, H. C. Lei, M. Dressel, and E. Uykur, Effect of magnetism and phonons on localized carriers in the ferrimagnetic kagome metals GdMn_6Sn_6 and TbMn_6Sn_6 , *Phys. Rev. B* **106**, L241108 (2022).
- [58] G. Kresse and J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, *Phys. Rev. B* **54**, 11169 (1996).

Supplemental Material for "Interplay of *d*- and *p*-States in RbTi_3Bi_5 and CsTi_3Bi_5 Flat-Band Kagome Metals"

M. Wenzel,^{1,*} E. Uykur,² A. A. Tsirlin,³ A. N. Capa Salinas,⁴ B. R. Ortiz,⁵ S. D. Wilson,⁴ and M. Dressel¹

¹*Physikalisches Institut, Universität Stuttgart, 70569 Stuttgart, Germany*

²*Helmholtz-Zentrum Dresden-Rossendorf, Institute of Ion Beam Physics and Materials Research, 01328 Dresden, Germany*

³*Felix Bloch Institute for Solid-State Physics, Leipzig University, 04103 Leipzig, Germany*

⁴*Materials Department and California Nanosystems Institute,*

University of California Santa Barbara, Santa Barbara, CA, 93106, USA

⁵*Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831, USA*

(Dated: January 31, 2025)

CRYSTAL STRUCTURE

ATi_3Bi_5 compounds crystallize in the $P6/mmm$ space group with Ti atoms forming kagome layers stacked along the *c*-axis. Bi1 atoms occupy the centers of the hexagons within these kagome networks, while a second Bi2 honeycomb sublattice, along with alkali ions, spatially separates the kagome layers. This arrangement results in well-isolated kagome planes and an overall quasi-two-dimensional (2D) structure, as shown in Fig. S1.

ATi_3Bi_5 (A = Rb, Cs)

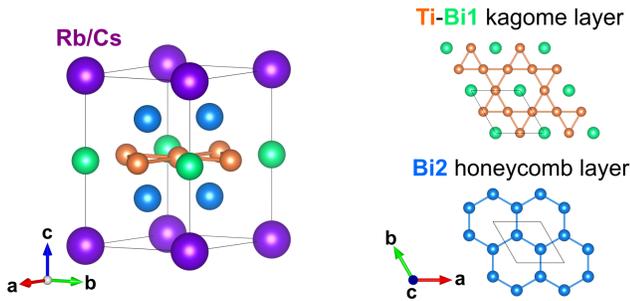


FIG. S1. Crystal structure of ATi_3Bi_5 compounds visualized using VESTA [S1, S2]. The right panel highlights the two different Bi sublattices.

EXPERIMENTAL DETAILS

Samples with lateral dimensions of $\sim 2 \times 3 \text{ mm}^2$ were freshly cleaved and prepared in a glove box under argon atmosphere. Prior to conducting temperature-dependent reflectivity measurements, we tested the air sensitivity of CsTi_3Bi_5 , summarized in Fig. S2(a). Here, the sample was exposed to air, and mid-infrared spectra were collected over a four-hour span. Within just three minutes, a noticeable dip began to form around 4000 cm^{-1} , which continued to increase upon longer exposure, indicating substantial alterations in the bulk electronic structure of the material. The far-infrared reflectivity spectrum of a degraded CsTi_3Bi_5 sample, collected four hours post-

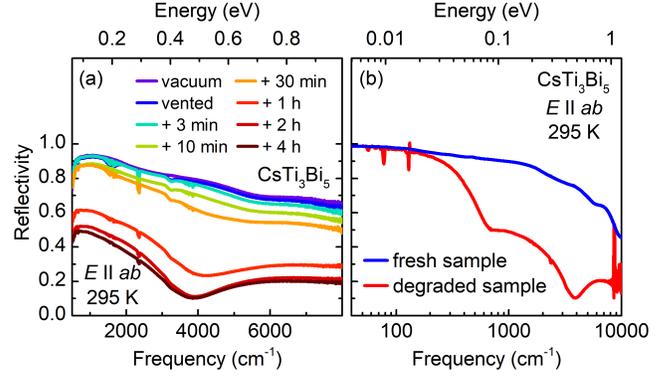


FIG. S2. (a) Reflectivity of CsTi_3Bi_5 in the mid-infrared range measured as a function of exposure time of the sample to air. The absolute curves are normalized to the far-infrared spectra. (b) Far- to mid-infrared spectra of CsTi_3Bi_5 for a fresh samples and a degraded sample. For the later case the sample was exposed to air for $> 4 \text{ h}$.

exposure to air, is presented in panel (b), merged with the mid-infrared data. The combined data reveal a substantial decrease in reflectivity already around 300 cm^{-1} , suggesting a pronounced shift of the plasma frequency to lower energies and, consequently, a significant reduction in carrier density. Visually, this degradation process leads to tarnishing of the sample's surface within just a few hours.

Temperature- and frequency-dependent reflectivity spectra were measured in the *ab*-plane utilizing two different spectrometer setups. For high energies ($600 \text{ cm}^{-1} \leq \omega \leq 18000 \text{ cm}^{-1}$), a Vertex80v spectrometer coupled to a Hyperion IR microscope was used. Freshly evaporated gold mirrors served as the reference throughout the measurements. The low-energy range ($50 \text{ cm}^{-1} \leq \omega < 600 \text{ cm}^{-1}$) was measured with an IFS113v spectrometer and a custom-built cryostat. To prevent degradation, the samples were mounted into the cryostats and aligned within the glovebox. The cryostat used for measurements in the high-energy range was sealed with aluminum tape, while a custom-built sleeve was used for the cryostat designed for far-infrared measurements, maintaining an argon atmosphere inside. The cryostats were

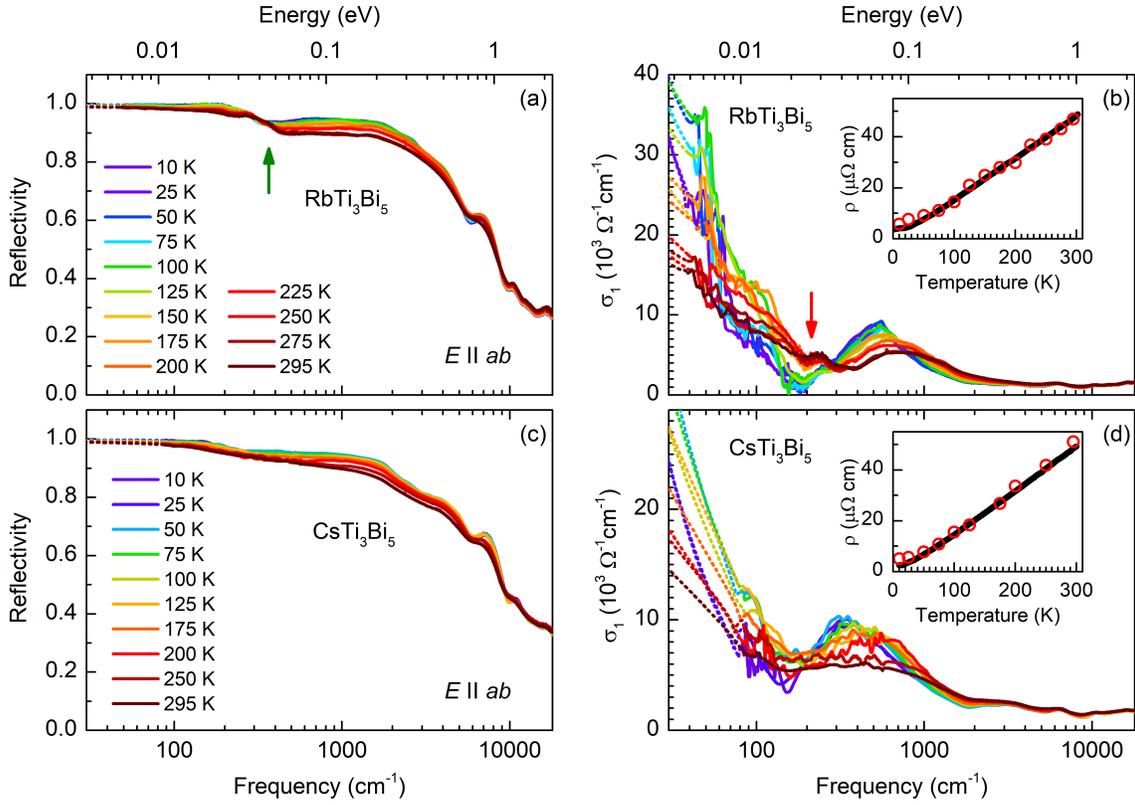


FIG. S3. (a) and (c) Temperature-dependent reflectivities of RbTi₃Bi₅ and CsTi₃Bi₅, respectively, measured in the *ab*-plane. Dotted lines indicate the Hagen-Rubens extrapolations to low energies. The green arrow marks the sudden drop in reflectivity leading to the sharp onset of the localization peak. (b) and (d) Calculated real part of the optical conductivities. The red arrow indicates the Fano resonance observed in the spectra of RbTi₃Bi₅. The insets show the dc resistivity taken from Ref. [S2] overlapped with the dc resistivity values obtained from the Hagen-Rubens fits of the measured spectra (open red circles). The dc resistivity curve was normalized to the values obtained by the optical studies.

then transferred to the experimental setups and promptly evacuated, reaching a pressure of $p < 10^{-2}$ mbar in under two minutes.

The absolute value of the reflectivity was determined with higher accuracy using the gold-overcoating technique as described in Ref. [S3] in the far-infrared range. However, using the usual gold evaporation parameters resulted in a tarnished gold coating, indicating a chemical reaction. Hence, for measurements in the far-infrared range, we chose to evaporate aluminum that preserved the shiny metallic surface of the samples, and used freshly prepared aluminum mirrors as reference.

Figs. S3(a) and (c) present the temperature-dependent reflectivity spectra of RbTi₃Bi₅ and CsTi₃Bi₅, respectively. The high reflectivity values throughout all temperatures demonstrate the metallic nature of the samples and assure that the samples remained intact without any signs of oxidation or degradation throughout the measurements. The Hagen-Rubens extrapolations at the low frequency limit are plotted with dotted lines. The obtained dc resistivity values match well with the four-probe dc resistivity adapted from Ref. [S2] after normal-

ization of the data [see insets of Figs. S3(b) and (d)]. For high-energies, the reflectivity data are extrapolated using x-ray scattering functions [S4]. The optical conductivities calculated via standard Kramers-Kronig analysis [S5] are given in Figs. S3(b) and (d).

DECOMPOSITION

Different contributions to the total optical conductivity are modeled with the Drude-Lorentz approach. The dielectric function [$\tilde{\epsilon} = \epsilon_1 + i\epsilon_2$] is expressed as

$$\tilde{\epsilon}(\omega) = \epsilon_\infty - \frac{\omega_{p,\text{Drude}}^2}{\omega^2 + i\omega/\tau_{\text{Drude}}} + \sum_j \frac{\Omega_j^2}{\omega_{0,j}^2 - \omega^2 - i\omega\gamma_j}, \quad (\text{S1})$$

with ϵ_∞ being the high-energy contributions to the real part of the dielectric permittivity. The Drude parameters $\omega_{p,\text{Drude}}$ and $1/\tau_{\text{Drude}}$ describe the plasma frequency and the scattering rate of the itinerant carriers, respectively. Lorentzians with the resonance frequency $\omega_{0,j}$, the strength of the oscillation Ω_j , and the width γ_j are

used to model the interband absorptions.

The complex optical conductivity $[\tilde{\sigma} = \sigma_1 + i\sigma_2]$ is calculated as

$$\tilde{\sigma}(\omega) = -i\omega\varepsilon_0[\tilde{\varepsilon}(\omega) - \varepsilon_\infty], \quad (\text{S2})$$

with ε_0 being the vacuum permittivity.

In addition to the classical Drude-Lorentz approach, we use the displaced Drude peak formalism proposed in 2014 by Fratini *et al.* [S6] to model the intraband response of localized charge carriers. Here, interactions of charge carriers with low-energy degrees of freedom, such as phonons and electric or magnetic fluctuations, can lead to a backscattering of the electrons, with a characteristic time τ_b . The resulting localization effect shifts the classical Drude peak from zero frequency to a finite value. The occurrence of such broad, low-energy, temperature-dependent absorption peaks is a common feature in strongly correlated electron systems [S7] and is also characteristic for the optical spectra of kagome metals [S8–S12]. The real part of the optical conductivity reads

$$\tilde{\sigma}_{\text{localization}}(\omega) = \frac{C}{\tau_b - \tau} \frac{\tanh\left\{\frac{\hbar\omega}{2k_B T}\right\}}{\hbar\omega} \cdot \text{Re} \left\{ \frac{1}{1 - i\omega\tau} - \frac{1}{1 - i\omega\tau_b} \right\}, \quad (\text{S3})$$

where C is a constant, \hbar is the reduced Planck constant, k_B the Boltzmann constant, and τ the elastic scattering time of the standard Drude model.

The asymmetric phonon mode observed in the spectra of RbTi_3Bi_5 , at approximately 200 cm^{-1} , is reproduced most accurately by the Fano model [S13]

$$\sigma_1(\omega) = \frac{\sigma_0\omega\gamma[\gamma\omega(q^2 - 1) + 2q(\omega^2 - \omega_0^2)]}{4\pi[(\omega^2 - \omega_0^2)^2 + \gamma^2\omega^2]}. \quad (\text{S4})$$

Here, σ_0 is the resonance strength, γ the damping and ω_0 the resonance frequency. The shape of the Fano resonance highly depends on the dimensionless parameter, q . The typical asymmetric line shape is obtained for moderate values of $|q|$, while for $|q| \rightarrow \infty$, the line evolves into a symmetric Lorentzian. For $q = 0$, a strong symmetric anti-resonance is observed.

The total optical conductivity takes the form

$$\tilde{\sigma}(\omega) = \underbrace{\tilde{\sigma}_{\text{Drude}} + \tilde{\sigma}_{\text{localization}}}_{\text{intraband}} + \underbrace{\tilde{\sigma}_{\text{Fano}}}_{\text{phonon}} + \underbrace{\tilde{\sigma}_{\text{Lorentzians}}}_{\text{interband}}. \quad (\text{S5})$$

The reliability of the fits is ensured by fitting the reflectivity, and the complex optical conductivity simultaneously. Fig. S4 displays the decomposed real part of the optical conductivity at selected temperatures.

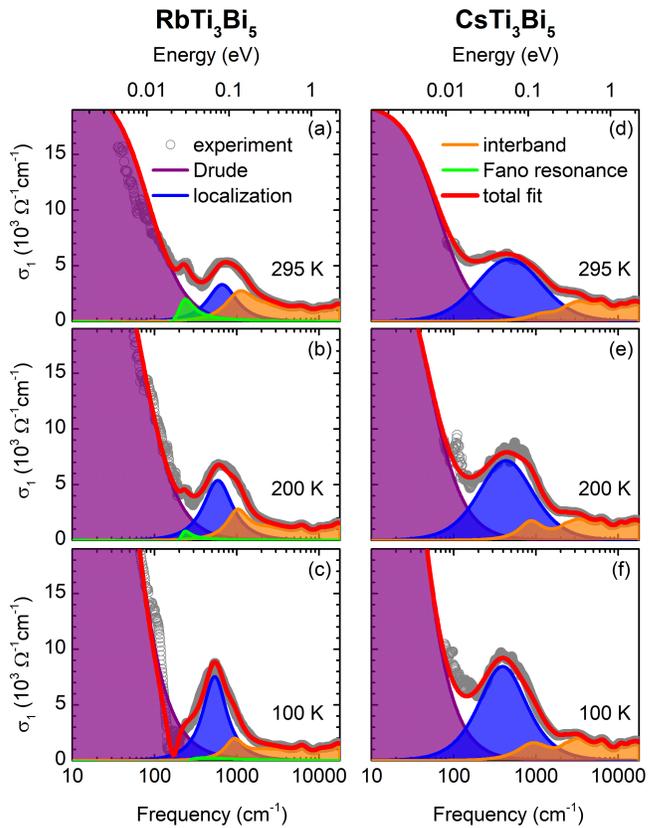


FIG. S4. Decomposed optical conductivities of RbTi_3Bi_5 (a-c) and CsTi_3Bi_5 (d-f) at selected temperatures, consisting of a Drude peak (purple), a localization peak (blue), several interband transitions (orange), and a Fano resonance (green) in the case of RbTi_3Bi_5 .

LOCALIZATION PEAK

In the absence of low-energy interband transitions, the absorption peaks below 1000 cm^{-1} should be interpreted as localization peaks, similar to GdMn_6Sn_6 and KV_3Sb_5 [S10, S11]. When focusing solely on the room temperature data, clear differences between the localization peaks in RbTi_3Bi_5 and CsTi_3Bi_5 become apparent. In RbTi_3Bi_5 , the response from localized carriers is significantly less intense, albeit much sharper than in CsTi_3Bi_5 . These characteristics mirror those of the vanadium-based AV_3Sb_5 counterparts [S9, S12], suggesting that the alkali ions may influence the behavior of localized carriers, potentially due to interactions between the alkali ions and the kagome layers, facilitated by the large ionic radius of the alkali ions.

In RbTi_3Bi_5 , the localization peak is so sharp that it cannot be modeled by Eq. S3. Specifically, the sharp onset of the peak at lower energies, which results from the sudden drop in reflectivity marked by the green arrow in Fig. S3(a), cannot be adequately captured by this model. Consequently, a simple Lorentzian was employed

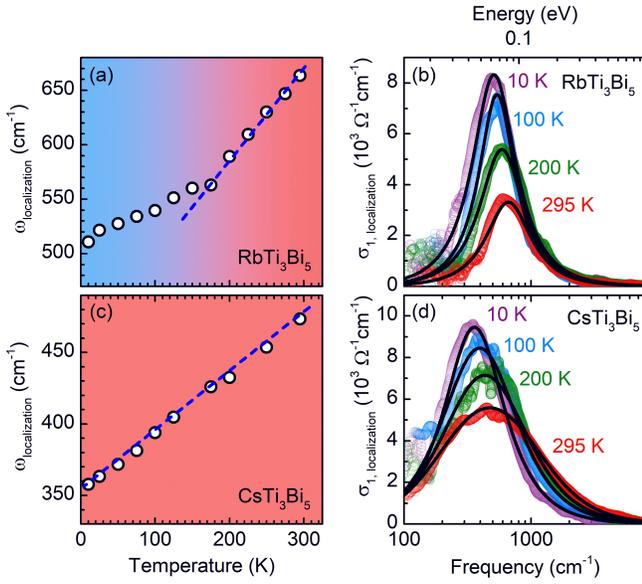


FIG. S5. (a) and (c) Temperature-dependent localization peak position in RbTi_3Bi_5 and CsTi_3Bi_5 , respectively. (b) and (d) Temperature evolution of the localization peak, obtained by subtracting the fitted Drude, interband contributions, and Fano resonance from the spectra. The solid lines are the fits of the localization peak from the decomposed optical conductivities given in Fig. S4.

to fit the localization peak in RbTi_3Bi_5 . Nonetheless, it is important to emphasize that these mathematical challenges in modeling the localization peak do not alter the fundamental understanding of its underlying physical mechanism.

In fact, a sharp absorption peak is in line with the theoretical framework by Fratini *et al.*, where a broader localization peak can evolve into a sharp resonance as the temperature reduces and the peak frequency approaches the frequency of the interacting bosonic mode [S14]. Upon reducing the temperature, the localization peak in RbTi_3Bi_5 shows only a slight, continuous sharpening as illustrated in Fig. S5(b).

The positions of the localization peaks as a function of temperature given in Figs. S5(a) and (c) for RbTi_3Bi_5 and CsTi_3Bi_5 , respectively, exhibit a linear red shift with decreasing temperature. In the case of CsTi_3Bi_5 , this trend continues down to the lowest temperatures, while for RbTi_3Bi_5 , a significant change in the slope is observed below ~ 150 K.

FANO RESONANCE

Γ -point phonons were calculated in VASP [S15] using the frozen-phonon method. These calculations reveal two infrared-active modes with energies comparable to the phonon mode observed in the room temperature spec-

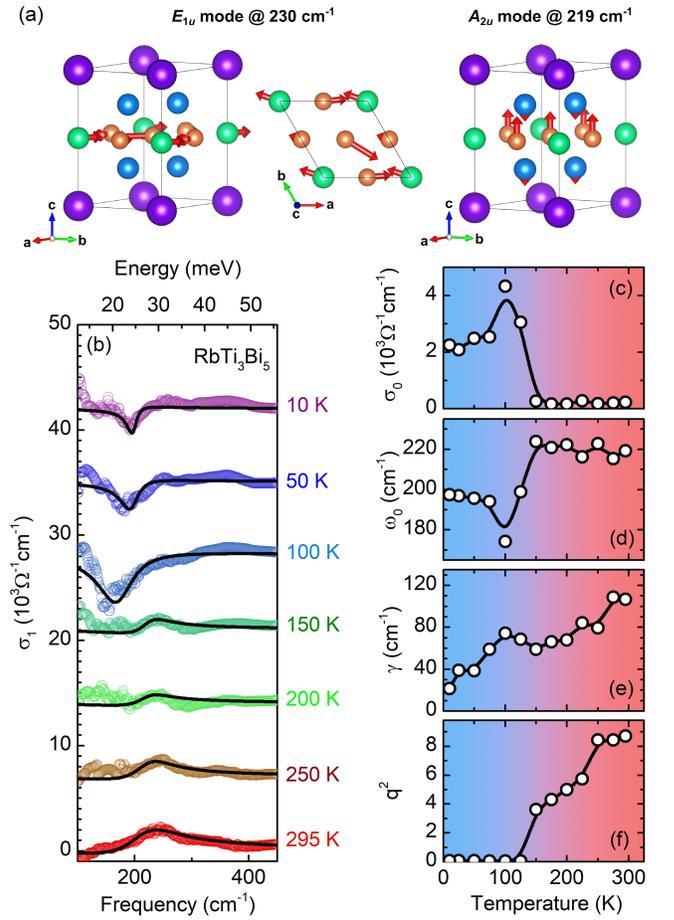


FIG. S6. (a) Sketch of the infrared-active in-plane E_{1u} (left) and out-of-plane A_{2u} (right) modes. (b) Optical conductivity at low energies presented as $\Delta\sigma_1(\omega)$ with intra- and interband contributions subtracted and the baselines shifted by $7000 \Omega^{-1}\text{cm}^{-1}$ for clarity. The solid black lines are the fits to the phonon mode using the Fano model with the fit parameters given in panels (c-f).

trum of RbTi_3Bi_5 . One is an in-plane E_{1u} mode at 230 cm^{-1} involving mainly atomic displacements within the kagome Ti-Bi1 network as sketched in Fig. S6(a). The second mode is an out-of-plane A_{2u} mode at 219 cm^{-1} and, therefore, is not expected to be detected in our in-plane optical measurements.

Fig. S6(b) displays the temperature evolution of the phonon mode observed in RbTi_3Bi_5 , obtained after subtracting the intra- and interband contributions from the optical conductivity. Solid black lines are the Fano fits obtained by decomposing the optical spectra. Below 150 K a sudden change in the shape of the mode is observed. Here, the mode evolves into a sharp, more symmetric antiresonance, which is further accompanied by a redshift of the mode as seen in the fit parameters in panels (c-f).

ADDITIONAL DFT RESULTS

Self-consistent density-functional calculations were performed on the k -mesh with $20 \times 20 \times 11$ points. Optical conductivity was calculated on a denser k -mesh with up to $46 \times 46 \times 23$ points. DFT+ U calculations were performed by adding a Hubbard U to the Ti d -orbitals with the FLL (fully localized limit) and AMF (around mean field) double-counting corrections.

Fig. S7 presents the calculated Fermi surface, band structure, and the band-resolved optical conductivity of CsTi_3Bi_5 . In contrast to RbTi_3Bi_5 , the additional Fermi surface pockets at $k_z = 0.5$ are formed by band F according to the labeling in panel (b). Overall, the same interband contributions are observed as for RbTi_3Bi_5 [see Fig. 3(c) in main text], however, the low-energy transitions between band E and F are dampened, while transitions between band C and D have larger spectral weight at very low energies. As discussed in the main text, these fine differences are attributed to modifications of the tilted Dirac bands along A - L and H - A . As presented in Fig. S8, the alkali ion leads to a shift of these Dirac points with respect to the Fermi energy, while the atomic contribution to the bands, namely Bi1 and Bi2 p_z states, remains unaffected as illustrated in Fig. S9 and Fig. 1(b) and (c).

As discussed in the main text, the best agreement between the experimental and calculated optical conductivities is obtained upon shifting the Fermi level by -177 meV (RbTi_3Bi_5) and -179 meV (CsTi_3Bi_5). Nominally, this shift corresponds to a hole doping of $-0.8e/f.u.$ (RbTi_3Bi_5) and $-0.9e/f.u.$ (CsTi_3Bi_5) but it reflects the renormalization of band energies in the vicinity of the correlated flat bands, because such large changes in the number of electrons could not be caused by defects, impurities, and minor off-stoichiometry. Alternatively, we tried to reproduce the experimental results using DFT+ U calculations, but the agreement was poor, as shown in Fig. S10. While additional low-energy spectral weight is created by adding an on-site Coulomb repulsion $U = 5$ eV, this essentially shifts the Ti flat bands farther away from the Fermi energy, as well as leads to band saddle points below E_F [see panel (b) green line], which is inconsistent with the ARPES studies. We have further tested the inclusion of Hund's coupling with $J = 1$ eV shown in blue, resulting in a similar downward shift of the flat bands and significant changes in the Fermi surface at $k_z = 0$.

PLASMA FREQUENCY

The experimental plasma frequencies are obtained from the spectral weight (SW) analysis of the Drude and

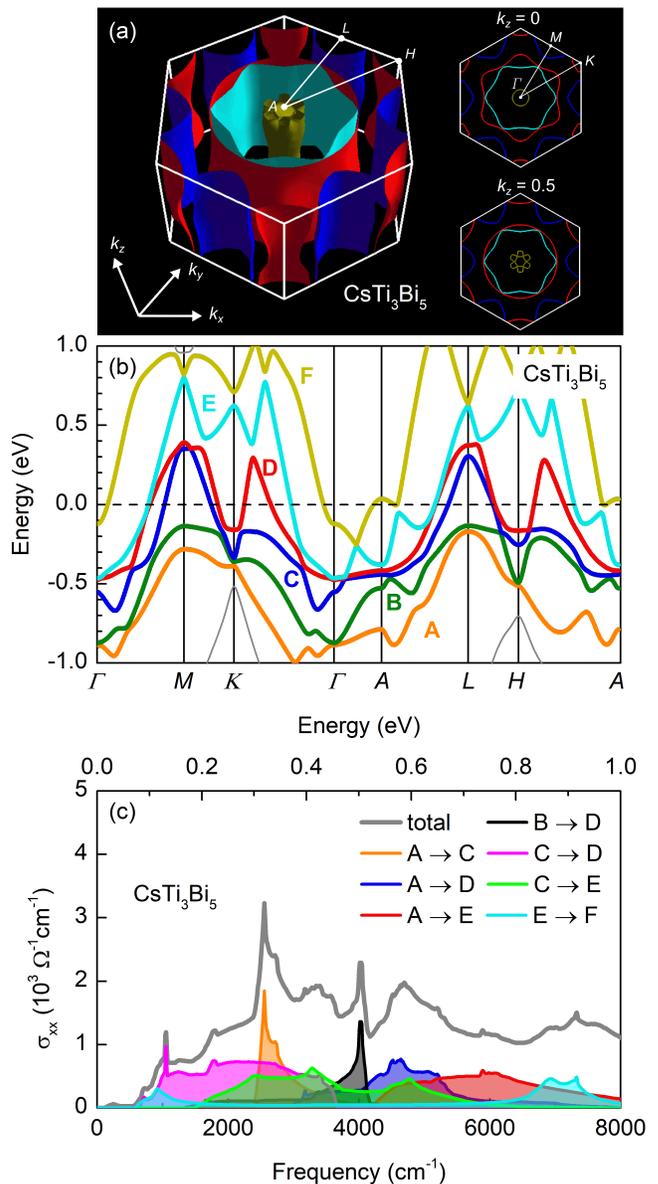


FIG. S7. (a) Fermi surface of CsTi_3Bi_5 constructed from the calculated band structure with the Fermi level shifted down by 179 meV to match the experimental data. FermiSurfer program was used for the visualization [S16]. (b) Calculated band structure of CsTi_3Bi_5 with the experimentally determined position of the Fermi level. (c) Band-resolved in-plane optical conductivity with different colors representing contributions from interband optical transitions between different bands following the labeling in panel (b). Note that no broadening is introduced to the calculations.

localization peaks according to

$$\omega_p = \sqrt{SW_{\text{Drude}} + SW_{\text{loc}}}. \quad (\text{S6})$$

The spectral weight is calculated from the optical data by integrating the real part of the optical conductivity of

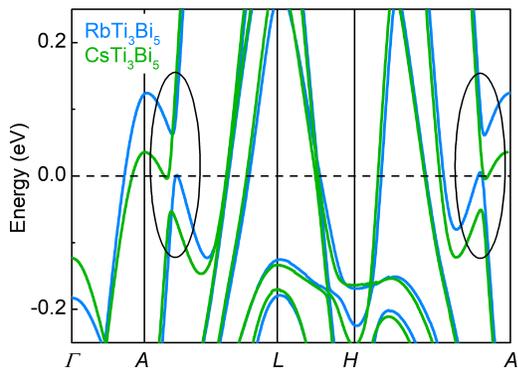


FIG. S8. Detailed view of the band structures at $k_z = 0.5$ for RbTi_3Bi_5 (blue) and CsTi_3Bi_5 (green). The Fermi levels are shifted downward as discussed in the main text. Black ovals mark the shift observed in the tilted Dirac-like bands along $A-L$ and $H-A$.

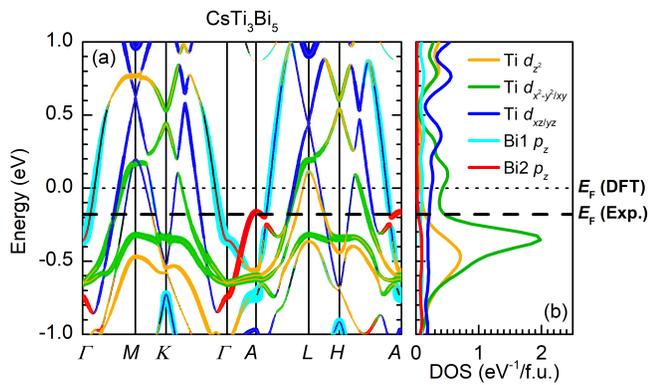


FIG. S9. (a) Band structure of CsTi_3Bi_5 with different colors representing contributions from different atomic orbitals as labeled in panel (b) showing the corresponding density of states (DOS). The experimentally determined position of the Fermi energy is shown by the dashed line.

the fitted Drude and localization peaks

$$SW = \frac{1}{\pi^2 \epsilon_0 c} \int_0^{\omega_c} \sigma_1(\omega) d\omega, \quad (\text{S7})$$

with c being the speed of light. The cut-off frequency is chosen as $\omega_c = 50000 \text{ cm}^{-1}$, taking into account the high-energy tail of the localization peak.

Considering the error bars in determining the plasma frequency arising from (i) only catching the high-energy tail of the sharp Drude contribution in our measurements and (ii) the localization peak overlapping with interband transitions and the Fano resonance in the case of RbTi_3Bi_5 , the experimental plasma frequency does not depend on temperature. This further supports the absence of a structural phase transition that would likely create changes in the carrier density and/or the effective mass and consequently, in ω_p .

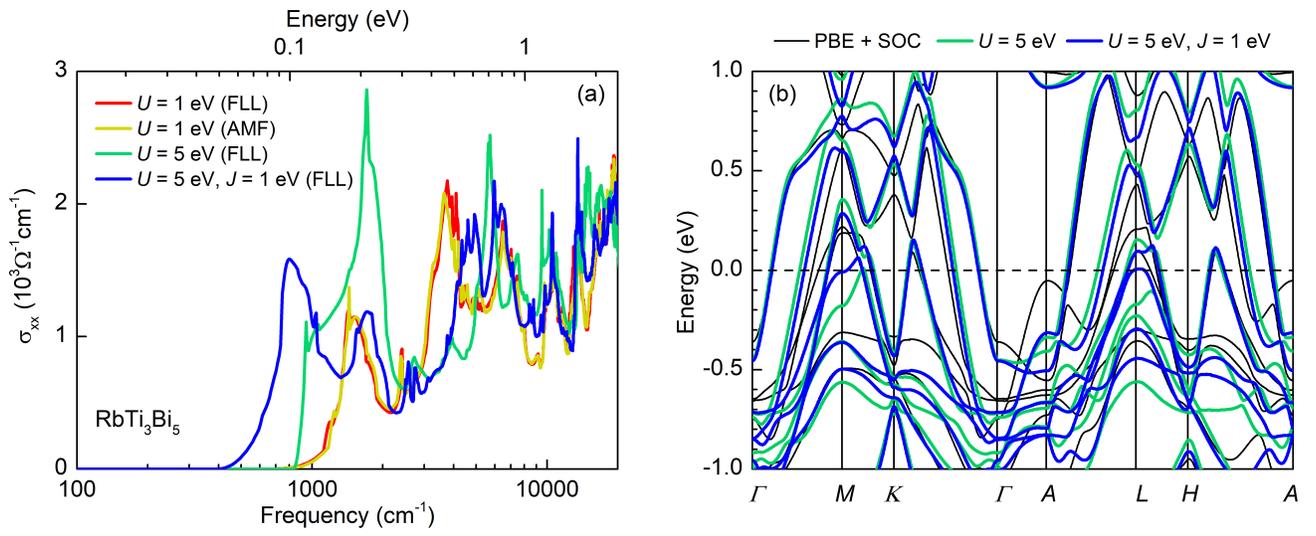


FIG. S10. (a) Calculated in-plane optical conductivities with different DFT+ U parameterizations. Note that no broadening is introduced to the calculations. While adding correlations to the Ti d -orbitals creates additional spectral weight at low energies similar to the experimental data, it significantly modifies the band structure as presented in panel (b). Most importantly, adding a Hubbard U shifts the Ti flat bands away from the Fermi energy, contradicting the observations by ARPES studies.

-
- * maxim.wenzel@pi1.physik.uni-stuttgart.de
- [S1] K. Momma and F. Izumi, *VESTA*: a three-dimensional visualization system for electronic and structural analysis, *J. Appl. Crystallogr.* **41**, 653 (2008).
- [S2] D. Werhahn, B. R. Ortiz, A. K. Hay, S. D. Wilson, R. Seshadri, and D. Johrendt, The kagomé metals RbTi_3Bi_5 and CsTi_3Bi_5 , *Z. Naturforsch. B* **77**, 757 (2022).
- [S3] C. C. Homes, M. Reedyk, D. A. Cradles, and T. Timusk, Technique for measuring the reflectance of irregular, submillimeter-sized samples, *Appl. Opt.* **32**, 2976 (1993).
- [S4] D. B. Tanner, Use of x-ray scattering functions in Kramers-Kronig analysis of reflectance, *Phys. Rev. B* **91**, 035123 (2015).
- [S5] M. Dressel and G. Grüner, *Electrodynamics of Solids: Optical Properties of Electrons in Matter* (Cambridge University Press, 2002).
- [S6] S. Fratini, S. Ciuchi, and D. Mayou, Phenomenological model for charge dynamics and optical response of disordered systems: Application to organic semiconductors, *Phys. Rev. B* **89**, 235201 (2014).
- [S7] S. Fratini and S. Ciuchi, Displaced Drude peak and bad metal from the interaction with slow fluctuations., *SciPost Phys.* **11**, 039 (2021).
- [S8] A. Biswas, O. Iakutkina, Q. Wang, H. C. Lei, M. Dressel, and E. Uykur, Spin-Reorientation-Induced Band Gap in Fe_3Sn_2 : Optical Signatures of Weyl Nodes, *Phys. Rev. Lett.* **125**, 076403 (2020).
- [S9] E. Uykur, B. R. Ortiz, O. Iakutkina, M. Wenzel, S. D. Wilson, M. Dressel, and A. A. Tsirlin, Low-energy optical properties of the nonmagnetic kagome metal CsV_3Sb_5 , *Phys. Rev. B* **104**, 045130 (2021).
- [S10] E. Uykur, B. R. Ortiz, S. D. Wilson, M. Dressel, and A. A. Tsirlin, Optical detection of the density-wave instability in the kagome metal KV_3Sb_5 , *npj Quantum Mater.* **7**, 16 (2022).
- [S11] M. Wenzel, A. A. Tsirlin, O. Iakutkina, Q. Yin, H. C. Lei, M. Dressel, and E. Uykur, Effect of magnetism and phonons on localized carriers in the ferrimagnetic kagome metals GdMn_6Sn_6 and TbMn_6Sn_6 , *Phys. Rev. B* **106**, L241108 (2022).
- [S12] M. Wenzel, B. R. Ortiz, S. D. Wilson, M. Dressel, A. A. Tsirlin, and E. Uykur, Optical study of RbV_3Sb_5 : Multiple density-wave gaps and phonon anomalies, *Phys. Rev. B* **105**, 245123 (2022).
- [S13] U. Fano, Effects of Configuration Interaction on Intensities and Phase Shifts, *Phys. Rev.* **124**, 1866 (1961).
- [S14] H. Rammal, A. Ralko, S. Ciuchi, and S. Fratini, Transient Localization from the Interaction with Quantum Bosons, *Phys. Rev. Lett.* **132**, 266502 (2024).
- [S15] G. Kresse and J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, *Phys. Rev. B* **54**, 11169 (1996).
- [S16] M. Kawamura, FermiSurfer: Fermi-surface viewer providing multiple representation schemes, *Comput. Phys. Commun.* **239**, 197 (2019).