Magnetic texture control in ion-implanted metamaterials

Christina Vantaraki,^{1, *} Kristina Ignatova,² Dmitrii Moldarev,¹ Matías P. Grassi,¹

Michael Foerster,³ Daniel Primetzhofer,¹ Unnar B. Arnalds,² and Vassilios Kapaklis^{1,†}

¹Department of Physics and Astronomy, Uppsala University, Box 516, 75120 Uppsala, Sweden

²Science Institute, University of Iceland, Dunhaga 3, Reykjavik 107, Iceland

³ALBA Synchrotron Light Facility, 08290-Cerdanyola del Valles, Barcelona, Spain

We study experimentally the impact of the additive fabrication method on the magnetic properties of Fe^+ implanted Pd square artificial spin ice lattices. Our findings show that these lattices undergo magnetic collapse at higher temperatures than their continuous film counterparts. This behavior is attributed to the additive fabrication process, which induces an inhomogeneous Fe concentration within the lattice building blocks. Moreover, the implantation process creates a magnetic depth profile, enabling temperature-dependent tunability of the magnetic thickness. These additional internal degrees of freedom broaden the design possibilities for magnetic metamaterials, allowing precise fine-tuning of their static and dynamic properties to achieve complex and customizable behaviors.

I. INTRODUCTION

Complex systems are characterized by interactions among their components that lead to the spontaneous emergence of collective properties. In condensed matter physics, magnetic metamaterials have become an exemplary platform for investigating such complexity. These systems consist of arrays of ferromagnetic elements of sub- μ m size that interact magnetostatically [1, 2], with these interactions giving rise to emergent phenomena, including collective magnetic order [3-8] and dynamics [9–15]. The building blocks of magnetic metamaterials, mesoscopic ferromagnetic elements, are often approximated as point-like magnetic dipoles or artificial magnetic atoms. While these analogies are useful, they fall short in capturing phenomena such as thermal fluctuations and phase transitions. Recent studies have provided a more nuanced analysis of the intrinsic magnetic properties and dynamics of these elements [16-20]. In a notable example, the initially simulated internal degrees of freedom, leading to excess entropy and modification of dynamics as reported by Gliga et al. [16]. were later experimentally verified, with their temperaturedependent behavior characterized in detail by Skovdal et al. [21]. These systems bridge theoretical models of complexity with experimental realizations, enabling studies of the interplay between competing interactions [22-24], frustration, and exotic magnetic phases [25, 26]. In addition to their fundamental significance, the complexity in magnetic metamaterials has fueled technological advancements in fields such as spintronics [27], data storage [28], and unconventional computation [29, 30].

In this work, we explore how magnetic metamaterials can serve as a platform to deepen our understanding of complexity in physics. Using electron-beam lithography and ion implantation techniques [31], we fabricated ferromagnetic elements with intrinsic compositional and magnetic inhomogeneities. Our investigation examines the effects of these inhomogeneities on the ordering temperature of extended arrays and the internal magnetic textures of individual elements. The study focuses on square artificial spin ice (ASI) lattices composed of elongated, stadium-shaped nanoelements—referred to as *mesospins*. While ASIs have been widely studied for emergent order [3, 5] and thermally induced dynamics [9, 21, 32] in mesospins made from isotropic and homogeneous magnetic materials, our work provides a direct comparison with systems exhibiting intrinsic mesospin inhomogeneities. This comparison not only enhances our understanding of their fundamental behavior but also underscores their potential for practical applications [16], as it enables the deliberate design of both the static and dynamic properties of magnetic metamaterials.

II. MATERIALS AND METHODS

A. Sample fabrication


Two samples were studied, having different Fe concentrations. Both were fabricated by implanting 30 keV 56 Fe⁺ into a Pd film through a patterned Cr mask. The Pd film, deposited using DC magnetron sputtering on a MgO substrate, consisted of a 60 nm Pd laver with a 5 nm V adhesion laver and a 6 nm Cr capping layer. This additive fabrication process yields flat Fe_xPd_{100-x} (where x stands for at.%) ferromagnetic structures, where Fe has a concentration-depth profile. A detailed description about the fabrication process is provided in Vantaraki et al. [31]. One sample was implanted with a nominal fluence of 2.7×10^{16} ions/cm², while the other was implanted with 3×10^{16} ions/cm². Higher fluences yield higher Fe concentration [33]. In both samples, the stadium-shaped elements have a length of L = 470 nm and width W = 170 nm, while the edge-to-edge gap between the elements is g = 170 nm (see Fig. 1).

B. Hysteresis protocols

The temperature-dependent hysteretic behavior of implanted ASIs was studied using a longitudinal magneto-

^{*} Contact author: christina.vantaraki@physics.uu.se

[†] Contact author: vassilios.kapaklis@physics.uu.se




E. Micromagnetic simulations

The magnetic texture of the inhomogeneous mesospins was explored by performing micromagnetic simulations using MuMax³ [36]. To mimic the experimental conditions, the simulations were performed with stadium-shaped elements of dimensions $470 \times 170 \text{ nm}^2$ arranged on a square lattice. The edge-to-edge gap between the elements was g = 170 nm. The elements were considered to be composed of Fe with a thickness 3.18 nm. This thickness corresponds to a continuous Fe layer implanted with a nominal fluence of $2.7 \times 10^{16} \text{ ions/cm}^2$ (see Supplemental Material). The elements were discretized into grid cells with cell size smaller than the exchange length and equal to 2.5 nm.

III. RESULTS AND DISCUSSION

We begin by comparing the amount of Fe implanted into the ASI array with that in its reference continuous film that was prepared and implanted next to the lattice, with a nominal fluence of 2.7×10^{16} ions/cm². To do so, we examine the ordering temperature for these two samples. The ordering temperature is defined as the temperature where the spontaneous magnetization vanishes. To a good approximation, this temperature coincides with the temperature where the remanent magnetization disappears [37]. As such, we examine the temperature-dependent behavior of the remanent magnetization M_{rem} from the MOKE measurements. As shown in Fig. 2 (a), the remanent magnetization vanishes at higher temperatures for the implanted ASIs compared to the reference implanted film, reflecting a higher ordering temperature. It is worth noting that the collapse of the magnetic order occurs at lower temperature for the continuous film compared to the lattice even when considering the saturation magnetization (see Supplemental Material). This observation highlights a higher Fe concentration for the patterned film. As shown schematically in the Fig. 2 (b), the additional Fe concentration in ASIs is attributed to the Fe ions that impinge the mask near the edges. Due to multiple scattering events, some ions manage to scatter back out of the mask, and then become embedded in the Pd film at an angle. As a consequence, the core area of the elements is enriched by additional Fe dopants, that are not implanted in the periphery of the elements or the reference continuous film. Similar mask proximity effects have been reported for CMOS devices [38-40]. Based on the increase of the critical temperature, we estimate that the ASI lattice has approximately 1-3% higher Fe concentration compared to the continuous film. This estimation was derived from the relationship between the Fe concentration and the ordering temperature found in Refs. [33, 41, 42].

To explore the implanted-Fe distribution, we performed Monte Carlo simulations using the SRIM software. The simulations provide qualitative information about the Fe^+ spread



planted square artificial spin ice lattice (ASI) with nominal fluence 2.7×10^{16} ions/cm².

optical Kerr effect (L-MOKE) setup and a vibrating sample magnetometry (VSM) system. In the L-MOKE setup, a ppolarized incident laser beam with a wavelength of 659 nm was modulated by a Faraday cell and subsequently reflected by the sample. The reflected beam was passed through an analyzer (with extinction ratio of 10^5) and then measured using a biased Si photodiode. The detector was connected with a pre-amplifier and lock-in amplifier. A sinusoidal external magnetic field with an amplitude of 50 mT and a frequency of 0.1 Hz was applied along the [11] and [01] directions of the ASI lattice. The 659 nm laser beam achieves a penetration depth of approximately 11.9 nm in Pd film (see Supplemental Material), detecting the magnetization response from the surface of the sample. The cryostat in the L-MOKE system operates up to 400 K. In addition to the MOKE measurements, magnetic hysteresis loops were recorded by Vibrating Sample Magnetometry (VSM) with a 2 T Lakeshore 8600 magnetometer, equipped with a single-stage variable temperature unit that can reach a temperature of 950 K. This technique records the magnetic response from the entire sample volume.

C. Magnetic imaging

The magnetic state of the implanted mesospins was directly imaged using photoemission electron microscopy, employing x-ray magnetic circular dichroism (PEEM-XMCD). These experiments were conducted at the CIRCE (bl24) beamline of the ALBA synchrotron [34]. The images were acquired at room temperature with an x-ray photon energy tuned to the Fe L₃-edge.

D. Monte-Carlo simulations

The Fe distribution within the mesospins was investigated by performing Stopping and Range of Ions in Matter (SRIM) simulations [35]. To imitate the experimental conditions, the simulations were performed for 30 keV Fe⁺ ions implanted in

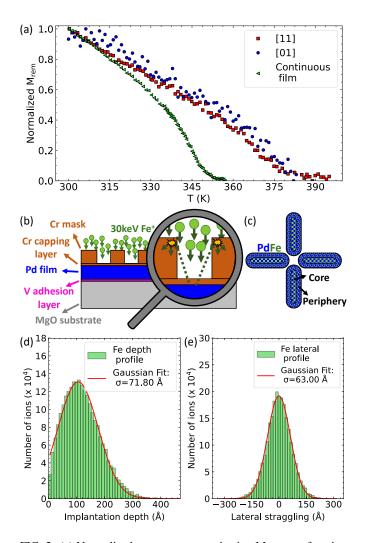


FIG. 2. (a) Normalized remanent magnetization M_{rem} as a function of temperature T for the ASI and its reference continuous film implanted with 30 keV Fe of nominal fluence 2.7×10^{16} ions/cm² measured with L-MOKE. The remanent magnetization for each dataset was normalized to a range between 0 and 1. (b) Schematic representation of the side view of the patterned film and the scattering events during Fe implantation. (c) Due to multiple scattering events, the implanted mesospins have higher Fe concentration in the core area compared to the periphery and the reference continuous film. (d,e) The simulated (d) depth- and (e) lateral-profile of Fe as a consequence of the ions straggling along the beam and perpendicular to it.


along the depth of the Pd film as well as perpendicular to it for a single point in space, without accounting mask proximity effects. As shown in Fig. 1 (d), the simulation results confirm the experimental observations that Fe has a concentration depth-profile [31]. In addition, the calculations demonstrate that Fe exhibits a concentration lateral-profile as a consequence of the lateral straggling of ions. The lateral implantation profile is often neglected in continuous films, as the lateral motion of ions creates a broader distribution due to the system's extension. However, the concentration lateralprofile can no longer be neglected in the lattices due to the clear boundary between the implanted and unimplanted regions [43]. Taking into account the mask proximity effects, the lateral implanted profile within the lattice building blocks is expected to be further amplified. As such, the implanted mesospins are both vertically and laterally inhomogeneous as a consequence of the ions straggling and mask proximity effects.

To directly illustrate the impact of the inhomogeneities on the magnetic state of mesospins, we image the ASI array at the remanent state by performing XMCD-PEEM experiments. Representative images are shown in Fig. 3 (a) and (b), when the field was applied along the [11] and [01] direction, respectively [44]. In both images, the elements are displayed in white and black contrast, confirming their single domain state. The ASI array has obtained a ferromagnetic (or Type II) remanent state when the field is applied along the [11] direction. Similarly, by applying a field along the [01] direction and then returning to the remanent state, results in a full ferromagnetic order for the elements parallel to the [01] direction. For the mesospins parallel to the [10] direction, a mixture of ferromagnetic and antiferromagnetic configurations is observed. However, the ferromagnetic order is more dominant than the antiferromagnetic one as it creates vertices of lower energy ($E_{Type II} < E_{Type III}$) (see Supplemental Material). Similar remanent states have been predicted for conventional lithographic ASI lattices [9].

To better resolve whether inhomogeneities influence the mesospin magnetization texture, we proceed by examining the remanent magnetization normalized by the saturation magnetization, M_{rem}/M_{sat}, from the L-MOKE measurements. This quantity separates the lattice from the material contributions, as M_{sat} is primarily an intrinsic material property [21]. For collinear magnetic texture, M_{rem}/M_{sat} has been predicted and measured to be equal with 0.707 for the [11] direction, and 0.5 for the [01] direction [9]. However, as shown in Fig. 3 (c), the implanted ASIs exhibit higher M_{rem}/M_{sat} values at temperatures below 350 K, approximately 0.8 for the [11] direction, and 0.6 for the [01] direction. These higher values reflect the presence of a non-collinear magnetization component. It is important to mention that such non-collinearities in mesospin texture have also been reported for conventional δ -doped Pd(Fe) ASI lattices at low temperatures [21]. However, the inhomogeneities inherent to implanted patterns seem to amplify the effect further.

Consequently, we perform micromagnetic simulations to investigate the non-collinearities in implanted mesospins. The simulations confirm the presence of a non-collinear magnetization component at the mesospin edges for any periphery lateral thickness (see Supplemental Material). Subsequently, we calculate the ratio M_{rem}/M_{sat} as a function of the angle θ between the collinear and non-collinear components, by assuming constant periphery thickness and non-collinearities at the whole mesospin edges (semicircles). For the calculation of the ratio M_{rem}/M_{sat} the system was not allowed to relax. The results are presented in Fig. 4. For collinear magnetic texture ($\theta = 0$), the ratio M_{rem}/M_{sat} is equal to 0.707 for the [11] direction and 0.5 for the [01] direction, as expected. By introducing non-collinearities ($\theta > 0$), M_{rem}/M_{sat} increases.

To explore the extent of the mesospin inhomogeneity ef-

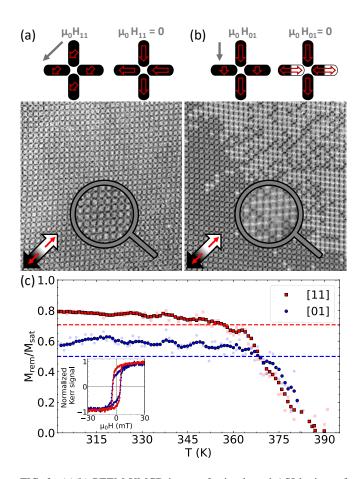

0.80 0.77 0.74 M_{rem}/M_{sat} [11]0.71 0.56 0.54 0.52 [01] 0.50 0 10 20 30 40

FIG. 3. (a)(b) PEEM-XMCD images for implanted ASI lattices of nominal fluence 2.7×10^{16} ions/cm². The images were captured at the remanence state after the field was applied along the (a) [11] and (b) [01] direction. (c) The ratio between the remanence and saturation magnetization, M_{rem}/M_{sat} , extracted from the L-MOKE measurements for the implanted ASI when the field was applied along the [11] and [01] direction. The saturation magnetization was determined from the hysteresis loops by averaging the values between 30 mT and 50 mT. Both the raw data (transparent points) and the smoothed data (non-transparent points), obtained using a five-point running average, are presented. The inset shows representative hysteresis loops for the ASI lattice. The dotted lines indicate the M_{rem}/M_{sat} values for collinear magnetic texture for the [11] (red) and [01] (blue) direction [9].

fects, we choose to investigate the same ASI lattice implanted with a higher nominal fluence of 3×10^{16} ions/cm². The pattern was investigated in the [11] direction and measured with the L-MOKE system at the temperature range of 200 - 370 K and the VSM system at the temperature range of 200 - 700 K. The remanent magnetization as a function of the temperature for the ASI lattice and its reference continuous film extracted from the VSM measurements is presented in Fig. 5 (a). The array magnetization collapses at higher temperatures compared to the film magnetization, verifying that the ordering temperature is higher for the array. The temperature-dependent ratio M_{rem}/M_{sat} from both L-MOKE and VSM measurements is shown in Fig. 5 (b). The MOKE measurements show that M_{rem}/M_{sat} has a plateau with a height

FIG. 4. The simulated ratio M_{rem}/M_{sat} as a function of the angle θ between the collinear and non-collinear magnetization components if a field had been applied along the (a) [11] and (b) [01] direction. The dotted lines indicate the M_{rem}/M_{sat} values for collinear magnetic texture [9].

θ (°)

of approximately 0.8, hinting towards non-collinearities in mesospin magnetic texture. However, the corresponding VSM measurements indicate lower values. As MOKE detects the surface magnetization, whereas VSM quantifies the volume magnetization, and the Fe concentration depth-profile decays from the sample surface towards the substrate [Fig. 5 (c)], the difference in M_{rem}/M_{sat} indicates that the magnetic moments are more rigid close to the sample surface but fluctuate deeper. This observation highlights a tunable magnetic thickness with temperature, for the implanted building blocks.

In conclusion, we have demonstrated that the magnetic order in Fe-implanted artificial spin ice (ASI) lattices collapses at higher temperatures than in their reference continuous films, with the mesospins exhibiting magnetic inhomogeneity both laterally and vertically. Furthermore, the implanted building blocks display a tunable magnetic thickness with temperature, introducing an additional degree of freedom. This tunability may allow the mesospins to adjust their magnetic dimensionality, transitioning from 2D behavior at higher temperatures to 3D behavior at lower temperatures, and enabling modifications to the dipolar coupling between building blocks. These findings open new pathways for tuning the

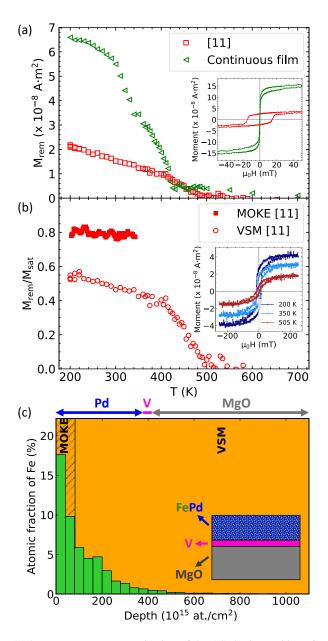


FIG. 5. (a) Remanent magnetization of the ASI lattice and its reference continuous film, implanted with 30 keV Fe and nominal fluence 3×10^{16} ions/cm², extracted from the VSM measurements. For both samples, the substrate remanent magnetization has been subtracted. The ASI exhibits lower magnetic moment due to the smaller coverage. (b) The ratio M_{rem}/M_{sat} for the implanted ASI lattice with nominal fluence 3×10^{16} ions/cm² as a function of temperature extracted from the L-MOKE and VSM measurements. The saturation magnetization was determined from the hysteresis loops by averaging the values between 30 mT and 50 mT for the MOKE measurements and between 150 mT and 250 mT for the VSM measurements. The inset shows hysteresis loops measured by the VSM. (c) The Fe concentration depth-profile for the continuous film implanted with 30 keV Fe and nominal fluence 3×10^{16} ions/cm² measured with time-of-flight elastic recoil detection analysis (ToF-ERDA). The background shading indicates the penetration depth of the MOKE and VSM measurement systems.

static and dynamic properties of magnetic materials by leveraging fabrication processes that go beyond traditional subtractive methods such as electron-beam lithography and milling. Such advances may significantly impact future applications of magnetic metamaterials. It was recently demonstrated that the ability to design and control magnetic textures in systems such as ASI enables the realization of tailored magnonic regimes. These emerging textures play a crucial role in defining the accessible ground states and governing transitions between magnetization states, thereby shaping the system's overall dynamics [19]. The engineering of energy landscapes through fabrication techniques like the ion implantation presented here-harnessing the internal degrees of freedom in mesospins-is expected to be important in the advancement of reconfigurable magnetic metamaterials [45], where dynamic behavior simultaneously functions as the readout. Furthermore, these enhanced internal dynamics, combined with the ability to tune mesospin couplings, open promising avenues for the development of reconfigurable reservoir computing networks based on magnetic metamaterials [46–48]. The thermal behavior described here is also critical for practical implementations of Ising machines using magnetic metamaterials [49]. The design and precise control of their stochastic dynamics are essential prerequisites for these systems to be effectively employed in solving optimization problems [50].

ACKNOWLEDGMENTS

The authors would like to thank Johan Oscarsson and Mauricio Sortica at the Uppsala Tandem Laboratory for help with ion implantations. The authors are thankful for an infrastructure grant by VR-RFI (grant number 2019-00191) supporting the accelerator operation. The authors also acknowledge support from the Swedish Research Council (projects no. 2019-03581 and 2023-06359). CV gratefully acknowledges financial support from the Colonias-Jansson Foundation, Thelin-Gertrud Foundation, Liljewalch and Sederholm Foundation. KI and UBA acknowledge funding from the Icelandic Research Fund project 2410333. We acknowledge Myfab Uppsala for providing facilities and experimental support. Myfab is funded by the Swedish Research Council (2020-00207) as a national research infrastructure. The PEEM-XMCD experiments were performed at CIRCE (bl24) beamline at ALBA Synchrotron with the collaboration of ALBA staff. MF acknowledges support from MICIN through grant number PID2021-122980OB-C54. The authors are deeply grateful for the support from ReMade@ARI, funded by the European Union as part of the Horizon Europe call HORIZON-INFRA-2021-SERV-01 under grant agreement number 101058414 and co-funded by UK Research and Innovation (UKRI) under the UK government's Horizon Europe funding guarantee (grant number 10039728) and by the Swiss State Secretariat for Education, Research and Innovation (SERI) under contract number 22.00187. VK and CV would like to thank Prof. Björgvin Hjörvarsson for discussions.

The data that support the findings of this study are available

- [1] L. J. Heyderman, J. Grollier, C. H. Marrows, P. Vavassori, D. Grundler, D. Makarov, and S. Pané, *Mesoscopic magnetic* systems: From fundamental properties to devices, Applied Physics Letters **119**, 080401 (2021).
- [2] L. J. Heyderman and R. L. Stamps, Artificial ferroic systems: novel functionality from structure, interactions and dynamics, Journal of Physics: Condensed Matter 25, 363201 (2013).
- [3] R. F. Wang, C. nisoli, R. S. Freitas, J. Li, W. Mcconville, B. J. Cooley, M. S. Lund, N. Samarth, C. Leighton, V. H. Crespi, and P. Schiffer, *Artificial 'spin ice' in a geometrically frustrated lattice of nanoscale ferromagnetic islands*, Nature 439, 303 (2006).
- [4] H. Stopfel, E. Östman, I.-A. Chioar, D. Greving, U. B. Arnalds, T. P. A. Hase, A. Stein, B. Hjörvarsson, and V. Kapaklis, *Magnetic order and energy-scale hierarchy in artificial spin-ice structures*, Physical Review B 98, 014435 (2018).
- [5] E. Östman, H. Stopfel, I.-A. Chioar, U. B. Arnalds, A. Stein, V. Kapaklis, and B. Hjörvarsson, *Interaction modifiers in artificial spin ices*, Nature Physics 14, 375 (2018).
- [6] Y. Perrin, B. Canals, and N. Rougemaille, *Extensive degeneracy, coulomb phase and magnetic monopoles in artificial square ice*, Nature 540, 410 (2016).
- [7] Y. Qi, T. Brintlinger, and J. Cumings, *Direct observation of the ice rule in an artificial kagome spin ice*, Physical Review B 77, 094418 (2008).
- [8] W. R. Branford, S. Ladak, D. E. Read, G. K. Perkins, and L. F. Cohen, *Direct observation of magnetic monopole defects in an artificial spin-ice system*, Nature Physics 6, 359 (2010).
- [9] V. Kapaklis, U. B. Arnalds, A. Harman-Clarke, E. T. Papaioannou, M. Karimipour, P. Korelis, A. Taroni, P. C. W. Holdsworth, S. T. Bramwell, and B. Hjörvarsson, *Melting artificial spin ice*, New Journal of Physics 14, 35009 (2012).
- [10] C. H. Marrows, J. P. Morgan, A. Stein, and S. Langridge, *Ther-mal ground-state ordering and elementary excitations in artificial magnetic square ice*, Nature Physics 7, 75 (2011).
- [11] S. A. Morley, D. Alba Venero, J. M. Porro, S. T. Riley, A. Stein, P. Steadman, R. L. Stamps, S. Langridge, and C. H. Marrows, *Vogel-fulcher-tammann freezing of a thermally fluctuating artificial spin ice probed by x-ray photon correlation spectroscopy*, Physical Review B **95**, 104422 (2017).
- [12] S. A. Morley, A. Stein, M. C. Rosamond, D. Alba Venero, A. Hrabec, P. M. Shepley, M.-Y. Im, P. Fischer, M. T. Bryan, D. A. Allwood, P. Steadman, S. Langridge, C. H. Marrows, H.-J. Drouhin, J.-E. Wegrowe, and M. Razeghi, *Temperature and magnetic-field driven dynamics in artificial magnetic square ice*, in *Proceedings of SPIE, the international society for optical engineering*, Vol. 9551, Brookhaven National Lab. (BNL), Upton, NY (United States) (SPIE, United States, 2015) p. 95511Q.
- [13] S. Gliga, E. Iacocca, and O. G. Heinonen, Dynamics of reconfigurable artificial spin ice: Toward magnonic functional materials, APL Materials 8, 040911 (2020).
- [14] V. Kapaklis, U. B. Arnalds, A. Farhan, R. V. Chopdekar, A. Balan, A. Scholl, L. J. Heyderman, and B. Hjörvarsson, *Thermal fluctuations in artificial spin ice*, Nature Nanotechnology 9, 514 (2014).
- [15] M. S. Andersson, S. D. Pappas, H. Stopfel, E. Östman, A. Stein, P. Nordblad, R. Mathieu, B. Hjörvarsson, and V. Kapaklis, *Thermally induced magnetic relaxation in square artificial spin*

ice, Scientific Reports **6**, 37097 (2016).

- [16] S. Gliga, A. Kákay, L. J. Heyderman, R. Hertel, and O. G. Heinonen, *Broken vertex symmetry and finite zero-point entropy in the artificial square ice ground state*, Physical Review B 92, 060413 (2015).
- [17] S. D. Slöetjes, B. Hjörvarsson, and V. Kapaklis, *The effect of confinement on thermal fluctuations in nanomagnets*, Applied Physics Letters **118**, 142407 (2021).
- [18] S. D. Slöetjes, B. Hjörvarsson, and V. Kapaklis, *Texture fluctuations and emergent dynamics in coupled nanomagnets*, Physical Review B 106, 104405 (2022).
- [19] S. Slöetjes, M. P. Grassi, and V. Kapaklis, *Modelling nano-magnet vertex dynamics through Coulomb charges*, Journal of Physics: Condensed Matter 36, 405804 (2024).
- [20] S. D. Slöetjes, M. P. Grassi, and V. Kapaklis, *Polymerization in magnetic metamaterials*, Physical Review Research 5, L032029 (2023).
- [21] B. E. Skovdal, S. D. Slöetjes, M. Pohlit, H. Stopfel, V. Kapaklis, and B. Hjörvarsson, *Thermal excitations within and among mesospins in artificial spin ice*, Physical Review B 107, L060406 (2023).
- [22] V.-D. Nguyen, Y. Perrin, S. Le Denmat, B. Canals, and N. Rougemaille, *Competing interactions in artificial spin chains*, Physical Review B 96, 014402 (2017).
- [23] C. Vantaraki, M. P. Grassi, K. Ignatova, M. Foerster, U. B. Arnalds, D. Primetzhofer, and V. Kapaklis, *Magnetic order and long-range interactions in mesoscopic ising chains*, Physical Review B 111, L020408 (2025).
- [24] H. Lou, W.-C. Yue, Z. Yuan, P. Huang, Y. Chen, Y.-L. Wang, S. Zhang, and D. Shi, *Competing interaction induced phase diagram and phase transition in artificial triangular spin ice*, *Physical Review B* 108, 184433 (2023).
- [25] I. Gilbert, C. Nisoli, and P. Schiffer, *Frustration by design*, Physics Today 69, 54 (2016).
- [26] C. Nisoli, V. Kapaklis, and P. Schiffer, *Deliberate exotic magnetism via frustration and topology*, Nature Physics 13, 200 (2017).
- [27] S. H. Skjærvø, C. H. Marrows, R. L. Stamps, and L. J. Heyderman, Advances in artificial spin ice, Nature Reviews Physics 2, 13 (2020).
- [28] J. C. Gartside, D. M. Arroo, D. M. Burn, V. L. Bemmer, A. Moskalenko, L. F. Cohen, and W. R. Branford, *Realization of ground state in artificial kagome spin ice via topological defect-driven magnetic writing*, Nature Nanotechnology 57, 53 (2017).
- [29] J. C. Gartside, S. G. Jung, S. Y. Yoo, D. M. Arroo, A. Vanstone, T. Dion, K. D. Stenning, and W. R. Branford, *Currentcontrolled nanomagnetic writing for reconfigurable magnonic crystals*, Communications Physics 3, 219 (2020).
- [30] O. Lee, T. Wei, K. D. Stenning, J. C. Gartside, D. Prestwood, S. Seki, A. Aqeel, K. Karube, N. Kanazawa, Y. Taguchi, C. Back, Y. Tokura, W. R. Branford, and H. Kurebayashi, *Taskadaptive physical reservoir computing*, Nature Materials 23, 79 (2024).
- [31] C. Vantaraki, P. Ström, T. T. Tran, M. P. Grassi, G. Fevola, M. Foerster, J. T. Sadowski, D. Primetzhofer, and V. Kapaklis, *Magnetic metamaterials by ion-implantation*, Applied Physics Letters 125, 202403 (2024).
- [32] M. Pohlit, G. Muscas, I.-A. Chioar, H. Stopfel, A. Ciuciulkaite,

E. Östman, S. D. Pappas, A. Stein, B. Hjörvarsson, P. E. Jönsson, and V. Kapaklis, *Collective magnetic dynamics in artificial spin ice probed by ac susceptibility*, Physical Review B **101**, 134404 (2020).

- [33] P. Ström, S. Ghorai, T. T. Tran, and D. Primetzhofer, Synthesis of ferromagnetic thin films and engineering of their magnetic properties by Fe ion implantation in polycrystalline Pd, Journal of Magnetism and Magnetic Materials 552, 169207 (2022).
- [34] L. Aballe, M. Foerster, E. Pellegrin, J. Nicolas, and S. Ferrer, *The ALBA spectroscopic LEEM-PEEM experimental station: layout and performance*, Journal of Synchrotron Radiation 22, 745 (2015).
- [35] J. F. Ziegler, M. Ziegler, and J. Biersack, *Srim the stopping and range of ions in matter (2010)*, Nuclear instruments & methods in physics research. Section B, Beam interactions with materials and atoms **268**, 1818–1823 (2010).
- [36] A. Vansteenkiste, J. Leliaert, M. Dvornik, M. Helsen, F. Garcia-Sanchez, and B. Van Waeyenberge, *The design and verification* of MuMax3, AIP Advances 4, 107133 (2014).
- [37] D. Kerkmann, D. Pescia, and R. Allenspach, *Two-dimensional magnet at curie temperature : epitaxial layers of Co on Cu(100)*, Physical Review Letters 68, 686 (1992).
- [38] T. Hook, J. Brown, P. Cottrell, E. Adler, D. Hoyniak, J. Johnson, and R. Mann, *Lateral ion implant straggle and mask proximity effect*, IEEE Transactions on Electron Devices 50, 1946 (2003).
- [39] G. Hobler and S. Selberherr, *Monte carlo simulation of ion implantation into two- and three-dimensional structures*, IEEE Transactions on Computer-aided Design of Integrated Circuits and Systems 8, 450 (1989).
- [40] Y.-M. Sheu, K.-W. Su, S.-J. Yang, H.-T. Chen, C.-C. Wang, M.-J. Chen, and S. Liu, *Modeling well edge proximity effect on highly-scaled mosfets*, in *Proceedings of the IEEE 2005 Custom Integrated Circuits Conference*, 2005 (IEEE, 2005) p. 831.
- [41] M. Hitzfeld, P. Ziemann, W. Buckel, and H. Claus, *Ferromag-netism of Pd-Fe alloys produced by low-temperature ion implantation*, Physical Review B 29, 5023 (1984).
- [42] L. Rohman, E. Supriyanto, K. Sa'diyah, and D. Djuhana, Curie temperatures and critical exponent properties of FePd ferromagnetic materials by data simulations approach, Journal of Physics: Conference Series 1170, 12018 (2019).
- [43] M. M. Faye, J. Beauvillain, P. Salles, L. Laanab, A. Yahia Messaoud, A. Martinez, and A. Claverie, *Two-dimensional damage* distribution induced by ion implantation in si under arbitrarily shaped mask edges : simulations and cross-sectional transmission electron microscopy observations, Journal of Applied Physics 72, 5117 (1992).
- [44] M. Foerster, J. Prat, V. Massana, N. Gonzalez, A. Fontsere, B. Molas, O. Matilla, E. Pellegrin, and L. Aballe, *Custom sample environments at the ALBA XPEEM*, Ultramicroscopy 171, 63 (2016).
- [45] J. C. Gartside, K. D. Stenning, A. Vanstone, H. H. Holder, D. M. Arroo, T. Dion, F. Caravelli, H. Kurebayashi, and W. R. Branford, *Reconfigurable training and reservoir computing in an artificial spin-vortex ice via spin-wave fingerprinting*, Nature Nanotechnology, 460 (2022).
- [46] S. Walczak and N. Cerpa, *Heuristic principles for the design of artificial neural networks*, Information and Software Technology 41, 107 (1999).
- [47] J. H. Jensen, E. Folven, and G. Tufte, Computation in artificial spin ice, in IEEE Symposium on Artificial Life (2018).
- [48] K. D. Stenning, J. C. Gartside, L. Manneschi, C. T. S. Cheung, T. Chen, A. Vanstone, J. Love, H. Holder, F. Caravelli, H. Kurebayashi, K. Everschor-Sitte, E. Vasilaki, and W. R. Branford, *Neuromorphic overparameterisation and few-shot learning in*

multilayer physical neural networks, Nature Communications **15**, 7377 (2024).

- [49] S. Bhanja, D. K. Karunaratne, R. Panchumarthy, S. Rajaram, and S. Sarkar, *Non-Boolean computing with nanomagnets for computer vision applications*, Nature Nanotechnology 11, 177 (2016).
- [50] N. Mohseni, P. L. McMahon, and T. Byrnes, *Ising machines as hardware solvers of combinatorial optimization problems*, Nature Reviews Physics 4, 363 (2022).
- [51] M. N. Polyanskiy, *Refractiveindex.info database of optical constants*, Scientific Data 11, 94 (2024).
- [52] B. E. Skovdal, N. Strandqvist, H. Stopfel, M. Pohlit, T. Warnatz, S. D. Slöetjes, V. Kapaklis, and B. Hjörvarsson, *Temperature-induced collapse of spin dimensionality in magnetic metamaterials*, Physical Review B **104**, 014434 (2021).

Supplemental Material: Magnetic texture control in ion-implanted metamaterials

IV. LASER PENETRATION DEPTH ON PD

We estimate the penetration depth *d* of a laser light with wavelength $\lambda = 659$ nm on a Pd material. The penetration depth *d* is the reciprocal of the absorption coefficient α :

$$d = \frac{1}{\alpha} \tag{S1}$$

The absorption coefficient α determines how far light can penetrate into a material before it is absorbed and is expressed as:

$$\alpha = \frac{4\pi k}{\lambda} \tag{S2}$$

where k is the extinction coefficient. For Pd material and light of wavelength $\lambda = 659$ nm, k = 4.42 [S51]. Consequently, the absorption coefficient is $\alpha = 0.084$ nm⁻¹ and the penetration depth is d = 11.9 nm.

V. THICKNESS OF IMPLANTED FE

To estimate the thickness of Fe layer implanted with nominal fluence $\Phi = 2.7 \times 10^{16}$ ions/cm², we consider that the implanted Fe has formed a compacted layer. To a first approximation, the mass of a single Fe⁺ ion is the same with the mass of a single Fe atom and equal to:

$$m_{\rm Fe} = \frac{A_{\rm Fe}}{N_A} = 9.27 \times 10^{-23} \,\mathrm{g}$$
 (S3)

where A_{Fe} is the atomic mass of Fe and N_A is the Avogadro's number. Consequently, the area density ρ_A , i.e total mass of Fe implanted per unit area, is:

$$\rho_A = \Phi \times m_{\rm Fe} = 25.029 \times 10^{-7} \, \frac{\rm g}{\rm cm^2}$$
 (S4)

By considering that the density of Fe is $\rho_{\text{Fe}} = 7.87 \text{ g/cm}^3$, the thickness of the implanted Fe as compacted layer is:


$$t = \frac{\rho_A}{\rho_{\rm Fe}} = 3.18\,\rm nm \tag{S5}$$

VI. COLLAPSE OF THE MAGNETIC ORDER

To verify that the ordering temperature is higher for the ASI lattice compared to its reference continuous film that was prepared and implanted next to the lattice with 30 keV Fe of nominal fluence 2.7×10^{16} ions/cm², we also examine the saturation magnetization as a function of the temperature. As shown in Fig. **S1**, the saturation magnetization vanishes at higher temperature for the lattice compared to the continuous film, reflecting a higher ordering temperature for the ASI array.

VII. VERTEX STATISTICS FOR THE REMANENT STATE [01]


To quantify the magnetic order established within the ASI lattice at the remanence state after the application of a field along the [01] direction, we determine the population of various types of vertex configuration. A vertex at which four elements converge can exhibit four distinct topologies, classified as Type I, II, III, and IV. Type I possesses the lowest energy, and Types II, III, and IV exhibit progressively higher energy. Vertex statistics are presented in Fig. **S2**. We notice that the ASI lattice has obtained a mixture of Type II and III configurations.

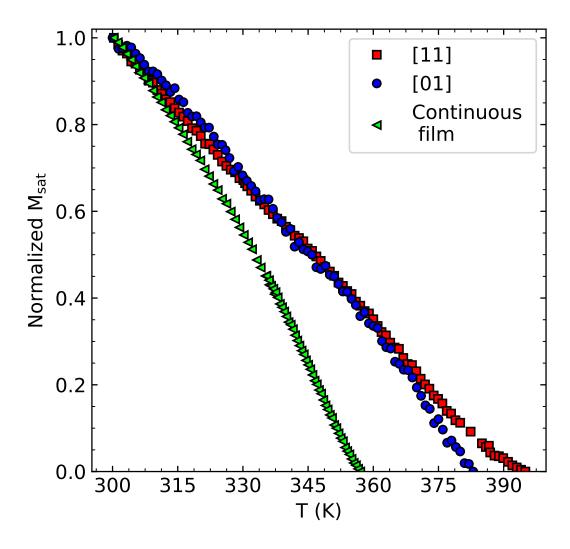


Supplementary FIG. **S1**. Normalized saturation magnetization M_{sat} as a function of temperature T for the ASI and its reference continuous film implanted with 30 keV Fe of nominal fluence 2.7×10^{16} ions/cm² measured with L-MOKE. The saturation magnetization was determined from the hysteresis loops by averaging the values between 30 mT and 50 mT.

VIII. NON-COLLINEARITIES AT MESOSPIN EDGES

We performed micromagnetic simulations to explore the non-collinearities in mesospin texture. For the simulations, we investigated a vertex using periodic boundary conditions (Fig. S3), while each element is made by a core and a periphery area. These two areas were described by different magnetic properties, saturation magnetization and exchange stiffness constant. Specifically, the saturation magnetization and the exchange stiffness constant for the core area of the elements were chosen based on previous studies ($M_{sat} = 3.5 \times 10^5$ A/m and $A_{ex} = 3.36 \times 10^{-12}$ J/m) [S52]. For the periphery, we assumed that the Fe concentration is lower by 2% compared to the core area of the elements, and that the magnetic properties follow a linear relationship with the Fe concentration. Consequently, the saturation magnetization and the exchange stiffness constant for the periphery were considered to be equal with $M_{sat} = 3.43 \times 10^5$ A/m and $A_{ex} = 3.2928 \times 10^{-12}$ J/m respectively. The magnetization of each mesospin was assumed uniform, and subsequently the system was relaxed into its ground state. The simulations were performed for various periphery lateral thicknesses. Fig. S3 shows a representative relaxed vertex state, confirming the presence of non-collinear magnetization component at mesospin edges.

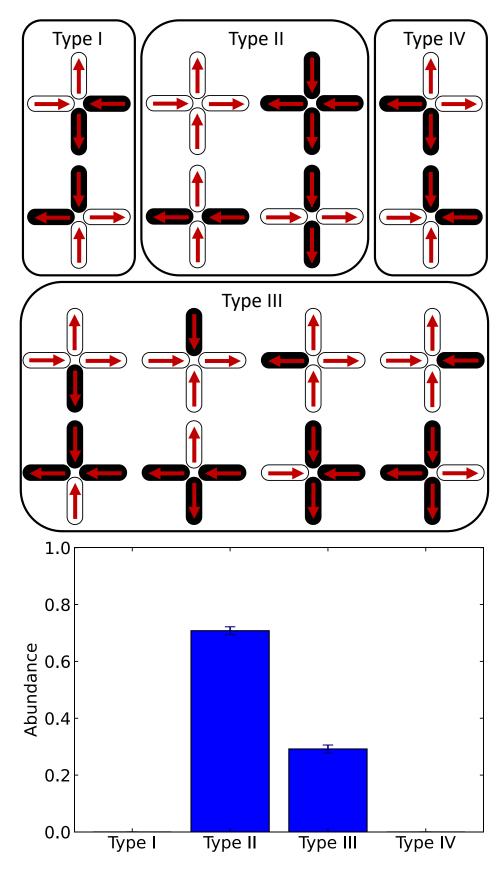

Supplementary FIG. **S2**. Definition of vertex types, and the vertex statistics for the implanted ASI lattices at the remanence state after the application of a field along the [01] direction.

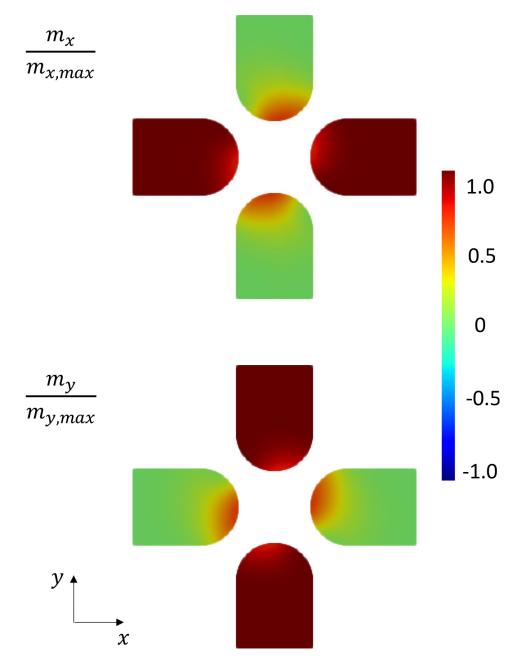

Supplementary FIG. **S3**. Micromagnetic state of a vertex comprised of mesospins with inhomogeneous magnetization as shown in Fig. 2 (c). The system was allowed to relax from a state polarized in the [11] direction (Type II vertex). Normalized moment values are presented for the x- and y-direction, highlighting the sizable non-collinearities at the mesospin edges, close to the vertex center.