

A New Monomeric Interpretation of Intrinsic Optical Bistability Observed in Yb^{3+} - Doped Bromide Materials

F. Ciccarello ^a

A. Napoli ^a

A. Messina ^a

S.R. Lüthi ^b

^a*INFN and MIUR, Dipartimento di Scienze Fisiche ed Astronomiche dell'Università di Palermo, via Archirafi 36, 90123 Palermo, Italy*

^b*Gemfire Corporation, 1220 Page Avenue, Fremont, CA - 94538, USA*

Abstract

We present a mechanism able to show intrinsic bistable behaviour involving single Yb^{3+} ions embedded into bromide lattices, in which intrinsic optical bistability (IOB) has been observed. The mechanism is based on the experimentally found coupling between the Yb^{3+} ion and the totally symmetric local mode of vibration of the $[YbBr_6]^{3-}$ coordination unit. The model reproduces the IOB observed in $CsCdBr_3 : 1\% Yb^{3+}$ and allows to understand the experimentally found presence of the phenomenon in the other bromides, but its absence in $Cs_3Lu_2Cl_9 : Yb^{3+}$.

Key words: IOB, Yb^{3+} , electron-phonon interaction

PACS: 42.65.Pc, 63.20.Kr, 63.20.Mt

A physical system without mirrors of an external cavity, exhibiting two stable outputs for a single input intensity of an exciting laser, is said to exhibit intrinsic optical bistability (IOB) [1,2,3]. Hehlen et al. [4,5,6,7] have discovered that Yb^{3+} - doped $Cs_3X_2Br_9$ [$X = Y, Lu$] and $CsCdBr_3$ show IOB when exciting into the ${}^2F_{7/2}(0) \rightarrow {}^2F_{5/2}(0')$ and ${}^2F_{7/2}(0) \rightarrow {}^2F_{5/2}(2')$ electronic transitions of the Yb^{3+} ion with a narrow band laser of suitable near-infrared (NIR) frequency. On the contrary, no IOB was observed under excitation into the ${}^2F_{7/2}(0) \rightarrow {}^2F_{5/2}(1')$ transition [8,9]. When doped in these crystalline bromide materials some Yb^{3+} ions form strongly interacting $Yb^{3+} - Yb^{3+}$ dimers

Email address: messina@fisica.unipa.it (A. Messina).

[10,11]. Due to this interaction, excitation of the $Yb^{3+} \ ^2F_{7/2} \rightarrow \ ^2F_{5/2}$ transition (around 10000 cm^{-1}) results in both, $\ ^2F_{5/2} \rightarrow \ ^2F_{7/2}$ emission of single Yb^{3+} ions in the NIR spectral range, as well as $Yb^{3+} - Yb^{3+}$ dimer emission in the visible (VIS) at twice the resonance frequency of the single Yb^{3+} ion [6,12,13] through a cooperative luminescence mechanism [14]. The IOB phenomenon consists of a temperature and excitation power dependent hysteretic behaviour of the transmitted, NIR and upconverted VIS emission intensity (with the system switching output intensity at two critical incident excitation powers). To date, it is discussed if the phenomenon is due to the presence of strongly interacting $Yb^{3+} - Yb^{3+}$ dimers or if it is a single Yb^{3+} ion property. The theories relying on the former interpretation are usually referred to as “dimeric” while those supporting the latter idea as “monomeric”. Dimeric theories substantially rely on the existence of intra-pair electronic coupling of $Yb^{3+} - Yb^{3+}$ dimers [4,5,15,16]. According to these theories, IOB should be observed *a fortiori* in Yb^{3+} - doped $Cs_3Lu_2Cl_9$, as this material is isostructural to Yb^{3+} - doped $Cs_3X_2Br_9$ [$X = Y, Lu$] [17,18] and exhibits a stronger electronic exchange interaction for $Yb^{3+} - Yb^{3+}$ dimers [10]. However, no experimental evidence for IOB was found in Yb^{3+} -doped $Cs_3Lu_2Cl_9$ [8,9]. Furthermore, in $Cs_3X_2Br_9 : Yb^{3+}$ ($X = Y, Lu$) only a few Yb^{3+} ions form dimers at low concentration of impurity ions. Nevertheless, both bromide lattices exhibit IOB even at a low Yb^{3+} - doping level [4,5,6]. A monomeric mechanism to account for IOB in these systems has been proposed by Gamelin et al. [9] who presented a phenomenological model, according to which IOB depends on a single - Yb^{3+} ion property in these materials. In this model, IOB is attributed to the interplay of a laser heating effect and a strongly increasing, non-linear dependence of the material’s absorbance with the internal temperature. With its phenomenological nature, this theory succeeds in reproducing many experimental trends, but does not provide the microscopic mechanism of IOB. In this letter, we present the first microscopic, monomeric mechanism that allows a single active ion to exhibit all essential aspects observed in IOB. To date, the microscopic theories presented in literature describing how a collection of two-level atoms can exhibit IOB are based on electronic coupling between two or more near absorbers [3,5,15,19]. In these cases, the electronic interaction between the coupled absorbers provides the feedback loop required to obtain intrinsic bistability. Together with the intrinsic two-level atom non linearity and the use of single-atom density matrix approach (an indispensable step in order to obtain non linear equations), this feedback loop gives rise to inversion dependent atomic resonance frequency renormalization, and thus possible IOB. With a few exceptions, the role played by the host lattice, and in particular of the first coordination sphere of the Yb^{3+} , in the mechanism responsible for IOB in Yb^{3+} -doped bromide host materials has generally been regarded as secondary. However, Hehlen et al. measured different internal temperatures for the system on the two branches of the hysteresis loop [5]. This suggests that with the first switch occurring, the lattice undergoes heating. Additionally, Lüthi [8] has found that $Cs_3Lu_2Br_9 : 10\% Yb^{3+}$ shows

bistable behaviour even when excited with a chopped laser and off-times as long as 75 *msec*. This means that the system prepared on the upper branch of the bistability region does not decay to the lower branch for times as long as 75 *msec* after turning off the exciting laser beam. If IOB were due to a cooperative mechanism based on electronic $Yb^{3+} - Yb^{3+}$ coupling, and the feedback loop provided by the same two ytterbium ions, it would be hard to justify this behavior. After 75 *msec*, all ions in their excited state are expected to have decayed to the ground state, and there seems to be no physical reason for the system to save memory of its past history. The fact that the nuclear relaxation times of the lattice are much longer than the electronic ones, suggests that the lattice nuclear degrees of freedom play a relevant role in the bistability mechanism. Supported by the findings of a Raman spectroscopy study on $CsCdBr_3 : 1\% Yb^{3+}$ [20] showing strong coupling between the electronic ${}^2F_{7/2}(0) \rightarrow {}^2F_{5/2}(2')$ transition of Yb^{3+} and the totally symmetric vibrational local mode of the $[YbBr_6]^{3-}$ coordination unit (into which Yb^{3+} is embedded in all bromide lattices showing IOB), we propose that this vibrational coupling provides the indispensable feedback loop to observe IOB (involving only a single Yb^{3+} ion).

Our physical system consists of the electronic structure of a single Yb^{3+} ion and the totally symmetric vibrational local mode A_{1g} of the $[YbBr_6]^{3-}$ octahedron. We treat the former as a two-level system ($|a\rangle$ and $|b\rangle$ ground and excited states, respectively, $\hbar\omega_0$ energy difference, $|i\rangle\langle j| = \sigma_{ij}$ $i, j = a, b$) and the latter as a quantum harmonic oscillator (a and a^+ annihilation and creation operators, respectively, and angular frequency ω_k). We write the free Hamiltonian H_0 of the system as

$$H_0 = H_{Yb} + H_k = \hbar\omega_0 \sigma_{bb} + \hbar\omega_k a^+ a \quad (1)$$

For the interaction Hamiltonian V_{Yb-k} between the ion and the A_{1g} local mode we choose a bilinear operatorial form (in order for the oscillation centre to depend on the electronic state in which the ion is [21])

$$V_{Yb-k} = \epsilon (\sigma_{bb} - \sigma_{aa}) (a + a^+) \quad (2)$$

When a coherent classical electromagnetic field is applied to the ion, using the rotating wave and the electric dipole approximations, the coupling between the Yb^{3+} ion and the external field is described by the observable $V_{Yb-L} = \frac{\hbar\Omega}{2}(\sigma_{ba}e^{-i\omega t} + \sigma_{ab}e^{i\omega t})$, where Ω and ω stand for the Rabi and the laser frequency. Denoting the total Hamiltonian operator of the system with $H = H_0 + V_{Yb-k} + V_{Yb-L}$, and taking into account both the ion spontaneous emission and the dissipative interaction of the ion and the local mode with the bulk modes of the lattice (described by a suitable superoperator S), the

dynamics of the system obeys the generalized Von-Neumann equation

$$\dot{F} = -\frac{i}{\hbar} [H, F] + SF \quad (3)$$

where F is the density operator of the whole system. $F(t)$ can be written as $F(t) = Tr_k F(t) Tr_{Yb} F(t) + F^{Yb-k}(t)$, where $Tr_k F$ and $Tr_{Yb} F$ are the reduced density operators of the ion and the local mode, respectively, while $F^{Yb-k}(t)$ represents the correlations existing at the time t between Yb and k . Assuming $V_{Yb-k} \ll H_0$, we approximate $F(t)$ with its factorized part

$$F(t) \simeq Tr_k F(t) Tr_{Yb} F(t) \quad (4)$$

This is the main hypothesis of our model. In this way, analogously to other theories [3,5,19,22], we *assume* that single-ion density matrix approach is allowed. A necessary condition for this approach to be valid is that V_{Yb-k} is much smaller than the free Hamiltonian H_0 (later on we will show this is the case). It must be remarked that the feasibility of this treatment - indispensable to have non linear equations and thus possible IOB - poses a delicate and lively debated [15,23,24] theoretical problem questioning even the existence of a microscopic explanation of some IOB phenomena [23]. We justify assumption (4) with the ability of our model to reproduce the observed IOB phenomena. Inserting eq.(4) in eq.(3) and doing the trace over k and Yb , we obtain two coupled master equations in $Tr_k F(t)$ and $Tr_{Yb} F(t)$. Performing the variable change $\rho'_{ab} = \rho_{ab} e^{i\omega t}$, it can be proved that the ion dynamic equations in $\dot{\rho}_{bb}$ and ρ'_{ab} differ from the usual optical Bloch equations in the rotating frame for the presence of an effective resonance frequency $\omega_0^{eff}(t) = \omega_0 + 2\frac{\epsilon}{\hbar} \langle a + a^+ \rangle(t)$, linearly dependent on the mean value of the local mode operator ($a + a^+$). This proves that the dynamic response of the ion to the applied field depends on the state of the local mode (in its turn depending on the ion state). It is easy to show that for stationary conditions (when setting all temporal derivatives to zero) the resonance frequency can be written as

$$\omega_0^{eff} = \omega_0 - \beta(\rho_{bb} - \rho_{aa}) \quad (5)$$

where

$$\beta = 4 \frac{\epsilon^2}{\hbar^2} \frac{\omega_k}{\omega_k^2 + \gamma^2} \quad (6)$$

with γ being the relaxation rate of the local mode. We thus find that the overall effect of the coupling between the electronic transition of the Yb^{3+} ion and the A_{1g} local mode of the $[YbBr_6]^{3-}$ unit, consists of an ion resonance frequency renormalization linearly dependent on inversion ($\rho_{bb} - \rho_{aa}$). Introducing the

absorption parameter $s = 2\rho_{bb}$ ($0 \leq s \leq 1$), it is possible to prove that, under stationary conditions, s and the incident excitation power P must obey the equation

$$c_3 s^3 + c_2 s^2 + (c_1 + b P) s - b P = 0 \quad (7)$$

with

$$c_3 = 4 \left(\frac{\beta}{\Gamma_h} \right)^2 \quad c_2 = -8 \frac{\beta}{\Gamma_h} \frac{\delta + \beta}{\Gamma_h} \quad c_1 = 4 \left(\frac{\delta + \beta}{\Gamma_h} \right)^2 + 1$$

$$b = \frac{3e^2}{\pi m c \epsilon_0} \frac{F_{ab}}{\hbar \omega_0} \cos^2 \varphi \frac{1}{\Gamma_1 \Gamma_h} \quad (8)$$

where Γ_h is the homogeneous linewidth of the electronic transition, $\delta = \omega_0 - \omega$ is the detuning of the laser frequency, $F_{ab} = (2m\omega_0/3\hbar)|\langle a|\mathbf{r}|b\rangle|^2$ stands for the oscillator strength of the transition $|a\rangle \rightarrow |b\rangle$, φ is the angle between the laser polarization versor and $\langle a|\mathbf{r}|b\rangle$, and Γ_1 is the ion longitudinal decay time. Eq.(7) is a third degree equation in the unknown s dependent on many parameters. It can be shown that the condition for the existence of a P -range inside which, for any value of P , two stable solutions for s are found (IOB) is

$$\frac{\beta}{\Gamma_h} \geq \frac{3\sqrt{3}}{2} \quad (9)$$

This provides a threshold value of the local mode - Yb^{3+} ion interaction strength required to observe intrinsic bistability compatibly with our microscopic feedback mechanism. Moreover, eq.(7) shows that, for an increasing value of the bistability parameter β/Γ_h , the incident power bistability range moves toward higher values of P and, in addition, becomes wider. We now use our theory to reproduce the two incident powers at which switching occurs measured in $CsCdBr_3 : 1\% Yb^{3+}$ [7]. Guillot-Noël et al. successfully performed an analogous simulation to test their dimeric theory [15]. In our study we use: $\delta = 0$ (perfect resonance), $\omega_0 = 10602.8 \text{ cm}^{-1}$ [7], $\Gamma_h = 0.6 \text{ cm}^{-1}$ [7], $1/\Gamma_1 = 7.8 \cdot 10^{-4} \text{ s}$ [13], $F_{ab} = 10^{-6}$ and, additionally, we take $\cos^2 \varphi = 1/2$, assuming that the incident laser beam is unpolarized [5]. Using the bistability parameter to optimise our simulation, good agreement is achieved between the theoretical prediction and the experimentally measured values [7] for the two incident powers at which switching occurs, as shown in Fig. 1. Using the optimised value of $\beta/\Gamma_h = 7.5$, the ion-local mode coupling constant ϵ [eq.(2)] can be estimated. From eq.(6) and taking into account the fact that the lattice nuclear relaxation times are typically very long compared to $1/\omega_k$, we get $\epsilon \simeq \frac{\hbar}{2} \sqrt{\beta \omega_k}$. With $\omega_k = 191 \text{ cm}^{-1}$ [20], we obtain $\epsilon = 14.66 \text{ cm}^{-1}$ for $CsCdBr_3 : 1\% Yb^{3+}$. This value confirms our *a priori* assumption that V_{Yb-k}

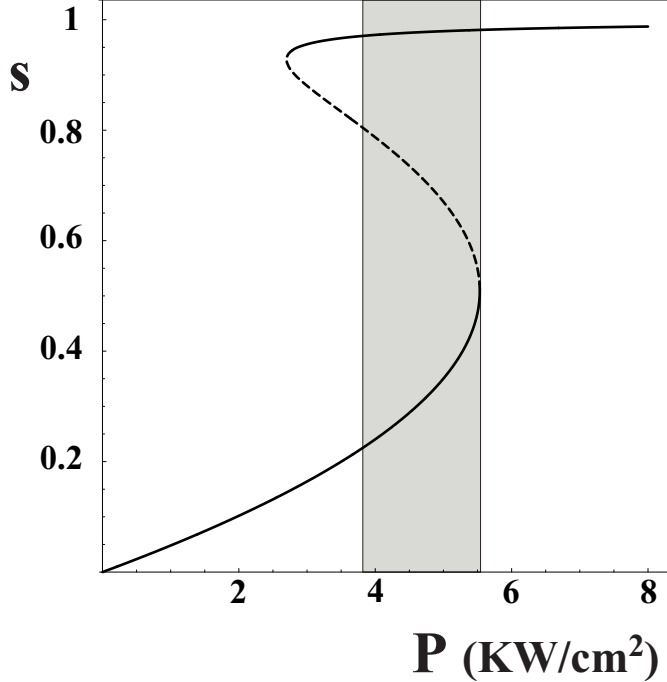


Fig. 1. Absorption parameter s of the Yb^{3+} ion as a function of the incident intensity P (kW/cm^2) in $CsCdBr_3 : 1\% Yb^{3+}$ at $7 K$ calculated from eq. (7) ($\beta/\Gamma_h = 7.5$, $\delta = 0$, $\omega_0 = 10602.8 \text{ cm}^{-1}$, $\Gamma_h = 0.6 \text{ cm}^{-1}$, $1/\Gamma_1 = 7.8 \cdot 10^{-4} \text{ sec}$, $F_{ab} = 10^{-6}$). The dashed line represents unstable solutions. The grey shaded area represents the experimentally observed bistable region for this compound [7].

is much weaker than H_0 . With this value for ϵ , the displacement of the oscillation centre for the local mode k , for an Yb^{3+} ion undergoing the transition from $|a\rangle$ to $|b\rangle$, as implied by the operatorial form assumed for V_{Yb-k} [eq.(2)], turns out to be in the order of 1 %. This result agrees with typical values found for lattice point defects due to incorporation of rare earth impurity ions [21], and confirms that the coupling constant ϵ we get from our model is of the correct order of magnitude.

Another relevant test for our theory is its ability to predict the presence of IOB in $Cs_3X_2Br_9 : Yb^{3+}$ [$X = Y, Lu$], but the absence of the phenomenon in $Cs_3Lu_2Cl_9 : Yb^{3+}$ [8,9]. In the bromide compounds, the angular frequency ω_k is 190 cm^{-1} [12], similar to the one found in $Cs_3Er_2Br_9$ [25]. From comparison of the absorption and emission spectra, we estimate Γ_h and ϵ to be comparable to the ones measured in $CsCdBr_3 : Yb^{3+}$ [8,20]. These assumptions made, we expect the bistability parameter β/Γ_h for $Cs_3X_2Br_9 : Yb^{3+}$ [$X = Y, Lu$] to have a comparable value to the one calculated for $CsCdBr_3 : 1\% Yb^{3+}$, and can understand why IOB is found in the former compounds. For the chloride, ω_k is 285 cm^{-1} [25]. From inspection of the absorption and emission spectra, we estimate Γ_h to fall in the range $0.3 - 0.7 \text{ cm}^{-1}$ [8], and the $Yb^{3+} - A_{1g}$ local mode coupling constant ϵ to be about 5 times smaller than in bromide

compounds. Based on these values, the bistability parameter β/Γ_h is estimated to be lower than the critical threshold of $3\sqrt{3}/2$ required for IOB. We finally notice that absorption spectra of $Cs_3Lu_2Br_9 : Yb^{3+}$ show that the Yb^{3+} ion ${}^2F_{7/2}(0) \rightarrow {}^2F_{5/2}(1')$ transition exhibits a very weak coupling to the A_{1g} local mode compared to $0 - 0'$ and $0 - 2'$. This explains why no IOB is observed under excitation into this peculiar transition.

In summary, we have presented the first microscopic mechanism according to which a single Yb^{3+} ion is able to exhibit IOB when doped in $Cs_3X_2Br_9$ [$X = Y, Lu$] or $CsCdBr_3$. The mechanism couples the electronic two-level system of the Yb^{3+} ion with the totally symmetric local mode of the vibration of the $[YbBr_6]^{3-}$ coordination unit. The theory has been used to reproduce basic aspects of the IOB observed in $CsCdBr_3 : 1\% Yb^{3+}$. We emphasize that our theory not only allows to understand, why IOB has been observed in $CsCdBr_3 : 1\% Yb^{3+}$ and $Cs_3X_2Br_9$ [$X = Y, Lu$], but also, why it is absent in the chloride compound $Cs_3Lu_2Cl_9 : Yb^{3+}$. These results provide new insight into the microscopic mechanism underlying the IOB phenomenon and guidelines for expanding the material basis in the search for IOB systems, and their potential applications.

We gratefully acknowledge inspiring discussions with O. Guillot-Noël of ENSCP, Paris and M.P. Hehlen of M. Lujan Jr. of Neutron Scattering Centre, Los Alamos National Laboratory, Los Alamos, New Mexico.

Note: Octahedral coordination of the $[YbBr_6]^{3-}$ unit, instead of the actual C_3 symmetry, is assumed throughout the text with no impact on our conclusions.

References

- [1] E. Abraham, and S.D. Smith, *Rep. Prog. Phys.*, **45** (1982) 138
- [2] C.M. Bowden, and C.C. Sung, *Phys. Rev. A* **19** (1979) 2392
- [3] F.A. Hopf, C.M. Bowden, and W.H. Louisell, *Phys. Rev. A* **29**(1984) 2591
- [4] M.P. Hehlen, H. U. Güdel, Q. Shu, J. Rai, S. Rai, and S. C. Rand, *Phys. Rev. Lett.* **73** (1994) 1103
- [5] M.P. Hehlen, H.U. Güdel, Q. Shu, and S.C. Rand, *J. Chem. Phys.* **104** (1996) 1232
- [6] S.R. Lüthi, M.P. Hehlen, T. Riedener, and H.U. Güdel, *J. Lumin.* **76& 77** (1998) 447
- [7] M.P. Hehlen, H.U. Güdel, J. Rai, S. Rai, and S.R. Lüthi, *Phys. Rev. Lett.* **82** (1999) 3050

- [8] S.R. Lüthi, *Ph.D. Thesis*, Universität Bern, Switzerland (1998)
- [9] D.R. Gamelin, S.R. Lüthi, and H.U. Güdel, *J. Phys. Chem. B* **104** (2000) 11045
- [10] H.U. Güdel, A. Furrer, and H. Blank, *Inorg. Chem.* **29** (1990) 4081
- [11] V. Mehta, O. Guillot-Noël, D. Simons, D. Gourier, Ph. Goldner, and F. Pellé, *J. All. and Comp.* **323-324** (2001) 308
- [12] M.P. Hehlen and H.U. Güdel, *J. Chem. Phys.* **98** (1993) 1768
- [13] Ph. Goldner, F. Pellé, D. Meichenin, and F. Auzel, *J. Lumin.* **71** (1997) 137
- [14] F.E. Auzel, *Proc. of the IEEE* **61** (1973) 758
- [15] O. Guillot-Noël, L. Binet, and D. Gourier, *Phys. Rev. B* **65** (2002) 245101
- [16] O. Guillot-Noël, Ph. Goldner, and D. Gourier, *Phys. Rev. A* **66** (2002) 063813
- [17] G. Meyer, and A. Schoenemund, *Mat. Res. Bull.* **15** (1980) 83
- [18] Th. Schleid and G. Meyer, *Z. Kristallogr.* **210** (1995) 145
- [19] J. Heber, *Z. Phys. B* **68** (1987) 115
- [20] M.P. Hehlen, A. Kuditcher, S.C. Rand and, M.A. Tischler, *J. Chem. Phys.* **107** (1997) 4886
- [21] M.H.L. Pryce, “Interaction of lattice vibrations with electrons at point defects” in *Phonons in Perfect Lattices and in Lattices with Point Imperfections*, edited by R.W.H. Stevenson, Oliver & Boyd, Edinburgh, 1966
- [22] N. Bodenschatz, and J. Heber, *Phys. Rev. A* **54** (1996) 4428
- [23] V.A. Malyshev, H. Glaeske, and K.H. Feller, *Phys. Rev. A* **58** (1998) 1496
- [24] J. Heber, *J. All. and Comp.* **300-301** (2000) 32
- [25] M.P. Hehlen, K. Krämer, H.U. Güdel, R.A. McFarlane, and R.N. Schwartz, *Phys. Rev. B* **49** (1994) 12475