

Thermal radiation of conducting nanoparticles

Yu.V.Martynenko, L.I.Ognev

*Nuclear Fusion Institute, Russian Research Center “Kurchatov Insitute”,
123182, Moscow, Kurchatov sq., 1*

martyn@nfi.kiae.ru, ognev@nfi.kiae.ru

Abstract

A simple and universal criterion was obtained for the thermal radiation energy loss efficiency by small conductive particles which include along with metals and graphite also most practically important metal carbides like tungsten carbide, titanium carbide and the number of others.

In recent years the amount of research in the field of nanotechnology, nanomaterials and nanosystems tremendously increased [1]. One of the most important trends in nanotechnology is obtaining and using of nanopowders, which can be used in metallurgy, microelectronics, medicine and food industry. Production of nanopowders and processing are frequently dealt with heating of nanoparticles to high temperatures when intensive thermal radiation can be expected.

In the recent times the great interest increased to dust plasma [2], and to the role of dust in fusion devices [3], where micro- and nano- particles are heated to high temperatures and in the energy balance of particles radiation energy losses can play decisive role.

For the calculation of nanoparticle energy balance the Stefan-Boltzmann law for black body radiation of the sphere can not be used, because for dimensions of the particles smaller than radiation length the Stefan-Boltzmann formula gives too overestimated results. Radiation losses for atomic clusters were discussed in the review [4].

For the calculation of a small body energy loss the Kirchhoff's law of thermal emission can be used [5]. Thermal emission of the body with the temperature T in the interval of angular frequencies $d\omega$ equals

$$dI(\omega) = 4\pi c \sigma(\omega) \frac{\hbar \omega^3}{4\pi^3 c^3 (e^{\frac{\hbar \omega}{kT}} - 1)} d\omega, \quad (1)$$

where $\sigma(\omega)$ - effective cross section for frequency ω , c – light velocity, T – temperature, k – Boltzmann constant.

According to [5], radiation absorption cross section for the sphere with the volume V can be expressed through electric α''_e and magnetic α''_m susceptibility, normalized by the volume,

$$\sigma(\omega) = \frac{4\pi\omega}{c} (\alpha''_e + \alpha''_m) \cdot V \quad (2)$$

In the case of conductors the magnetic susceptibility prevails, that is why it is only taken into account and used in the calculations used.

Although in the frame of G. Mie theory, the most profound approach to the scattering and absorption of electromagnetic radiation on small particles, it is not possible to obtain sufficiently common dependencies for cross section on parameters of particles [6], in the case of conducting spheres the approximate approach can be used which is based on the account of the depth of penetration of the radiation in the substance [5]. In the frame of the approach the

magnetic susceptibility of a sphere with radius r_0 depends on dimensionless parameter (r_0/δ) , where $\delta=c/(2\pi\sigma\omega)^{1/2}$ – penetration depth of the radiation into conductor as

$$\alpha_m'' = -\frac{9\delta^2}{16\pi r_0^2} \left[1 - \frac{r_0}{\delta} \frac{sh(2r_0/\delta) - \sin(2r_0/\delta)}{ch(2r_0/\delta) - \cos(2r_0/\delta)} \right] \quad (3).$$

For small radii ($r_0/\delta \ll 1$, small frequencies) approximation is possible

$$\alpha_m'' = \frac{1}{20\pi} \left(\frac{r_0^2}{\delta^2} \right) = \frac{r_0^2 \sigma \omega}{10c^2}. \quad (4)$$

For large radii of particles ($r_0/\delta \gg 1$, large frequencies) approximation looks like

$$\alpha_m'' = \frac{9\delta}{16\pi r_0} = \frac{9c}{16\pi r_0 \sqrt{2\pi\sigma\omega}}. \quad (5)$$

Here σ - static conductivity of a substance.

Dependencies (3), (4) and (5) are shown on Fig. 1. Substitution of the expression (5) for high energies into the integral for radiation (1) results in disappearance of the radius of a particle r_0 from final formula, similar to the expression of black body thermal emission.

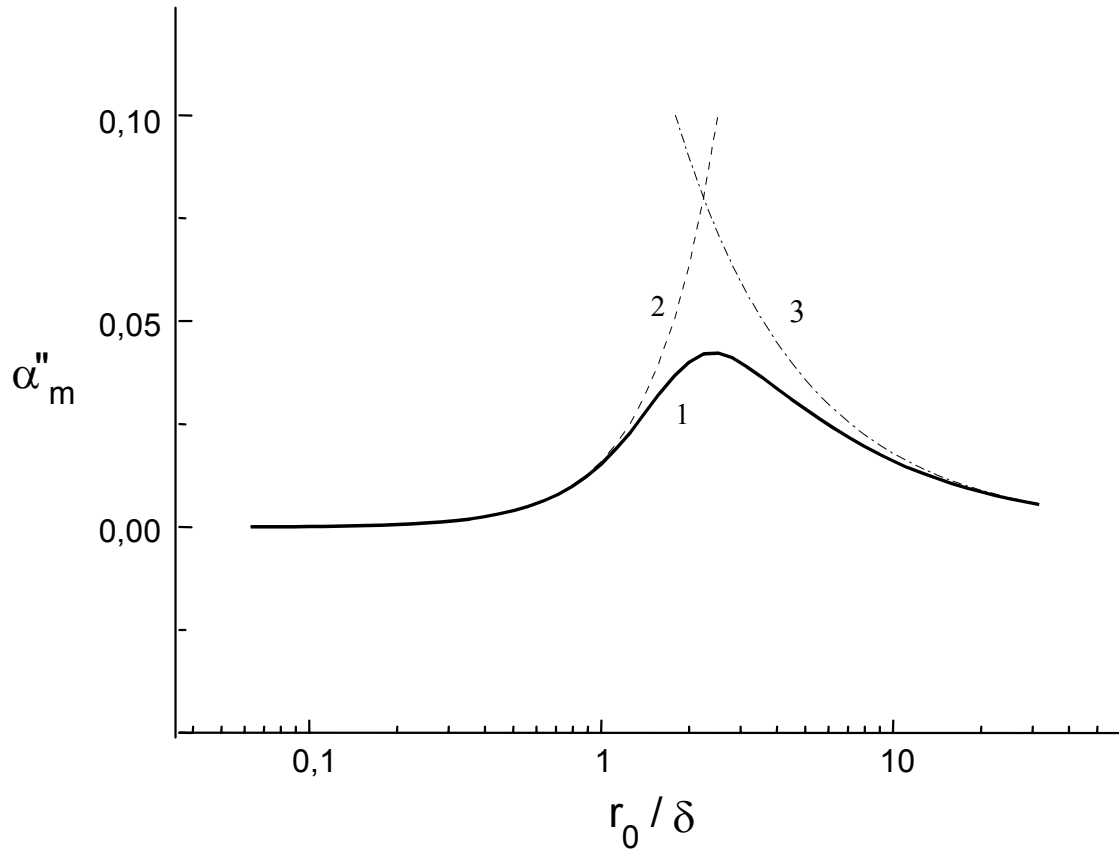


Fig. 1. Dependence of imaginary part of magnetic susceptibility α''_m normalized by the volume on dimensionless parameter (r_0/δ) for exact formula (curve 1) and for approximations at small frequencies ($r_0/\delta \ll 1$, curve 2) and high frequencies ($r_0/\delta \gg 1$, curve 3).

Introducing dimensionless parameter p , which takes into account conductivity of a substance, particle radius and its temperature,

$$p = \frac{r_0}{c} \sqrt{\frac{2\pi\sigma kT}{\hbar}} \quad (6)$$

expression (1) for thermal emission for sphere after integration over frequencies can be transformed to

$$I = \frac{16}{3} \cdot \frac{T^5 r_0^3}{c^3 \hbar^4} \cdot J(p). \quad (7)$$

Dependence of the integral $J(p)$ on dimensionless parameter p , included into expression (7),

$$J(p) = \int_0^\infty \alpha_m''(p\sqrt{x}) \frac{x^4 dx}{e^x - 1}, \quad (8)$$

is shown on Fig. 2. In the expression (8) dimensionless variable $x = \hbar\omega / kT$ was used. It is worth noting reversed proportionality $J(p) \sim 1/p$ at $p \gg 1$, that corresponds the case of high temperatures or large radii of particles, and quadratic asymptotic $J(p) \sim p^2$ at $p \ll 1$. In the last case asymptotic reflects high power dependence of normalized cross section $\sigma(\omega)/(\pi r_0^2)$ on small radii of spherical particles which also results from calculations in the frame of Mie theory[6].

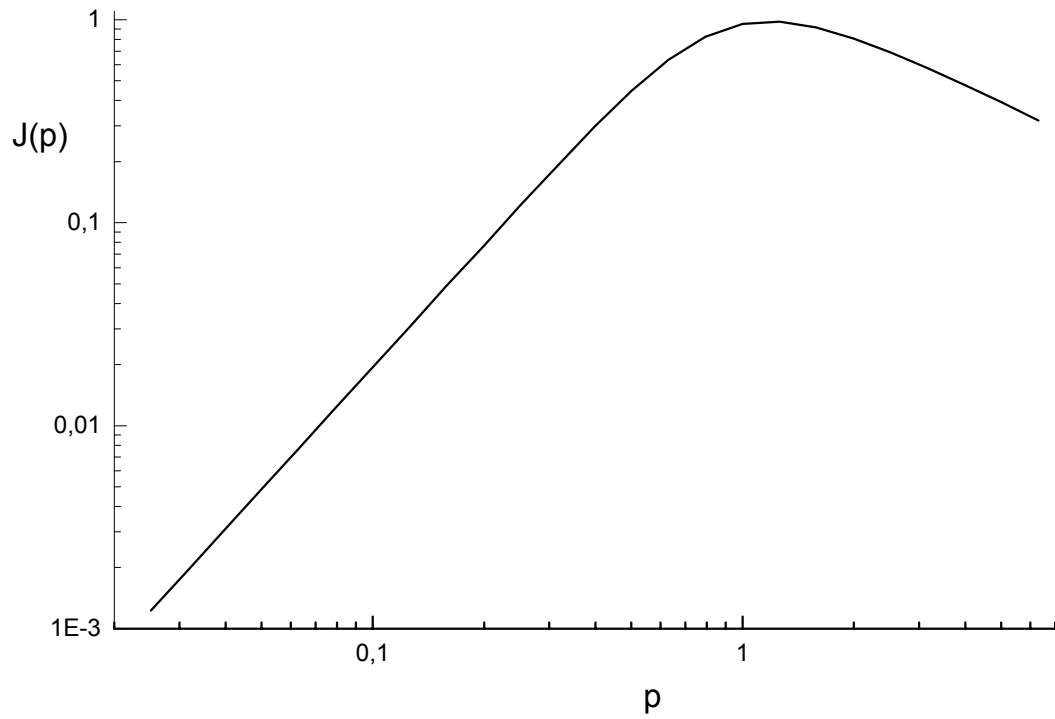


Fig. 2. Dependence of the emission frequency integral $J(p)$ on dimensionless parameter

$$p = (r_0 / c) \cdot (2\pi\sigma kT / \hbar)^{1/2}$$

For more clearness the expression for intensity of thermal emission is normalized by black body emission I_b

$$\frac{I}{I_b} = \frac{80kT}{\pi^3 c \hbar} \cdot r_0 J(p) \quad (9)$$

Due to above mentioned asymptotic $J(p) \sim 1/p$ in the case of large particles the dependence normalized intensity on radius disappears and on the temperature becomes weak. Residual temperature dependence can be accounted for not perfect accuracy of the model for absorption of radiation by conducting balls at high temperatures.

The dependence of normalized emissivity (“blackness”) I/I_b on radius of a particle r_0 at temperatures $T=1773$ °K, 1273 °K and 773 °K for micro particles of copper with account for temperature dependence of conductivity of the material [9] is shown on Fig.3. The similar results for micro particles of graphite at temperatures $T= 2773$ °K, 2273 °K, 1273 °K and 773 °K are shown on Fig. 4.

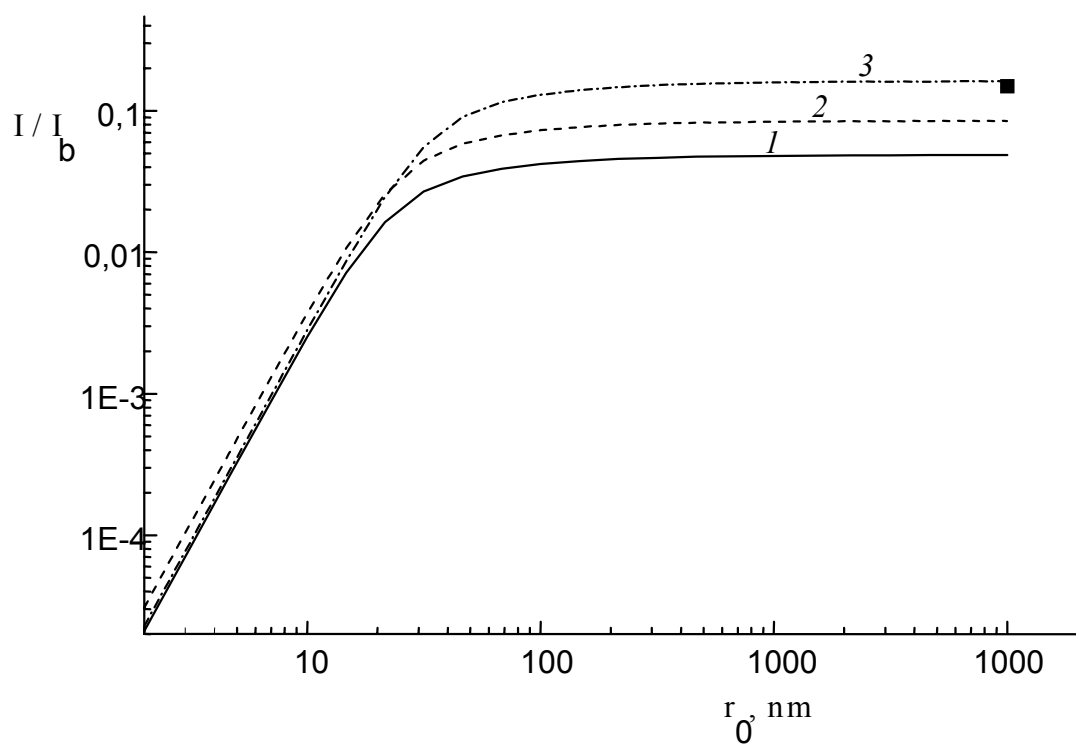


Fig. 3 Normalized emissivity of copper micro particles at temperatures 1773 °K, 1273 °K and 773 °K.

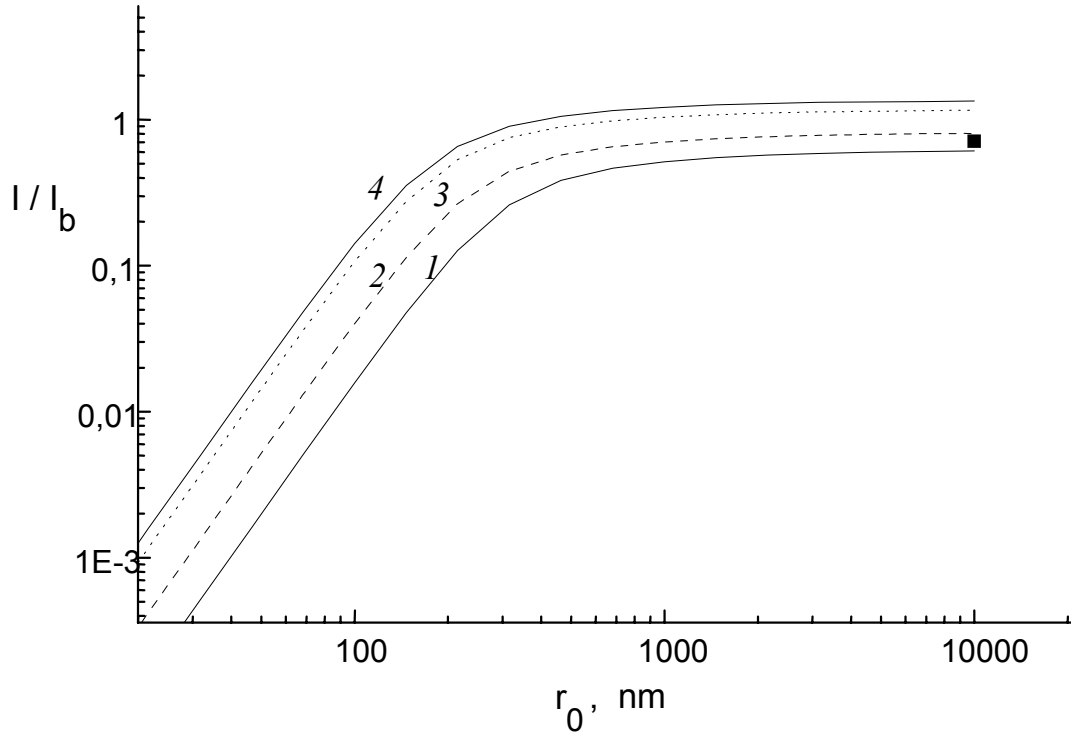


Fig. 4. Normalized emissivity of graphite micro particles at temperatures 2773 °K, 2273 °K, 1273 °K and 773 °K.

The dependence of emissivity normalized by black body emissivity, I/I_b (“blackness”) on spherical particles dimensions looks like cubic dependence of normalized cross section of absorption on radius of nano particles and leads to constant value for large radii particles that coincides with the values given in reference books. For molten cooper at temperatures 1100 – 1300 °C “blackness” equals 0.13-0.15 [7], that is in a good agreement with calculations for particles with the radius greater than 1 μm (see Fig. 3). For graphite at temperature 500 °C “blackness” equals to 0.71 [8], that agrees with the results in the frame of chosen model of emitting conducting balls. Overestimated results of emissivity of graphite at elevated temperatures should be explained by certain inaccuracy of the model. The model is valid for frequency range $\omega/(2\pi) \ll \sigma$. Normalized cross section of absorption at spherical particles for high frequencies, corresponding to asymptotic (5), can be transformed to

$\sigma(\omega)/(\pi r_0^2) = 3[\omega/(2\pi\sigma)]^{1/2}$. For more precise model of absorption of radiation by conducting substance in the asymptotic exist also terms of an expansion of the order of $\omega/(2\pi\sigma)$ [6], which taken into account should result in better agreement with experiments for big radii of the particles at elevated temperatures. It is also worth noting that in a practically important case of metal carbides the criterion is of the validity of the approach is well satisfied.

For both examples of copper and graphite considerable decrease of emissivity for particles compared with Stephan-Boltzmann black body law for small radii shown on Fig.3 and 4 takes place near the value of dimensionless parameter $p \leq 1$. So the dimensionless parameter $p = (r_0/c) \cdot (2\pi\sigma kT/\hbar)^{1/2}$ characterizes emissivity of small conducting particles depending on their dimension and conductivity.

It is worth noting that the emissivity of nano particles being small compared to black body is greater than emission of the same amount of gas and thus can be used as a light source[4].

In the case of dielectric particles it is not possible to develop rather simple dependence of cross section of absorption of the radiation on the radius of the spherical particle. But due a number of results based on the G. Mie theory for scattering and absorption of the electromagnetic wave on spherical absorbing particles [6], it is possible to conclude that cross section of the absorption weakly varies for wavelengths $2\pi\lambda(n-1)/r_0 \leq 6$, where n - index of refraction of substance. Since at elevated temperatures maximum of thermal emission spectrum due to Wien's displacement law [7] falls at the wavelength $\lambda_{\max} = B/T$, so considerable decrease of emissivity of dielectric particles should be expected for particles with dimensions $r_0 \leq (n-1)B/T$.

CONCLUSION

Efficiency of energy loss by hot conducting particles which include apart metals and graphite also the most practically important metal carbides like tungsten carbide, titan carbide and a number of others which have high conductivity [10], strongly depends on their dimensions. For dimensions smaller than the wavelength of the maximum of the spectrum of thermal emission efficiency depends on temperature T , and on conductivity σ of the substance of the particle. The universal criterion $p=(r_0/c) \cdot (2\pi\sigma kT/\hbar)^{1/2} > 1$ allows determine the range where the Stefan-Boltzmann law can be used for emission losses of small conducting particles for dimensions smaller than $r_0 \leq \lambda_{\max} = B/T$.

REFERENCES

1. Gusev A.I., PHYSICS-USPEKHI, 1998, v. 41, iss.1, p.49.
2. Fortov V.E. Iakubov I.T., THE PHYSICS OF NON-IDEAL PLASMA, World Scientific Publishing , 416pp., 1999.
3. Tsytovich V.N., Winter J., ON THE ROLE OF DUST IN FUSION DEVICES, PHYSICS-USPEKHI, 1998, v. 41, iss. 8, p.815.
4. Smirnov B.M., CLUSTER-INVOLVING PROCESSES IN PLASMAS AND GASES, PHYSICS-USPEKHI, 1997, v.40, iss. 11, p.1117.
5. Lifshitz E. M., Landau L. D., Pitaevskii L. P., Electrodynamics of Continuous Media : Volume 8 (Course of Theoretical Physics), Butterworth-Heinemann, 1984, . 460pp.
6. Born M., Wolf E., “Principles of optics” Pergamon Press, Oxford, L., Edinburgh, N.Y., P., Frankfurt, 1964.
7. Blokh A.G., “Basis of radiation heat transfer”, Moscow-Leningrad, Gosenergoizdat, 1962. 332 pp. (in Russian).
8. Emissivity of Specific Materials, <http://www.coleparmer.com/techinfo/>
9. Kikoin I. K. (ed) 1992, Tables of Physical Quantities: A Handbook (Moscow: Science)
10. Samsonov, GV, ed. Handbook of the Physiochemical Properties of the Elements. New York: Plenum, 1968.